



Products contained in this shipment may be subject to ITAR regulations.

Warning:

The export of these commodity(ies), technology, or software are subject either to the U.S. Commerce Department Export Administration Regulations (E.A.R.), or to the U.S. State Department International Traffic In Arms Regulations (I.T.A.R.). Diversion, the shipment to unauthorized locations or entities, or the disclosure of related technical data or software to unauthorized foreign nationals is contrary to U.S. law and is prohibited. If export is authorized to a specific country or end-users, compliance with the U.S. export laws is required prior to transfer, transshipment on a non-continuous voyage, or disposal in any other country, or to any other end-user of these commodities, either in their original form or after being incorporated into other end-items.



Radiation Lot Acceptance Testing (RLAT) of the RH1013MH Dual Precision Operational Amplifier for Linear Technology

Customer: Linear Technology, PO# 68651L

RAD Job Number: 14-0247

Part Type Tested: RH1013MH Dual Precision Operational Amplifier, Linear Technology RH1013M Datasheet Revision E

Traceability Information: Fab Lot Number: W10905043.1, Lot Number: 709855, Wafer Number: 18, Date Code: 1314A. See photograph of unit under test in Appendix A.

Quantity of Units: 12 units received, 5 units for biased irradiation, 5 units for unbiased irradiation and 2 units for control. Serial numbers 27, 28, 29, 30 and 31 were biased during irradiation, serial numbers 32, 33, 34, 35 and 36 were unbiased during irradiation and serial numbers 37 and 38 were used as control. See Appendix B for the radiation bias connection table.

Radiation and Electrical Test Increments: 50rad(Si)/s ionizing radiation with electrical test increments: pre-irradiation, 20krad(Si), 50krad(Si), 100krad(Si) and 200krad(Si).

Pre-Irradiation Burn-In: Burn-In performed by Linear Technology prior to receipt by RAD

Overtest and Post-Irradiation Anneal: No overtest. 24-hour room temperature anneal followed by a 168-hour 100°C anneal. Both anneals were performed in the same electrical bias condition as the irradiations. Electrical measurements were made following each anneal increment.

Radiation Test Standard: MIL-STD-750 TM1019 and/or MIL-STD-883 TM1019 Condition A and Linear Technology RH1013M Datasheet Revision E.

Test Hardware and Software: LTS2020 Automated Tester, Entity ID TS03, Calibration Date: 4/30/2014, Calibration Due: 4/30/2015. LTS2101 Family Board, Entity ID FB10. LTS0600 Test Fixture, Entity ID TF03. RH1013 DUT Board. Test Program: RH1013LT.SRC

Facility and Radiation Source: Aeroflex RAD's, Colorado Springs, CO. Gamma rays provided by JLSA 81-24 Co60 source. Dosimetry performed by Air Ionization Chamber (AIC) traceable to NIST. Aeroflex RAD's dosimetry has been audited by DLA and Aeroflex RAD has been awarded Laboratory Suitability for MIL-STD-750 and MIL-STD-883 TM 1019.

Irradiation and Test Temperature: Room temperature controlled to 24°C±6°C per MIL-STD-883 and MIL-STD-750.

Test Result:

- **PASSED the total ionizing dose test to the 200krad(Si) dose level**
- **PASSED following 24-hour room temperature anneal**
- **PASSED following 168-hour 100°C anneal**



1.0. Overview and Background

It is well known that total dose ionizing radiation can cause parametric degradation and ultimately functional failure in electronic devices. The damage occurs via electron-hole pair production, transport and trapping in the dielectric and interface regions. In discrete devices the bulk of the damage is frequently manifested as a reduction in the gain and/or breakdown voltage of the device. The damage will usually anneal with time following the end of the radiation exposure. Due to this annealing, and to ensure a worst-case test condition MIL-STD-883H TM1019 calls out a dose rate of 50 to 300rad(Si)/s as Condition A and further specifies that the time from the end of an incremental radiation exposure and electrical testing shall be 1-hour or less and the total time from the end of one incremental irradiation to the beginning of the next incremental radiation step should be 2-hours or less. The work described in this report was performed to meet MIL-STD-883H TM1019 Condition A.

2.0. Radiation Test Apparatus

The total ionizing dose testing described in this final report was performed using the facilities at Aeroflex RAD's Longmire Laboratories in Colorado Springs, CO. The high dose rate total ionizing dose (TID) source is a JLSA 81-24 irradiator modified to provide a panoramic exposure. The Co-60 rods are held in the base of the irradiator heavily shielded by lead. During the radiation exposures the rod is raised by an electronic timer/controller and the exposure is performed in air. The dose rate for this irradiator in this configuration ranges from <1rad(Si)/s to a maximum of approximately 300rad(Si)/s, determined by the distance from the source. For high-dose rate experiments the bias boards are placed in a radial fashion equidistant from the raised Co-60 rods with the distance adjusted to provide the required dose rate. The irradiator calibration is maintained by Aeroflex RAD Longmire Laboratories using air ionization chamber (AIC) equipment calibrated with traceability to the National Institute of Standards and Technology (NIST). Figure 2.1 shows a photograph of the JLSA 81-24 Co-60 irradiator at Aeroflex RAD's Longmire Laboratory facility.

Aeroflex RAD is currently certified by the Defense Supply Center Columbus (DLA) for Laboratory Suitability under MIL STD 750 and MIL-STD-883H. Additional details regarding Aeroflex RAD dosimetry for TM1019 Condition A testing are available in Aeroflex RAD's report to DLA entitled: "Dose Rate Mapping of the J.L. Shepherd and Associates Model 81 Irradiator Installed by Radiation Assured Devices".



Figure 2.1. Aeroflex RAD's high dose rate Co-60 irradiator. The dose rate is obtained by positioning the device-under-test at a fixed distance from the gamma cell. The dose rate for this irradiator varies from approximately 300rad(Si)/s close to the rods down to 1rad(Si)/s at a distance of approximately 2-feet.



3.0. Radiation Test Conditions

The RH1013MH Dual Precision Operational Amplifier described in this final report were irradiated using a split 15V supply and with all pins tied to ground, that is biased and unbiased. See the TID Bias Table in Appendix B for the full bias circuits. In our opinion, this bias circuit satisfies the requirements of MIL-STD-883H TM1019 Section 3.9.3 Bias and Loading Conditions which states "The bias applied to the test devices shall be selected to produce the greatest radiation induced damage or the worst-case damage for the intended application, if known. While maximum voltage is often worst case some bipolar linear device parameters (e.g. input bias current or maximum output load current) exhibit more degradation with 0 V bias."

The devices were irradiated to a maximum total ionizing dose level of 200krad(Si) with incremental readings at 20krad(Si), 50krad(Si) and 100krad(Si). Electrical testing occurred within one hour following the end of each irradiation segment. For intermediate irradiations, the parts were tested and returned to total dose exposure within two hours from the end of the previous radiation increment.

The TID bias board was positioned in the Co-60 cell to provide the required minimum of 50rad(Si)/s and was located inside a lead-aluminum enclosure. The lead-aluminum enclosure is required under MIL-STD-883H TM1019 Section 3.4 that reads as follows: "Lead/Aluminum (Pb/Al) container. Test specimens shall be enclosed in a Pb/Al container to minimize dose enhancement effects caused by low-energy, scattered radiation. A minimum of 1.5 mm Pb, surrounding an inner shield of at least 0.7 mm Al, is required. This Pb/Al container produces an approximate charged particle equilibrium for Si and for TLDs such as CaF₂. The radiation field intensity shall be measured inside the Pb/Al container (1) initially, (2) when the source is changed, or (3) when the orientation or configuration of the source, container, or test-fixture is changed. This measurement shall be performed by placing a dosimeter (e.g., a TLD) in the device-irradiation container at the approximate test-device position. If it can be demonstrated that low energy scattered radiation is small enough that it will not cause dosimetry errors due to dose enhancement, the Pb/Al container may be omitted."

The final dose rate within the high dose rate lead-aluminum enclosure was determined using calibration calculations based on air ionization chamber (AIC) dosimetry performed just prior to beginning the total dose irradiations. The final dose rate for this work was 55.3rad(Si)/s with a precision of $\pm 5\%$.

4.0. Tested Parameters

During the total ionizing dose characterization testing the following electrical parameters were measured pre- and post-irradiation:

1. Positive Supply Current 15V (A) @ VS=+/-15V, VCM=0V
2. Negative Supply Current 15V (A) @ VS=+/-15V, VCM=0V
3. Input Offset Voltage1 15V (V) @ VS=+/-15V, VCM=0V
4. Input Offset Voltage2 15V (V) @ VS=+/-15V, VCM=0V
5. Input Offset Current1 15V (A) @ VS=+/-15V, VCM=0V
6. Input Offset Current2 15V (A) @ VS=+/-15V, VCM=0V
7. Positive Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V
8. Positive Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V
9. Negative Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V
10. Negative Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V
11. Common Mode Rejection Ratio1 15V (dB) @ VCM=+13V, -15V
12. Common Mode Rejection Ratio2 15V (dB) @ VCM=+13V, -15V
13. Power Supply Rejection Ratio1 15V (dB) @ VS=+/-10V to +/-18V
14. Power Supply Rejection Ratio2 15V (dB) @ VS=+/-10V to +/-18V
15. Large-Signal Voltage Gain1 15V (V/mV) @ RL=10K, VO=+/-10V
16. Large-Signal Voltage Gain2 15V (V/mV) @ RL=10K, VO=+/-10V
17. Positive Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
18. Positive Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
19. Negative Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
20. Negative Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
21. Positive Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V
22. Positive Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V
23. Negative Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V
24. Negative Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V
25. Positive Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V
26. Negative Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V
27. Input Offset Voltage1 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
28. Input Offset Voltage2 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
29. Input Offset Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
30. Input Offset Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
31. Positive Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
32. Positive Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
33. Negative Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
34. Negative Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
35. Positive Output Voltage High 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
36. Positive Output Voltage High 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
37. Positive Output Voltage High 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

38. Positive Output Voltage High 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω
39. Negative Output Voltage Low 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
40. Negative Output Voltage Low 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
41. Negative Output Voltage Low 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω
42. Negative Output Voltage Low 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω
43. Negative Output Voltage Low 5V 1mA 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA
44. Negative Output Voltage Low 5V 1mA 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA

Appendix C details the measured parameters, test conditions, pre-irradiation specification and measurement resolution for each of the measurements.

The parametric data was obtained as "read and record" and all the raw data plus an attributes summary are contained in this report as well as in a separate Excel file. The attributes data contains the average, standard deviation and the average with the KTL values applied. The KTL value used in this work is 2.742 per MIL-HDBK-814 using one sided tolerance limits of 90/90 and a 5-piece sample size. The 90/90 KTL values were selected to match the statistical levels specified in the MIL-PRF-38535 sampling plan for the qualification of a radiation hardness assured (RHA) component. Note that the following criteria must be met for a device to pass the total ionizing dose test: following the radiation exposure each of the 5 pieces irradiated under electrical bias shall pass the specification value. The units irradiated without electrical bias and the KTL statistics are included in this report for reference only. If any of the 5 pieces irradiated under electrical bias exceed the device post radiation data sheet specification limits, then the lot could be logged as a failure.



5.0. Total Ionizing Dose Test Results

Based on this criterion the RH1013MH Dual Precision Operational Amplifier (from the lot traceability information provided on the first page of this test report) the units-under-test:

- PASSED the total ionizing dose test to the 200krad(Si) dose level
- PASSED following 24-hour room temperature anneal
- PASSED following 168-hour 100°C anneal

Figures 5.1 through 5.44 show plots of all the measured parameters versus total ionizing dose while Tables 5.1 - 5.44 show the corresponding raw data for each of these parameters. In the data plots the solid diamonds are the average of the measured data points for the sample irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the units irradiated with all pins tied to ground. The black lines (solid or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the sample irradiated in the biased condition while the shaded lines (solid or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the sample irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

The control units, as expected, show no significant changes to any of the parameters. Therefore we can conclude that the electrical testing remained in control throughout the duration of the tests and the observed degradation was due to the radiation exposure. Appendix D lists the figures used in this section to facilitate the location of a particular parameter.

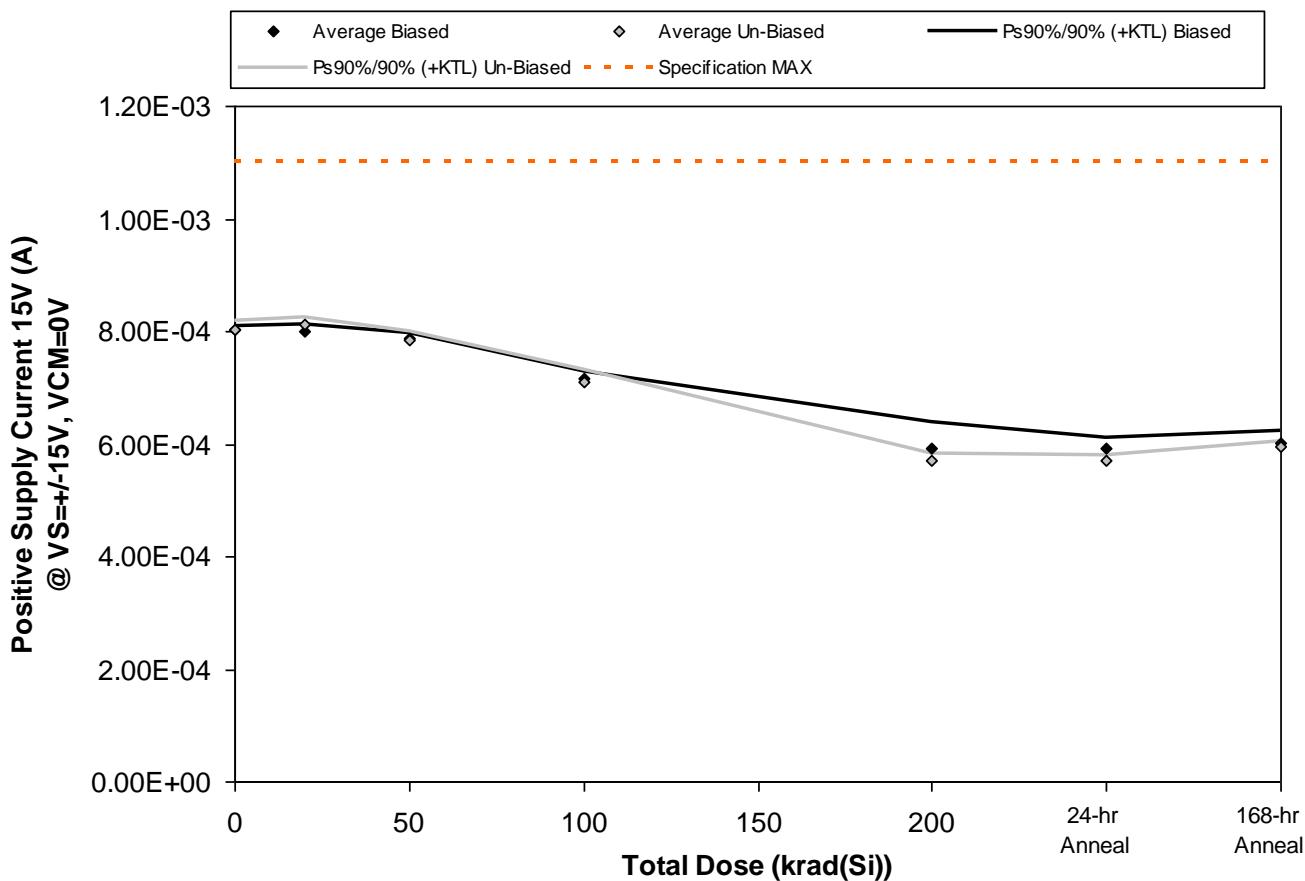


Figure 5.1. Plot of Positive Supply Current 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.1. Raw data for Positive Supply Current 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Supply Current 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	8.01E-04	8.00E-04	7.84E-04	7.18E-04	5.68E-04	5.84E-04	5.99E-04
28	8.02E-04	8.09E-04	7.91E-04	7.17E-04	6.02E-04	5.94E-04	6.14E-04
29	8.02E-04	7.98E-04	7.82E-04	7.08E-04	5.87E-04	5.83E-04	5.93E-04
30	8.02E-04	7.99E-04	7.87E-04	7.19E-04	6.05E-04	5.97E-04	6.06E-04
31	8.08E-04	7.99E-04	7.88E-04	7.19E-04	6.05E-04	5.98E-04	6.00E-04
32	7.99E-04	8.08E-04	7.81E-04	7.07E-04	5.73E-04	5.70E-04	5.96E-04
33	7.95E-04	8.09E-04	7.79E-04	7.05E-04	5.72E-04	5.70E-04	5.91E-04
34	8.08E-04	8.18E-04	7.93E-04	7.13E-04	5.68E-04	5.65E-04	5.95E-04
35	8.09E-04	8.17E-04	7.85E-04	7.07E-04	5.69E-04	5.68E-04	5.99E-04
36	8.05E-04	8.11E-04	7.84E-04	7.23E-04	5.77E-04	5.76E-04	6.00E-04
37	8.15E-04	8.14E-04	8.12E-04	8.13E-04	8.11E-04	8.12E-04	8.15E-04
38	8.01E-04	8.03E-04	8.01E-04	8.00E-04	7.99E-04	8.03E-04	8.01E-04
Biased Statistics							
Average Biased	8.03E-04	8.01E-04	7.86E-04	7.16E-04	5.93E-04	5.91E-04	6.02E-04
Std Dev Biased	2.83E-06	4.53E-06	3.51E-06	4.66E-06	1.60E-05	7.19E-06	7.96E-06
Ps90%/90% (+KTL) Biased	8.11E-04	8.13E-04	7.96E-04	7.29E-04	6.37E-04	6.11E-04	6.24E-04
Ps90%/90% (-KTL) Biased	7.95E-04	7.89E-04	7.77E-04	7.03E-04	5.49E-04	5.71E-04	5.81E-04
Un-Biased Statistics							
Average Un-Biased	8.03E-04	8.13E-04	7.84E-04	7.11E-04	5.72E-04	5.70E-04	5.96E-04
Std Dev Un-Biased	6.02E-06	4.62E-06	5.37E-06	7.35E-06	3.56E-06	4.02E-06	3.56E-06
Ps90%/90% (+KTL) Un-Biased	8.20E-04	8.25E-04	7.99E-04	7.31E-04	5.82E-04	5.81E-04	6.06E-04
Ps90%/90% (-KTL) Un-Biased	7.87E-04	8.00E-04	7.70E-04	6.91E-04	5.62E-04	5.59E-04	5.86E-04
Specification MAX	1.10E-03	1.10E-03	1.10E-03	1.10E-03	1.10E-03	1.10E-03	1.10E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

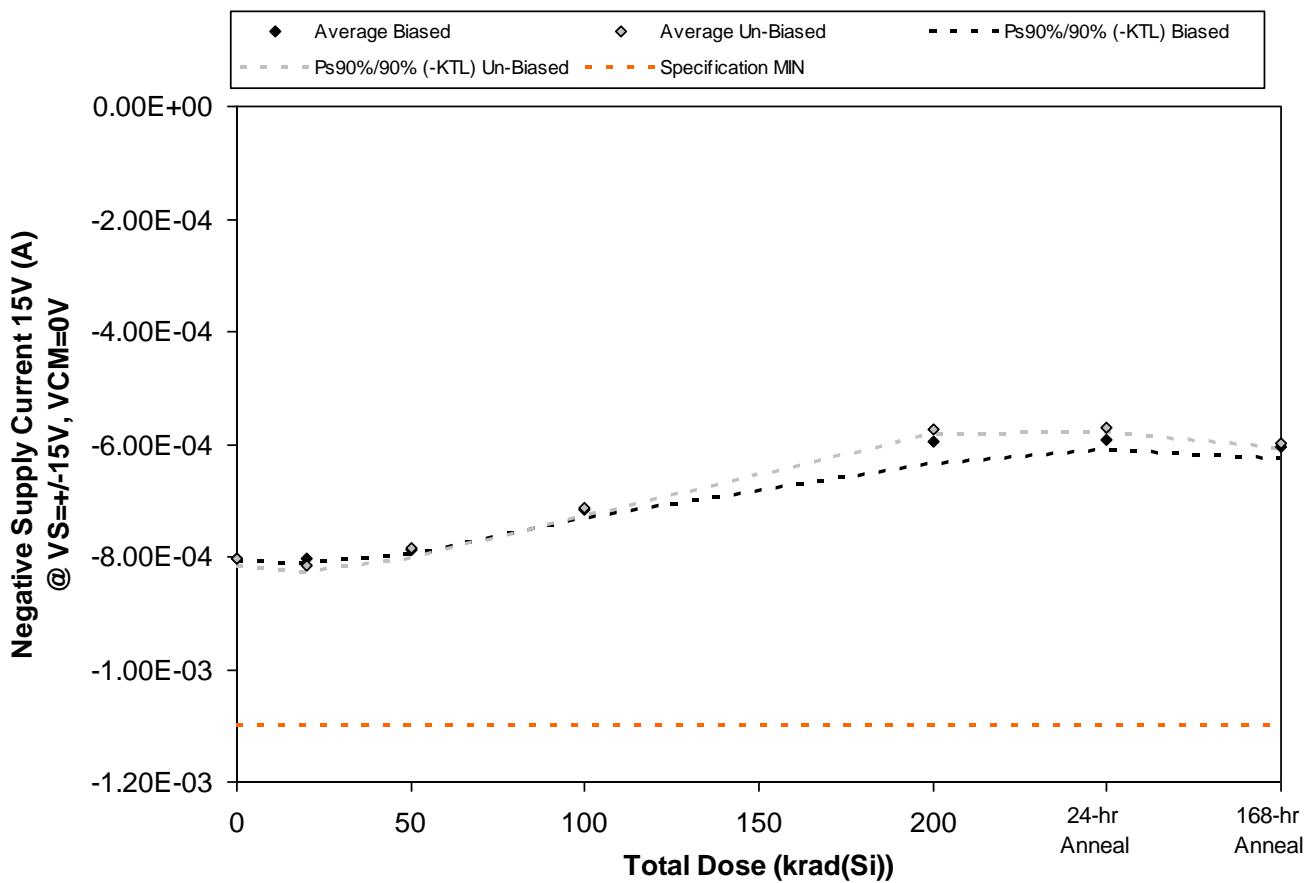


Figure 5.2. Plot of Negative Supply Current 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.2. Raw data for Negative Supply Current 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Supply Current 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	-8.00E-04	-8.02E-04	-7.86E-04	-7.19E-04	-5.69E-04	-5.84E-04	-6.01E-04
28	-8.05E-04	-8.09E-04	-7.92E-04	-7.19E-04	-6.02E-04	-5.93E-04	-6.14E-04
29	-8.00E-04	-7.98E-04	-7.82E-04	-7.09E-04	-5.88E-04	-5.85E-04	-5.93E-04
30	-8.02E-04	-8.01E-04	-7.89E-04	-7.19E-04	-6.06E-04	-5.99E-04	-6.08E-04
31	-8.06E-04	-8.01E-04	-7.89E-04	-7.21E-04	-6.04E-04	-5.99E-04	-6.00E-04
32	-8.01E-04	-8.10E-04	-7.83E-04	-7.10E-04	-5.76E-04	-5.70E-04	-5.96E-04
33	-7.96E-04	-8.10E-04	-7.79E-04	-7.08E-04	-5.74E-04	-5.72E-04	-5.92E-04
34	-8.11E-04	-8.19E-04	-7.95E-04	-7.14E-04	-5.71E-04	-5.66E-04	-5.97E-04
35	-8.06E-04	-8.19E-04	-7.85E-04	-7.08E-04	-5.72E-04	-5.68E-04	-6.00E-04
36	-8.01E-04	-8.13E-04	-7.86E-04	-7.22E-04	-5.79E-04	-5.75E-04	-6.01E-04
37	-8.16E-04	-8.14E-04	-8.13E-04	-8.12E-04	-8.12E-04	-8.14E-04	-8.17E-04
38	-8.02E-04	-8.05E-04	-8.03E-04	-8.01E-04	-8.01E-04	-8.04E-04	-8.02E-04
Biased Statistics							
Average Biased	-8.03E-04	-8.02E-04	-7.88E-04	-7.17E-04	-5.94E-04	-5.92E-04	-6.03E-04
Std Dev Biased	2.79E-06	4.09E-06	3.78E-06	4.77E-06	1.56E-05	7.28E-06	8.04E-06
Ps90%/90% (+KTL) Biased	-7.95E-04	-7.91E-04	-7.77E-04	-7.04E-04	-5.51E-04	-5.72E-04	-5.81E-04
Ps90%/90% (-KTL) Biased	-8.10E-04	-8.13E-04	-7.98E-04	-7.30E-04	-6.36E-04	-6.12E-04	-6.25E-04
Un-Biased Statistics							
Average Un-Biased	-8.03E-04	-8.14E-04	-7.86E-04	-7.12E-04	-5.74E-04	-5.70E-04	-5.97E-04
Std Dev Un-Biased	5.70E-06	4.55E-06	5.90E-06	5.90E-06	3.21E-06	3.49E-06	3.56E-06
Ps90%/90% (+KTL) Un-Biased	-7.87E-04	-8.02E-04	-7.69E-04	-6.96E-04	-5.66E-04	-5.61E-04	-5.87E-04
Ps90%/90% (-KTL) Un-Biased	-8.19E-04	-8.27E-04	-8.02E-04	-7.29E-04	-5.83E-04	-5.80E-04	-6.07E-04
Specification MIN	-1.10E-03	-1.10E-03	-1.10E-03	-1.10E-03	-1.10E-03	-1.10E-03	-1.10E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

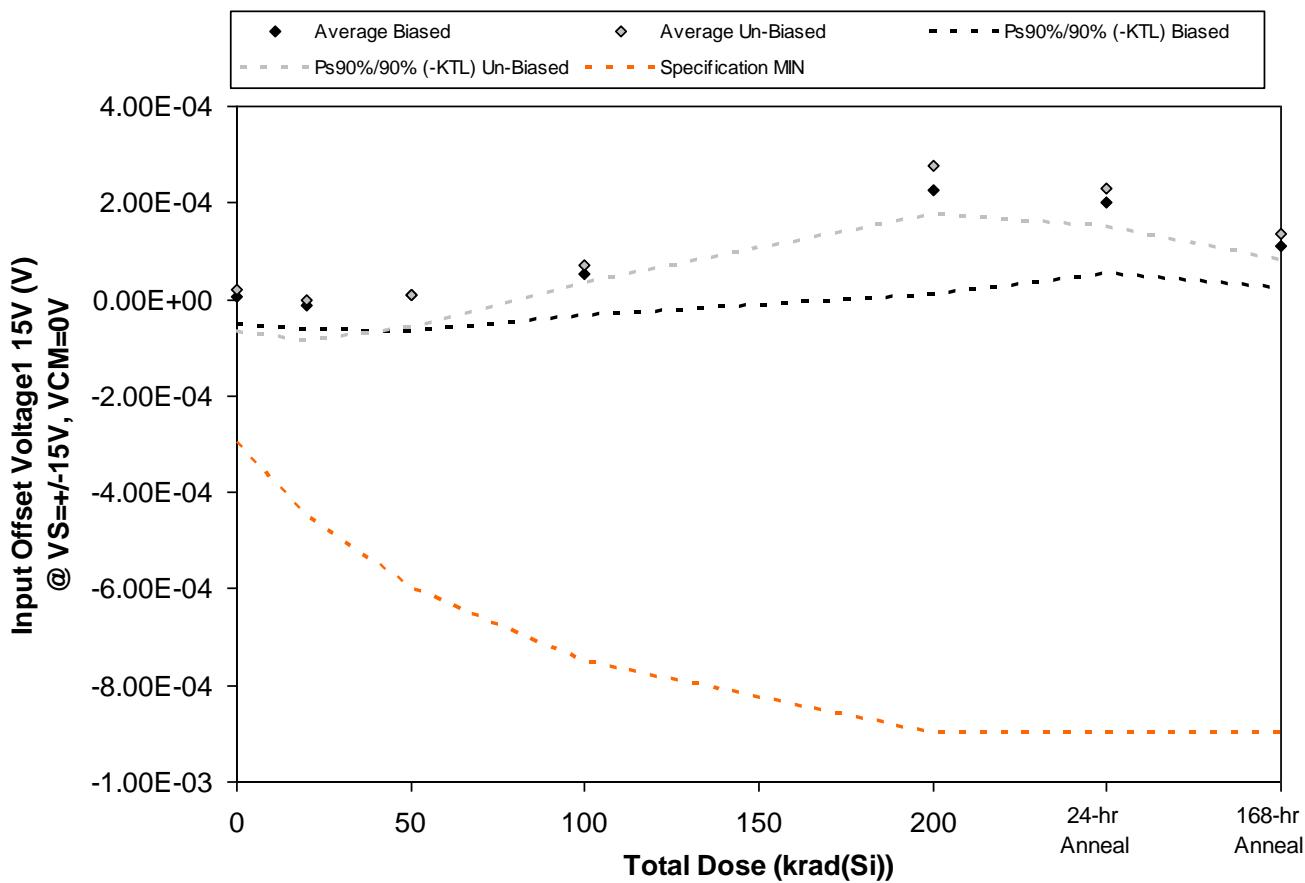


Figure 5.3. Plot of Input Offset Voltage1 15V (V) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.3. Raw data for Input Offset Voltage1 15V (V) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Voltage1 15V (V) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	3.97E-06	-1.41E-05	4.39E-06	5.90E-05	3.33E-04	2.65E-04	1.39E-04
28	-1.99E-05	-3.84E-05	-3.29E-05	2.82E-06	1.15E-04	1.21E-04	5.80E-05
29	3.54E-05	1.28E-05	3.03E-05	8.47E-05	2.32E-04	2.18E-04	1.18E-04
30	-7.73E-06	-1.97E-05	3.50E-07	4.90E-05	2.03E-04	1.80E-04	1.09E-04
31	1.36E-05	-4.90E-06	3.64E-05	7.37E-05	2.50E-04	2.21E-04	1.34E-04
32	3.78E-05	1.54E-05	2.87E-05	7.65E-05	2.79E-04	2.27E-04	1.35E-04
33	-3.02E-06	-2.25E-05	-1.56E-05	5.08E-05	2.75E-04	2.21E-04	1.15E-04
34	6.17E-05	4.27E-05	4.03E-05	7.18E-05	2.20E-04	1.86E-04	1.65E-04
35	-1.64E-05	-3.49E-05	-1.54E-05	6.62E-05	3.03E-04	2.46E-04	1.22E-04
36	1.67E-05	-2.48E-06	1.63E-05	8.41E-05	3.16E-04	2.63E-04	1.38E-04
37	8.46E-05	8.32E-05	8.50E-05	8.29E-05	8.39E-05	8.85E-05	9.01E-05
38	6.74E-05	6.83E-05	7.03E-05	6.46E-05	6.57E-05	7.58E-05	6.50E-05
Biased Statistics							
Average Biased	5.07E-06	-1.29E-05	7.71E-06	5.38E-05	2.27E-04	2.01E-04	1.12E-04
Std Dev Biased	2.11E-05	1.89E-05	2.76E-05	3.16E-05	7.88E-05	5.41E-05	3.24E-05
Ps90%/90% (+KTL) Biased	6.29E-05	3.89E-05	8.34E-05	1.41E-04	4.43E-04	3.49E-04	2.01E-04
Ps90%/90% (-KTL) Biased	-5.28E-05	-6.46E-05	-6.79E-05	-3.29E-05	1.07E-05	5.24E-05	2.29E-05
Un-Biased Statistics							
Average Un-Biased	1.93E-05	-3.72E-07	1.09E-05	6.99E-05	2.78E-04	2.29E-04	1.35E-04
Std Dev Un-Biased	3.13E-05	3.08E-05	2.55E-05	1.25E-05	3.68E-05	2.89E-05	1.91E-05
Ps90%/90% (+KTL) Un-Biased	1.05E-04	8.40E-05	8.08E-05	1.04E-04	3.79E-04	3.08E-04	1.88E-04
Ps90%/90% (-KTL) Un-Biased	-6.64E-05	-8.48E-05	-5.91E-05	3.56E-05	1.77E-04	1.49E-04	8.29E-05
Specification MIN	-3.00E-04	-4.50E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-04	4.50E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

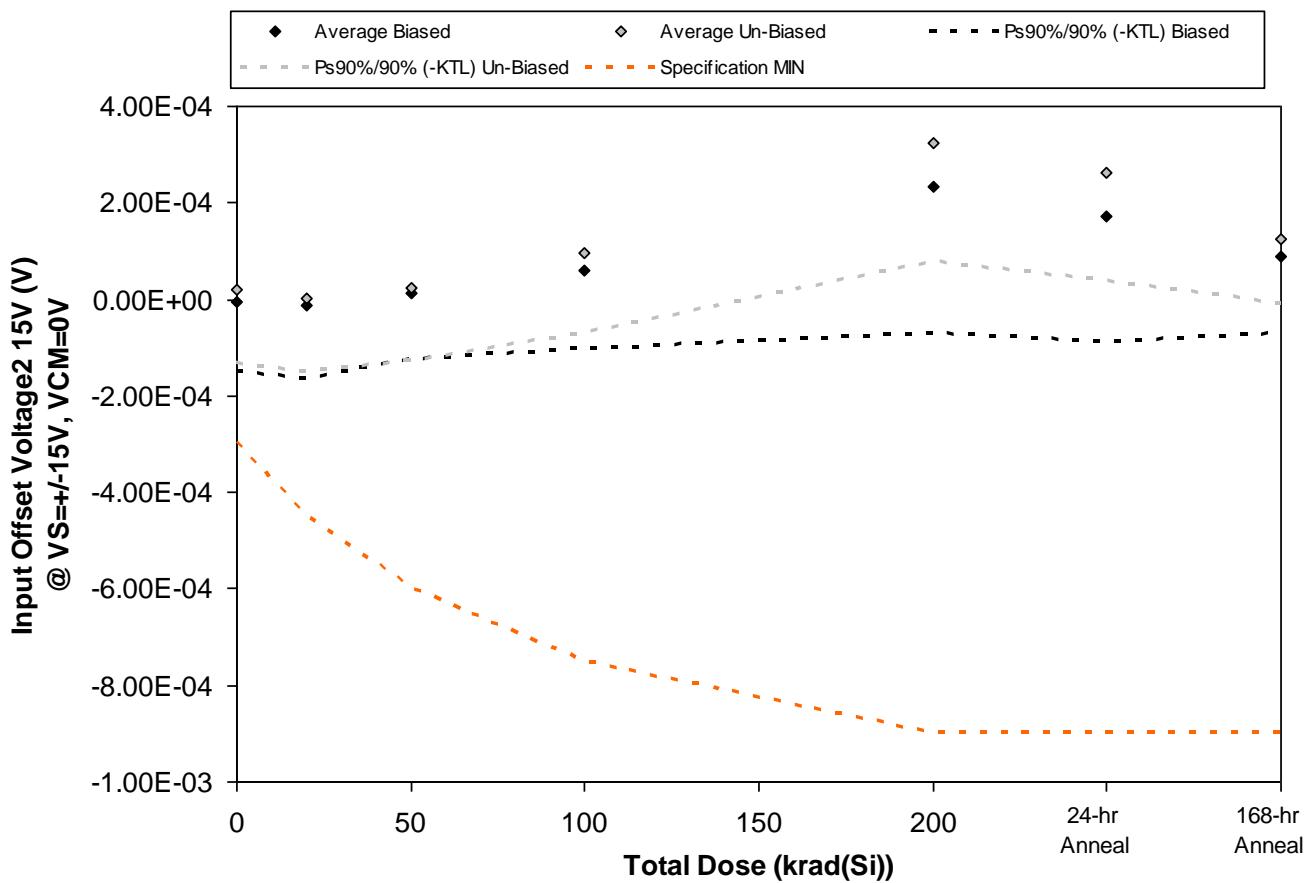


Figure 5.4. Plot of Input Offset Voltage2 15V (V) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.4. Raw data for Input Offset Voltage2 15V (V) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Voltage2 15V (V) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	5.90E-05	5.52E-05	7.09E-05	1.34E-04	4.12E-04	3.19E-04	1.67E-04
28	-1.21E-05	-3.05E-05	-1.45E-05	1.62E-05	1.27E-04	1.11E-04	4.62E-05
29	-4.15E-05	-4.31E-05	-1.59E-05	3.29E-05	1.91E-04	1.38E-04	5.54E-05
30	4.17E-05	3.55E-05	6.18E-05	1.13E-04	2.58E-04	2.14E-04	1.30E-04
31	-6.51E-05	-7.68E-05	-3.72E-05	5.96E-06	1.74E-04	8.28E-05	3.92E-05
32	9.14E-05	6.86E-05	9.40E-05	1.58E-04	3.79E-04	3.24E-04	1.71E-04
33	-4.47E-06	-3.38E-05	-3.39E-06	8.25E-05	3.35E-04	2.63E-04	1.09E-04
34	-9.10E-07	-3.06E-05	-2.74E-05	1.74E-05	1.78E-04	1.36E-04	8.20E-05
35	-4.36E-05	-5.20E-05	-1.45E-05	6.46E-05	3.15E-04	2.42E-04	8.30E-05
36	6.73E-05	5.42E-05	7.77E-05	1.57E-04	4.13E-04	3.41E-04	1.85E-04
37	8.84E-05	8.70E-05	8.48E-05	8.14E-05	8.52E-05	7.96E-05	8.33E-05
38	4.94E-05	5.01E-05	5.34E-05	4.90E-05	5.19E-05	4.69E-05	5.36E-05
Biased Statistics							
Average Biased	-3.61E-06	-1.19E-05	1.30E-05	6.05E-05	2.32E-04	1.73E-04	8.75E-05
Std Dev Biased	5.31E-05	5.54E-05	4.96E-05	5.90E-05	1.11E-04	9.50E-05	5.74E-05
Ps90%/90% (+KTL) Biased	1.42E-04	1.40E-04	1.49E-04	2.22E-04	5.37E-04	4.33E-04	2.45E-04
Ps90%/90% (-KTL) Biased	-1.49E-04	-1.64E-04	-1.23E-04	-1.01E-04	-7.16E-05	-8.75E-05	-6.99E-05
Un-Biased Statistics							
Average Un-Biased	2.19E-05	1.28E-06	2.53E-05	9.58E-05	3.24E-04	2.61E-04	1.26E-04
Std Dev Un-Biased	5.57E-05	5.57E-05	5.62E-05	6.09E-05	9.04E-05	8.11E-05	4.91E-05
Ps90%/90% (+KTL) Un-Biased	1.75E-04	1.54E-04	1.79E-04	2.63E-04	5.72E-04	4.84E-04	2.61E-04
Ps90%/90% (-KTL) Un-Biased	-1.31E-04	-1.52E-04	-1.29E-04	-7.13E-05	7.63E-05	3.87E-05	-8.42E-06
Specification MIN	-3.00E-04	-4.50E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-04	4.50E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

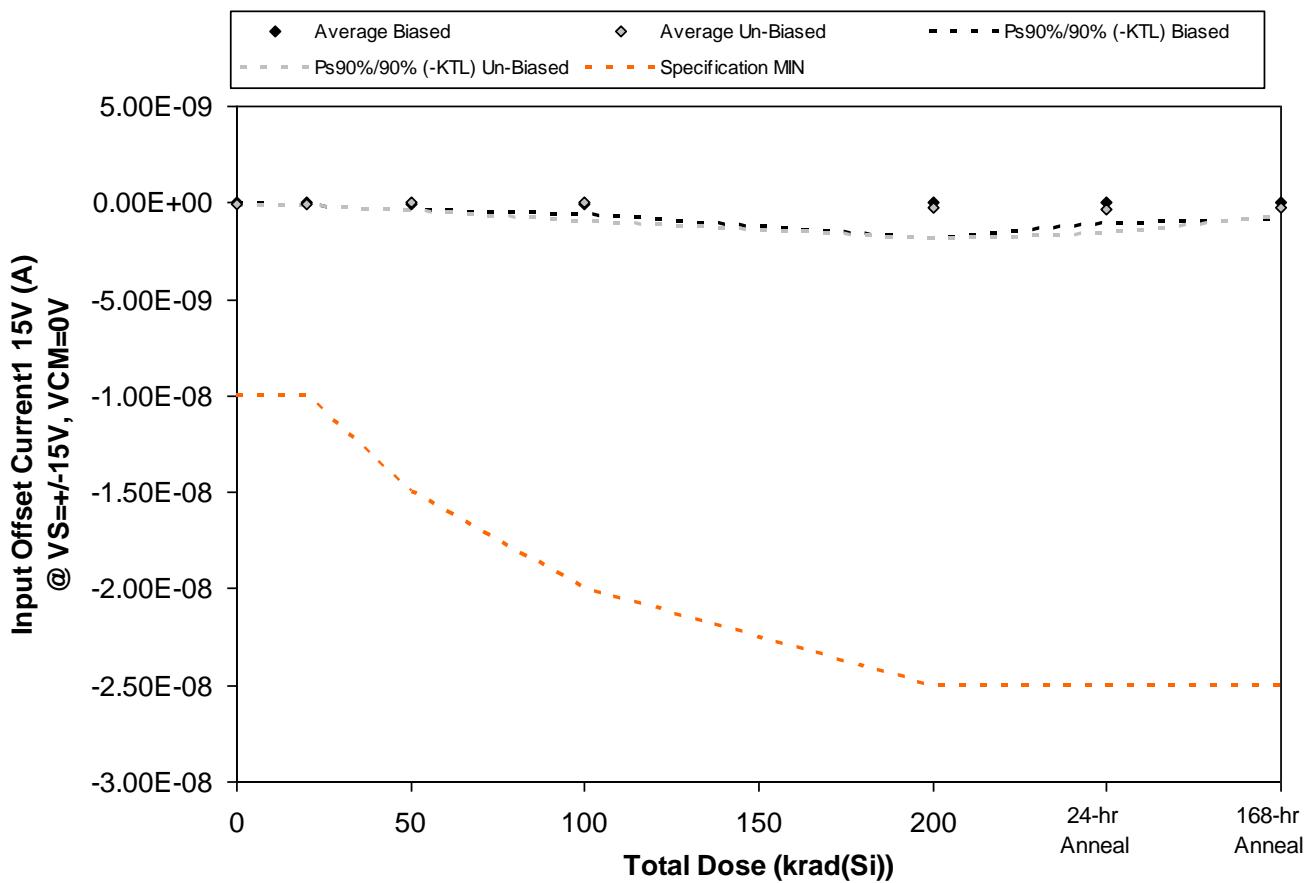


Figure 5.5. Plot of Input Offset Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.5. Raw data for Input Offset Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Current1 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	3.40E-11	-2.50E-11	-8.60E-11	-3.90E-11	9.22E-10	3.39E-10	4.97E-10
28	3.00E-12	1.40E-11	-1.83E-10	-2.21E-10	-1.59E-10	-1.84E-10	-1.01E-10
29	5.90E-11	2.70E-11	5.30E-11	-1.26E-10	-5.16E-10	-2.57E-10	-1.04E-10
30	-3.60E-11	-8.10E-11	-2.37E-10	-2.90E-10	-6.81E-10	-4.02E-10	-3.90E-10
31	8.90E-11	8.60E-11	9.30E-11	1.72E-10	5.48E-10	4.99E-10	4.90E-11
32	3.00E-12	9.00E-12	5.70E-11	5.90E-11	-2.00E-11	-8.00E-12	-3.19E-10
33	-8.00E-11	-3.70E-11	4.90E-11	-3.00E-12	-2.02E-10	-4.88E-10	-1.64E-10
34	-5.60E-11	-9.60E-11	-2.23E-10	-6.01E-10	-1.26E-09	-1.06E-09	-4.39E-10
35	3.00E-11	4.90E-11	2.40E-10	2.10E-10	1.38E-10	-6.30E-11	-1.83E-10
36	-2.90E-11	-2.50E-11	3.50E-11	2.61E-10	9.40E-11	4.70E-11	-3.40E-11
37	3.40E-11	3.30E-11	4.30E-11	5.90E-11	4.60E-11	3.40E-11	1.70E-11
38	-2.10E-11	-8.00E-12	-7.00E-12	-6.00E-12	-9.00E-12	0.00E+00	-8.00E-12
Biased Statistics							
Average Biased	2.98E-11	4.20E-12	-7.20E-11	-1.01E-10	2.28E-11	-1.00E-12	-9.80E-12
Std Dev Biased	4.85E-11	6.21E-11	1.44E-10	1.80E-10	6.90E-10	3.95E-10	3.25E-10
Ps90%/90% (+KTL) Biased	1.63E-10	1.74E-10	3.22E-10	3.92E-10	1.91E-09	1.08E-09	8.81E-10
Ps90%/90% (-KTL) Biased	-1.03E-10	-1.66E-10	-4.66E-10	-5.93E-10	-1.87E-09	-1.09E-09	-9.00E-10
Un-Biased Statistics							
Average Un-Biased	-2.64E-11	-2.00E-11	3.16E-11	-1.48E-11	-2.50E-10	-3.15E-10	-2.28E-10
Std Dev Un-Biased	4.42E-11	5.41E-11	1.65E-10	3.45E-10	5.80E-10	4.68E-10	1.55E-10
Ps90%/90% (+KTL) Un-Biased	9.47E-11	1.28E-10	4.85E-10	9.31E-10	1.34E-09	9.68E-10	1.98E-10
Ps90%/90% (-KTL) Un-Biased	-1.47E-10	-1.68E-10	-4.21E-10	-9.61E-10	-1.84E-09	-1.60E-09	-6.54E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.50E-08	-2.50E-08	-2.50E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.50E-08	2.50E-08	2.50E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

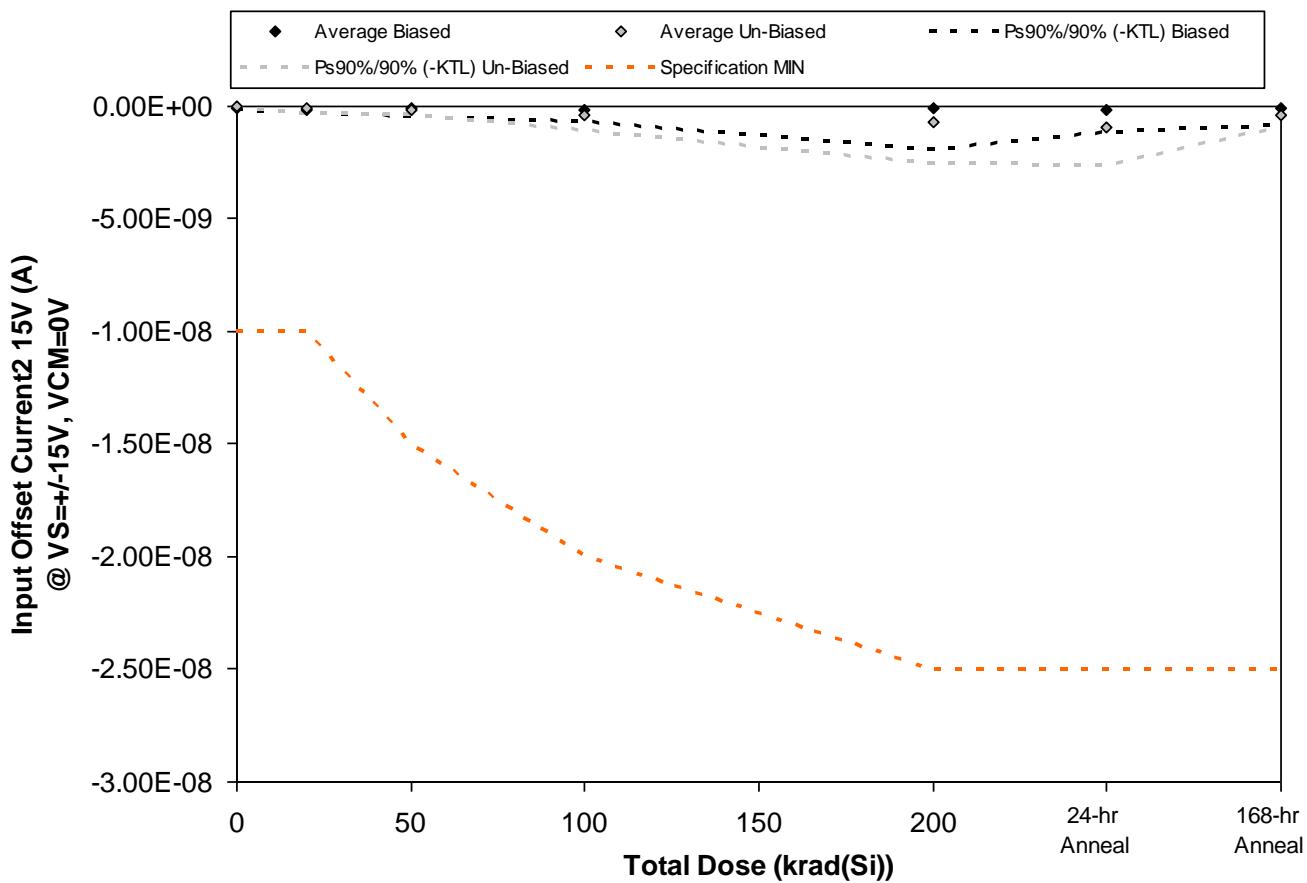


Figure 5.6. Plot of Input Offset Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.6. Raw data for Input Offset Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Current2 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	-8.00E-12	-1.12E-10	-7.20E-11	-1.70E-10	9.93E-10	3.31E-10	3.30E-10
28	-6.00E-11	-1.04E-10	-6.00E-12	-2.48E-10	-4.02E-10	-5.14E-10	-3.36E-10
29	-9.80E-11	-2.23E-10	-1.99E-10	-4.40E-10	-7.17E-10	-2.47E-10	-1.78E-10
30	-4.60E-11	-7.30E-11	-2.70E-10	-1.68E-10	-4.78E-10	-4.30E-10	-3.60E-11
31	-1.14E-10	-1.05E-10	2.00E-12	6.90E-11	7.90E-11	2.24E-10	-2.58E-10
32	-6.00E-11	-1.34E-10	-4.20E-11	-4.70E-10	-7.18E-10	-9.96E-10	-5.42E-10
33	-6.40E-11	-1.15E-10	-1.71E-10	-3.62E-10	-6.69E-10	-7.80E-10	-2.06E-10
34	-2.60E-11	-5.20E-11	-2.55E-10	-7.70E-10	-1.79E-09	-1.97E-09	-4.19E-10
35	-1.20E-11	-1.78E-10	-7.30E-11	-1.19E-10	3.00E-11	-4.48E-10	-1.21E-10
36	-1.40E-11	-1.50E-11	-6.50E-11	-2.86E-10	-5.24E-10	-5.59E-10	-5.35E-10
37	-3.70E-11	-3.80E-11	-4.00E-11	-4.00E-11	-2.50E-11	-3.90E-11	-2.80E-11
38	-8.00E-12	-1.50E-11	0.00E+00	-5.00E-12	-2.20E-11	-1.50E-11	-7.00E-12
Biased Statistics							
Average Biased	-6.52E-11	-1.23E-10	-1.09E-10	-1.91E-10	-1.05E-10	-1.27E-10	-9.56E-11
Std Dev Biased	4.22E-11	5.77E-11	1.21E-10	1.83E-10	6.78E-10	3.84E-10	2.63E-10
Ps90%/90% (+KTL) Biased	5.05E-11	3.47E-11	2.22E-10	3.10E-10	1.76E-09	9.25E-10	6.24E-10
Ps90%/90% (-KTL) Biased	-1.81E-10	-2.82E-10	-4.40E-10	-6.93E-10	-1.97E-09	-1.18E-09	-8.15E-10
Un-Biased Statistics							
Average Un-Biased	-3.52E-11	-9.88E-11	-1.21E-10	-4.01E-10	-7.35E-10	-9.51E-10	-3.65E-10
Std Dev Un-Biased	2.51E-11	6.52E-11	8.96E-11	2.42E-10	6.62E-10	6.08E-10	1.92E-10
Ps90%/90% (+KTL) Un-Biased	3.36E-11	7.99E-11	1.25E-10	2.63E-10	1.08E-09	7.16E-10	1.63E-10
Ps90%/90% (-KTL) Un-Biased	-1.04E-10	-2.77E-10	-3.67E-10	-1.07E-09	-2.55E-09	-2.62E-09	-8.92E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.50E-08	-2.50E-08	-2.50E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.50E-08	2.50E-08	2.50E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

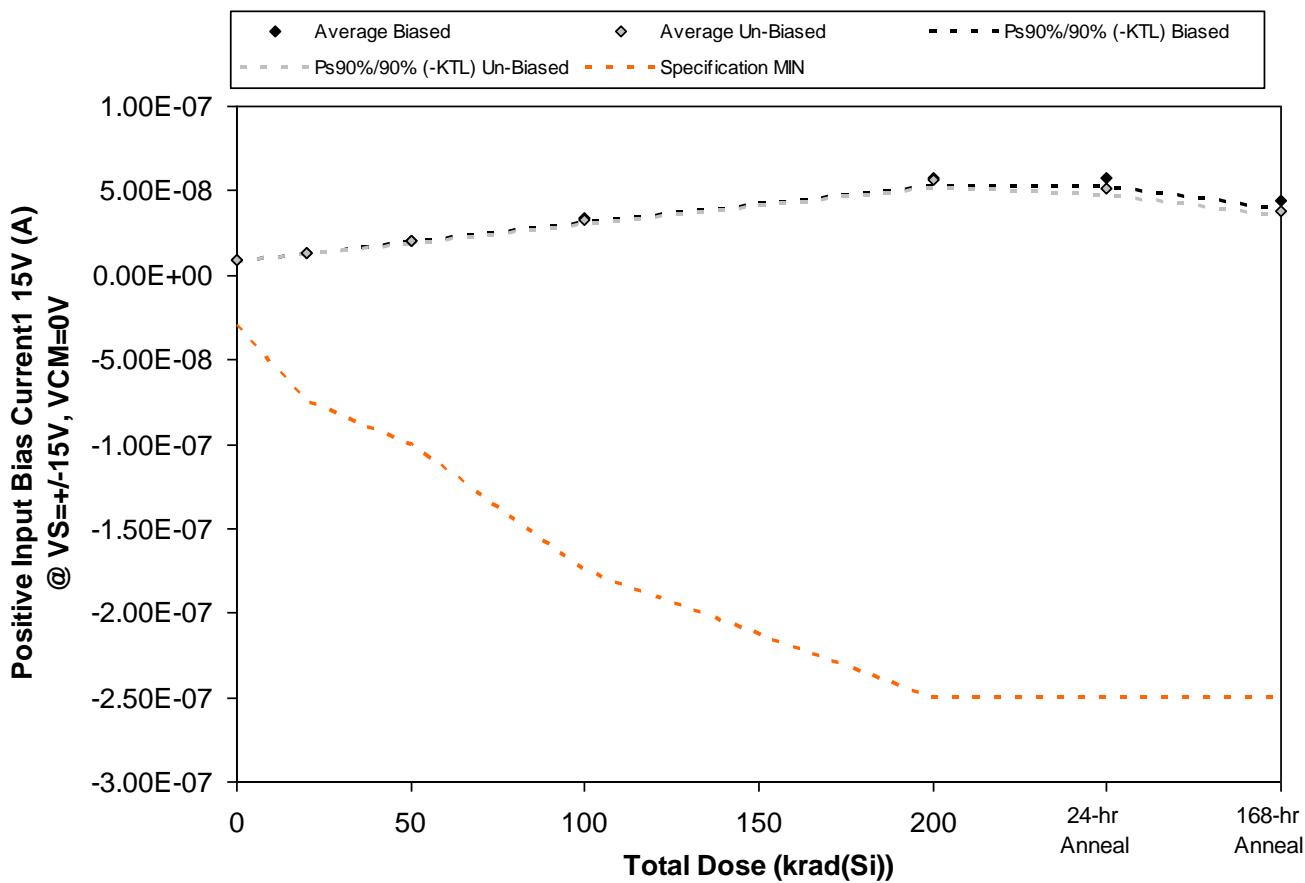


Figure 5.7. Plot of Positive Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.7. Raw data for Positive Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	9.09E-09	1.31E-08	2.06E-08	3.49E-08	5.94E-08	5.88E-08	4.33E-08
28	8.91E-09	1.31E-08	2.05E-08	3.34E-08	5.68E-08	5.69E-08	4.23E-08
29	9.59E-09	1.37E-08	2.10E-08	3.40E-08	5.88E-08	5.91E-08	4.52E-08
30	1.01E-08	1.42E-08	2.14E-08	3.45E-08	5.90E-08	5.93E-08	4.61E-08
31	9.17E-09	1.31E-08	2.00E-08	3.18E-08	5.44E-08	5.52E-08	4.25E-08
32	9.04E-09	1.29E-08	1.99E-08	3.16E-08	5.49E-08	5.04E-08	3.67E-08
33	9.87E-09	1.39E-08	2.11E-08	3.36E-08	5.76E-08	5.34E-08	3.96E-08
34	9.22E-09	1.34E-08	2.09E-08	3.37E-08	5.88E-08	5.37E-08	3.84E-08
35	9.89E-09	1.39E-08	2.11E-08	3.33E-08	5.62E-08	5.21E-08	3.86E-08
36	9.25E-09	1.31E-08	1.97E-08	3.16E-08	5.41E-08	4.99E-08	3.69E-08
37	8.50E-09	8.47E-09	8.48E-09	8.46E-09	8.48E-09	8.48E-09	8.52E-09
38	8.60E-09	8.61E-09	8.60E-09	8.59E-09	8.59E-09	8.61E-09	8.59E-09
Biased Statistics							
Average Biased	9.36E-09	1.34E-08	2.07E-08	3.37E-08	5.77E-08	5.78E-08	4.39E-08
Std Dev Biased	4.58E-10	4.77E-10	5.13E-10	1.22E-09	2.07E-09	1.79E-09	1.70E-09
Ps90%/90% (+KTL) Biased	1.06E-08	1.47E-08	2.21E-08	3.70E-08	6.33E-08	6.27E-08	4.85E-08
Ps90%/90% (-KTL) Biased	8.11E-09	1.21E-08	1.93E-08	3.04E-08	5.20E-08	5.29E-08	3.92E-08
Un-Biased Statistics							
Average Un-Biased	9.45E-09	1.34E-08	2.05E-08	3.27E-08	5.63E-08	5.19E-08	3.80E-08
Std Dev Un-Biased	3.97E-10	4.70E-10	7.01E-10	1.09E-09	1.91E-09	1.71E-09	1.20E-09
Ps90%/90% (+KTL) Un-Biased	1.05E-08	1.47E-08	2.24E-08	3.57E-08	6.15E-08	5.66E-08	4.13E-08
Ps90%/90% (-KTL) Un-Biased	8.37E-09	1.21E-08	1.86E-08	2.98E-08	5.11E-08	4.72E-08	3.47E-08
Specification MIN	-3.00E-08	-7.50E-08	-1.00E-07	-1.75E-07	-2.50E-07	-2.50E-07	-2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-08	7.50E-08	1.00E-07	1.75E-07	2.50E-07	2.50E-07	2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

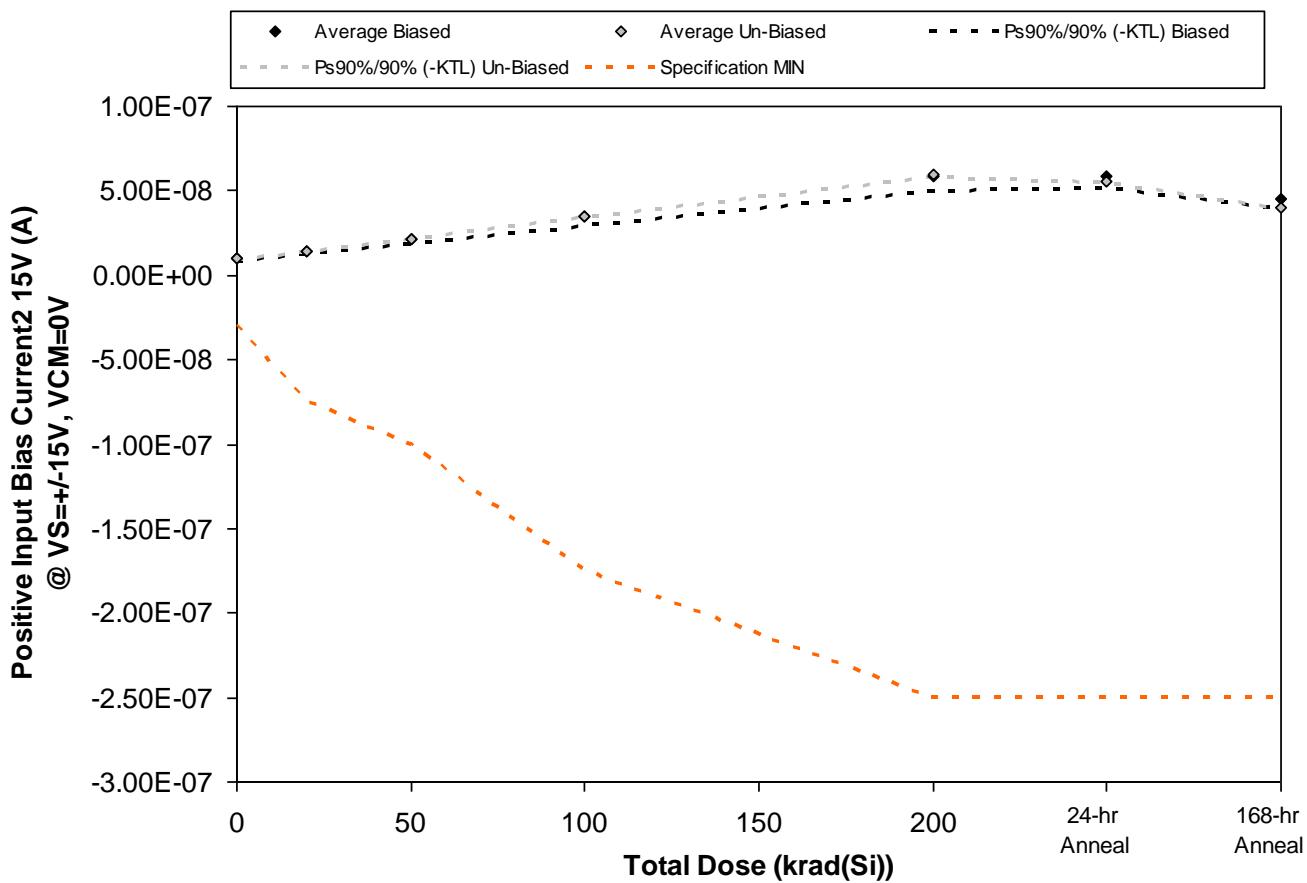


Figure 5.8. Plot of Positive Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.8. Raw data for Positive Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	9.91E-09	1.42E-08	2.23E-08	3.76E-08	6.36E-08	6.30E-08	4.68E-08
28	8.73E-09	1.29E-08	1.99E-08	3.28E-08	5.60E-08	5.62E-08	4.15E-08
29	9.81E-09	1.42E-08	2.17E-08	3.54E-08	6.09E-08	6.12E-08	4.70E-08
30	9.91E-09	1.39E-08	2.09E-08	3.39E-08	5.77E-08	5.81E-08	4.50E-08
31	9.58E-09	1.36E-08	2.06E-08	3.27E-08	5.63E-08	5.67E-08	4.40E-08
32	9.88E-09	1.41E-08	2.16E-08	3.45E-08	5.95E-08	5.51E-08	4.00E-08
33	9.99E-09	1.43E-08	2.18E-08	3.46E-08	5.93E-08	5.53E-08	4.08E-08
34	9.54E-09	1.38E-08	2.16E-08	3.49E-08	6.04E-08	5.58E-08	3.95E-08
35	1.03E-08	1.46E-08	2.20E-08	3.47E-08	5.86E-08	5.47E-08	4.04E-08
36	1.03E-08	1.43E-08	2.17E-08	3.50E-08	5.96E-08	5.54E-08	4.13E-08
37	9.41E-09	9.43E-09	9.42E-09	9.42E-09	9.37E-09	9.39E-09	9.44E-09
38	9.42E-09	9.43E-09	9.44E-09	9.41E-09	9.42E-09	9.41E-09	9.43E-09
Biased Statistics							
Average Biased	9.59E-09	1.38E-08	2.11E-08	3.45E-08	5.89E-08	5.90E-08	4.49E-08
Std Dev Biased	4.98E-10	5.46E-10	9.35E-10	2.04E-09	3.29E-09	2.93E-09	2.22E-09
Ps90%/90% (+KTL) Biased	1.10E-08	1.53E-08	2.37E-08	4.01E-08	6.79E-08	6.71E-08	5.09E-08
Ps90%/90% (-KTL) Biased	8.22E-09	1.23E-08	1.85E-08	2.89E-08	4.99E-08	5.10E-08	3.88E-08
Un-Biased Statistics							
Average Un-Biased	9.99E-09	1.42E-08	2.17E-08	3.47E-08	5.95E-08	5.53E-08	4.04E-08
Std Dev Un-Biased	3.09E-10	2.76E-10	1.76E-10	2.03E-10	6.58E-10	4.35E-10	6.69E-10
Ps90%/90% (+KTL) Un-Biased	1.08E-08	1.50E-08	2.22E-08	3.53E-08	6.13E-08	5.64E-08	4.22E-08
Ps90%/90% (-KTL) Un-Biased	9.15E-09	1.35E-08	2.13E-08	3.42E-08	5.77E-08	5.41E-08	3.86E-08
Specification MIN	-3.00E-08	-7.50E-08	-1.00E-07	-1.75E-07	-2.50E-07	-2.50E-07	-2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-08	7.50E-08	1.00E-07	1.75E-07	2.50E-07	2.50E-07	2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

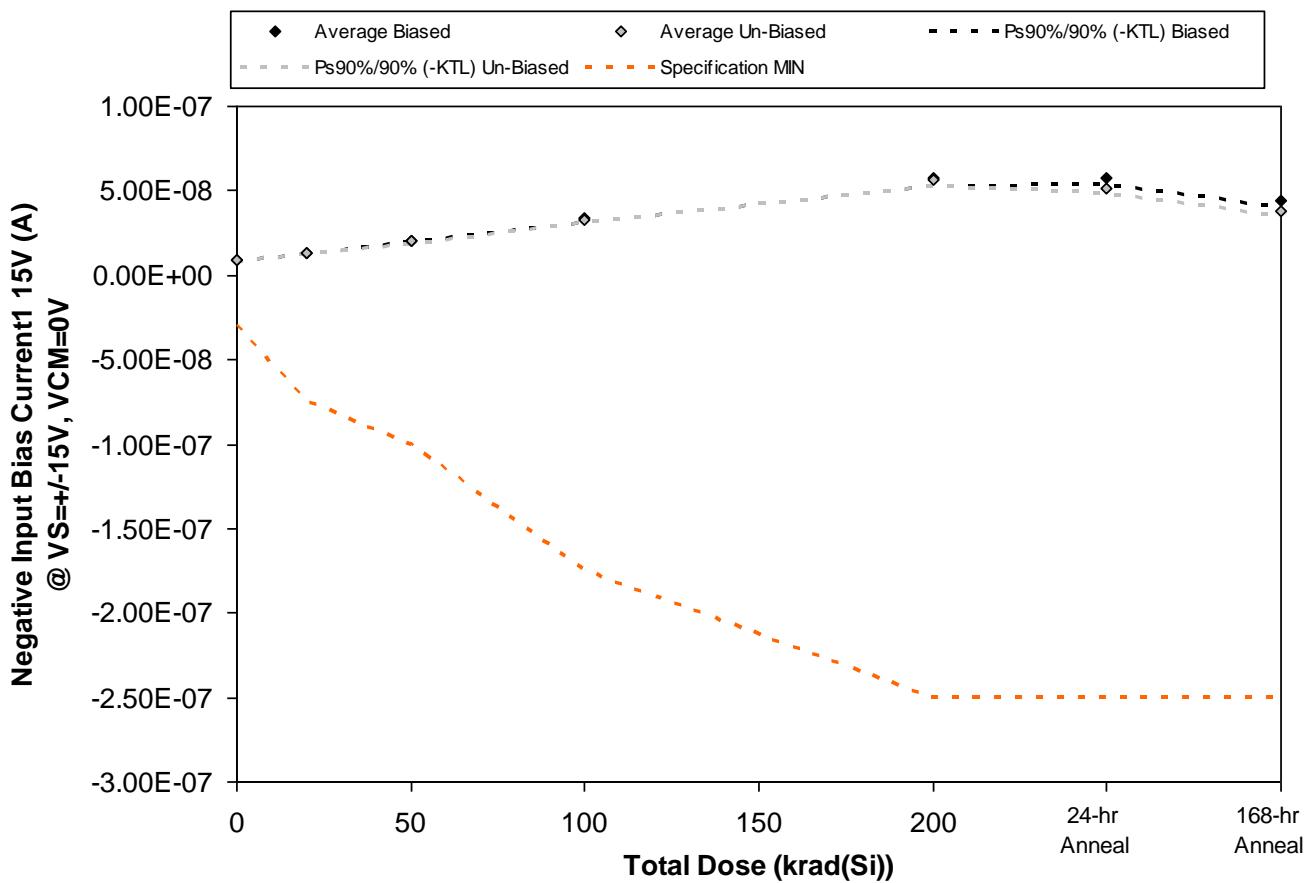


Figure 5.9. Plot of Negative Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.9. Raw data for Negative Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	9.13E-09	1.30E-08	2.06E-08	3.49E-08	6.05E-08	5.93E-08	4.39E-08
28	8.87E-09	1.31E-08	2.04E-08	3.33E-08	5.68E-08	5.68E-08	4.23E-08
29	9.62E-09	1.37E-08	2.11E-08	3.40E-08	5.84E-08	5.89E-08	4.52E-08
30	1.00E-08	1.41E-08	2.12E-08	3.43E-08	5.84E-08	5.90E-08	4.58E-08
31	9.28E-09	1.32E-08	2.01E-08	3.20E-08	5.51E-08	5.58E-08	4.26E-08
32	9.01E-09	1.29E-08	1.99E-08	3.18E-08	5.50E-08	5.06E-08	3.65E-08
33	9.76E-09	1.39E-08	2.13E-08	3.36E-08	5.75E-08	5.32E-08	3.95E-08
34	9.16E-09	1.33E-08	2.08E-08	3.33E-08	5.76E-08	5.29E-08	3.80E-08
35	9.93E-09	1.40E-08	2.13E-08	3.36E-08	5.64E-08	5.22E-08	3.85E-08
36	9.26E-09	1.31E-08	1.98E-08	3.18E-08	5.44E-08	5.02E-08	3.70E-08
37	8.51E-09	8.54E-09	8.50E-09	8.53E-09	8.50E-09	8.50E-09	8.53E-09
38	8.60E-09	8.64E-09	8.61E-09	8.62E-09	8.59E-09	8.60E-09	8.58E-09
Biased Statistics							
Average Biased	9.38E-09	1.34E-08	2.07E-08	3.37E-08	5.78E-08	5.80E-08	4.40E-08
Std Dev Biased	4.47E-10	4.62E-10	4.60E-10	1.10E-09	2.01E-09	1.57E-09	1.55E-09
Ps90%/90% (+KTL) Biased	1.06E-08	1.47E-08	2.19E-08	3.67E-08	6.33E-08	6.23E-08	4.82E-08
Ps90%/90% (-KTL) Biased	8.16E-09	1.22E-08	1.94E-08	3.07E-08	5.23E-08	5.36E-08	3.97E-08
Un-Biased Statistics							
Average Un-Biased	9.42E-09	1.34E-08	2.06E-08	3.28E-08	5.62E-08	5.18E-08	3.79E-08
Std Dev Un-Biased	3.99E-10	4.86E-10	7.17E-10	9.34E-10	1.46E-09	1.36E-09	1.20E-09
Ps90%/90% (+KTL) Un-Biased	1.05E-08	1.47E-08	2.26E-08	3.54E-08	6.02E-08	5.55E-08	4.12E-08
Ps90%/90% (-KTL) Un-Biased	8.33E-09	1.21E-08	1.86E-08	3.03E-08	5.22E-08	4.81E-08	3.46E-08
Specification MIN	-3.00E-08	-7.50E-08	-1.00E-07	-1.75E-07	-2.50E-07	-2.50E-07	-2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-08	7.50E-08	1.00E-07	1.75E-07	2.50E-07	2.50E-07	2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

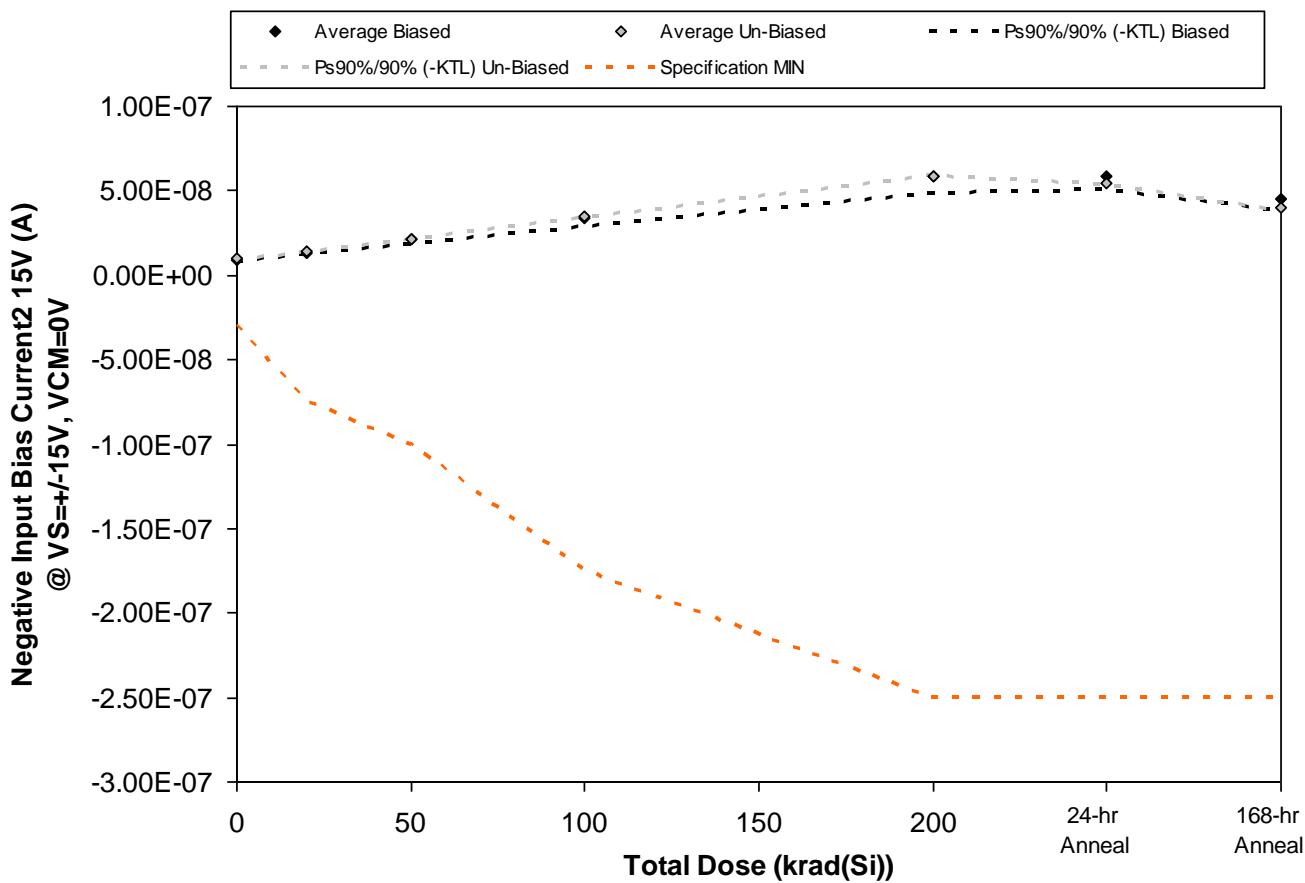


Figure 5.10. Plot of Negative Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.10. Raw data for Negative Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	9.88E-09	1.41E-08	2.23E-08	3.75E-08	6.47E-08	6.34E-08	4.72E-08
28	8.64E-09	1.28E-08	2.00E-08	3.26E-08	5.57E-08	5.58E-08	4.13E-08
29	9.71E-09	1.40E-08	2.15E-08	3.51E-08	6.03E-08	6.11E-08	4.69E-08
30	9.87E-09	1.39E-08	2.07E-08	3.38E-08	5.73E-08	5.78E-08	4.51E-08
31	9.44E-09	1.35E-08	2.07E-08	3.29E-08	5.65E-08	5.70E-08	4.39E-08
32	9.85E-09	1.40E-08	2.16E-08	3.41E-08	5.89E-08	5.42E-08	3.95E-08
33	9.97E-09	1.42E-08	2.17E-08	3.43E-08	5.88E-08	5.47E-08	4.06E-08
34	9.49E-09	1.38E-08	2.14E-08	3.41E-08	5.88E-08	5.41E-08	3.91E-08
35	1.02E-08	1.45E-08	2.20E-08	3.48E-08	5.88E-08	5.45E-08	4.03E-08
36	1.02E-08	1.44E-08	2.17E-08	3.48E-08	5.92E-08	5.50E-08	4.08E-08
37	9.36E-09	9.37E-09	9.39E-09	9.34E-09	9.38E-09	9.35E-09	9.40E-09
38	9.40E-09	9.42E-09	9.40E-09	9.41E-09	9.40E-09	9.43E-09	9.39E-09
Biased Statistics							
Average Biased	9.51E-09	1.37E-08	2.10E-08	3.44E-08	5.89E-08	5.90E-08	4.48E-08
Std Dev Biased	5.17E-10	5.15E-10	8.91E-10	1.98E-09	3.69E-09	3.15E-09	2.40E-09
Ps90%/90% (+KTL) Biased	1.09E-08	1.51E-08	2.35E-08	3.98E-08	6.90E-08	6.77E-08	5.14E-08
Ps90%/90% (-KTL) Biased	8.09E-09	1.23E-08	1.86E-08	2.89E-08	4.88E-08	5.04E-08	3.83E-08
Un-Biased Statistics							
Average Un-Biased	9.96E-09	1.41E-08	2.17E-08	3.44E-08	5.89E-08	5.45E-08	4.01E-08
Std Dev Un-Biased	3.12E-10	2.74E-10	2.16E-10	3.21E-10	1.91E-10	3.59E-10	7.11E-10
Ps90%/90% (+KTL) Un-Biased	1.08E-08	1.49E-08	2.23E-08	3.53E-08	5.94E-08	5.55E-08	4.20E-08
Ps90%/90% (-KTL) Un-Biased	9.10E-09	1.34E-08	2.11E-08	3.35E-08	5.84E-08	5.35E-08	3.81E-08
Specification MIN	-3.00E-08	-7.50E-08	-1.00E-07	-1.75E-07	-2.50E-07	-2.50E-07	-2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	3.00E-08	7.50E-08	1.00E-07	1.75E-07	2.50E-07	2.50E-07	2.50E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

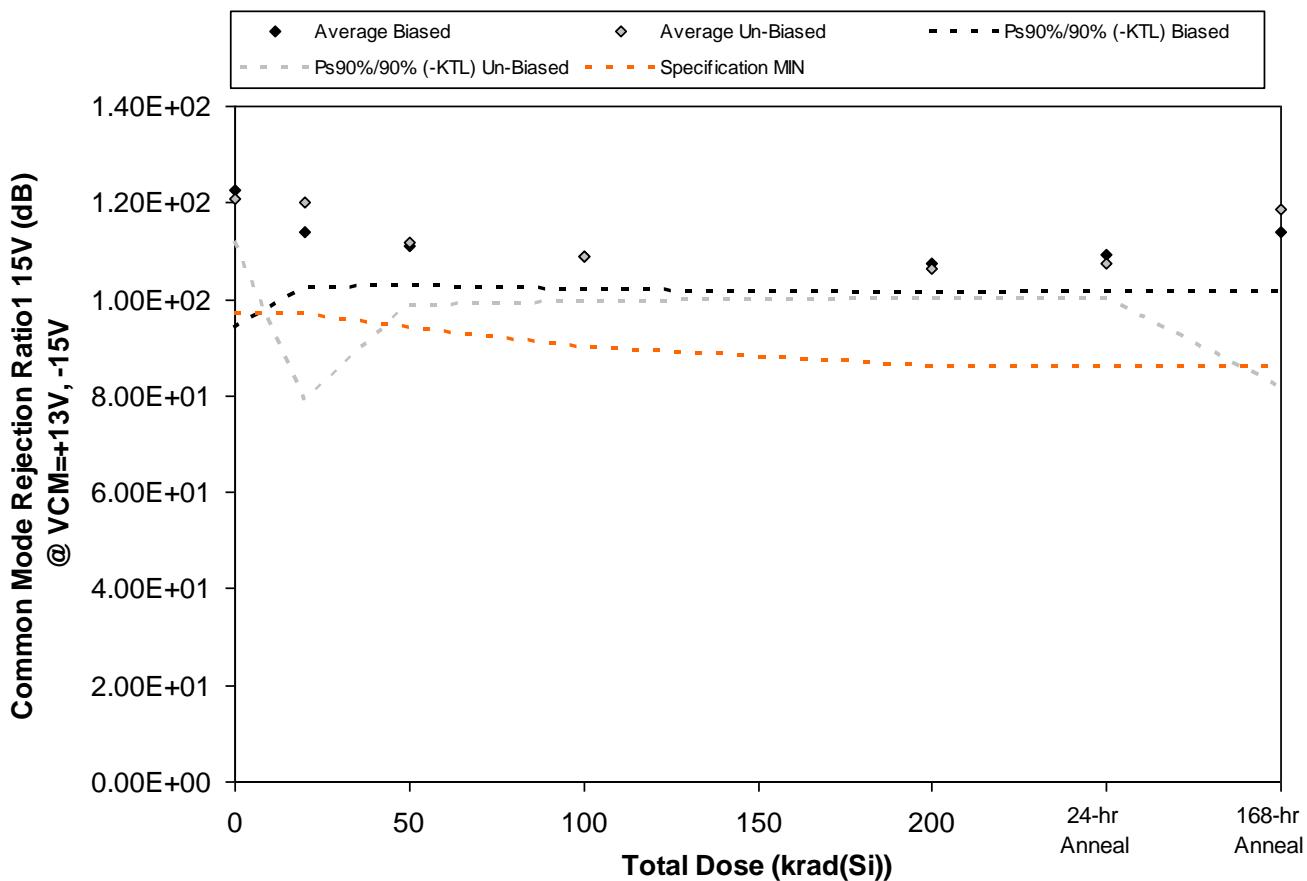


Figure 5.11. Plot of Common Mode Rejection Ratio1 15V (dB) @ VCM=+13V, -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.11. Raw data for Common Mode Rejection Ratio1 15V (dB) @ VCM=+13V, -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio1 15V (dB) @ VCM=+13V, -15V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.19E+02	1.13E+02	1.10E+02	1.09E+02	1.07E+02	1.09E+02	1.14E+02
28	1.38E+02	1.19E+02	1.15E+02	1.12E+02	1.10E+02	1.13E+02	1.19E+02
29	1.15E+02	1.11E+02	1.09E+02	1.07E+02	1.06E+02	1.07E+02	1.10E+02
30	1.28E+02	1.17E+02	1.13E+02	1.11E+02	1.09E+02	1.11E+02	1.17E+02
31	1.13E+02	1.09E+02	1.08E+02	1.06E+02	1.05E+02	1.06E+02	1.09E+02
32	1.25E+02	1.15E+02	1.11E+02	1.09E+02	1.07E+02	1.08E+02	1.15E+02
33	1.16E+02	1.11E+02	1.08E+02	1.06E+02	1.04E+02	1.05E+02	1.11E+02
34	1.20E+02	1.47E+02	1.20E+02	1.15E+02	1.10E+02	1.12E+02	1.42E+02
35	1.21E+02	1.14E+02	1.10E+02	1.08E+02	1.05E+02	1.06E+02	1.12E+02
36	1.21E+02	1.14E+02	1.10E+02	1.07E+02	1.05E+02	1.07E+02	1.13E+02
37	1.21E+02	1.21E+02	1.21E+02	1.21E+02	1.21E+02	1.21E+02	1.22E+02
38	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02
Biased Statistics							
Average Biased	1.23E+02	1.14E+02	1.11E+02	1.09E+02	1.07E+02	1.09E+02	1.14E+02
Std Dev Biased	1.04E+01	4.24E+00	3.07E+00	2.52E+00	2.14E+00	2.81E+00	4.41E+00
Ps90%/90% (+KTL) Biased	1.51E+02	1.26E+02	1.19E+02	1.16E+02	1.13E+02	1.17E+02	1.26E+02
Ps90%/90% (-KTL) Biased	9.41E+01	1.02E+02	1.03E+02	1.02E+02	1.01E+02	1.02E+02	1.02E+02
Un-Biased Statistics							
Average Un-Biased	1.21E+02	1.20E+02	1.12E+02	1.09E+02	1.06E+02	1.08E+02	1.19E+02
Std Dev Un-Biased	3.27E+00	1.50E+01	4.81E+00	3.42E+00	2.21E+00	2.67E+00	1.34E+01
Ps90%/90% (+KTL) Un-Biased	1.30E+02	1.61E+02	1.25E+02	1.18E+02	1.12E+02	1.15E+02	1.55E+02
Ps90%/90% (-KTL) Un-Biased	1.12E+02	7.89E+01	9.87E+01	9.96E+01	1.00E+02	1.00E+02	8.19E+01
Specification MIN	9.70E+01	9.70E+01	9.40E+01	9.00E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

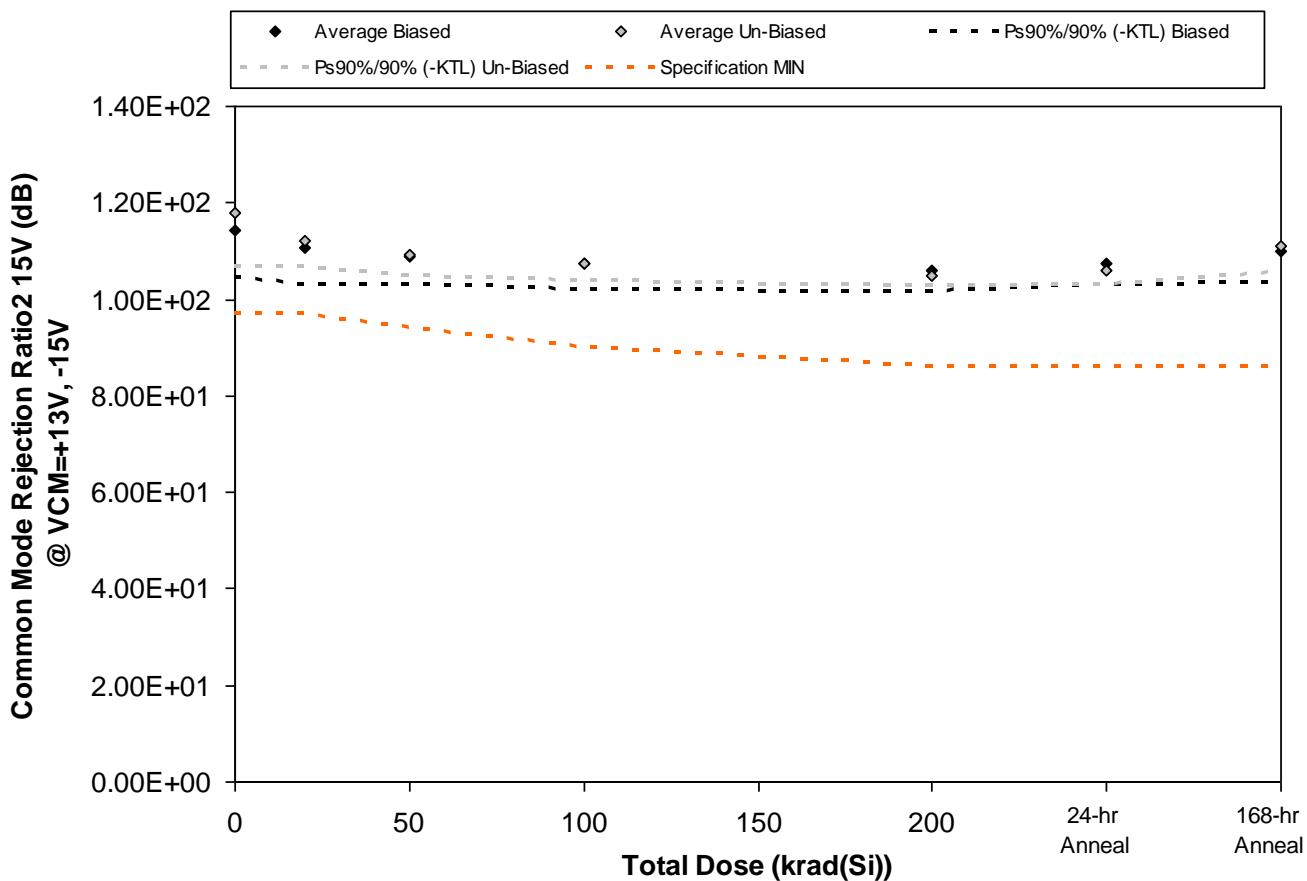


Figure 5.12. Plot of Common Mode Rejection Ratio2 15V (dB) @ VCM=+13V, -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.12. Raw data for Common Mode Rejection Ratio2 15V (dB) @ VCM=+13V, -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio2 15V (dB) @ VCM=+13V, -15V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.19E+02	1.14E+02	1.11E+02	1.09E+02	1.07E+02	1.09E+02	1.12E+02
28	1.17E+02	1.13E+02	1.11E+02	1.09E+02	1.08E+02	1.09E+02	1.12E+02
29	1.10E+02	1.08E+02	1.06E+02	1.05E+02	1.04E+02	1.05E+02	1.07E+02
30	1.14E+02	1.10E+02	1.09E+02	1.08E+02	1.06E+02	1.08E+02	1.10E+02
31	1.12E+02	1.09E+02	1.07E+02	1.06E+02	1.04E+02	1.07E+02	1.08E+02
32	1.18E+02	1.13E+02	1.10E+02	1.08E+02	1.06E+02	1.07E+02	1.11E+02
33	1.17E+02	1.12E+02	1.09E+02	1.07E+02	1.05E+02	1.06E+02	1.11E+02
34	1.25E+02	1.15E+02	1.12E+02	1.09E+02	1.06E+02	1.08E+02	1.15E+02
35	1.14E+02	1.10E+02	1.08E+02	1.06E+02	1.04E+02	1.05E+02	1.09E+02
36	1.16E+02	1.11E+02	1.09E+02	1.07E+02	1.05E+02	1.05E+02	1.11E+02
37	1.27E+02	1.26E+02	1.26E+02	1.27E+02	1.26E+02	1.26E+02	1.26E+02
38	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02
Biased Statistics							
Average Biased	1.14E+02	1.11E+02	1.09E+02	1.07E+02	1.06E+02	1.08E+02	1.10E+02
Std Dev Biased	3.59E+00	2.76E+00	2.07E+00	1.90E+00	1.46E+00	1.63E+00	2.34E+00
Ps90%/90% (+KTL) Biased	1.24E+02	1.18E+02	1.14E+02	1.12E+02	1.10E+02	1.12E+02	1.16E+02
Ps90%/90% (-KTL) Biased	1.05E+02	1.03E+02	1.03E+02	1.02E+02	1.02E+02	1.03E+02	1.04E+02
Un-Biased Statistics							
Average Un-Biased	1.18E+02	1.12E+02	1.09E+02	1.07E+02	1.05E+02	1.06E+02	1.11E+02
Std Dev Un-Biased	4.11E+00	2.05E+00	1.62E+00	1.32E+00	8.99E-01	1.07E+00	2.07E+00
Ps90%/90% (+KTL) Un-Biased	1.29E+02	1.18E+02	1.14E+02	1.11E+02	1.08E+02	1.09E+02	1.17E+02
Ps90%/90% (-KTL) Un-Biased	1.07E+02	1.07E+02	1.05E+02	1.04E+02	1.03E+02	1.03E+02	1.06E+02
Specification MIN	9.70E+01	9.70E+01	9.40E+01	9.00E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

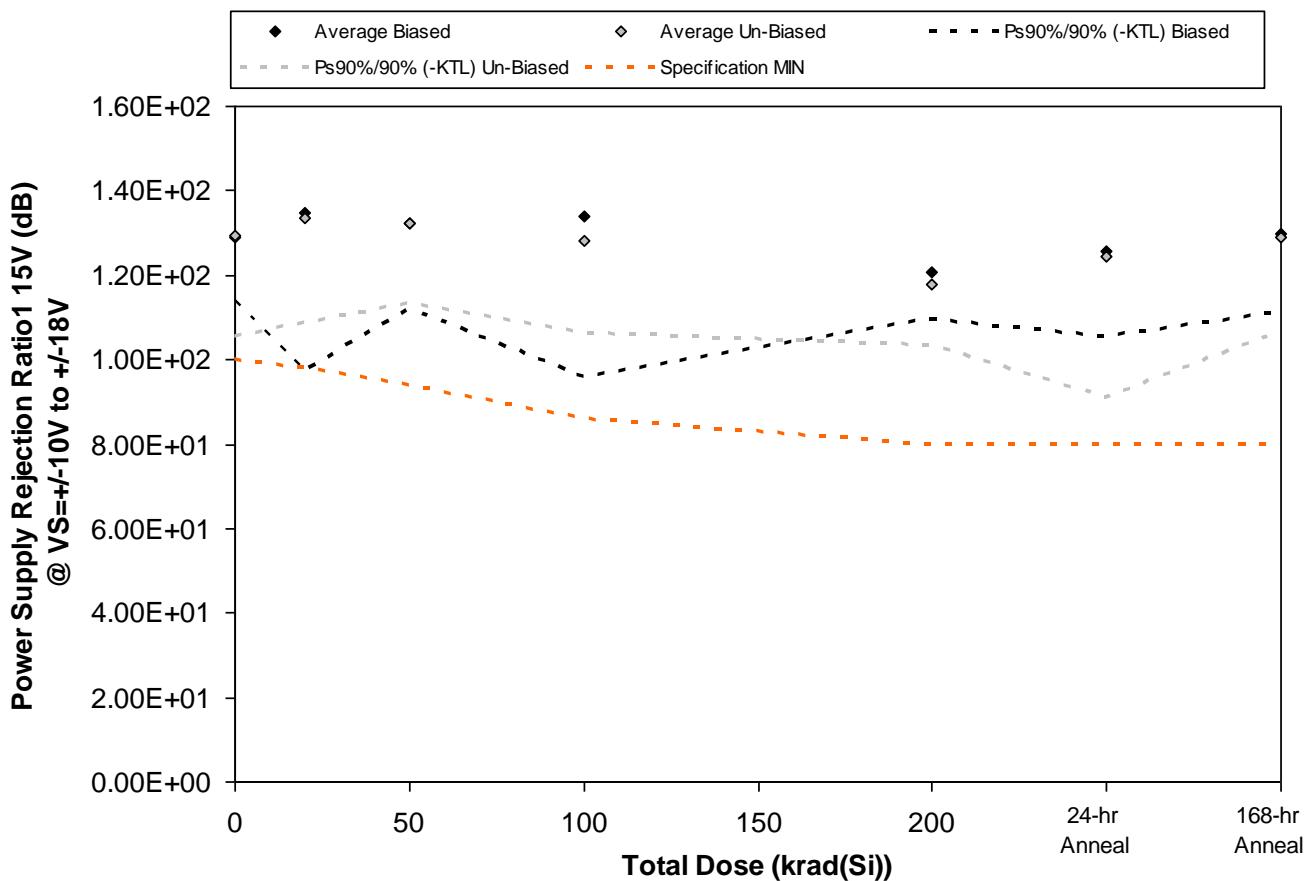


Figure 5.13. Plot of Power Supply Rejection Ratio1 15V (dB) @ VS=+/-10V to +/-18V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.13. Raw data for Power Supply Rejection Ratio1 15V (dB) @ VS=+/-10V to +/-18V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio1 15V (dB) @ VS=+/-10V to +/-18V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.22E+02	1.25E+02	1.29E+02	1.42E+02	1.22E+02	1.34E+02	1.22E+02
28	1.25E+02	1.28E+02	1.34E+02	1.54E+02	1.27E+02	1.33E+02	1.28E+02
29	1.31E+02	1.39E+02	1.42E+02	1.28E+02	1.21E+02	1.24E+02	1.37E+02
30	1.36E+02	1.57E+02	1.33E+02	1.26E+02	1.19E+02	1.22E+02	1.36E+02
31	1.30E+02	1.25E+02	1.22E+02	1.20E+02	1.16E+02	1.17E+02	1.25E+02
32	1.25E+02	1.28E+02	1.39E+02	1.42E+02	1.18E+02	1.23E+02	1.25E+02
33	1.43E+02	1.39E+02	1.29E+02	1.22E+02	1.15E+02	1.18E+02	1.33E+02
34	1.19E+02	1.21E+02	1.23E+02	1.28E+02	1.27E+02	1.46E+02	1.19E+02
35	1.32E+02	1.44E+02	1.32E+02	1.23E+02	1.15E+02	1.17E+02	1.40E+02
36	1.29E+02	1.35E+02	1.39E+02	1.25E+02	1.16E+02	1.18E+02	1.29E+02
37	1.22E+02	1.22E+02	1.22E+02	1.22E+02	1.22E+02	1.22E+02	1.22E+02
38	1.40E+02	1.39E+02	1.41E+02	1.42E+02	1.40E+02	1.41E+02	1.41E+02
Biased Statistics							
Average Biased	1.29E+02	1.35E+02	1.32E+02	1.34E+02	1.21E+02	1.26E+02	1.30E+02
Std Dev Biased	5.52E+00	1.36E+01	7.26E+00	1.38E+01	4.09E+00	7.44E+00	6.74E+00
Ps90%/90% (+KTL) Biased	1.44E+02	1.72E+02	1.52E+02	1.72E+02	1.32E+02	1.46E+02	1.48E+02
Ps90%/90% (-KTL) Biased	1.14E+02	9.73E+01	1.12E+02	9.59E+01	1.10E+02	1.05E+02	1.11E+02
Un-Biased Statistics							
Average Un-Biased	1.29E+02	1.33E+02	1.32E+02	1.28E+02	1.18E+02	1.24E+02	1.29E+02
Std Dev Un-Biased	8.79E+00	8.94E+00	6.90E+00	8.01E+00	5.34E+00	1.21E+01	8.17E+00
Ps90%/90% (+KTL) Un-Biased	1.54E+02	1.58E+02	1.51E+02	1.50E+02	1.33E+02	1.57E+02	1.51E+02
Ps90%/90% (-KTL) Un-Biased	1.05E+02	1.09E+02	1.13E+02	1.06E+02	1.03E+02	9.10E+01	1.07E+02
Specification MIN	1.00E+02	9.80E+01	9.40E+01	8.60E+01	8.00E+01	8.00E+01	8.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

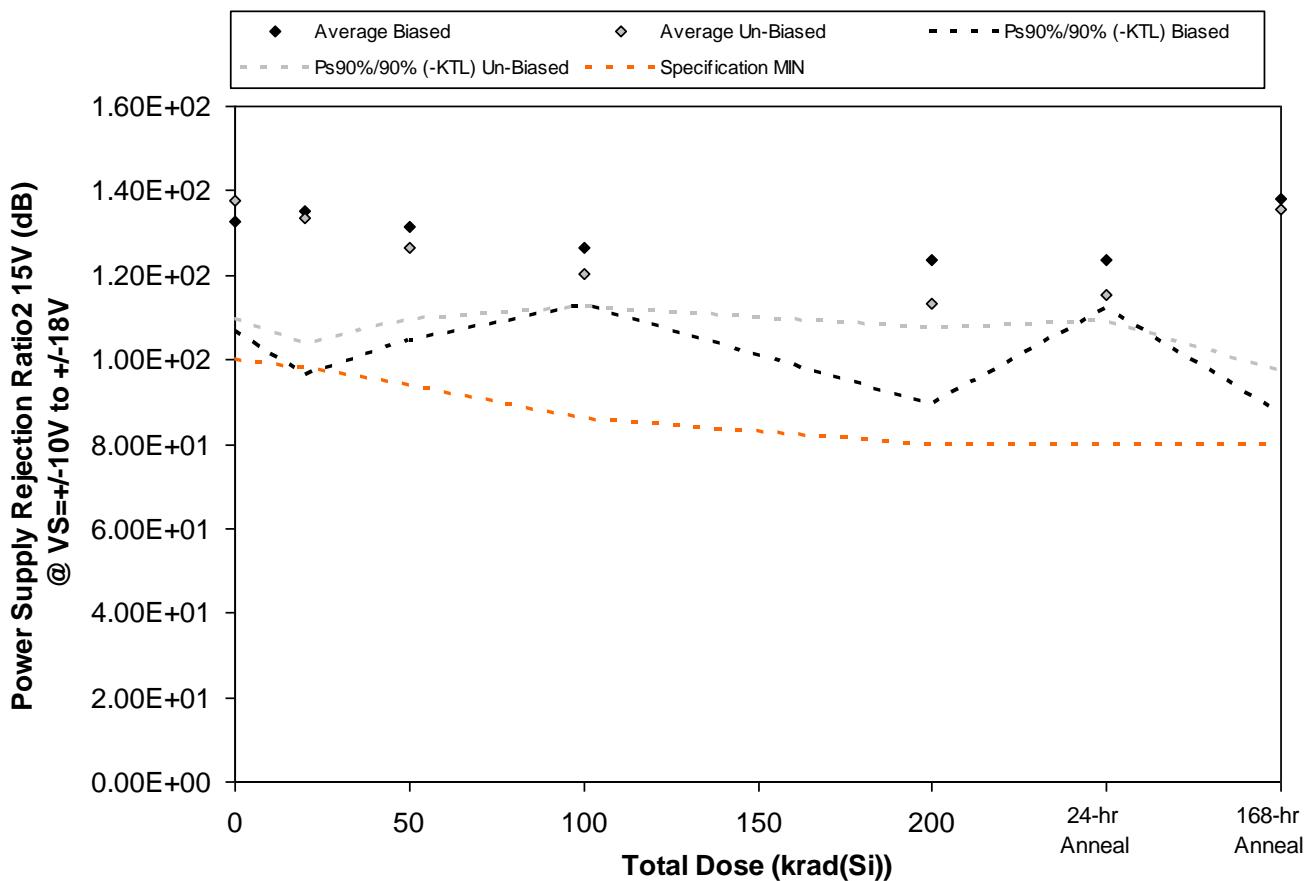


Figure 5.14. Plot of Power Supply Rejection Ratio2 15V (dB) @ VS=+/-10V to +/-18V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.14. Raw data for Power Supply Rejection Ratio2 15V (dB) @ VS=+/-10V to +/-18V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio2 15V (dB) @ VS=+/-10V to +/-18V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.27E+02	1.31E+02	1.47E+02	1.34E+02	1.18E+02	1.25E+02	1.34E+02
28	1.21E+02	1.23E+02	1.25E+02	1.28E+02	1.46E+02	1.30E+02	1.21E+02
29	1.46E+02	1.34E+02	1.28E+02	1.23E+02	1.19E+02	1.22E+02	1.43E+02
30	1.35E+02	1.59E+02	1.34E+02	1.27E+02	1.20E+02	1.24E+02	1.68E+02
31	1.35E+02	1.28E+02	1.24E+02	1.21E+02	1.16E+02	1.18E+02	1.25E+02
32	1.35E+02	1.29E+02	1.24E+02	1.20E+02	1.13E+02	1.15E+02	1.27E+02
33	1.54E+02	1.35E+02	1.27E+02	1.20E+02	1.13E+02	1.16E+02	1.40E+02
34	1.32E+02	1.52E+02	1.37E+02	1.25E+02	1.17E+02	1.19E+02	1.58E+02
35	1.27E+02	1.23E+02	1.20E+02	1.17E+02	1.11E+02	1.13E+02	1.23E+02
36	1.40E+02	1.29E+02	1.26E+02	1.20E+02	1.12E+02	1.14E+02	1.31E+02
37	1.26E+02	1.26E+02	1.26E+02	1.25E+02	1.26E+02	1.26E+02	1.26E+02
38	1.38E+02	1.39E+02	1.39E+02	1.38E+02	1.39E+02	1.37E+02	1.38E+02
Biased Statistics							
Average Biased	1.33E+02	1.35E+02	1.32E+02	1.27E+02	1.24E+02	1.24E+02	1.38E+02
Std Dev Biased	9.50E+00	1.42E+01	9.78E+00	4.96E+00	1.25E+01	4.27E+00	1.86E+01
Ps90%/90% (+KTL) Biased	1.59E+02	1.74E+02	1.58E+02	1.40E+02	1.58E+02	1.35E+02	1.89E+02
Ps90%/90% (-KTL) Biased	1.07E+02	9.62E+01	1.05E+02	1.13E+02	8.94E+01	1.12E+02	8.72E+01
Un-Biased Statistics							
Average Un-Biased	1.38E+02	1.34E+02	1.27E+02	1.20E+02	1.13E+02	1.15E+02	1.36E+02
Std Dev Un-Biased	1.02E+01	1.08E+01	6.18E+00	2.93E+00	2.01E+00	2.17E+00	1.40E+01
Ps90%/90% (+KTL) Un-Biased	1.65E+02	1.63E+02	1.44E+02	1.28E+02	1.19E+02	1.21E+02	1.74E+02
Ps90%/90% (-KTL) Un-Biased	1.10E+02	1.04E+02	1.10E+02	1.12E+02	1.08E+02	1.09E+02	9.73E+01
Specification MIN	1.00E+02	9.80E+01	9.40E+01	8.60E+01	8.00E+01	8.00E+01	8.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

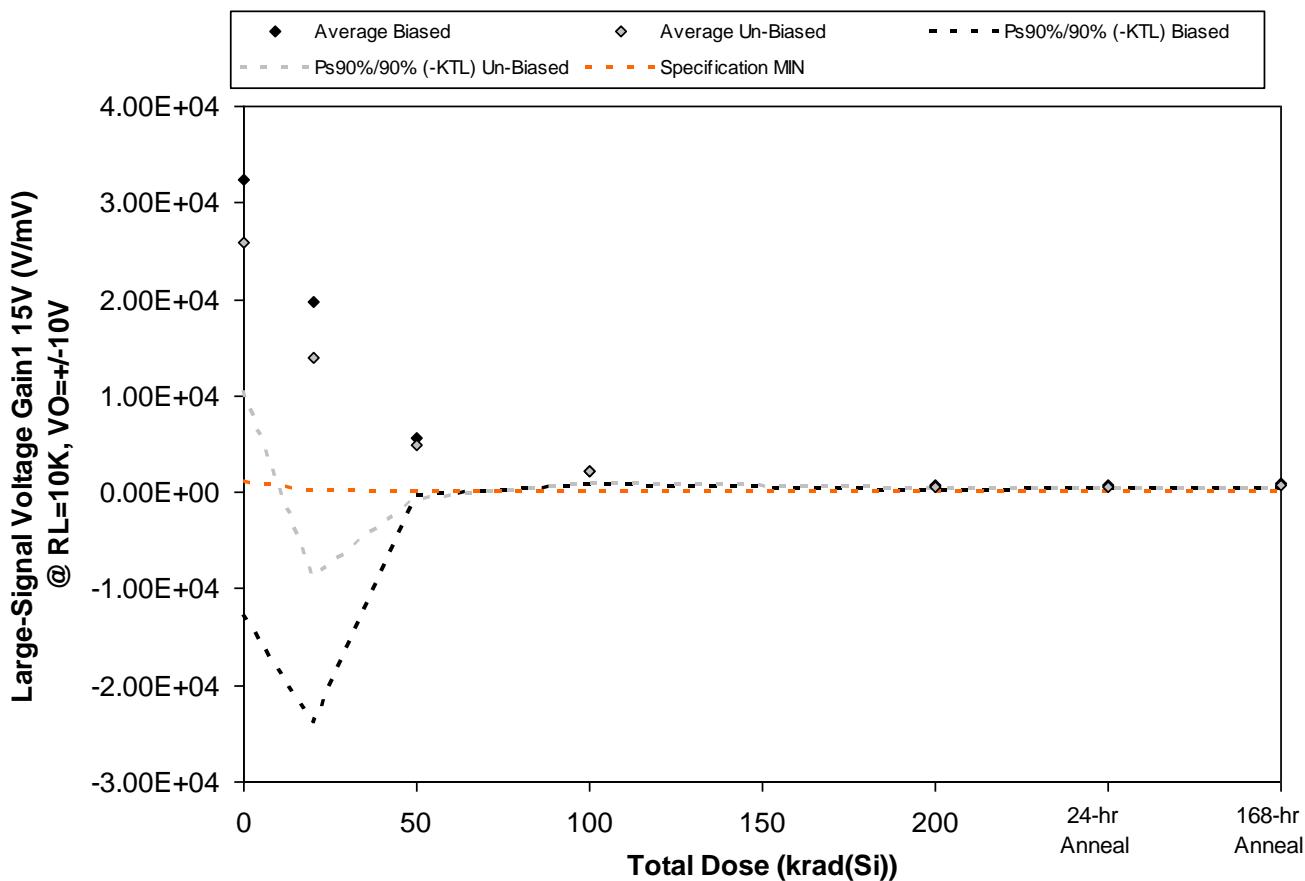


Figure 5.15. Plot of Large-Signal Voltage Gain1 15V (V/mV) @ RL=10K, VO=+/-10V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.15. Raw data for Large-Signal Voltage Gain1 15V (V/mV) @ RL=10K, VO=+/-10V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Large-Signal Voltage Gain1 15V (V/mV) @ RL=10K, VO=+/-10V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	2.43E+04	1.21E+04	4.47E+03	1.94E+03	5.03E+02	6.00E+02	8.32E+02
28	5.11E+04	4.73E+04	9.11E+03	3.04E+03	9.91E+02	9.33E+02	1.30E+03
29	1.93E+04	1.04E+04	3.88E+03	1.82E+03	6.26E+02	6.61E+02	8.15E+02
30	4.97E+04	2.02E+04	6.66E+03	2.27E+03	7.79E+02	7.61E+02	9.07E+02
31	1.80E+04	8.78E+03	4.17E+03	1.85E+03	6.90E+02	6.40E+02	7.61E+02
32	2.99E+04	1.19E+04	4.44E+03	2.44E+03	6.61E+02	7.08E+02	8.78E+02
33	2.61E+04	1.02E+04	3.73E+03	1.88E+03	5.66E+02	6.16E+02	6.95E+02
34	3.28E+04	2.87E+04	8.40E+03	2.85E+03	7.43E+02	8.17E+02	1.09E+03
35	2.08E+04	9.90E+03	3.52E+03	1.96E+03	5.40E+02	5.38E+02	6.54E+02
36	2.00E+04	9.28E+03	4.18E+03	1.88E+03	5.66E+02	6.04E+02	7.15E+02
37	1.37E+06	7.93E+05	2.43E+05	4.79E+05	2.43E+05	2.48E+05	8.62E+04
38	7.56E+04	6.21E+04	5.21E+04	1.07E+05	5.43E+04	5.68E+04	1.70E+05
Biased Statistics							
Average Biased	3.25E+04	1.98E+04	5.66E+03	2.18E+03	7.18E+02	7.19E+02	9.23E+02
Std Dev Biased	1.65E+04	1.60E+04	2.22E+03	5.14E+02	1.83E+02	1.34E+02	2.17E+02
Ps90%/90% (+KTL) Biased	7.79E+04	6.36E+04	1.17E+04	3.59E+03	1.22E+03	1.09E+03	1.52E+03
Ps90%/90% (-KTL) Biased	-1.29E+04	-2.41E+04	-4.21E+02	7.74E+02	2.16E+02	3.53E+02	3.29E+02
Un-Biased Statistics							
Average Un-Biased	2.59E+04	1.40E+04	4.85E+03	2.20E+03	6.15E+02	6.57E+02	8.07E+02
Std Dev Un-Biased	5.59E+03	8.30E+03	2.02E+03	4.30E+02	8.50E+01	1.08E+02	1.80E+02
Ps90%/90% (+KTL) Un-Biased	4.12E+04	3.68E+04	1.04E+04	3.38E+03	8.48E+02	9.53E+02	1.30E+03
Ps90%/90% (-KTL) Un-Biased	1.06E+04	-8.75E+03	-6.76E+02	1.02E+03	3.82E+02	3.60E+02	3.12E+02
Specification MIN	1.20E+03	2.00E+02	1.00E+02	5.00E+01	2.50E+01	2.50E+01	2.50E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

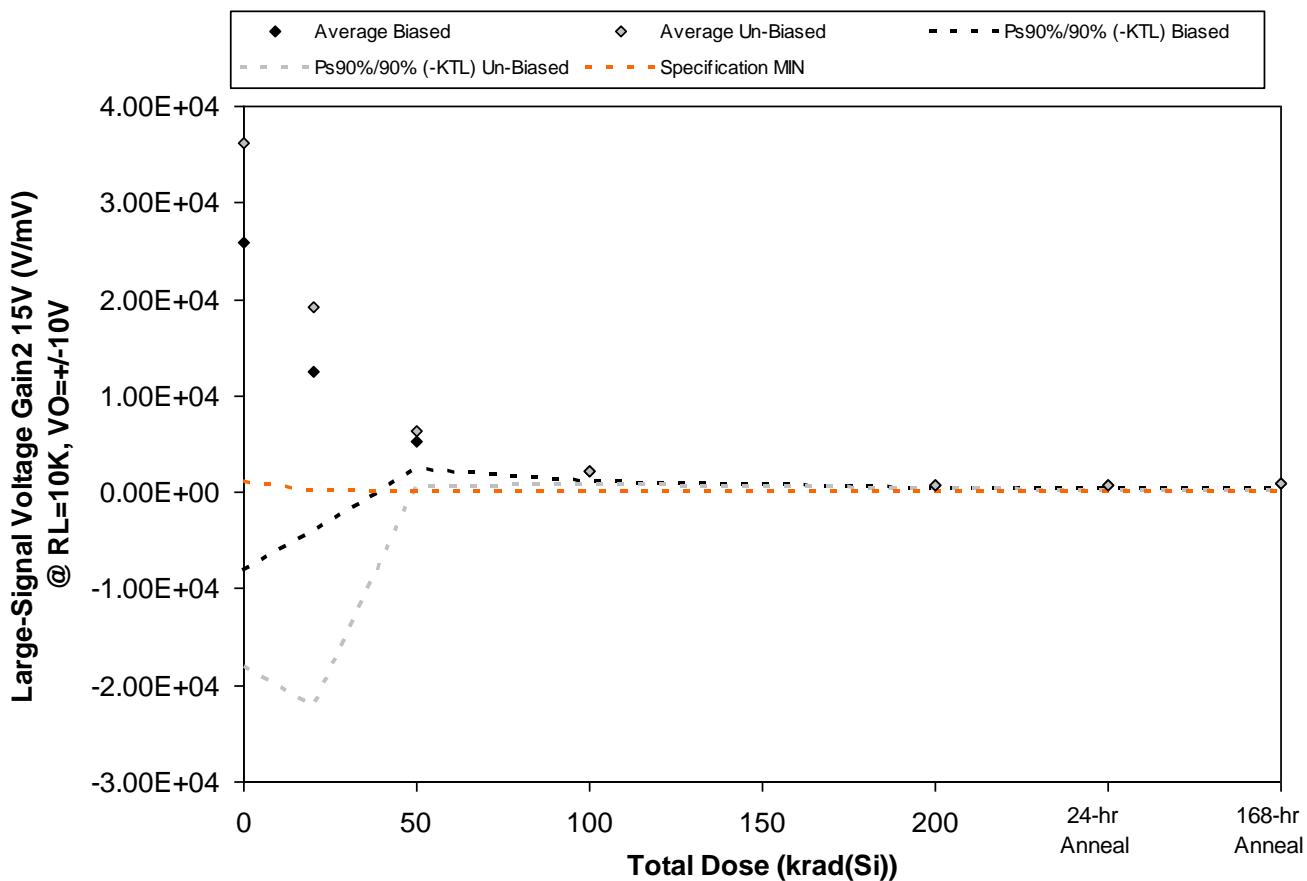


Figure 5.16. Plot of Large-Signal Voltage Gain2 15V (V/mV) @ RL=10K, VO=+/-10V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.16. Raw data for Large-Signal Voltage Gain2 15V (V/mV) @ RL=10K, VO=+/-10V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Large-Signal Voltage Gain2 15V (V/mV) @ RL=10K, VO=+/-10V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	4.32E+04	1.31E+04	5.62E+03	2.09E+03	5.20E+02	6.34E+02	8.45E+02
28	3.42E+04	2.26E+04	6.93E+03	2.75E+03	9.05E+02	9.06E+02	1.32E+03
29	1.79E+04	9.68E+03	4.32E+03	1.83E+03	6.97E+02	6.49E+02	8.24E+02
30	1.99E+04	9.80E+03	4.73E+03	2.06E+03	7.73E+02	7.69E+02	9.74E+02
31	1.39E+04	7.22E+03	4.70E+03	1.86E+03	6.85E+02	6.85E+02	7.89E+02
32	7.09E+04	2.15E+04	7.02E+03	2.16E+03	7.56E+02	7.64E+02	9.53E+02
33	2.27E+04	1.15E+04	5.07E+03	2.02E+03	6.05E+02	6.64E+02	7.20E+02
34	2.93E+04	4.48E+04	9.56E+03	3.19E+03	8.64E+02	9.36E+02	1.22E+03
35	2.57E+04	1.03E+04	4.29E+03	1.83E+03	5.39E+02	5.44E+02	6.73E+02
36	3.23E+04	8.25E+03	5.47E+03	1.98E+03	6.23E+02	6.30E+02	7.54E+02
37	4.50E+04	4.23E+04	7.50E+04	7.42E+04	6.65E+04	6.19E+04	4.42E+04
38	4.05E+04	3.71E+04	6.38E+04	7.48E+04	4.78E+04	6.62E+04	7.27E+04
Biased Statistics							
Average Biased	2.58E+04	1.25E+04	5.26E+03	2.12E+03	7.16E+02	7.29E+02	9.51E+02
Std Dev Biased	1.24E+04	6.04E+03	1.05E+03	3.71E+02	1.40E+02	1.12E+02	2.19E+02
Ps90%/90% (+KTL) Biased	5.97E+04	2.90E+04	8.13E+03	3.13E+03	1.10E+03	1.04E+03	1.55E+03
Ps90%/90% (-KTL) Biased	-8.10E+03	-4.07E+03	2.38E+03	1.10E+03	3.31E+02	4.21E+02	3.51E+02
Un-Biased Statistics							
Average Un-Biased	3.62E+04	1.93E+04	6.28E+03	2.24E+03	6.77E+02	7.08E+02	8.63E+02
Std Dev Un-Biased	1.98E+04	1.52E+04	2.09E+03	5.46E+02	1.31E+02	1.50E+02	2.24E+02
Ps90%/90% (+KTL) Un-Biased	9.04E+04	6.08E+04	1.20E+04	3.73E+03	1.04E+03	1.12E+03	1.48E+03
Ps90%/90% (-KTL) Un-Biased	-1.80E+04	-2.23E+04	5.64E+02	7.39E+02	3.19E+02	2.96E+02	2.48E+02
Specification MIN	1.20E+03	2.00E+02	1.00E+02	5.00E+01	2.50E+01	2.50E+01	2.50E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

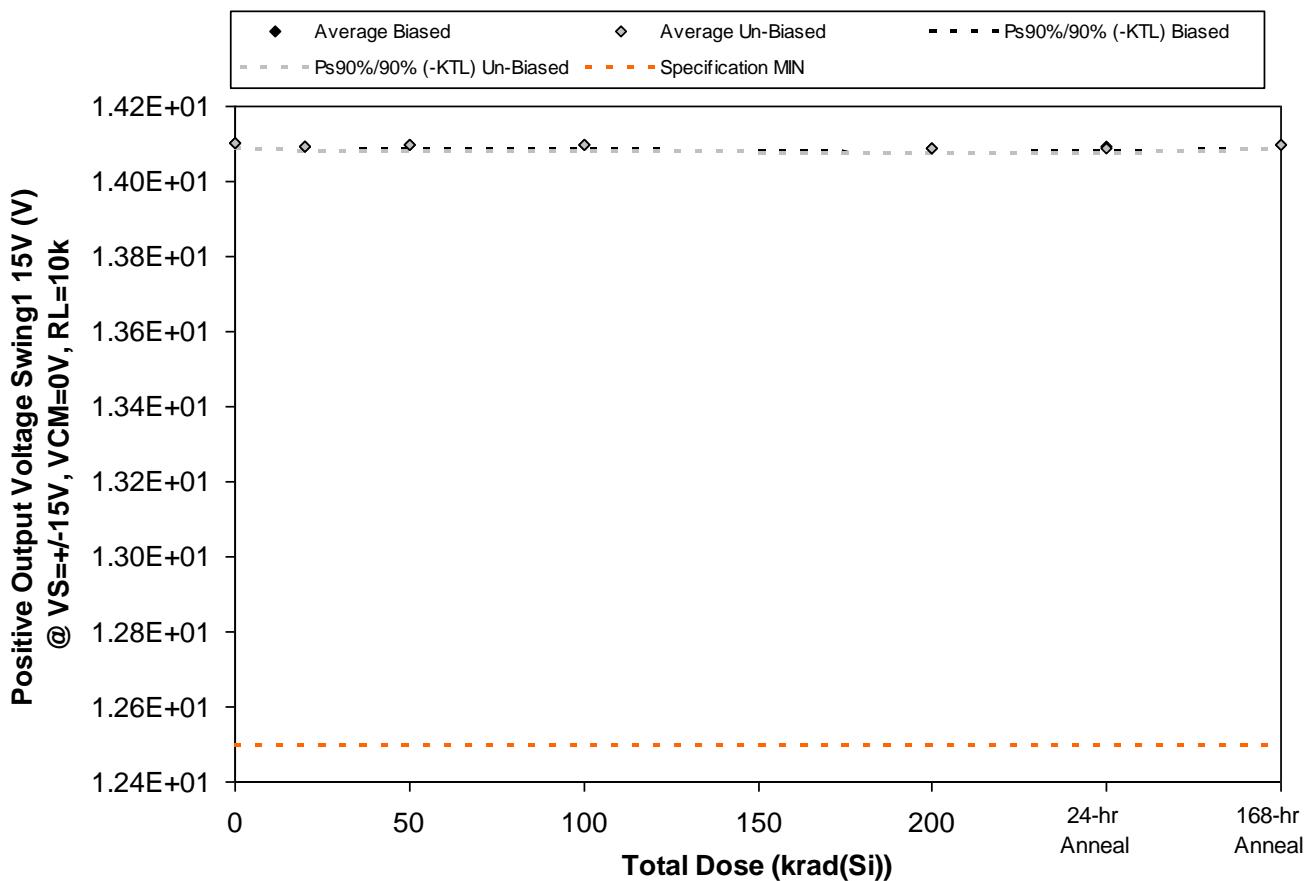


Figure 5.17. Plot of Positive Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.17. Raw data for Positive Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
28	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
29	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
30	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
31	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
32	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
33	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
34	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
35	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
36	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
37	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
38	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Biased Statistics							
Average Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Std Dev Biased	4.36E-03	5.45E-03	4.47E-03	5.17E-03	5.22E-03	5.10E-03	5.66E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Un-Biased Statistics							
Average Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Std Dev Un-Biased	5.43E-03	5.18E-03	6.02E-03	5.55E-03	5.76E-03	6.31E-03	5.76E-03
Ps90%/90% (+KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

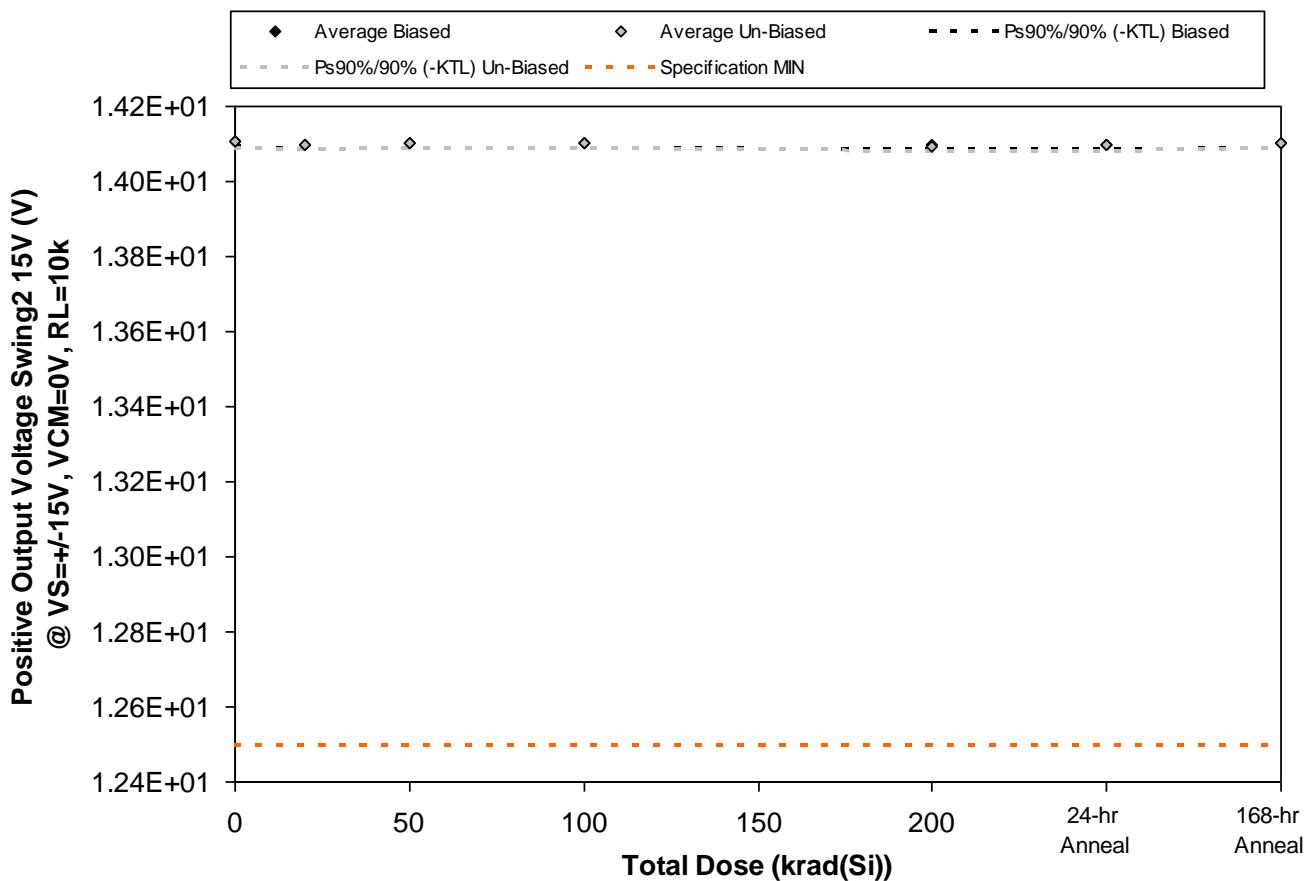


Figure 5.18. Plot of Positive Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.18. Raw data for Positive Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
28	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
29	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
30	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
31	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
32	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
33	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
34	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
35	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
36	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
37	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
38	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Biased Statistics							
Average Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Std Dev Biased	3.96E-03	5.73E-03	5.02E-03	5.37E-03	5.07E-03	5.10E-03	5.12E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Un-Biased Statistics							
Average Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Std Dev Un-Biased	5.54E-03	4.85E-03	5.37E-03	5.46E-03	5.76E-03	6.14E-03	5.76E-03
Ps90%/90% (+KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

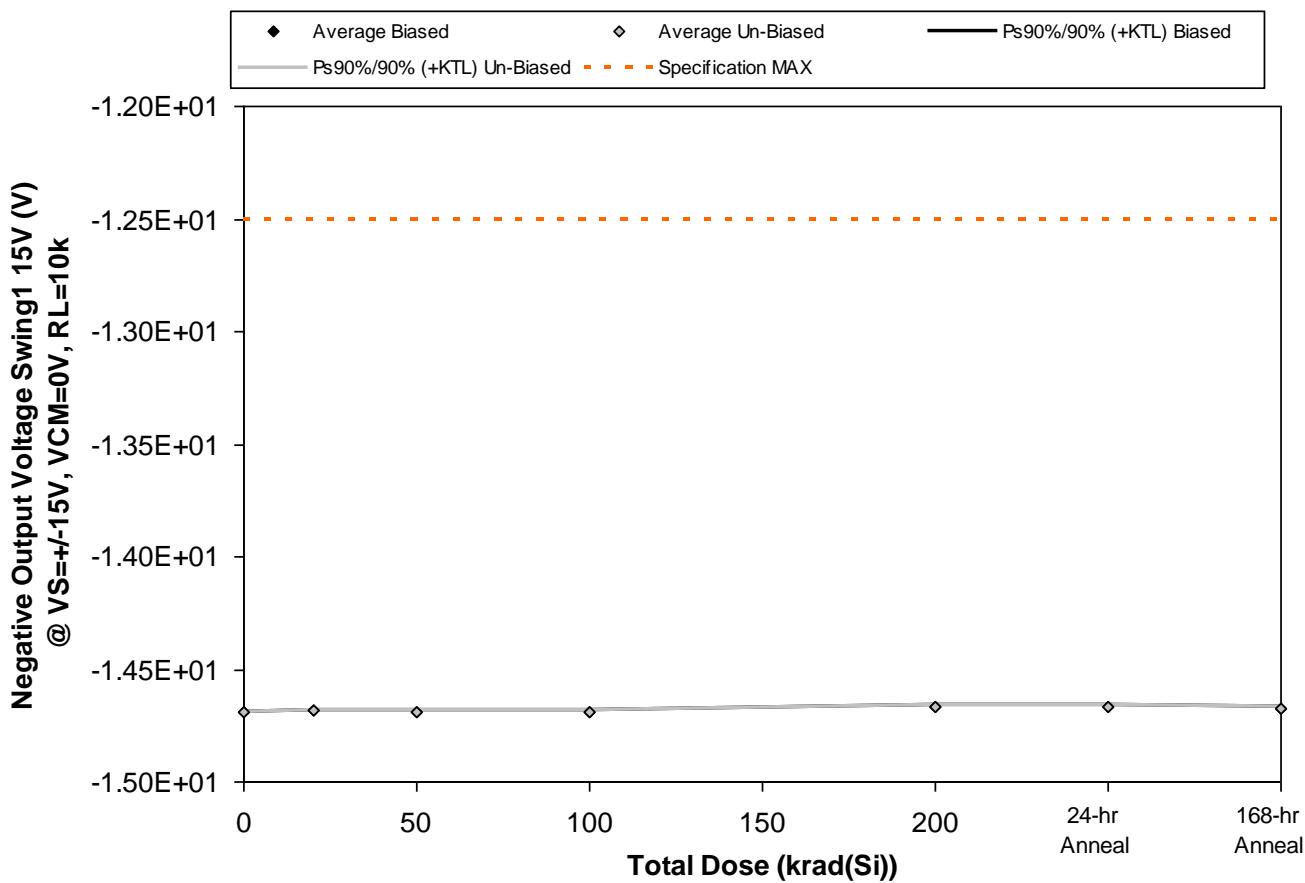


Figure 5.19. Plot of Negative Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.19. Raw data for Negative Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
28	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
29	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
30	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
31	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
32	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
33	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
34	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
35	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
36	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
37	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
38	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Biased Statistics								
Average Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Std Dev Biased		1.14E-03	8.94E-04	1.48E-03	2.28E-03	2.49E-03	2.95E-03	2.95E-03
Ps90%/90% (+KTL) Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Ps90%/90% (-KTL) Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Un-Biased Statistics								
Average Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Std Dev Un-Biased		2.24E-03	2.55E-03	2.19E-03	2.35E-03	2.19E-03	2.28E-03	2.61E-03
Ps90%/90% (+KTL) Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Ps90%/90% (-KTL) Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Specification MAX		-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

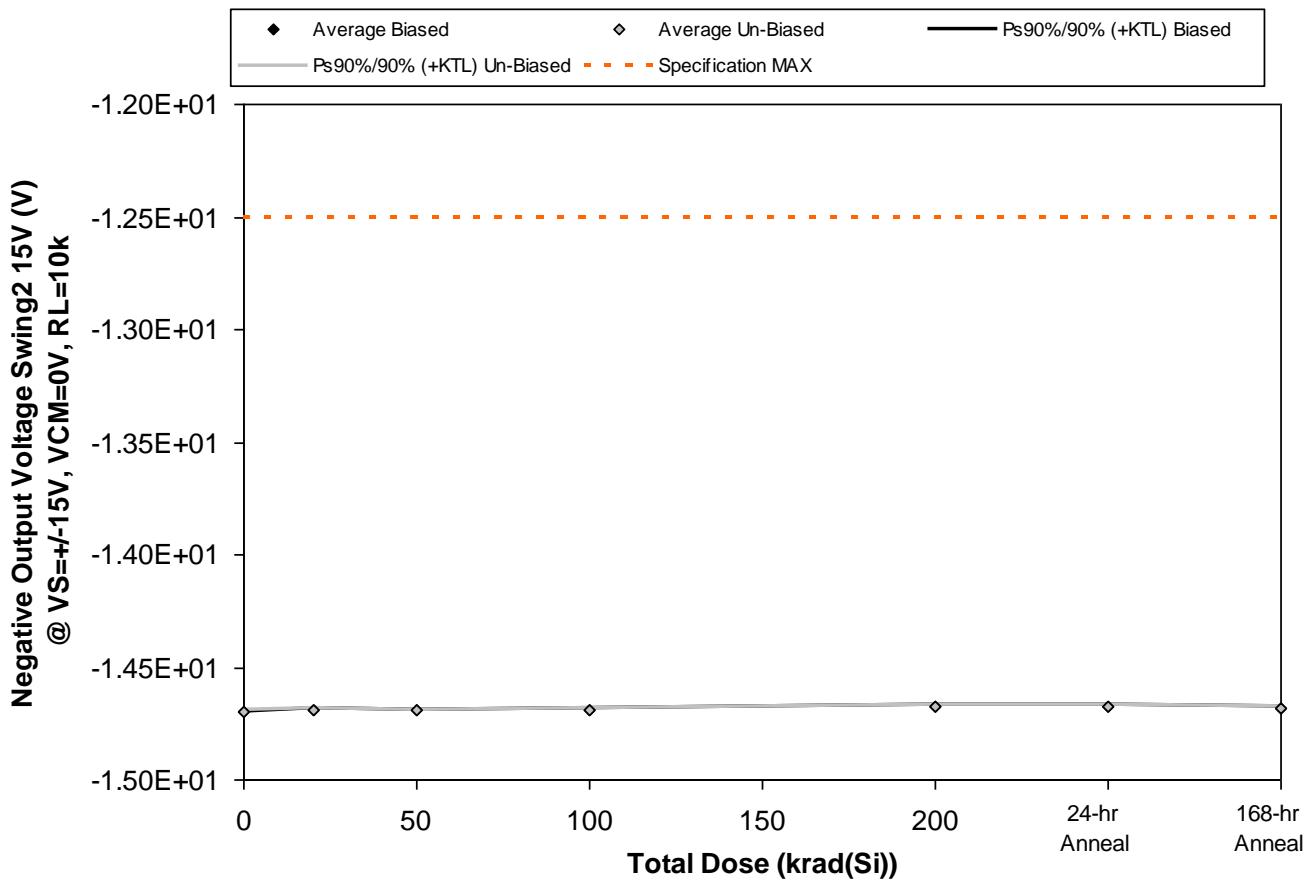


Figure 5.20. Plot of Negative Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.20. Raw data for Negative Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
28	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
29	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
30	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
31	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
32	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
33	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
34	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
35	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
36	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
37	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
38	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Biased Statistics								
Average Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Std Dev Biased		1.10E-03	1.10E-03	1.48E-03	2.24E-03	2.49E-03	2.17E-03	2.61E-03
Ps90%/90% (+KTL) Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Ps90%/90% (-KTL) Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Un-Biased Statistics								
Average Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Std Dev Un-Biased		1.73E-03	2.68E-03	2.19E-03	2.19E-03	2.28E-03	2.19E-03	2.45E-03
Ps90%/90% (+KTL) Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Ps90%/90% (-KTL) Un-Biased		-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01	-1.47E+01
Specification MAX		-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

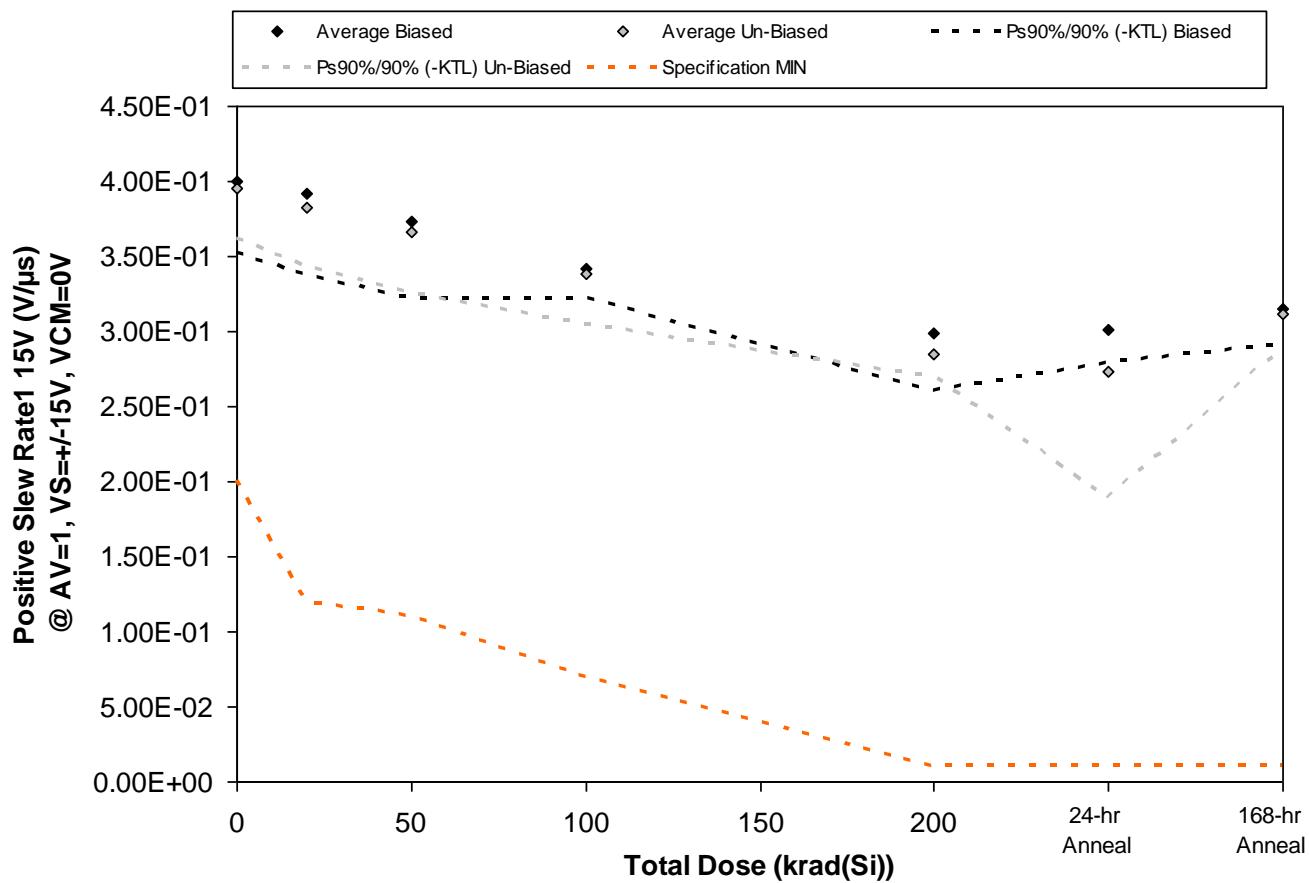


Figure 5.21. Plot of Positive Slew Rate1 15V ($V/\mu s$) @ $AV=1$, $VS=+/-15V$, $VCM=0V$ versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.21. Raw data for Positive Slew Rate1 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	3.96E-01	3.90E-01	3.84E-01	3.36E-01	2.94E-01	3.01E-01	3.11E-01
28	4.29E-01	4.05E-01	4.01E-01	3.46E-01	3.18E-01	3.05E-01	3.31E-01
29	4.00E-01	3.69E-01	3.53E-01	3.43E-01	2.91E-01	3.11E-01	3.12E-01
30	3.81E-01	4.17E-01	3.67E-01	3.33E-01	3.08E-01	3.00E-01	3.12E-01
31	3.96E-01	3.76E-01	3.64E-01	3.50E-01	2.83E-01	2.89E-01	3.12E-01
32	4.06E-01	3.90E-01	3.73E-01	3.56E-01	2.87E-01	2.81E-01	3.13E-01
33	3.98E-01	3.64E-01	3.68E-01	3.36E-01	2.79E-01	2.78E-01	3.09E-01
34	4.01E-01	4.02E-01	3.79E-01	3.40E-01	2.90E-01	3.03E-01	3.25E-01
35	3.96E-01	3.84E-01	3.71E-01	3.22E-01	2.79E-01	2.21E-01	3.04E-01
36	3.74E-01	3.74E-01	3.41E-01	3.35E-01	2.89E-01	2.86E-01	3.05E-01
37	4.16E-01	3.96E-01	3.90E-01	4.01E-01	3.92E-01	3.92E-01	3.91E-01
38	4.02E-01	4.10E-01	4.26E-01	4.03E-01	4.04E-01	3.94E-01	4.14E-01
Biased Statistics							
Average Biased	4.00E-01	3.91E-01	3.74E-01	3.42E-01	2.99E-01	3.01E-01	3.16E-01
Std Dev Biased	1.76E-02	1.99E-02	1.88E-02	7.02E-03	1.40E-02	8.07E-03	8.62E-03
Ps90%/90% (+KTL) Biased	4.49E-01	4.46E-01	4.25E-01	3.61E-01	3.37E-01	3.23E-01	3.39E-01
Ps90%/90% (-KTL) Biased	3.52E-01	3.37E-01	3.22E-01	3.22E-01	2.60E-01	2.79E-01	2.92E-01
Un-Biased Statistics							
Average Un-Biased	3.95E-01	3.83E-01	3.66E-01	3.38E-01	2.85E-01	2.74E-01	3.11E-01
Std Dev Un-Biased	1.23E-02	1.46E-02	1.48E-02	1.22E-02	5.40E-03	3.11E-02	8.50E-03
Ps90%/90% (+KTL) Un-Biased	4.29E-01	4.23E-01	4.07E-01	3.71E-01	3.00E-01	3.59E-01	3.34E-01
Ps90%/90% (-KTL) Un-Biased	3.61E-01	3.43E-01	3.26E-01	3.04E-01	2.70E-01	1.89E-01	2.88E-01
Specification MIN	2.00E-01	1.20E-01	1.10E-01	7.00E-02	1.00E-02	1.00E-02	1.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

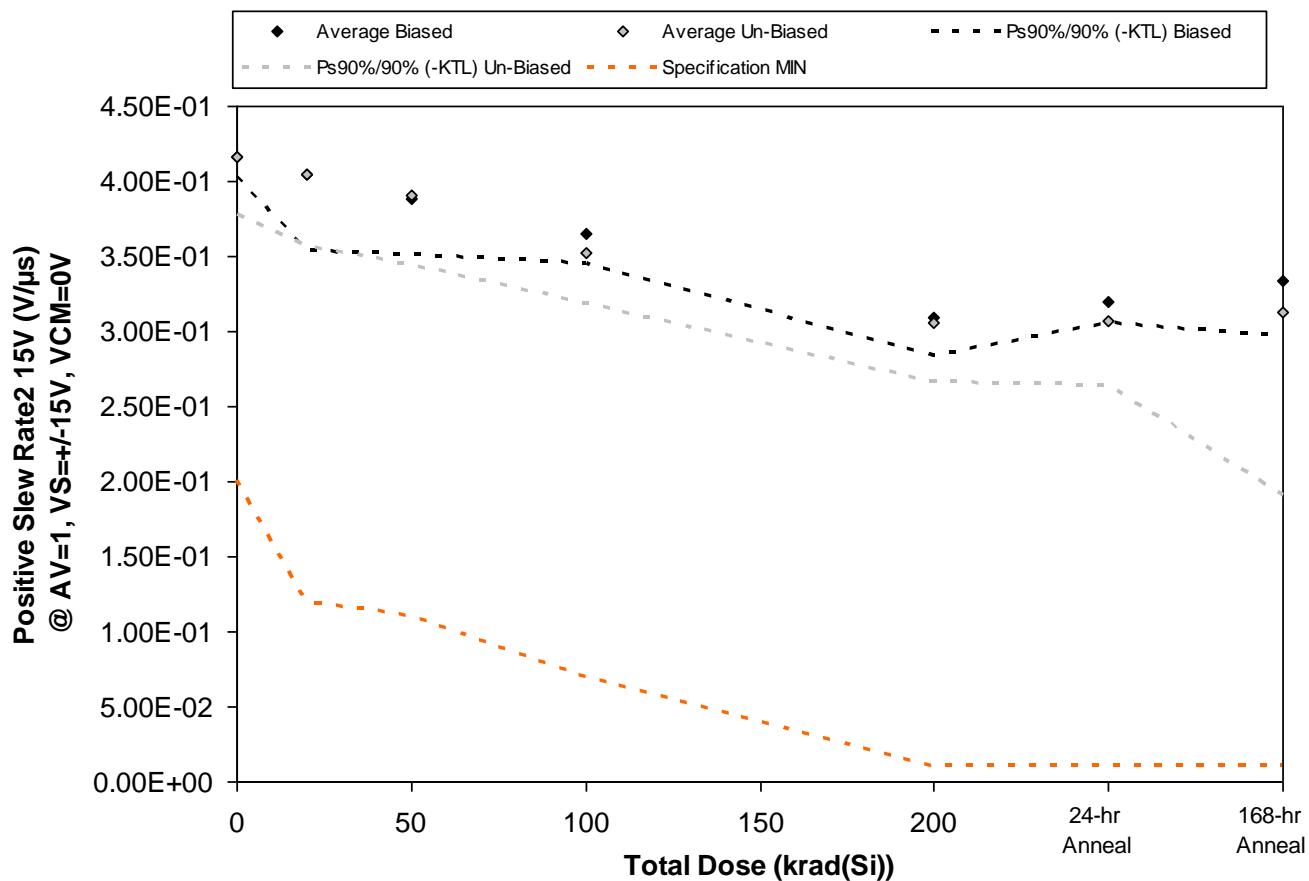


Figure 5.22. Plot of Positive Slew Rate2 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.22. Raw data for Positive Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	4.18E-01	4.27E-01	3.65E-01	3.64E-01	3.09E-01	3.27E-01	3.22E-01
28	4.21E-01	4.20E-01	3.99E-01	3.76E-01	3.19E-01	3.21E-01	3.45E-01
29	4.11E-01	3.82E-01	3.90E-01	3.61E-01	2.99E-01	3.19E-01	3.27E-01
30	4.11E-01	3.95E-01	3.93E-01	3.57E-01	3.20E-01	3.13E-01	3.51E-01
31	4.21E-01	3.99E-01	3.95E-01	3.67E-01	3.02E-01	3.19E-01	3.23E-01
32	4.15E-01	4.13E-01	3.98E-01	3.50E-01	2.97E-01	3.14E-01	3.27E-01
33	4.38E-01	4.02E-01	3.69E-01	3.48E-01	3.01E-01	2.98E-01	3.20E-01
34	4.20E-01	4.30E-01	4.07E-01	3.73E-01	3.21E-01	3.28E-01	3.59E-01
35	4.05E-01	3.87E-01	3.77E-01	3.44E-01	2.89E-01	2.87E-01	3.19E-01
36	4.04E-01	3.91E-01	4.03E-01	3.45E-01	3.20E-01	3.08E-01	2.39E-01
37	4.25E-01	4.38E-01	4.29E-01	4.56E-01	4.13E-01	4.17E-01	4.40E-01
38	4.17E-01	4.28E-01	4.38E-01	4.30E-01	4.36E-01	3.88E-01	4.29E-01
Biased Statistics							
Average Biased	4.16E-01	4.05E-01	3.88E-01	3.65E-01	3.10E-01	3.20E-01	3.34E-01
Std Dev Biased	5.08E-03	1.85E-02	1.35E-02	7.18E-03	9.58E-03	5.02E-03	1.34E-02
Ps90%/90% (+KTL) Biased	4.30E-01	4.55E-01	4.25E-01	3.85E-01	3.36E-01	3.34E-01	3.70E-01
Ps90%/90% (-KTL) Biased	4.02E-01	3.54E-01	3.51E-01	3.45E-01	2.84E-01	3.06E-01	2.97E-01
Un-Biased Statistics							
Average Un-Biased	4.16E-01	4.05E-01	3.91E-01	3.52E-01	3.06E-01	3.07E-01	3.13E-01
Std Dev Un-Biased	1.38E-02	1.74E-02	1.68E-02	1.20E-02	1.43E-02	1.56E-02	4.44E-02
Ps90%/90% (+KTL) Un-Biased	4.54E-01	4.52E-01	4.37E-01	3.85E-01	3.45E-01	3.50E-01	4.34E-01
Ps90%/90% (-KTL) Un-Biased	3.78E-01	3.57E-01	3.45E-01	3.19E-01	2.66E-01	2.64E-01	1.91E-01
Specification MIN	2.00E-01	1.20E-01	1.10E-01	7.00E-02	1.00E-02	1.00E-02	1.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

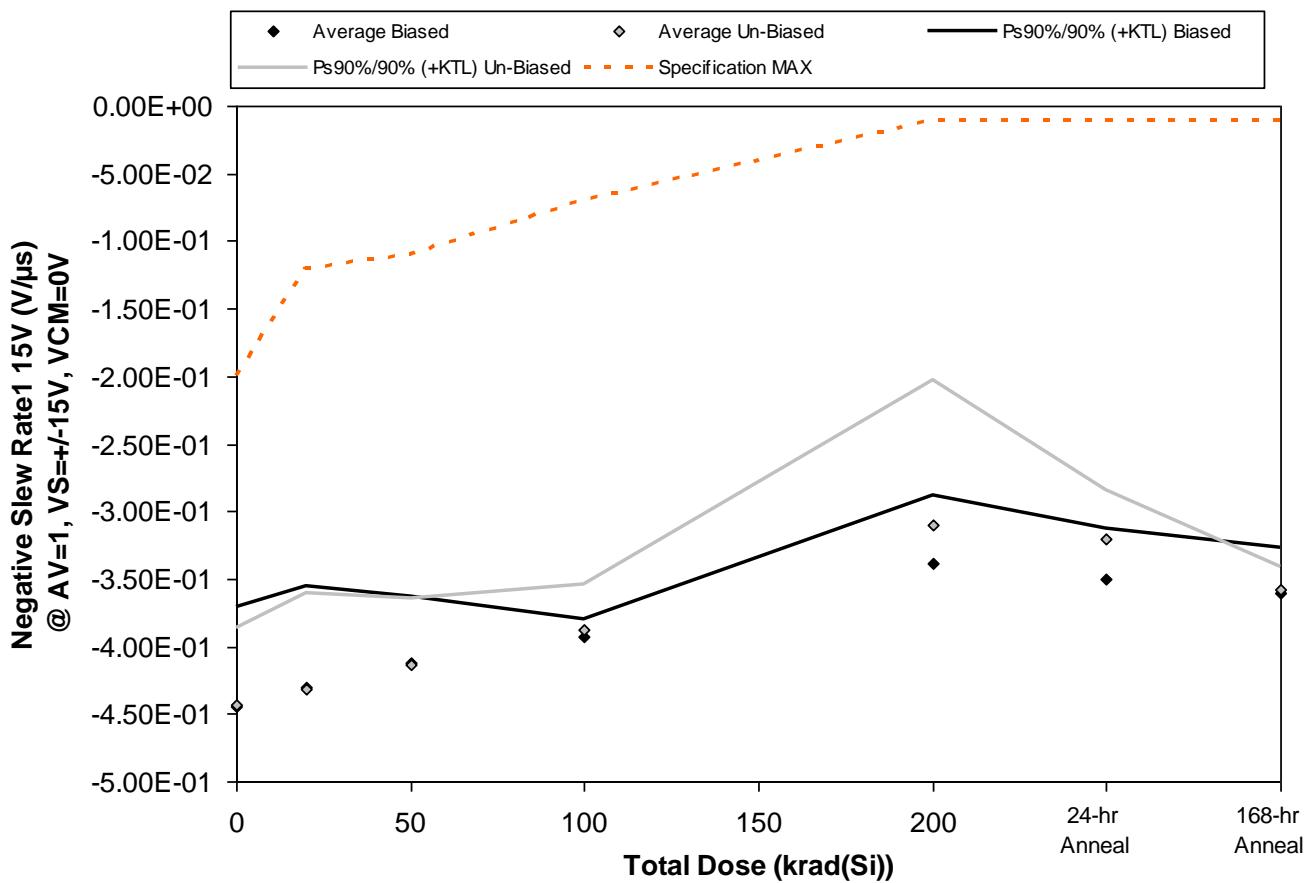


Figure 5.23. Plot of Negative Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.23. Raw data for Negative Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate1 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	-4.45E-01	-4.28E-01	-4.19E-01	-3.94E-01	-3.27E-01	-3.49E-01	-3.69E-01	
28	-4.86E-01	-4.77E-01	-4.25E-01	-3.92E-01	-3.62E-01	-3.72E-01	-3.75E-01	
29	-4.43E-01	-4.19E-01	-3.86E-01	-3.95E-01	-3.18E-01	-3.36E-01	-3.55E-01	
30	-4.14E-01	-4.04E-01	-4.03E-01	-3.98E-01	-3.51E-01	-3.49E-01	-3.62E-01	
31	-4.31E-01	-4.26E-01	-4.29E-01	-3.85E-01	-3.32E-01	-3.43E-01	-3.43E-01	
32	-4.44E-01	-4.13E-01	-3.96E-01	-4.07E-01	-3.37E-01	-3.33E-01	-3.64E-01	
33	-4.25E-01	-4.19E-01	-4.17E-01	-3.89E-01	-3.16E-01	-3.06E-01	-3.54E-01	
34	-4.77E-01	-4.77E-01	-4.43E-01	-3.91E-01	-3.39E-01	-3.35E-01	-3.63E-01	
35	-4.38E-01	-4.21E-01	-4.10E-01	-3.77E-01	-2.43E-01	-3.12E-01	-3.58E-01	
36	-4.29E-01	-4.29E-01	-4.04E-01	-3.77E-01	-3.14E-01	-3.15E-01	-3.50E-01	
37	-4.56E-01	-4.35E-01	-4.72E-01	-4.34E-01	-4.61E-01	-4.66E-01	-4.60E-01	
38	-4.57E-01	-4.36E-01	-4.42E-01	-4.68E-01	-4.44E-01	-4.51E-01	-4.55E-01	
Biased Statistics								
Average Biased		-4.44E-01	-4.31E-01	-4.12E-01	-3.93E-01	-3.38E-01	-3.50E-01	-3.61E-01
Std Dev Biased		2.66E-02	2.75E-02	1.78E-02	4.87E-03	1.80E-02	1.35E-02	1.25E-02
Ps90%/90% (+KTL) Biased		-3.71E-01	-3.55E-01	-3.64E-01	-3.79E-01	-2.89E-01	-3.13E-01	-3.27E-01
Ps90%/90% (-KTL) Biased		-5.17E-01	-5.06E-01	-4.61E-01	-4.06E-01	-3.87E-01	-3.87E-01	-3.95E-01
Un-Biased Statistics								
Average Un-Biased		-4.43E-01	-4.32E-01	-4.14E-01	-3.88E-01	-3.10E-01	-3.20E-01	-3.58E-01
Std Dev Un-Biased		2.06E-02	2.59E-02	1.80E-02	1.24E-02	3.91E-02	1.30E-02	5.93E-03
Ps90%/90% (+KTL) Un-Biased		-3.86E-01	-3.61E-01	-3.65E-01	-3.54E-01	-2.03E-01	-2.84E-01	-3.42E-01
Ps90%/90% (-KTL) Un-Biased		-4.99E-01	-5.03E-01	-4.63E-01	-4.22E-01	-4.17E-01	-3.56E-01	-3.74E-01
Specification MAX		-2.00E-01	-1.20E-01	-1.10E-01	-7.00E-02	-1.00E-02	-1.00E-02	-1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS

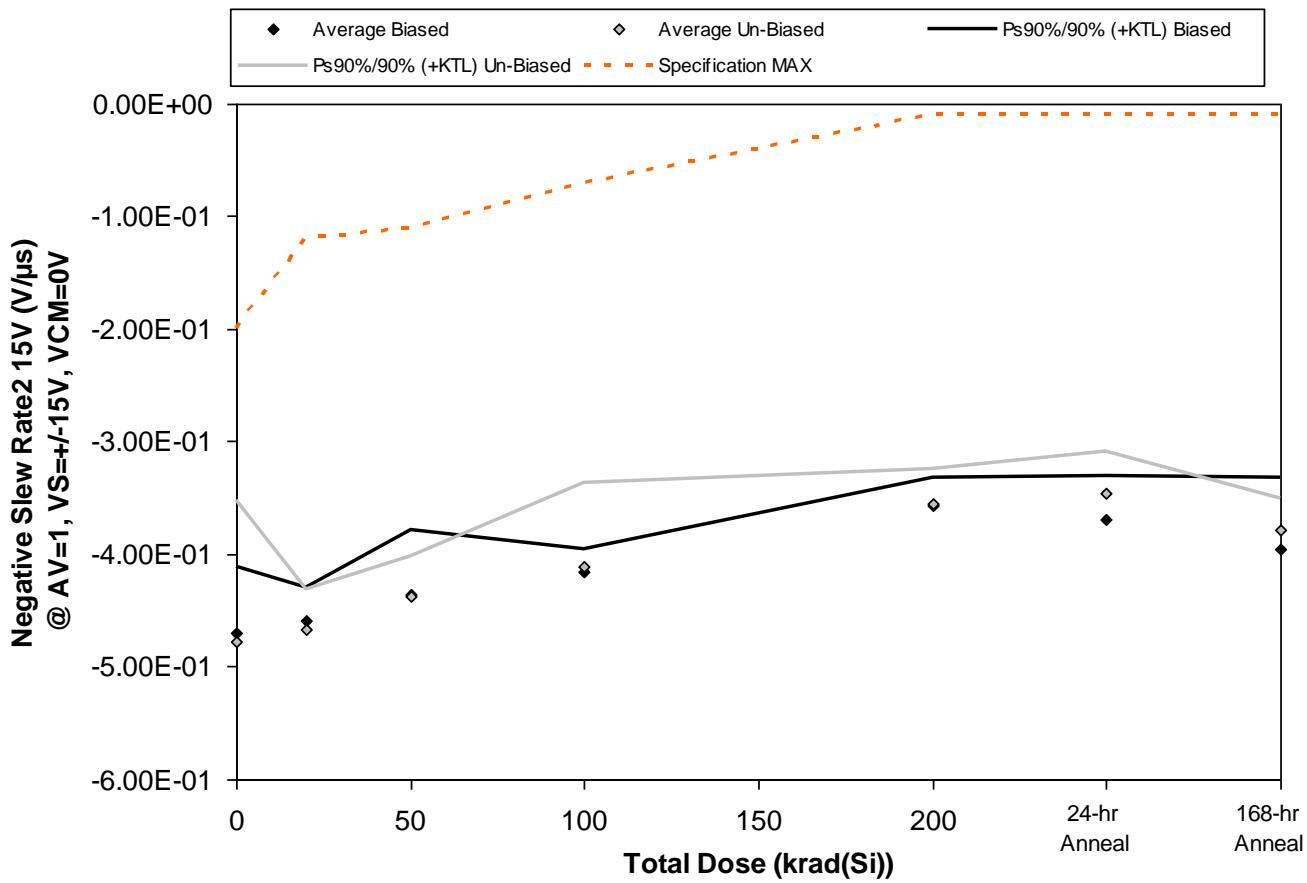


Figure 5.24. Plot of Negative Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.24. Raw data for Negative Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate2 15V (V/μs) @ AV=1, VS=+/-15V, VCM=0V		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	-4.90E-01	-4.51E-01	-4.47E-01	-4.24E-01	-3.58E-01	-3.52E-01	-4.01E-01	
28	-4.71E-01	-4.64E-01	-4.45E-01	-4.05E-01	-3.70E-01	-3.91E-01	-4.23E-01	
29	-4.87E-01	-4.68E-01	-4.01E-01	-4.13E-01	-3.45E-01	-3.63E-01	-3.59E-01	
30	-4.59E-01	-4.44E-01	-4.30E-01	-4.20E-01	-3.54E-01	-3.68E-01	-3.98E-01	
31	-4.38E-01	-4.69E-01	-4.52E-01	-4.16E-01	-3.59E-01	-3.73E-01	-3.97E-01	
32	-4.74E-01	-4.58E-01	-4.24E-01	-4.34E-01	-3.69E-01	-3.39E-01	-3.70E-01	
33	-4.73E-01	-4.67E-01	-4.37E-01	-4.01E-01	-3.42E-01	-3.40E-01	-3.68E-01	
34	-5.55E-01	-4.87E-01	-4.53E-01	-4.44E-01	-3.63E-01	-3.71E-01	-3.90E-01	
35	-4.57E-01	-4.53E-01	-4.48E-01	-3.81E-01	-3.45E-01	-3.40E-01	-3.76E-01	
36	-4.32E-01	-4.68E-01	-4.25E-01	-3.93E-01	-3.55E-01	-3.41E-01	-3.87E-01	
37	-4.66E-01	-4.80E-01	-4.50E-01	-4.66E-01	-4.76E-01	-4.72E-01	-4.91E-01	
38	-4.60E-01	-4.63E-01	-4.70E-01	-4.79E-01	-4.71E-01	-4.58E-01	-4.73E-01	
Biased Statistics								
Average Biased		-4.69E-01	-4.59E-01	-4.35E-01	-4.16E-01	-3.57E-01	-3.69E-01	-3.96E-01
Std Dev Biased		2.14E-02	1.11E-02	2.07E-02	7.23E-03	9.04E-03	1.44E-02	2.31E-02
Ps90%/90% (+KTL) Biased		-4.10E-01	-4.29E-01	-3.78E-01	-3.96E-01	-3.32E-01	-3.30E-01	-3.32E-01
Ps90%/90% (-KTL) Biased		-5.28E-01	-4.90E-01	-4.92E-01	-4.35E-01	-3.82E-01	-4.09E-01	-4.59E-01
Un-Biased Statistics								
Average Un-Biased		-4.78E-01	-4.67E-01	-4.37E-01	-4.11E-01	-3.55E-01	-3.46E-01	-3.78E-01
Std Dev Un-Biased		4.62E-02	1.30E-02	1.31E-02	2.71E-02	1.15E-02	1.39E-02	9.91E-03
Ps90%/90% (+KTL) Un-Biased		-3.52E-01	-4.31E-01	-4.01E-01	-3.36E-01	-3.23E-01	-3.08E-01	-3.51E-01
Ps90%/90% (-KTL) Un-Biased		-6.05E-01	-5.02E-01	-4.73E-01	-4.85E-01	-3.86E-01	-3.84E-01	-4.05E-01
Specification MAX		-2.00E-01	-1.20E-01	-1.10E-01	-7.00E-02	-1.00E-02	-1.00E-02	-1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS

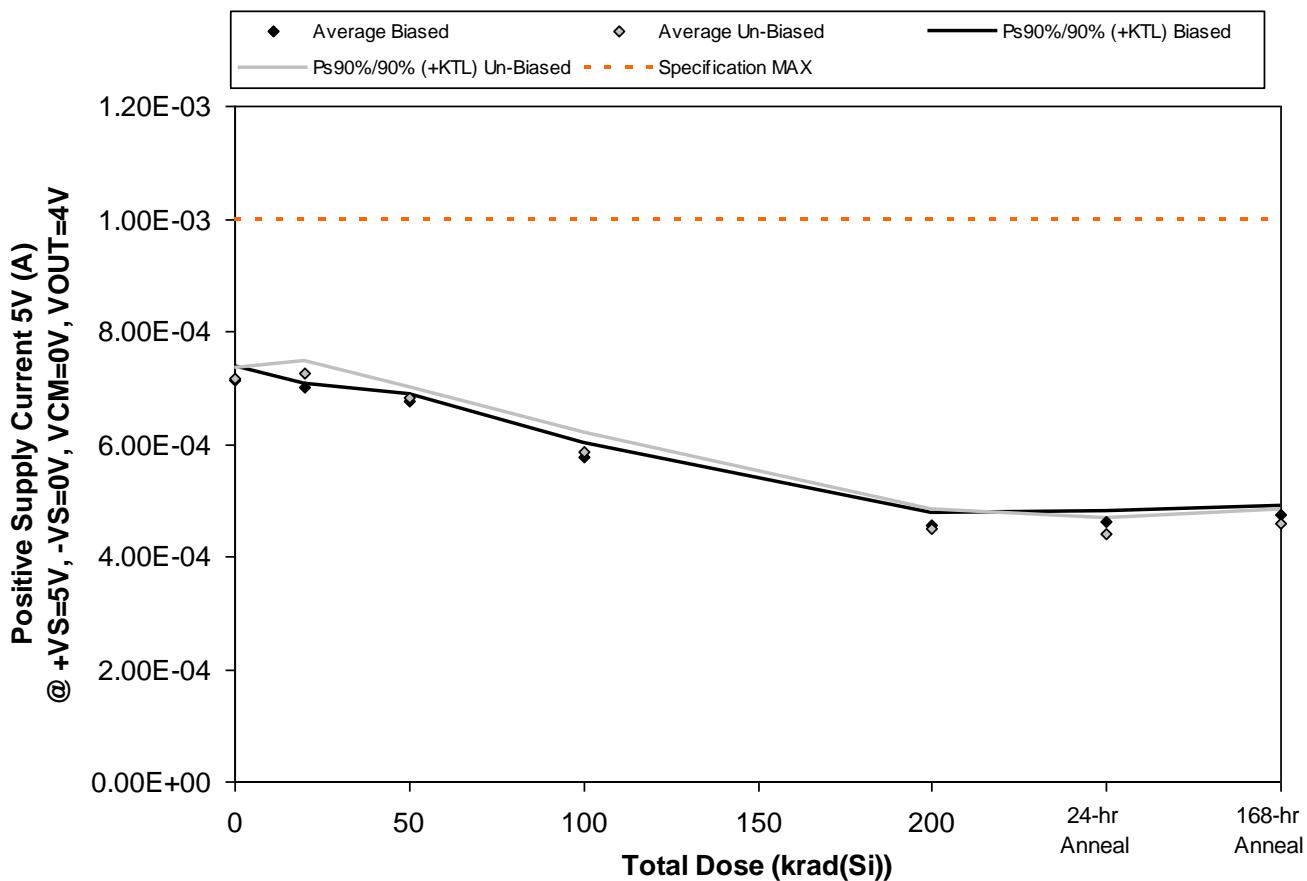


Figure 5.25. Plot of Positive Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.25. Raw data for Positive Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	7.10E-04	6.97E-04	6.72E-04	5.72E-04	4.49E-04	4.57E-04	4.67E-04
28	7.06E-04	6.99E-04	6.70E-04	5.69E-04	4.50E-04	4.53E-04	4.74E-04
29	7.13E-04	7.01E-04	6.72E-04	5.72E-04	4.51E-04	4.55E-04	4.72E-04
30	7.16E-04	7.01E-04	6.78E-04	5.83E-04	4.63E-04	4.68E-04	4.80E-04
31	7.28E-04	7.04E-04	6.82E-04	5.89E-04	4.67E-04	4.70E-04	4.80E-04
32	7.13E-04	7.18E-04	6.76E-04	5.81E-04	4.46E-04	4.38E-04	4.53E-04
33	7.11E-04	7.24E-04	6.81E-04	5.88E-04	4.55E-04	4.45E-04	4.59E-04
34	7.11E-04	7.21E-04	6.74E-04	5.67E-04	4.31E-04	4.26E-04	4.44E-04
35	7.27E-04	7.36E-04	6.89E-04	5.90E-04	4.57E-04	4.47E-04	4.67E-04
36	7.18E-04	7.31E-04	6.89E-04	6.01E-04	4.61E-04	4.50E-04	4.65E-04
37	7.17E-04	7.15E-04	7.16E-04	7.15E-04	7.15E-04	7.13E-04	7.16E-04
38	7.12E-04	7.15E-04	7.11E-04	7.13E-04	7.12E-04	7.13E-04	7.13E-04
Biased Statistics							
Average Biased	7.15E-04	7.00E-04	6.75E-04	5.77E-04	4.56E-04	4.61E-04	4.75E-04
Std Dev Biased	8.35E-06	2.61E-06	5.02E-06	8.57E-06	8.37E-06	7.83E-06	5.55E-06
Ps90%/90% (+KTL) Biased	7.38E-04	7.08E-04	6.89E-04	6.01E-04	4.79E-04	4.82E-04	4.90E-04
Ps90%/90% (-KTL) Biased	6.92E-04	6.93E-04	6.61E-04	5.53E-04	4.33E-04	4.39E-04	4.59E-04
Un-Biased Statistics							
Average Un-Biased	7.16E-04	7.26E-04	6.82E-04	5.85E-04	4.50E-04	4.41E-04	4.58E-04
Std Dev Un-Biased	6.78E-06	7.38E-06	7.05E-06	1.25E-05	1.20E-05	9.58E-06	9.37E-06
Ps90%/90% (+KTL) Un-Biased	7.35E-04	7.46E-04	7.01E-04	6.20E-04	4.83E-04	4.67E-04	4.83E-04
Ps90%/90% (-KTL) Un-Biased	6.97E-04	7.06E-04	6.62E-04	5.51E-04	4.17E-04	4.15E-04	4.32E-04
Specification MAX	1.00E-03	1.00E-03	1.00E-03	1.00E-03	1.00E-03	1.00E-03	1.00E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

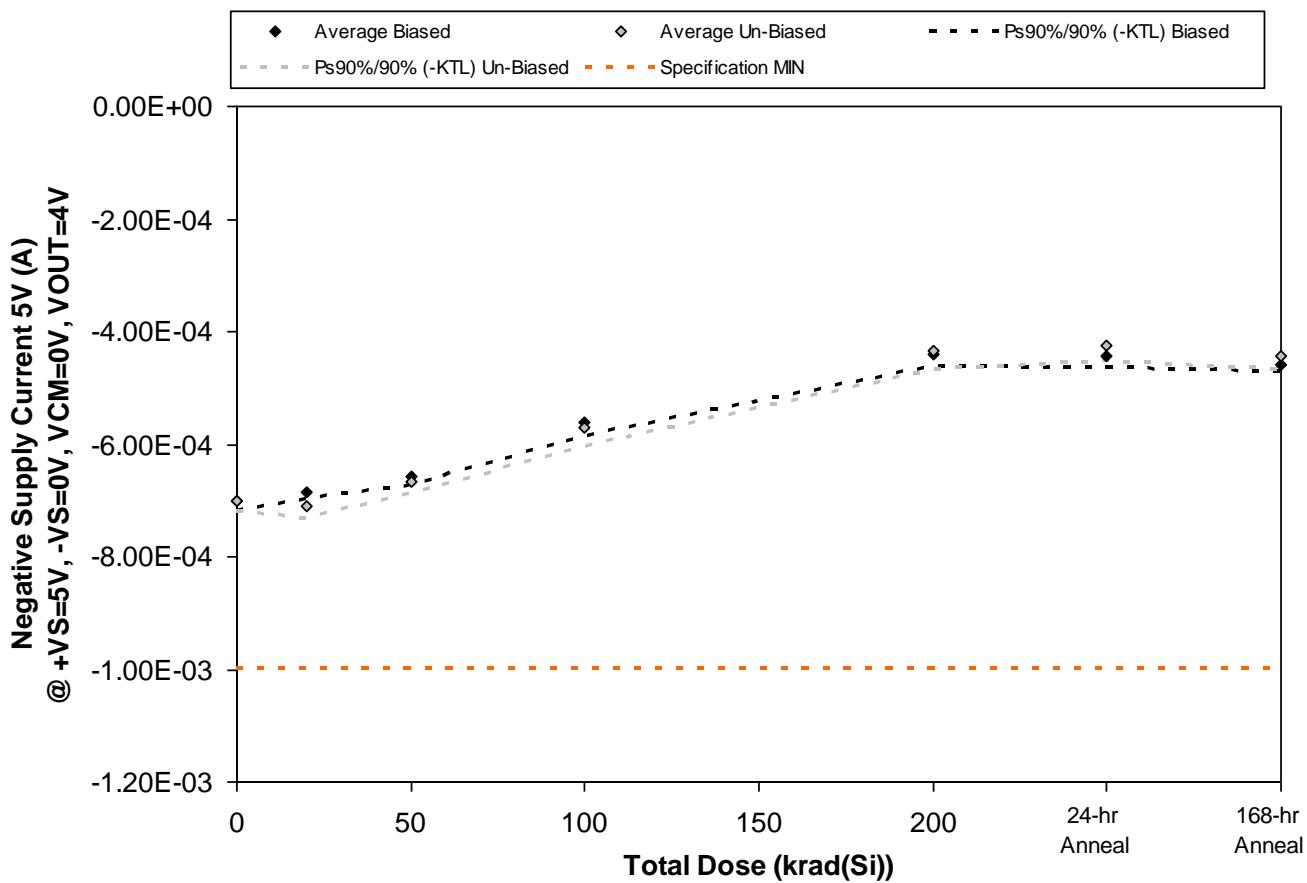


Figure 5.26. Plot of Negative Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.26. Raw data for Negative Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	-6.97E-04	-6.83E-04	-6.56E-04	-5.57E-04	-4.33E-04	-4.39E-04	-4.54E-04
28	-6.93E-04	-6.81E-04	-6.53E-04	-5.54E-04	-4.35E-04	-4.37E-04	-4.61E-04
29	-7.00E-04	-6.88E-04	-6.56E-04	-5.55E-04	-4.37E-04	-4.41E-04	-4.57E-04
30	-7.00E-04	-6.88E-04	-6.61E-04	-5.67E-04	-4.47E-04	-4.51E-04	-4.63E-04
31	-7.12E-04	-6.92E-04	-6.67E-04	-5.75E-04	-4.52E-04	-4.55E-04	-4.63E-04
32	-6.96E-04	-7.04E-04	-6.61E-04	-5.66E-04	-4.31E-04	-4.23E-04	-4.40E-04
33	-6.96E-04	-7.09E-04	-6.66E-04	-5.73E-04	-4.40E-04	-4.30E-04	-4.44E-04
34	-6.96E-04	-7.04E-04	-6.56E-04	-5.53E-04	-4.13E-04	-4.10E-04	-4.27E-04
35	-7.12E-04	-7.20E-04	-6.75E-04	-5.74E-04	-4.40E-04	-4.32E-04	-4.52E-04
36	-7.02E-04	-7.17E-04	-6.74E-04	-5.86E-04	-4.44E-04	-4.34E-04	-4.49E-04
37	-7.02E-04	-7.02E-04	-7.01E-04	-7.01E-04	-7.01E-04	-7.02E-04	-7.02E-04
38	-6.96E-04	-6.97E-04	-6.97E-04	-6.97E-04	-6.95E-04	-6.96E-04	-6.95E-04
Biased Statistics							
Average Biased	-7.00E-04	-6.86E-04	-6.59E-04	-5.62E-04	-4.41E-04	-4.45E-04	-4.60E-04
Std Dev Biased	7.09E-06	4.39E-06	5.50E-06	9.10E-06	8.26E-06	7.92E-06	3.97E-06
Ps90%/90% (+KTL) Biased	-6.81E-04	-6.74E-04	-6.44E-04	-5.37E-04	-4.18E-04	-4.23E-04	-4.49E-04
Ps90%/90% (-KTL) Biased	-7.20E-04	-6.98E-04	-6.74E-04	-5.87E-04	-4.63E-04	-4.66E-04	-4.70E-04
Un-Biased Statistics							
Average Un-Biased	-7.00E-04	-7.11E-04	-6.66E-04	-5.70E-04	-4.34E-04	-4.26E-04	-4.42E-04
Std Dev Un-Biased	6.99E-06	7.40E-06	8.20E-06	1.21E-05	1.25E-05	9.76E-06	9.76E-06
Ps90%/90% (+KTL) Un-Biased	-6.81E-04	-6.91E-04	-6.44E-04	-5.37E-04	-3.99E-04	-3.99E-04	-4.16E-04
Ps90%/90% (-KTL) Un-Biased	-7.20E-04	-7.31E-04	-6.89E-04	-6.04E-04	-4.68E-04	-4.53E-04	-4.69E-04
Specification MIN	-1.00E-03	-1.00E-03	-1.00E-03	-1.00E-03	-1.00E-03	-1.00E-03	-1.00E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

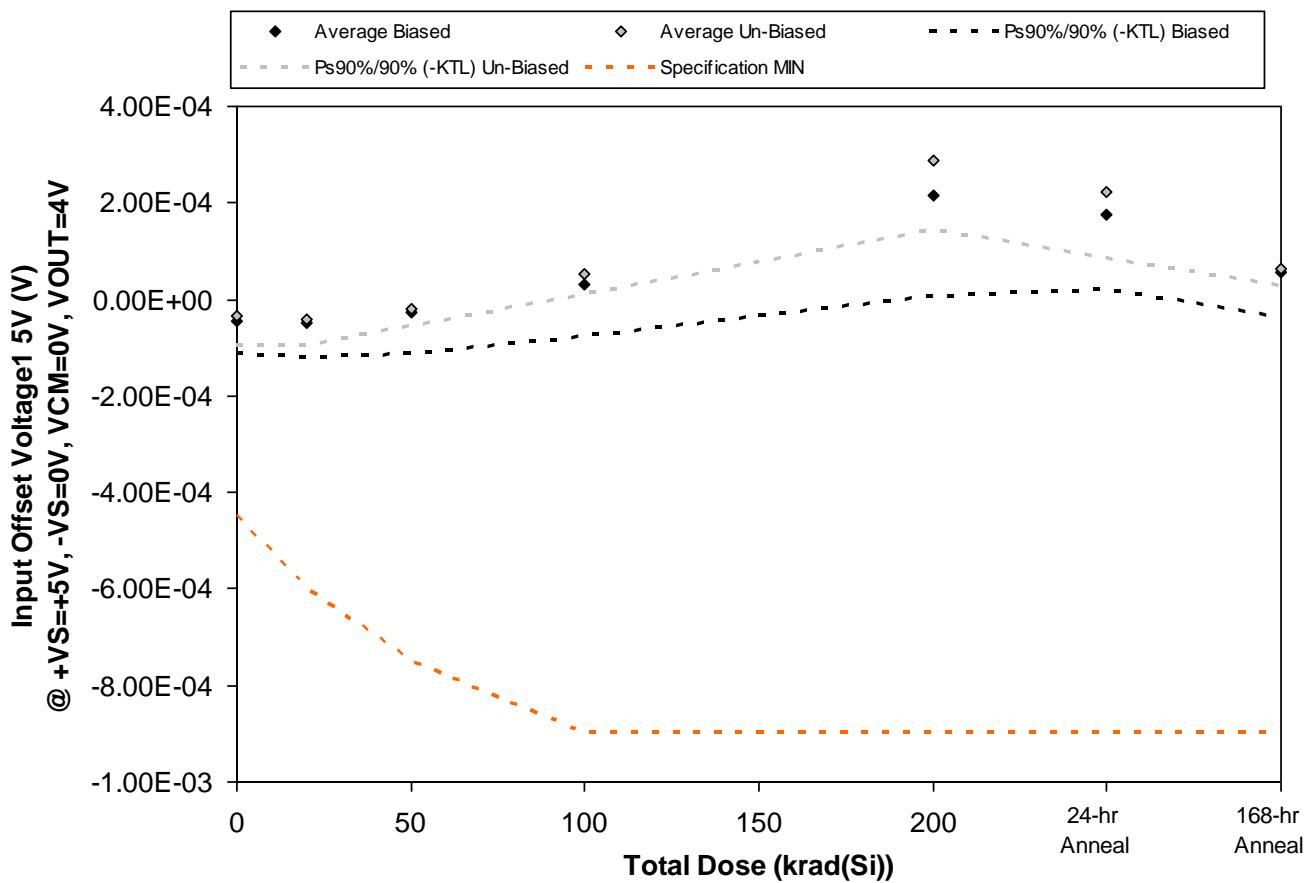


Figure 5.27. Plot of Input Offset Voltage1 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.27. Raw data for Input Offset Voltage1 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Voltage1 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	-5.68E-05	-6.32E-05	-3.77E-05	1.78E-05	2.97E-04	2.18E-04	5.74E-05
28	-7.39E-05	-8.11E-05	-6.76E-05	-2.57E-05	9.78E-05	8.47E-05	2.16E-06
29	-1.74E-05	-2.14E-05	1.62E-06	6.65E-05	2.19E-04	1.92E-04	5.93E-05
30	-5.61E-05	-5.89E-05	-3.72E-05	2.68E-05	1.95E-04	1.58E-04	6.09E-05
31	-2.04E-05	-2.26E-05	9.64E-06	7.15E-05	2.65E-04	2.20E-04	9.67E-05
32	-2.31E-05	-3.02E-05	-1.68E-05	5.28E-05	2.72E-04	2.08E-04	5.64E-05
33	-4.65E-05	-4.98E-05	-2.93E-05	4.58E-05	3.01E-04	2.31E-04	5.29E-05
34	-6.46E-06	-1.72E-05	-9.24E-06	3.54E-05	2.03E-04	1.47E-04	7.92E-05
35	-6.50E-05	-7.04E-05	-3.92E-05	5.75E-05	3.29E-04	2.62E-04	5.12E-05
36	-3.18E-05	-3.58E-05	-9.72E-06	7.93E-05	3.29E-04	2.73E-04	6.97E-05
37	2.74E-05	2.69E-05	2.69E-05	2.68E-05	2.76E-05	2.76E-05	2.81E-05
38	3.54E-05	3.44E-05	3.55E-05	3.44E-05	3.56E-05	3.68E-05	3.63E-05
Biased Statistics							
Average Biased	-4.49E-05	-4.94E-05	-2.62E-05	3.14E-05	2.15E-04	1.74E-04	5.53E-05
Std Dev Biased	2.48E-05	2.64E-05	3.17E-05	3.97E-05	7.64E-05	5.60E-05	3.39E-05
Ps90%/90% (+KTL) Biased	2.31E-05	2.29E-05	6.07E-05	1.40E-04	4.24E-04	3.28E-04	1.48E-04
Ps90%/90% (-KTL) Biased	-1.13E-04	-1.22E-04	-1.13E-04	-7.74E-05	5.22E-06	2.09E-05	-3.76E-05
Un-Biased Statistics							
Average Un-Biased	-3.46E-05	-4.07E-05	-2.08E-05	5.42E-05	2.87E-04	2.24E-04	6.18E-05
Std Dev Un-Biased	2.24E-05	2.03E-05	1.30E-05	1.63E-05	5.22E-05	5.01E-05	1.21E-05
Ps90%/90% (+KTL) Un-Biased	2.68E-05	1.50E-05	1.49E-05	9.89E-05	4.30E-04	3.62E-04	9.50E-05
Ps90%/90% (-KTL) Un-Biased	-9.59E-05	-9.64E-05	-5.66E-05	9.36E-06	1.44E-04	8.66E-05	2.86E-05
Specification MIN	-4.50E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	4.50E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

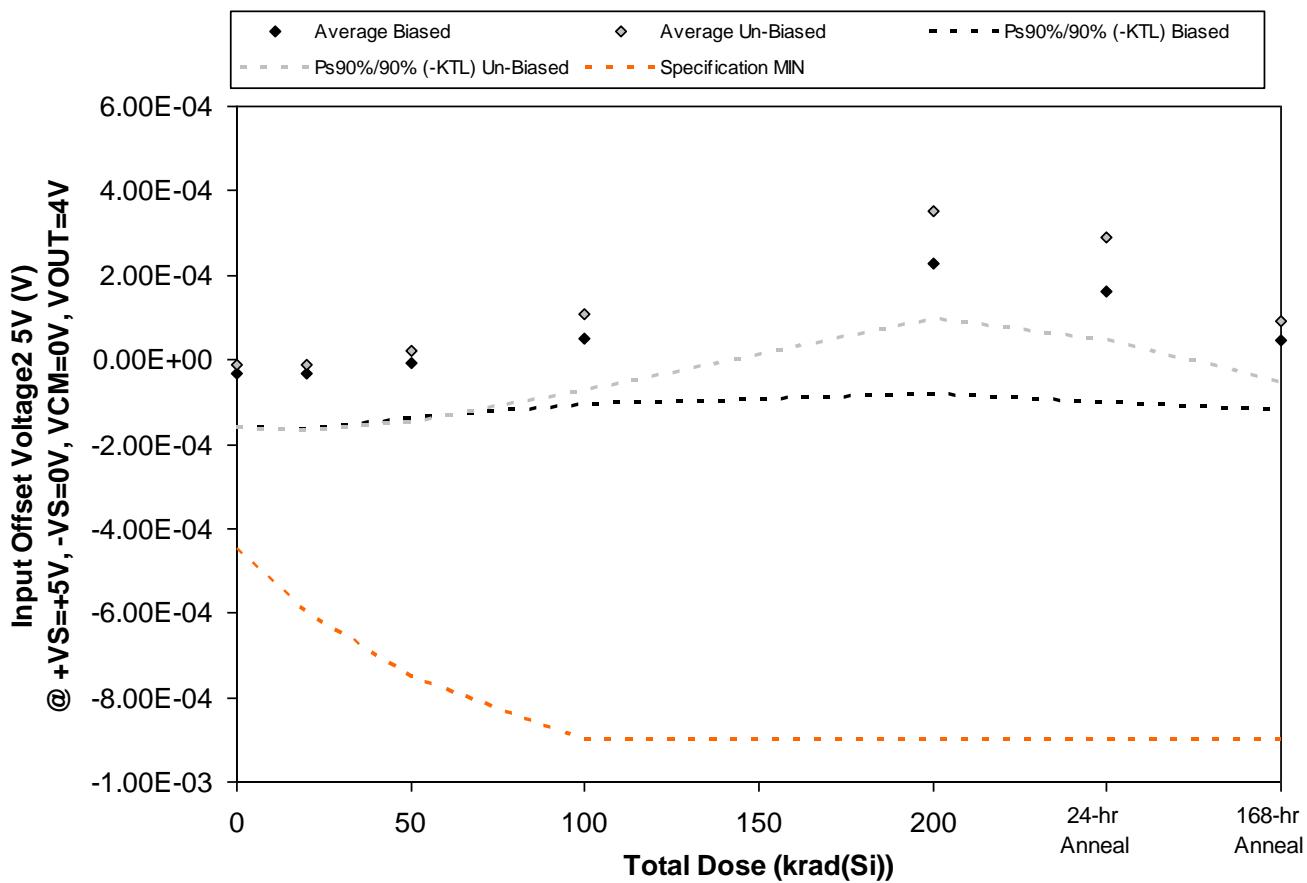


Figure 5.28. Plot of Input Offset Voltage2 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.28. Raw data for Input Offset Voltage2 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Voltage2 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.58E-05	1.39E-05	4.45E-05	1.15E-04	4.04E-04	3.00E-04	1.24E-04
28	-5.83E-05	-6.78E-05	-4.80E-05	-1.51E-05	9.28E-05	6.74E-05	-1.05E-05
29	-5.29E-05	-4.62E-05	-2.20E-05	3.30E-05	2.00E-04	1.45E-04	2.32E-05
30	1.80E-05	2.03E-05	4.51E-05	1.03E-04	2.55E-04	2.11E-04	1.01E-04
31	-8.55E-05	-8.70E-05	-5.21E-05	1.43E-05	1.94E-04	8.12E-05	-4.90E-07
32	5.82E-05	5.73E-05	8.58E-05	1.66E-04	3.94E-04	3.41E-04	1.41E-04
33	-4.35E-05	-4.78E-05	-6.76E-06	8.78E-05	3.60E-04	2.89E-04	6.47E-05
34	-4.41E-05	-5.18E-05	-4.39E-05	1.30E-05	1.96E-04	1.44E-04	3.37E-05
35	-6.05E-05	-5.77E-05	-2.05E-05	9.13E-05	3.60E-04	2.93E-04	5.98E-05
36	4.01E-05	4.44E-05	8.40E-05	1.73E-04	4.45E-04	3.77E-04	1.51E-04
37	3.26E-05	3.24E-05	3.28E-05	3.21E-05	3.41E-05	3.16E-05	3.30E-05
38	2.51E-05	2.21E-05	2.43E-05	2.33E-05	2.54E-05	2.32E-05	2.53E-05
Biased Statistics							
Average Biased	-3.26E-05	-3.34E-05	-6.50E-06	5.01E-05	2.29E-04	1.61E-04	4.74E-05
Std Dev Biased	4.68E-05	4.83E-05	4.82E-05	5.67E-05	1.14E-04	9.64E-05	6.11E-05
Ps90%/90% (+KTL) Biased	9.59E-05	9.91E-05	1.26E-04	2.05E-04	5.41E-04	4.25E-04	2.15E-04
Ps90%/90% (-KTL) Biased	-1.61E-04	-1.66E-04	-1.39E-04	-1.05E-04	-8.29E-05	-1.04E-04	-1.20E-04
Un-Biased Statistics							
Average Un-Biased	-9.94E-06	-1.11E-05	1.97E-05	1.06E-04	3.51E-04	2.89E-04	9.01E-05
Std Dev Un-Biased	5.47E-05	5.69E-05	6.09E-05	6.58E-05	9.33E-05	8.89E-05	5.26E-05
Ps90%/90% (+KTL) Un-Biased	1.40E-04	1.45E-04	1.87E-04	2.87E-04	6.07E-04	5.32E-04	2.34E-04
Ps90%/90% (-KTL) Un-Biased	-1.60E-04	-1.67E-04	-1.47E-04	-7.42E-05	9.54E-05	4.50E-05	-5.42E-05
Specification MIN	-4.50E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	4.50E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

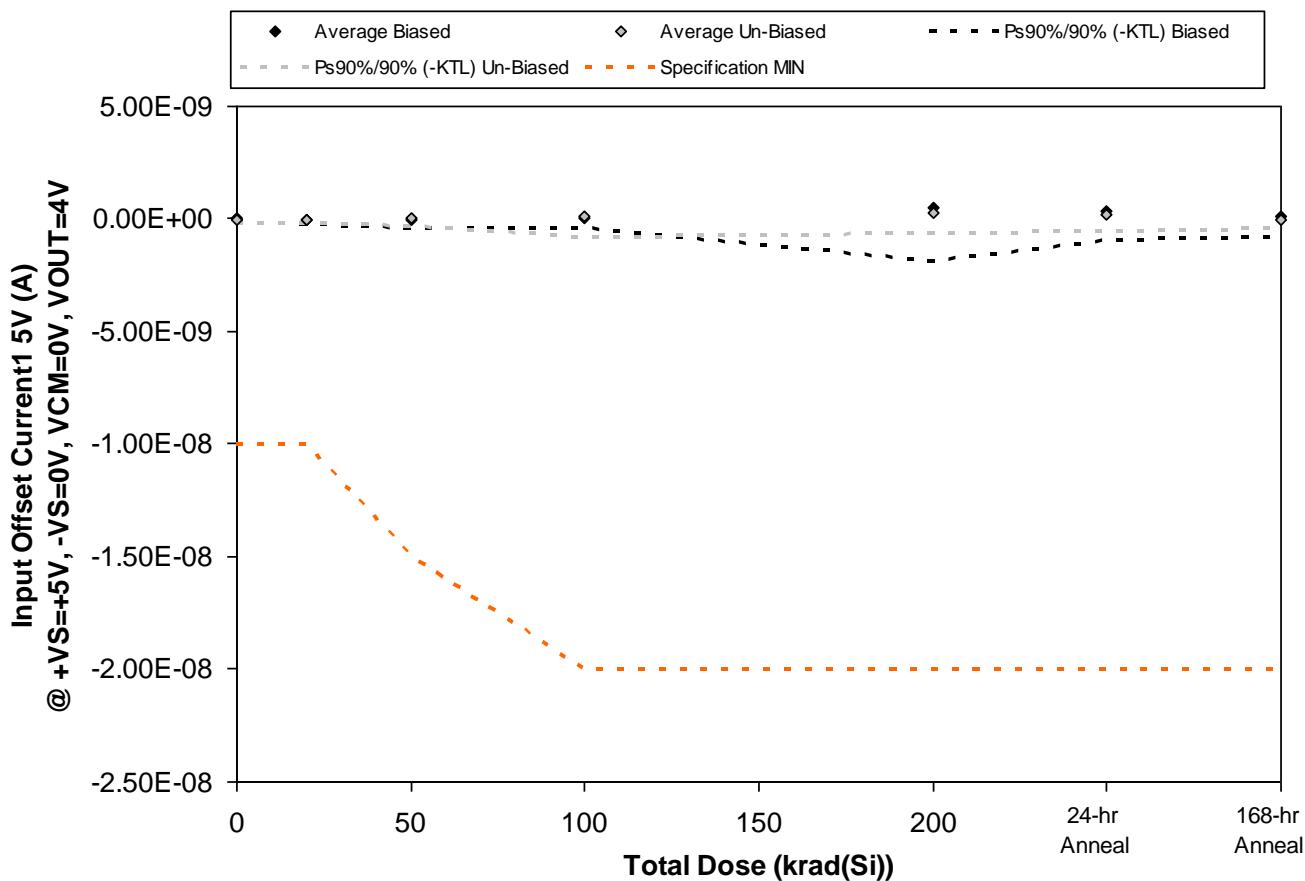


Figure 5.29. Plot of Input Offset Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.29. Raw data for Input Offset Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	4.70E-11	-4.80E-11	-3.80E-11	1.04E-10	1.91E-09	1.01E-09	7.13E-10
28	2.40E-11	-7.80E-11	-1.19E-10	-1.70E-11	2.01E-10	7.00E-11	-5.00E-12
29	9.40E-11	2.10E-11	1.03E-10	-4.30E-11	-8.80E-11	3.40E-11	3.90E-11
30	-2.20E-11	-1.32E-10	-2.20E-10	-1.86E-10	-2.87E-10	-1.00E-10	-2.48E-10
31	1.28E-10	6.00E-11	1.48E-10	2.64E-10	8.28E-10	7.40E-10	1.38E-10
32	1.20E-11	-2.70E-11	5.50E-11	7.80E-11	4.46E-10	4.25E-10	-1.69E-10
33	-8.80E-11	-3.10E-11	5.40E-11	-8.00E-12	2.15E-10	9.60E-11	1.03E-10
34	-7.80E-11	-1.17E-10	-1.65E-10	-3.87E-10	-2.40E-10	-2.17E-10	-1.29E-10
35	3.10E-11	7.80E-11	2.04E-10	2.75E-10	3.85E-10	1.64E-10	-8.60E-11
36	-2.00E-11	-3.80E-11	3.30E-11	4.74E-10	6.93E-10	4.87E-10	1.49E-10
37	4.30E-11	7.00E-12	4.50E-11	3.20E-11	3.00E-11	4.00E-11	1.60E-11
38	2.90E-11	2.80E-11	-1.50E-11	-1.40E-11	-1.80E-11	-1.20E-11	-1.30E-11
Biased Statistics							
Average Biased	5.42E-11	-3.54E-11	-2.52E-11	2.44E-11	5.12E-10	3.50E-10	1.27E-10
Std Dev Biased	5.87E-11	7.68E-11	1.53E-10	1.69E-10	8.86E-10	4.91E-10	3.57E-10
Ps90%/90% (+KTL) Biased	2.15E-10	1.75E-10	3.94E-10	4.88E-10	2.94E-09	1.70E-09	1.11E-09
Ps90%/90% (-KTL) Biased	-1.07E-10	-2.46E-10	-4.44E-10	-4.39E-10	-1.92E-09	-9.97E-10	-8.51E-10
Un-Biased Statistics							
Average Un-Biased	-2.86E-11	-2.70E-11	3.62E-11	8.64E-11	3.00E-10	1.91E-10	-2.64E-11
Std Dev Un-Biased	5.30E-11	6.94E-11	1.32E-10	3.24E-10	3.47E-10	2.82E-10	1.43E-10
Ps90%/90% (+KTL) Un-Biased	1.17E-10	1.63E-10	3.97E-10	9.74E-10	1.25E-09	9.65E-10	3.66E-10
Ps90%/90% (-KTL) Un-Biased	-1.74E-10	-2.17E-10	-3.25E-10	-8.01E-10	-6.52E-10	-5.83E-10	-4.19E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

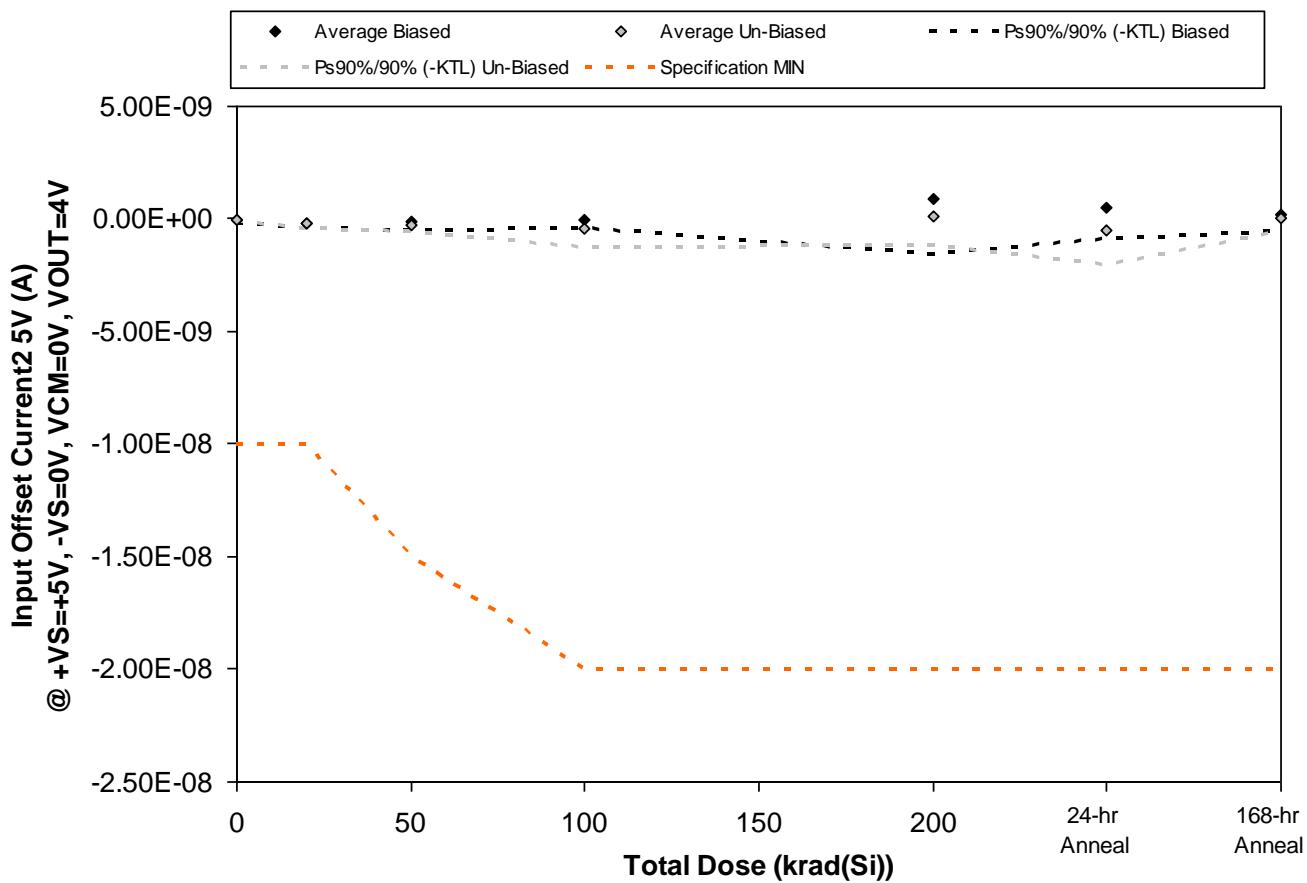


Figure 5.30. Plot of Input Offset Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.30. Raw data for Input Offset Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Input Offset Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	-1.00E-11	-2.07E-10	-1.36E-10	-7.00E-12	2.36E-09	1.39E-09	6.59E-10
28	-5.80E-11	-8.60E-11	-1.17E-10	-1.55E-10	3.25E-10	1.04E-10	-1.29E-10
29	-1.15E-10	-3.11E-10	-2.04E-10	-1.71E-10	2.29E-10	2.45E-10	1.70E-10
30	-5.50E-11	-1.70E-10	-3.23E-10	-7.00E-11	4.54E-10	2.95E-10	1.79E-10
31	-1.09E-10	-1.70E-10	3.40E-11	2.12E-10	9.19E-10	6.23E-10	4.50E-11
32	-4.70E-11	-2.63E-10	-2.57E-10	-4.14E-10	1.22E-10	-7.75E-10	-2.63E-10
33	-4.30E-11	-2.69E-10	-3.66E-10	-2.59E-10	1.55E-10	-3.36E-10	2.69E-10
34	0.00E+00	-1.57E-10	-4.58E-10	-9.31E-10	-6.49E-10	-1.31E-09	1.42E-10
35	-2.50E-11	-2.20E-10	-1.76E-10	-2.29E-10	6.75E-10	8.00E-11	2.76E-10
36	-3.20E-11	-8.00E-11	-2.39E-10	-1.67E-10	2.99E-10	-9.20E-11	-7.30E-11
37	-4.30E-11	-4.80E-11	-3.40E-11	-1.50E-11	-3.80E-11	-4.20E-11	-4.00E-11
38	5.00E-12	0.00E+00	-5.00E-12	-2.80E-11	-1.40E-11	-1.70E-11	8.00E-12
Biased Statistics							
Average Biased	-6.94E-11	-1.89E-10	-1.49E-10	-3.82E-11	8.57E-10	5.31E-10	1.85E-10
Std Dev Biased	4.33E-11	8.15E-11	1.30E-10	1.55E-10	8.80E-10	5.15E-10	2.93E-10
Ps90%/90% (+KTL) Biased	4.94E-11	3.45E-11	2.08E-10	3.86E-10	3.27E-09	1.94E-09	9.88E-10
Ps90%/90% (-KTL) Biased	-1.88E-10	-4.12E-10	-5.07E-10	-4.63E-10	-1.56E-09	-8.82E-10	-6.18E-10
Un-Biased Statistics							
Average Un-Biased	-2.94E-11	-1.98E-10	-2.99E-10	-4.00E-10	1.20E-10	-4.87E-10	7.02E-11
Std Dev Un-Biased	1.86E-11	7.96E-11	1.12E-10	3.10E-10	4.83E-10	5.62E-10	2.34E-10
Ps90%/90% (+KTL) Un-Biased	2.16E-11	2.05E-11	8.17E-12	4.51E-10	1.44E-09	1.06E-09	7.11E-10
Ps90%/90% (-KTL) Un-Biased	-8.04E-11	-4.16E-10	-6.07E-10	-1.25E-09	-1.20E-09	-2.03E-09	-5.71E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

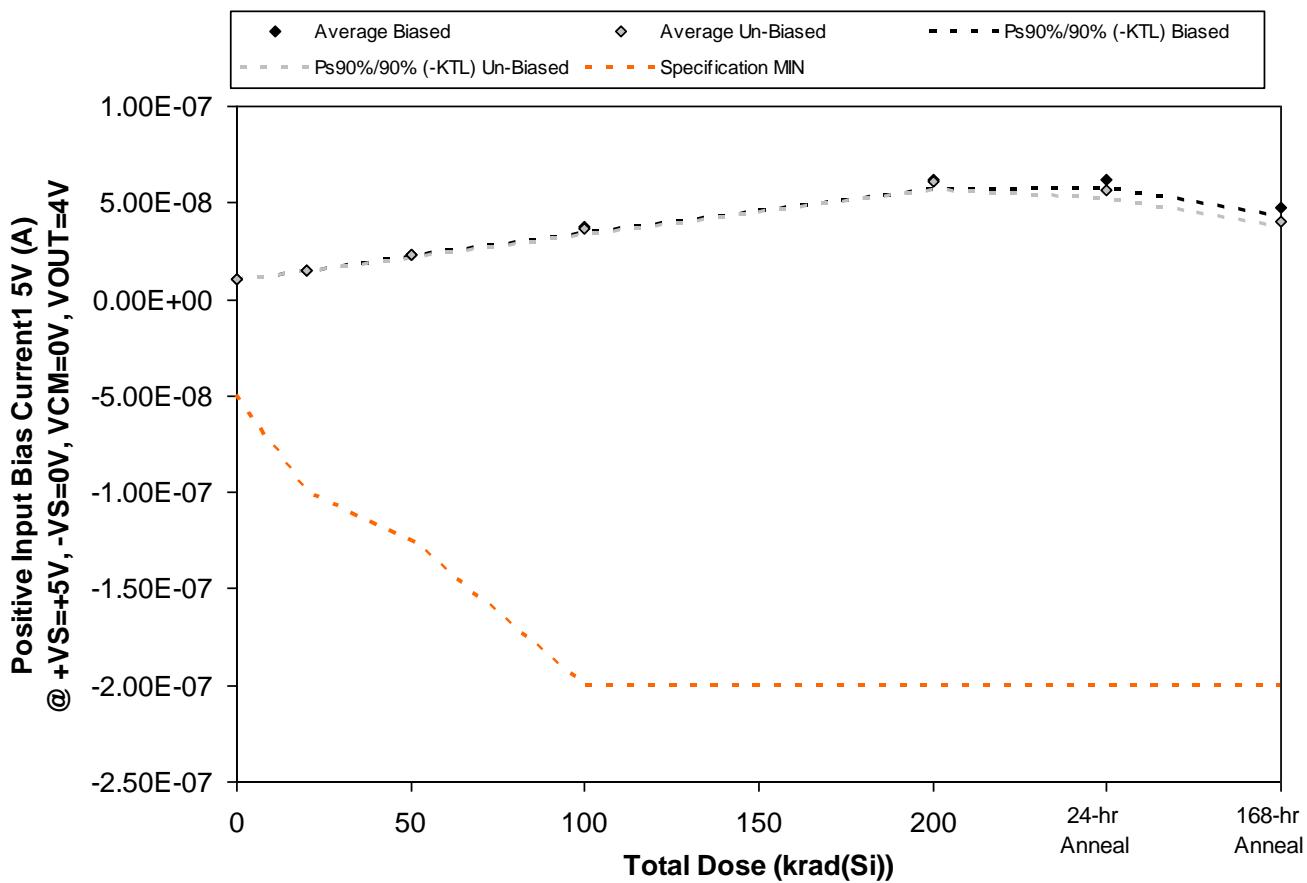


Figure 5.31. Plot of Positive Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.31. Raw data for Positive Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.02E-08	1.46E-08	2.33E-08	3.85E-08	6.40E-08	6.34E-08	4.65E-08
28	1.00E-08	1.49E-08	2.32E-08	3.74E-08	6.15E-08	6.14E-08	4.63E-08
29	1.06E-08	1.53E-08	2.35E-08	3.77E-08	6.26E-08	6.27E-08	4.84E-08
30	1.11E-08	1.58E-08	2.39E-08	3.82E-08	6.32E-08	6.34E-08	4.96E-08
31	1.03E-08	1.47E-08	2.25E-08	3.54E-08	5.86E-08	5.92E-08	4.59E-08
32	1.01E-08	1.46E-08	2.26E-08	3.59E-08	5.96E-08	5.52E-08	3.92E-08
33	1.10E-08	1.57E-08	2.40E-08	3.79E-08	6.26E-08	5.81E-08	4.18E-08
34	1.04E-08	1.53E-08	2.38E-08	3.84E-08	6.30E-08	5.78E-08	4.08E-08
35	1.10E-08	1.56E-08	2.39E-08	3.76E-08	6.09E-08	5.65E-08	4.09E-08
36	1.03E-08	1.48E-08	2.24E-08	3.54E-08	5.91E-08	5.49E-08	3.95E-08
37	9.59E-09	9.57E-09	9.59E-09	9.57E-09	9.55E-09	9.54E-09	9.56E-09
38	9.67E-09	9.69E-09	9.68E-09	9.69E-09	9.69E-09	9.68E-09	9.71E-09
Biased Statistics							
Average Biased	1.04E-08	1.51E-08	2.32E-08	3.74E-08	6.20E-08	6.20E-08	4.73E-08
Std Dev Biased	4.45E-10	4.78E-10	5.17E-10	1.20E-09	2.10E-09	1.78E-09	1.60E-09
Ps90%/90% (+KTL) Biased	1.16E-08	1.64E-08	2.47E-08	4.07E-08	6.77E-08	6.69E-08	5.17E-08
Ps90%/90% (-KTL) Biased	9.21E-09	1.37E-08	2.18E-08	3.41E-08	5.62E-08	5.71E-08	4.29E-08
Un-Biased Statistics							
Average Un-Biased	1.06E-08	1.52E-08	2.33E-08	3.70E-08	6.11E-08	5.65E-08	4.04E-08
Std Dev Un-Biased	4.12E-10	4.87E-10	7.81E-10	1.30E-09	1.74E-09	1.47E-09	1.09E-09
Ps90%/90% (+KTL) Un-Biased	1.17E-08	1.65E-08	2.55E-08	4.06E-08	6.58E-08	6.05E-08	4.34E-08
Ps90%/90% (-KTL) Un-Biased	9.43E-09	1.38E-08	2.12E-08	3.35E-08	5.63E-08	5.25E-08	3.75E-08
Specification MIN	-5.00E-08	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	5.00E-08	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

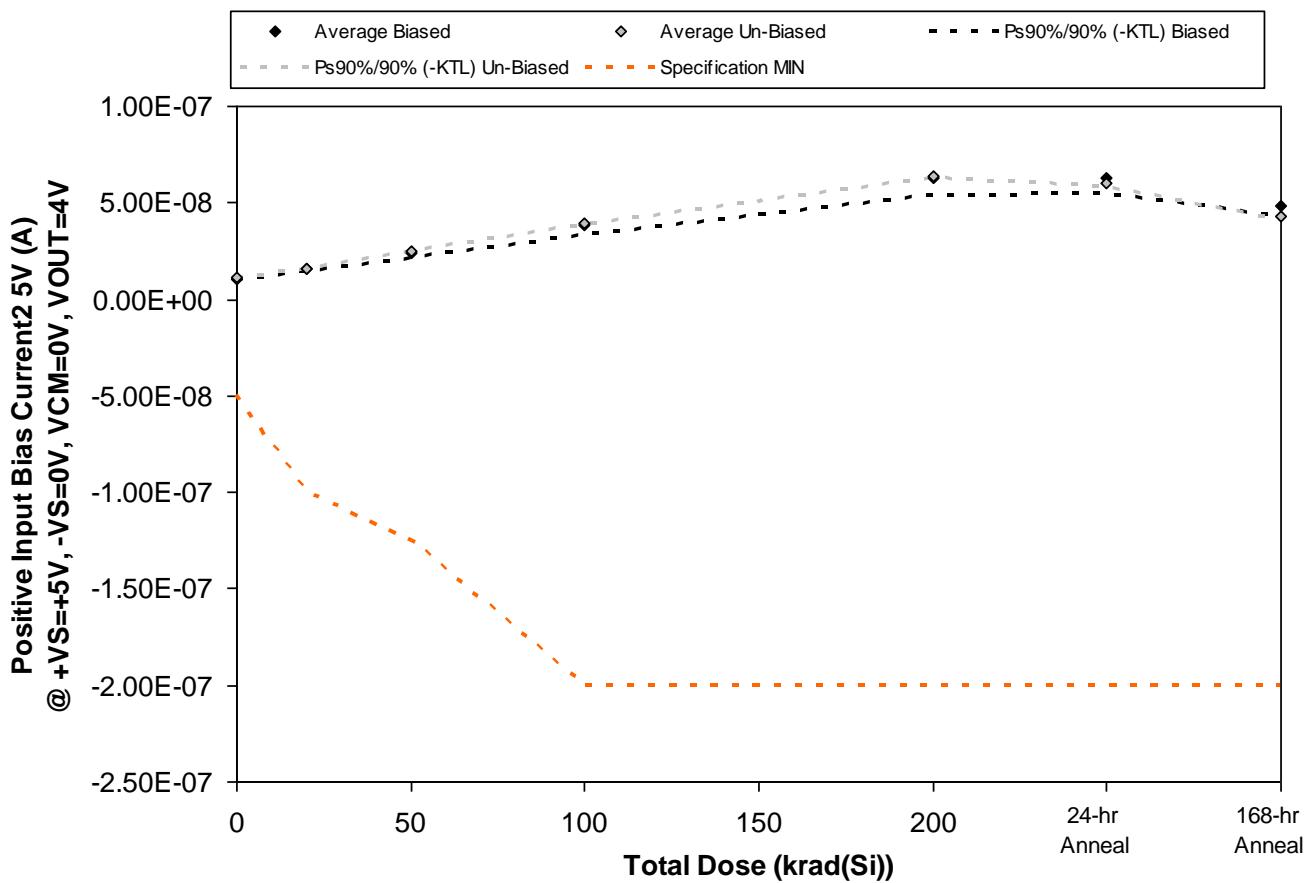


Figure 5.32. Plot of Positive Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.32. Raw data for Positive Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.10E-08	1.60E-08	2.51E-08	4.13E-08	6.81E-08	6.74E-08	5.00E-08
28	9.84E-09	1.46E-08	2.27E-08	3.68E-08	6.04E-08	6.04E-08	4.55E-08
29	1.09E-08	1.60E-08	2.44E-08	3.92E-08	6.46E-08	6.51E-08	5.04E-08
30	1.10E-08	1.57E-08	2.36E-08	3.77E-08	6.17E-08	6.20E-08	4.86E-08
31	1.07E-08	1.54E-08	2.34E-08	3.65E-08	6.03E-08	6.09E-08	4.75E-08
32	1.11E-08	1.60E-08	2.48E-08	3.91E-08	6.42E-08	6.03E-08	4.25E-08
33	1.12E-08	1.62E-08	2.49E-08	3.91E-08	6.42E-08	6.03E-08	4.29E-08
34	1.08E-08	1.59E-08	2.49E-08	3.98E-08	6.47E-08	6.03E-08	4.18E-08
35	1.14E-08	1.64E-08	2.51E-08	3.94E-08	6.31E-08	5.91E-08	4.26E-08
36	1.14E-08	1.63E-08	2.48E-08	3.93E-08	6.46E-08	6.07E-08	4.38E-08
37	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08
38	1.06E-08	1.06E-08	1.06E-08	1.05E-08	1.06E-08	1.06E-08	1.06E-08
Biased Statistics							
Average Biased	1.07E-08	1.55E-08	2.38E-08	3.83E-08	6.30E-08	6.31E-08	4.84E-08
Std Dev Biased	4.97E-10	5.77E-10	9.45E-10	1.99E-09	3.34E-09	2.97E-09	1.99E-09
Ps90%/90% (+KTL) Biased	1.21E-08	1.71E-08	2.64E-08	4.38E-08	7.22E-08	7.13E-08	5.38E-08
Ps90%/90% (-KTL) Biased	9.34E-09	1.39E-08	2.12E-08	3.29E-08	5.39E-08	5.50E-08	4.29E-08
Un-Biased Statistics							
Average Un-Biased	1.12E-08	1.62E-08	2.49E-08	3.93E-08	6.41E-08	6.01E-08	4.27E-08
Std Dev Un-Biased	2.62E-10	2.13E-10	1.05E-10	2.79E-10	6.05E-10	5.93E-10	7.00E-10
Ps90%/90% (+KTL) Un-Biased	1.19E-08	1.67E-08	2.52E-08	4.01E-08	6.58E-08	6.18E-08	4.46E-08
Ps90%/90% (-KTL) Un-Biased	1.04E-08	1.56E-08	2.46E-08	3.86E-08	6.25E-08	5.85E-08	4.08E-08
Specification MIN	-5.00E-08	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	5.00E-08	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

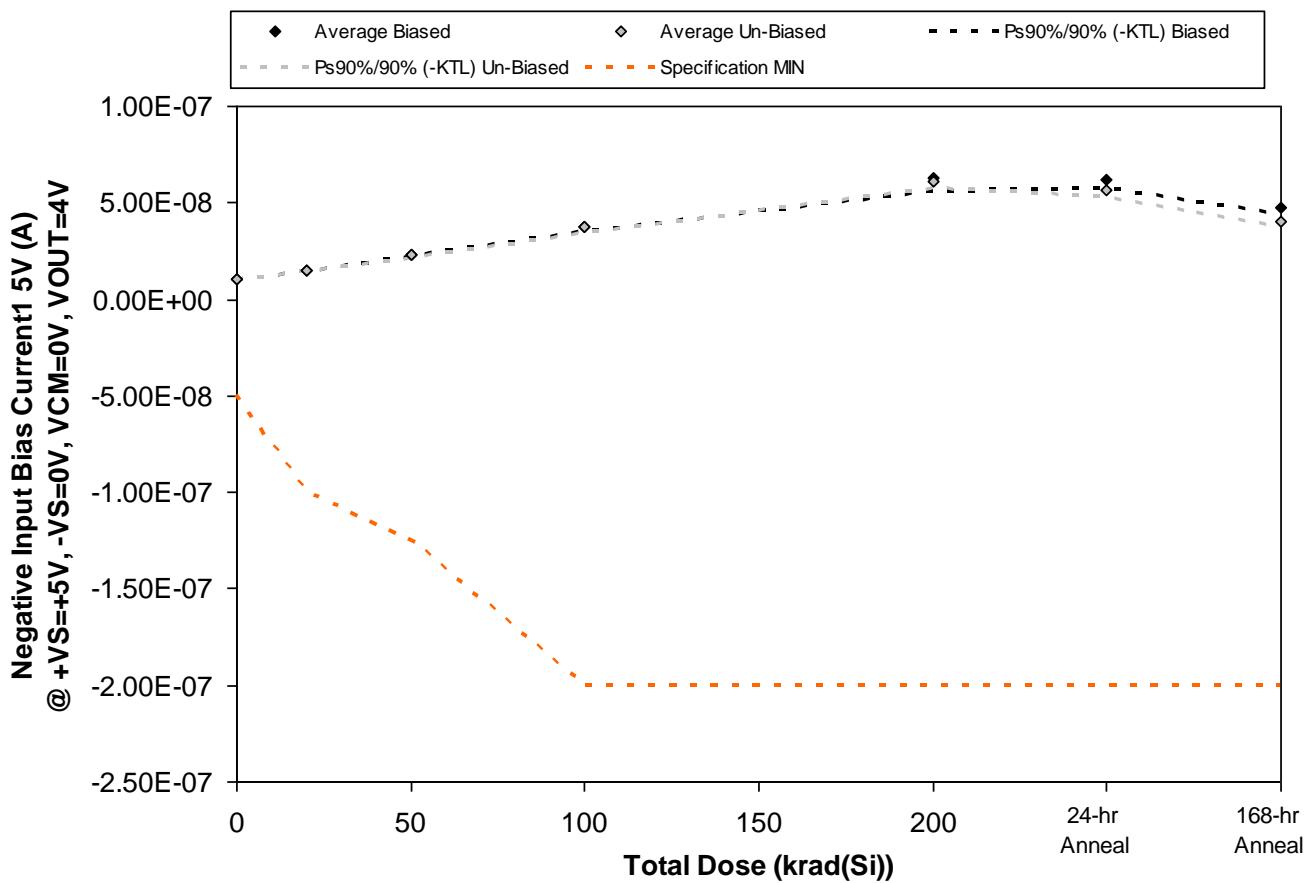


Figure 5.33. Plot of Negative Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.33. Raw data for Negative Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.01E-08	1.46E-08	2.32E-08	3.86E-08	6.60E-08	6.45E-08	4.72E-08
28	1.00E-08	1.48E-08	2.31E-08	3.74E-08	6.17E-08	6.15E-08	4.63E-08
29	1.07E-08	1.53E-08	2.36E-08	3.77E-08	6.26E-08	6.28E-08	4.86E-08
30	1.11E-08	1.57E-08	2.37E-08	3.81E-08	6.30E-08	6.34E-08	4.95E-08
31	1.04E-08	1.48E-08	2.27E-08	3.58E-08	5.95E-08	6.00E-08	4.61E-08
32	1.01E-08	1.46E-08	2.27E-08	3.61E-08	6.02E-08	5.57E-08	3.91E-08
33	1.09E-08	1.56E-08	2.41E-08	3.80E-08	6.29E-08	5.84E-08	4.20E-08
34	1.03E-08	1.51E-08	2.37E-08	3.80E-08	6.29E-08	5.77E-08	4.06E-08
35	1.11E-08	1.58E-08	2.41E-08	3.79E-08	6.13E-08	5.67E-08	4.09E-08
36	1.03E-08	1.47E-08	2.25E-08	3.59E-08	5.98E-08	5.55E-08	3.96E-08
37	9.63E-09	9.62E-09	9.62E-09	9.63E-09	9.60E-09	9.62E-09	9.65E-09
38	9.69E-09	9.73E-09	9.73E-09	9.73E-09	9.70E-09	9.72E-09	9.70E-09
Biased Statistics							
Average Biased	1.05E-08	1.51E-08	2.33E-08	3.75E-08	6.26E-08	6.25E-08	4.75E-08
Std Dev Biased	4.35E-10	4.42E-10	4.07E-10	1.07E-09	2.36E-09	1.74E-09	1.46E-09
Ps90%/90% (+KTL) Biased	1.17E-08	1.63E-08	2.44E-08	4.05E-08	6.91E-08	6.72E-08	5.15E-08
Ps90%/90% (-KTL) Biased	9.27E-09	1.38E-08	2.21E-08	3.46E-08	5.61E-08	5.77E-08	4.35E-08
Un-Biased Statistics							
Average Un-Biased	1.05E-08	1.52E-08	2.34E-08	3.72E-08	6.14E-08	5.68E-08	4.05E-08
Std Dev Un-Biased	4.04E-10	5.17E-10	7.62E-10	1.09E-09	1.44E-09	1.24E-09	1.14E-09
Ps90%/90% (+KTL) Un-Biased	1.16E-08	1.66E-08	2.55E-08	4.02E-08	6.54E-08	6.02E-08	4.36E-08
Ps90%/90% (-KTL) Un-Biased	9.42E-09	1.38E-08	2.13E-08	3.42E-08	5.75E-08	5.34E-08	3.74E-08
Specification MIN	-5.00E-08	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	5.00E-08	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

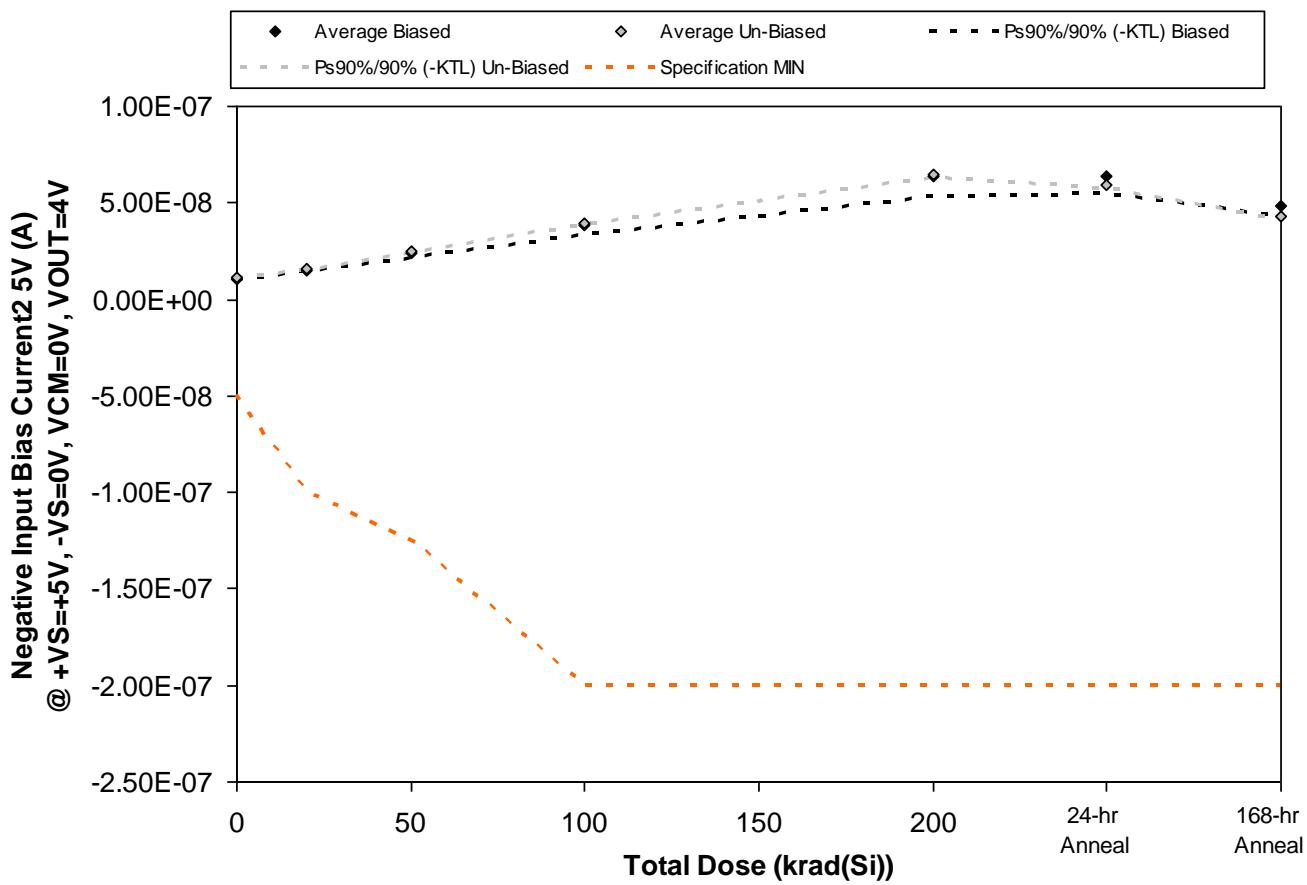


Figure 5.34. Plot of Negative Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.34. Raw data for Negative Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.10E-08	1.58E-08	2.50E-08	4.14E-08	7.06E-08	6.89E-08	5.07E-08
28	9.75E-09	1.45E-08	2.26E-08	3.67E-08	6.08E-08	6.07E-08	4.54E-08
29	1.08E-08	1.57E-08	2.42E-08	3.91E-08	6.49E-08	6.54E-08	5.07E-08
30	1.10E-08	1.55E-08	2.33E-08	3.77E-08	6.22E-08	6.24E-08	4.89E-08
31	1.06E-08	1.52E-08	2.34E-08	3.69E-08	6.13E-08	6.16E-08	4.77E-08
32	1.10E-08	1.58E-08	2.46E-08	3.88E-08	6.44E-08	5.96E-08	4.23E-08
33	1.11E-08	1.60E-08	2.46E-08	3.90E-08	6.44E-08	6.01E-08	4.33E-08
34	1.07E-08	1.57E-08	2.44E-08	3.89E-08	6.42E-08	5.91E-08	4.20E-08
35	1.14E-08	1.63E-08	2.49E-08	3.92E-08	6.39E-08	5.92E-08	4.29E-08
36	1.15E-08	1.63E-08	2.46E-08	3.92E-08	6.50E-08	6.07E-08	4.37E-08
37	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08
38	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08	1.06E-08
Biased Statistics							
Average Biased	1.06E-08	1.53E-08	2.37E-08	3.83E-08	6.40E-08	6.38E-08	4.87E-08
Std Dev Biased	5.24E-10	5.24E-10	9.35E-10	1.97E-09	4.02E-09	3.36E-09	2.22E-09
Ps90%/90% (+KTL) Biased	1.21E-08	1.68E-08	2.63E-08	4.37E-08	7.50E-08	7.30E-08	5.48E-08
Ps90%/90% (-KTL) Biased	9.20E-09	1.39E-08	2.11E-08	3.30E-08	5.29E-08	5.46E-08	4.26E-08
Un-Biased Statistics							
Average Un-Biased	1.12E-08	1.60E-08	2.46E-08	3.90E-08	6.44E-08	5.97E-08	4.28E-08
Std Dev Un-Biased	3.09E-10	2.50E-10	1.88E-10	1.96E-10	3.89E-10	6.72E-10	7.09E-10
Ps90%/90% (+KTL) Un-Biased	1.20E-08	1.67E-08	2.51E-08	3.96E-08	6.55E-08	6.16E-08	4.48E-08
Ps90%/90% (-KTL) Un-Biased	1.03E-08	1.53E-08	2.41E-08	3.85E-08	6.33E-08	5.79E-08	4.09E-08
Specification MIN	-5.00E-08	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS
	5.00E-08	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

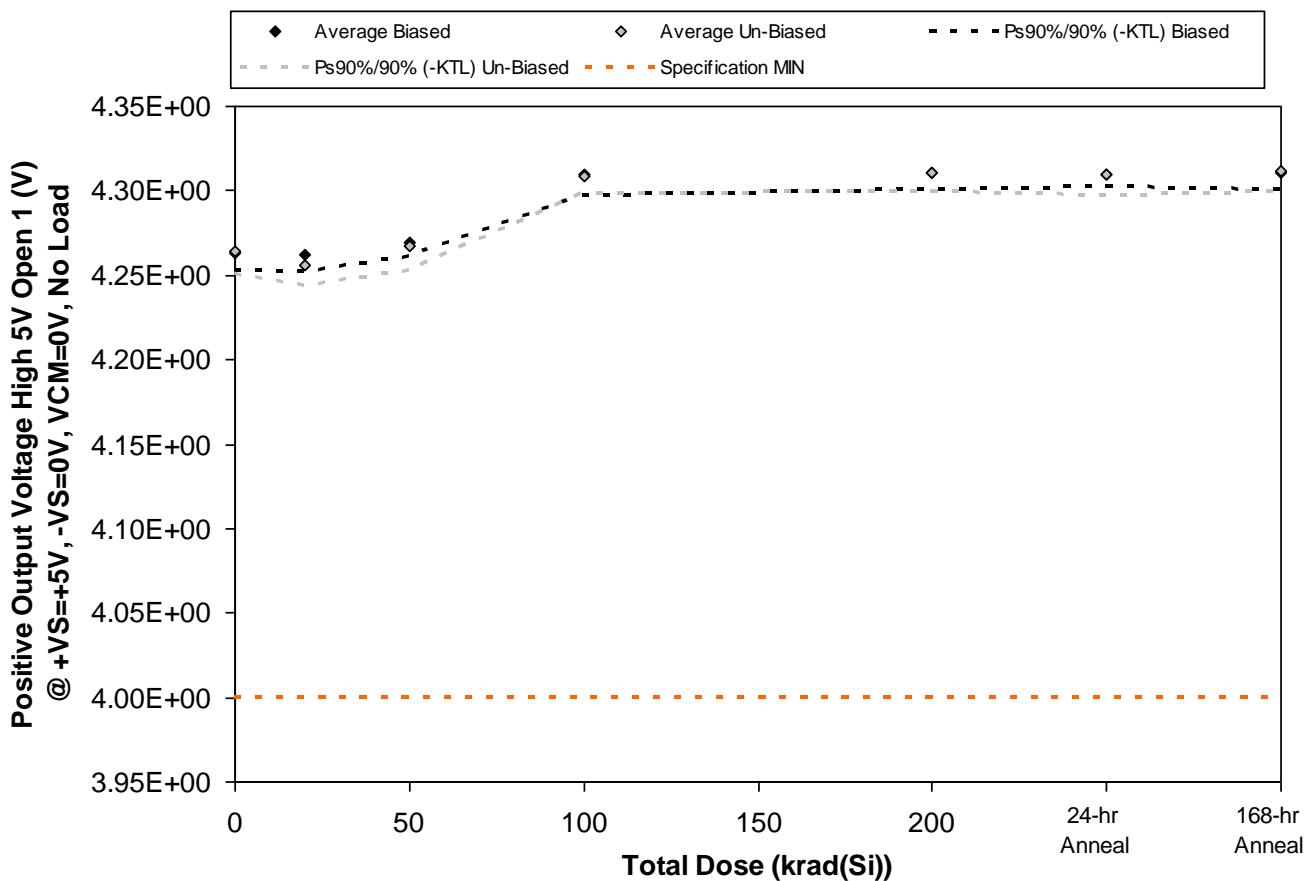


Figure 5.35. Plot of Positive Output Voltage High 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.35. Raw data for Positive Output Voltage High 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage High 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
28	4.27E+00	4.27E+00	4.27E+00	4.31E+00	4.32E+00	4.31E+00	4.32E+00
29	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
30	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
31	4.26E+00	4.26E+00	4.27E+00	4.30E+00	4.31E+00	4.31E+00	4.31E+00
32	4.27E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
33	4.26E+00	4.25E+00	4.26E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
34	4.27E+00	4.26E+00	4.27E+00	4.32E+00	4.32E+00	4.32E+00	4.32E+00
35	4.26E+00	4.25E+00	4.26E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
36	4.26E+00	4.25E+00	4.26E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
37	4.27E+00	4.26E+00	4.27E+00	4.27E+00	4.26E+00	4.27E+00	4.27E+00
38	4.26E+00	4.26E+00	4.26E+00	4.27E+00	4.26E+00	4.26E+00	4.27E+00
Biased Statistics							
Average Biased	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
Std Dev Biased	3.63E-03	4.04E-03	3.13E-03	4.62E-03	3.77E-03	2.86E-03	4.00E-03
Ps90%/90% (+KTL) Biased	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00	4.32E+00
Ps90%/90% (-KTL) Biased	4.25E+00	4.25E+00	4.26E+00	4.30E+00	4.30E+00	4.30E+00	4.30E+00
Un-Biased Statistics							
Average Un-Biased	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00	4.31E+00
Std Dev Un-Biased	4.95E-03	4.44E-03	5.18E-03	3.94E-03	4.15E-03	4.53E-03	4.53E-03
Ps90%/90% (+KTL) Un-Biased	4.28E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00	4.32E+00
Ps90%/90% (-KTL) Un-Biased	4.25E+00	4.24E+00	4.25E+00	4.30E+00	4.30E+00	4.30E+00	4.30E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

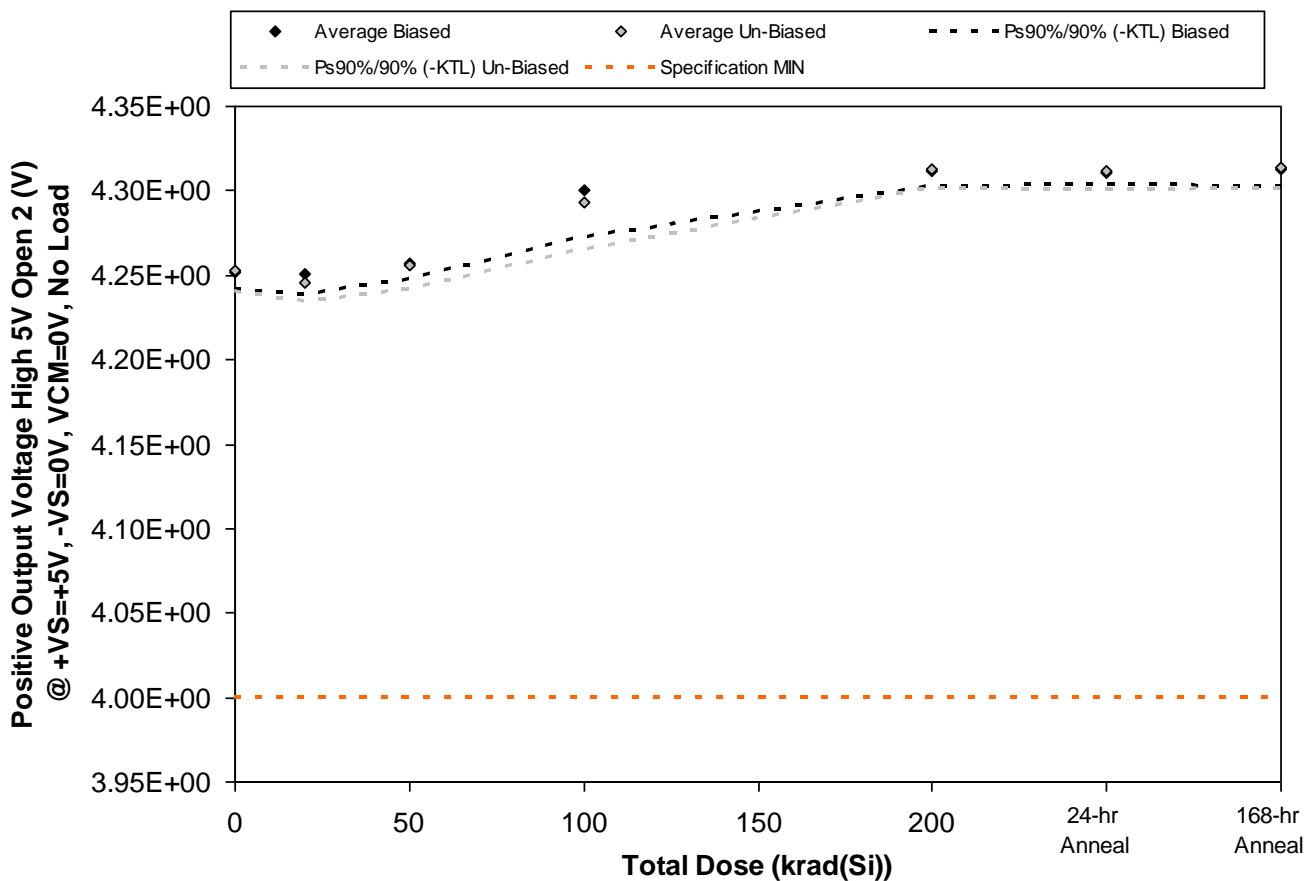


Figure 5.36. Plot of Positive Output Voltage High 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.36. Raw data for Positive Output Voltage High 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage High 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	4.25E+00	4.25E+00	4.26E+00	4.32E+00	4.31E+00	4.31E+00	4.31E+00
28	4.26E+00	4.26E+00	4.26E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
29	4.25E+00	4.25E+00	4.26E+00	4.30E+00	4.31E+00	4.31E+00	4.31E+00
30	4.25E+00	4.25E+00	4.26E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
31	4.25E+00	4.25E+00	4.25E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
32	4.26E+00	4.25E+00	4.26E+00	4.30E+00	4.32E+00	4.31E+00	4.32E+00
33	4.25E+00	4.25E+00	4.25E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
34	4.26E+00	4.25E+00	4.26E+00	4.31E+00	4.32E+00	4.32E+00	4.32E+00
35	4.25E+00	4.24E+00	4.25E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
36	4.25E+00	4.24E+00	4.25E+00	4.28E+00	4.31E+00	4.31E+00	4.31E+00
37	4.26E+00	4.25E+00	4.26E+00	4.26E+00	4.25E+00	4.25E+00	4.26E+00
38	4.25E+00	4.25E+00	4.25E+00	4.25E+00	4.25E+00	4.25E+00	4.25E+00
Biased Statistics							
Average Biased	4.25E+00	4.25E+00	4.26E+00	4.30E+00	4.31E+00	4.31E+00	4.31E+00
Std Dev Biased	3.77E-03	4.62E-03	3.39E-03	1.03E-02	3.70E-03	2.86E-03	3.71E-03
Ps90%/90% (+KTL) Biased	4.26E+00	4.26E+00	4.27E+00	4.33E+00	4.32E+00	4.32E+00	4.32E+00
Ps90%/90% (-KTL) Biased	4.24E+00	4.24E+00	4.25E+00	4.27E+00	4.30E+00	4.30E+00	4.30E+00
Un-Biased Statistics							
Average Un-Biased	4.25E+00	4.25E+00	4.26E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
Std Dev Un-Biased	4.49E-03	4.09E-03	5.03E-03	1.04E-02	4.15E-03	4.15E-03	4.28E-03
Ps90%/90% (+KTL) Un-Biased	4.27E+00	4.26E+00	4.27E+00	4.32E+00	4.32E+00	4.32E+00	4.33E+00
Ps90%/90% (-KTL) Un-Biased	4.24E+00	4.23E+00	4.24E+00	4.26E+00	4.30E+00	4.30E+00	4.30E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

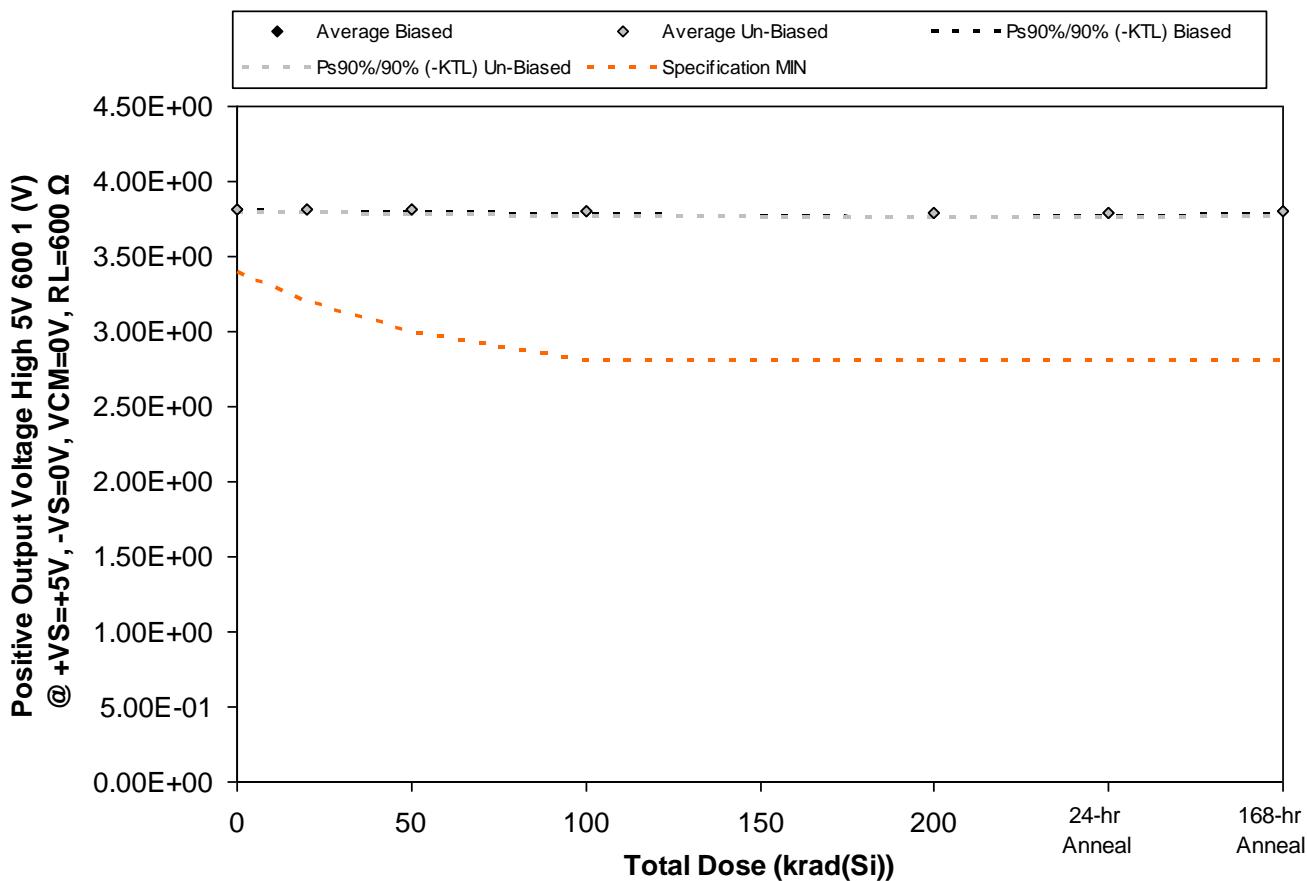


Figure 5.37. Plot of Positive Output Voltage High 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.37. Raw data for Positive Output Voltage High 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage High 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.79E+00	3.80E+00	3.81E+00
28	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.82E+00
29	3.82E+00	3.81E+00	3.81E+00	3.80E+00	3.79E+00	3.79E+00	3.80E+00
30	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.79E+00	3.80E+00	3.81E+00
31	3.81E+00	3.80E+00	3.80E+00	3.79E+00	3.77E+00	3.78E+00	3.79E+00
32	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.81E+00
33	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.78E+00	3.79E+00	3.80E+00
34	3.84E+00	3.83E+00	3.83E+00	3.82E+00	3.81E+00	3.81E+00	3.82E+00
35	3.81E+00	3.81E+00	3.80E+00	3.79E+00	3.78E+00	3.78E+00	3.79E+00
36	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.78E+00	3.78E+00	3.79E+00
37	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
38	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
Biased Statistics							
Average Biased	3.82E+00	3.81E+00	3.81E+00	3.80E+00	3.79E+00	3.79E+00	3.80E+00
Std Dev Biased	7.33E-03	9.07E-03	8.76E-03	9.97E-03	1.17E-02	1.09E-02	1.02E-02
Ps90%/90% (+KTL) Biased	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.83E+00
Ps90%/90% (-KTL) Biased	3.80E+00	3.79E+00	3.79E+00	3.78E+00	3.76E+00	3.76E+00	3.78E+00
Un-Biased Statistics							
Average Un-Biased	3.82E+00	3.81E+00	3.81E+00	3.80E+00	3.79E+00	3.79E+00	3.80E+00
Std Dev Un-Biased	1.00E-02	9.96E-03	1.08E-02	1.17E-02	1.41E-02	1.42E-02	1.29E-02
Ps90%/90% (+KTL) Un-Biased	3.85E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.84E+00
Ps90%/90% (-KTL) Un-Biased	3.79E+00	3.79E+00	3.78E+00	3.77E+00	3.75E+00	3.75E+00	3.77E+00
Specification MIN	3.40E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00	2.80E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

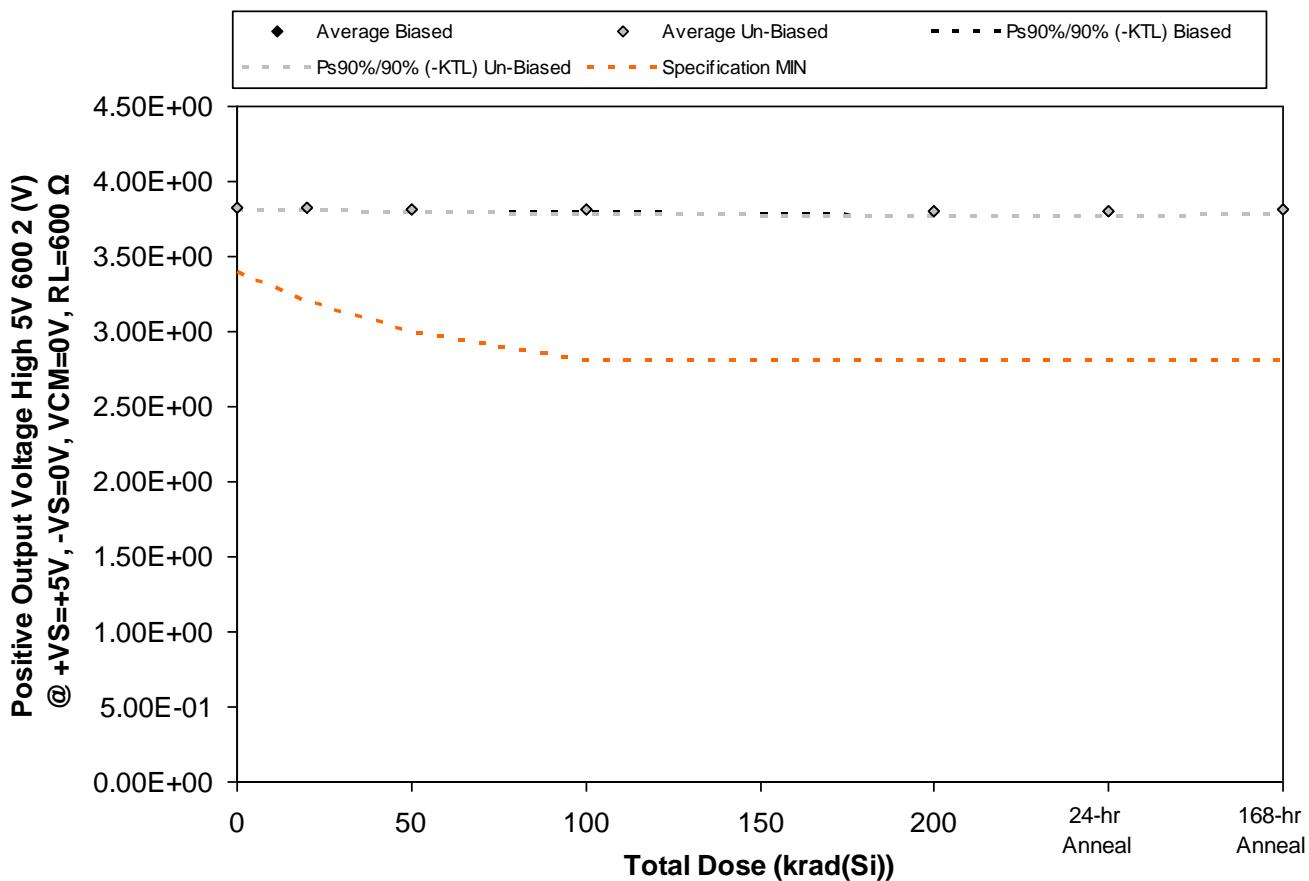


Figure 5.38. Plot of Positive Output Voltage High 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.38. Raw data for Positive Output Voltage High 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Output Voltage High 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
	27	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.80E+00	3.80E+00	3.81E+00
	28	3.84E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.83E+00
	29	3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.80E+00	3.80E+00	3.81E+00
	30	3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.80E+00	3.81E+00	3.82E+00
	31	3.82E+00	3.81E+00	3.81E+00	3.80E+00	3.78E+00	3.79E+00	3.80E+00
	32	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.82E+00
	33	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.79E+00	3.79E+00	3.80E+00
	34	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.82E+00	3.82E+00	3.83E+00
	35	3.82E+00	3.82E+00	3.81E+00	3.80E+00	3.79E+00	3.79E+00	3.80E+00
	36	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.79E+00	3.79E+00	3.81E+00
	37	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
	38	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
Biased Statistics								
Average Biased		3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.80E+00	3.80E+00	3.81E+00
Std Dev Biased		7.53E-03	9.28E-03	8.62E-03	9.75E-03	1.18E-02	1.11E-02	1.04E-02
Ps90%/90% (+KTL) Biased		3.85E+00	3.85E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.84E+00
Ps90%/90% (-KTL) Biased		3.81E+00	3.80E+00	3.80E+00	3.79E+00	3.77E+00	3.77E+00	3.78E+00
Un-Biased Statistics								
Average Un-Biased		3.83E+00	3.82E+00	3.82E+00	3.81E+00	3.80E+00	3.80E+00	3.81E+00
Std Dev Un-Biased		9.12E-03	9.18E-03	1.01E-02	1.07E-02	1.33E-02	1.29E-02	1.20E-02
Ps90%/90% (+KTL) Un-Biased		3.85E+00	3.85E+00	3.85E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
Ps90%/90% (-KTL) Un-Biased		3.80E+00	3.80E+00	3.79E+00	3.78E+00	3.76E+00	3.77E+00	3.78E+00
Specification MIN		3.40E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00	2.80E+00
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS

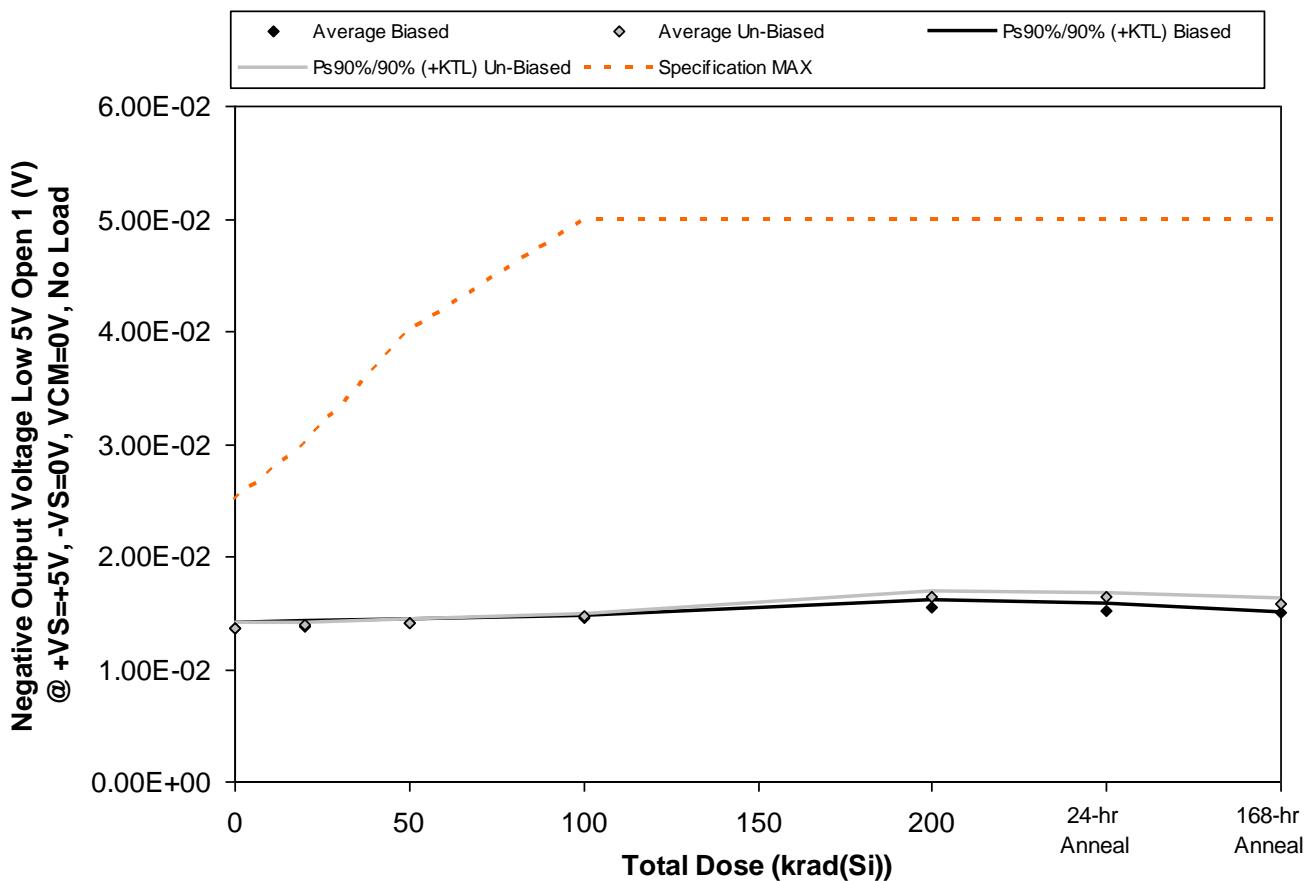


Figure 5.39. Plot of Negative Output Voltage Low 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.39. Raw data for Negative Output Voltage Low 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.36E-02	1.37E-02	1.40E-02	1.46E-02	1.59E-02	1.56E-02	1.50E-02
28	1.39E-02	1.41E-02	1.42E-02	1.45E-02	1.52E-02	1.51E-02	1.49E-02
29	1.36E-02	1.38E-02	1.41E-02	1.45E-02	1.55E-02	1.52E-02	1.50E-02
30	1.36E-02	1.39E-02	1.41E-02	1.45E-02	1.53E-02	1.50E-02	1.50E-02
31	1.35E-02	1.38E-02	1.39E-02	1.44E-02	1.54E-02	1.51E-02	1.50E-02
32	1.37E-02	1.39E-02	1.41E-02	1.48E-02	1.64E-02	1.63E-02	1.58E-02
33	1.35E-02	1.39E-02	1.42E-02	1.47E-02	1.66E-02	1.63E-02	1.60E-02
34	1.39E-02	1.40E-02	1.43E-02	1.48E-02	1.63E-02	1.62E-02	1.56E-02
35	1.38E-02	1.38E-02	1.41E-02	1.48E-02	1.66E-02	1.65E-02	1.60E-02
36	1.36E-02	1.38E-02	1.42E-02	1.47E-02	1.65E-02	1.65E-02	1.58E-02
37	1.39E-02	1.39E-02	1.38E-02	1.39E-02	1.38E-02	1.39E-02	1.39E-02
38	1.38E-02	1.38E-02	1.38E-02	1.38E-02	1.38E-02	1.38E-02	1.38E-02
Biased Statistics							
Average Biased	1.36E-02	1.39E-02	1.41E-02	1.45E-02	1.55E-02	1.52E-02	1.50E-02
Std Dev Biased	1.52E-04	1.52E-04	1.14E-04	7.07E-05	2.70E-04	2.35E-04	4.47E-05
Ps90%/90% (+KTL) Biased	1.41E-02	1.43E-02	1.44E-02	1.47E-02	1.62E-02	1.58E-02	1.51E-02
Ps90%/90% (-KTL) Biased	1.32E-02	1.34E-02	1.37E-02	1.43E-02	1.47E-02	1.46E-02	1.49E-02
Un-Biased Statistics							
Average Un-Biased	1.37E-02	1.39E-02	1.42E-02	1.48E-02	1.65E-02	1.64E-02	1.58E-02
Std Dev Un-Biased	1.58E-04	8.37E-05	8.37E-05	5.48E-05	1.30E-04	1.34E-04	1.67E-04
Ps90%/90% (+KTL) Un-Biased	1.41E-02	1.41E-02	1.44E-02	1.49E-02	1.68E-02	1.67E-02	1.63E-02
Ps90%/90% (-KTL) Un-Biased	1.33E-02	1.37E-02	1.40E-02	1.46E-02	1.61E-02	1.60E-02	1.54E-02
Specification MAX	2.50E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

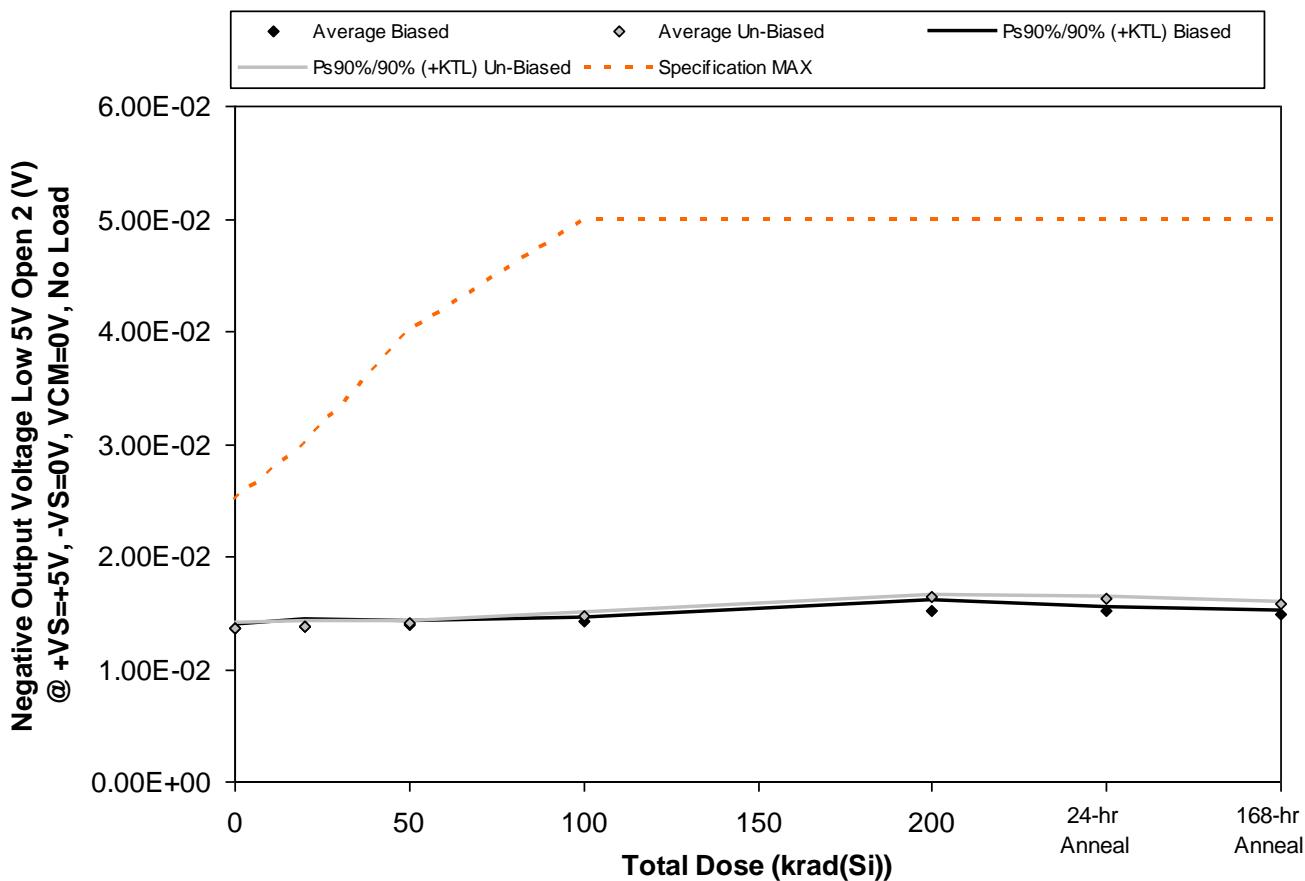


Figure 5.40. Plot of Negative Output Voltage Low 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.40. Raw data for Negative Output Voltage Low 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load	Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
	0	20	50	100	200		
Device							
27	1.36E-02	1.38E-02	1.39E-02	1.44E-02	1.58E-02	1.53E-02	1.49E-02
28	1.38E-02	1.41E-02	1.40E-02	1.44E-02	1.50E-02	1.50E-02	1.47E-02
29	1.35E-02	1.38E-02	1.40E-02	1.43E-02	1.51E-02	1.52E-02	1.49E-02
30	1.37E-02	1.36E-02	1.41E-02	1.44E-02	1.51E-02	1.50E-02	1.50E-02
31	1.35E-02	1.36E-02	1.39E-02	1.42E-02	1.51E-02	1.51E-02	1.50E-02
32	1.36E-02	1.39E-02	1.41E-02	1.46E-02	1.63E-02	1.62E-02	1.57E-02
33	1.34E-02	1.38E-02	1.40E-02	1.46E-02	1.64E-02	1.63E-02	1.57E-02
34	1.39E-02	1.41E-02	1.42E-02	1.48E-02	1.63E-02	1.62E-02	1.57E-02
35	1.35E-02	1.38E-02	1.40E-02	1.48E-02	1.65E-02	1.64E-02	1.59E-02
36	1.35E-02	1.37E-02	1.41E-02	1.47E-02	1.63E-02	1.62E-02	1.57E-02
37	1.37E-02	1.37E-02	1.37E-02	1.38E-02	1.37E-02	1.38E-02	1.37E-02
38	1.37E-02	1.36E-02	1.37E-02	1.38E-02	1.38E-02	1.38E-02	1.36E-02
Biased Statistics							
Average Biased	1.36E-02	1.38E-02	1.40E-02	1.43E-02	1.52E-02	1.51E-02	1.49E-02
Std Dev Biased	1.30E-04	2.05E-04	8.37E-05	8.94E-05	3.27E-04	1.30E-04	1.22E-04
Ps90%/90% (+KTL) Biased	1.40E-02	1.43E-02	1.42E-02	1.46E-02	1.61E-02	1.55E-02	1.52E-02
Ps90%/90% (-KTL) Biased	1.33E-02	1.32E-02	1.38E-02	1.41E-02	1.43E-02	1.48E-02	1.46E-02
Un-Biased Statistics							
Average Un-Biased	1.36E-02	1.39E-02	1.41E-02	1.47E-02	1.64E-02	1.63E-02	1.57E-02
Std Dev Un-Biased	1.92E-04	1.52E-04	8.37E-05	1.00E-04	8.94E-05	8.94E-05	8.94E-05
Ps90%/90% (+KTL) Un-Biased	1.41E-02	1.43E-02	1.43E-02	1.50E-02	1.66E-02	1.65E-02	1.60E-02
Ps90%/90% (-KTL) Un-Biased	1.31E-02	1.34E-02	1.39E-02	1.44E-02	1.61E-02	1.60E-02	1.55E-02
Specification MAX	2.50E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS

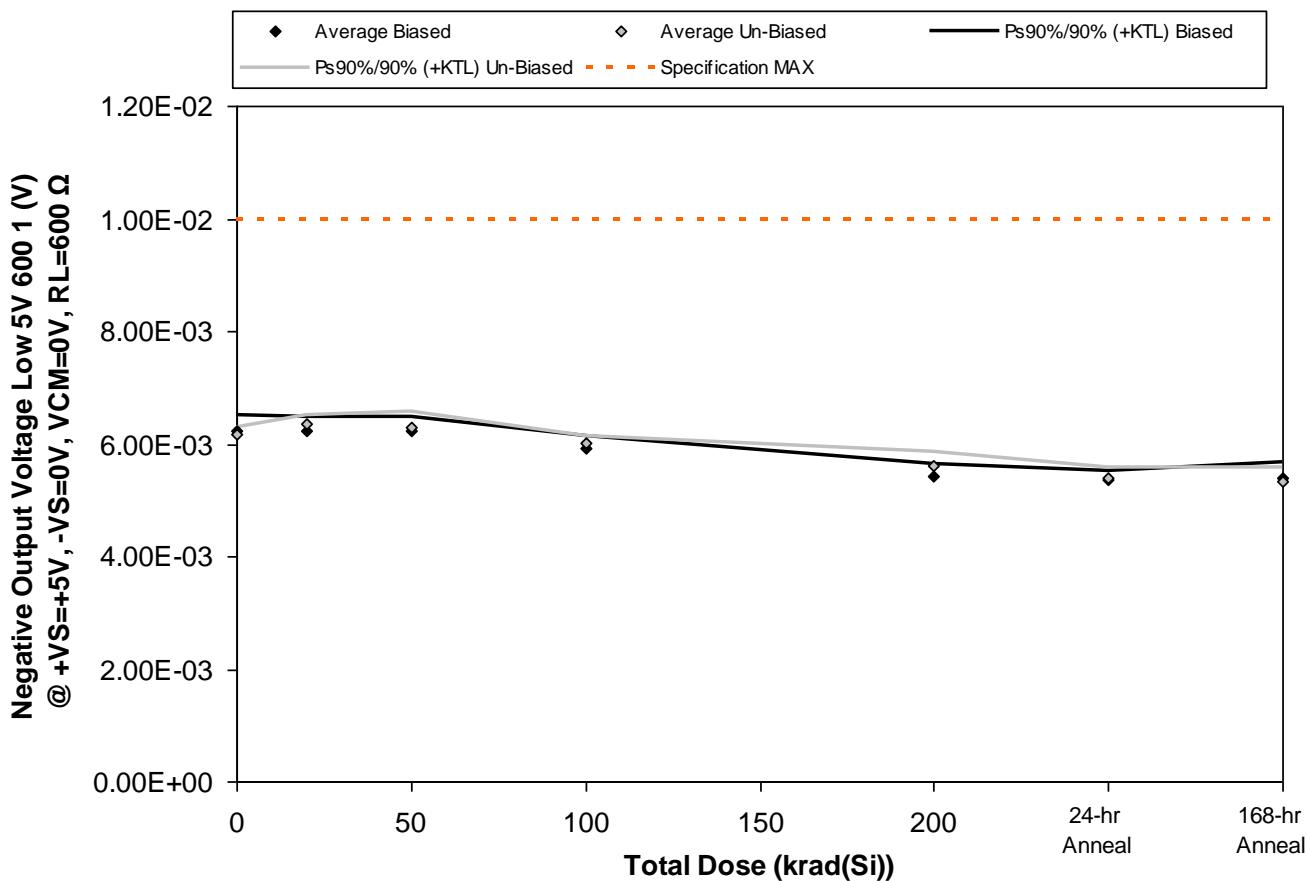


Figure 5.41. Plot of Negative Output Voltage Low 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.41. Raw data for Negative Output Voltage Low 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	6.30E-03	6.20E-03	6.10E-03	5.90E-03	5.50E-03	5.40E-03	5.30E-03	
28	6.30E-03	6.40E-03	6.30E-03	6.00E-03	5.40E-03	5.30E-03	5.50E-03	
29	6.10E-03	6.20E-03	6.20E-03	6.00E-03	5.30E-03	5.40E-03	5.30E-03	
30	6.10E-03	6.20E-03	6.30E-03	5.80E-03	5.50E-03	5.40E-03	5.50E-03	
31	6.30E-03	6.20E-03	6.30E-03	5.90E-03	5.40E-03	5.30E-03	5.40E-03	
32	6.20E-03	6.30E-03	6.40E-03	6.00E-03	5.60E-03	5.40E-03	5.40E-03	
33	6.20E-03	6.40E-03	6.30E-03	6.00E-03	5.70E-03	5.40E-03	5.20E-03	
34	6.20E-03	6.40E-03	6.40E-03	6.10E-03	5.50E-03	5.30E-03	5.30E-03	
35	6.10E-03	6.40E-03	6.20E-03	6.00E-03	5.70E-03	5.50E-03	5.40E-03	
36	6.20E-03	6.30E-03	6.20E-03	6.00E-03	5.60E-03	5.40E-03	5.40E-03	
37	6.30E-03	6.40E-03	6.30E-03	6.30E-03	6.50E-03	6.40E-03	6.30E-03	
38	6.30E-03	6.30E-03	6.60E-03	6.50E-03	6.40E-03	6.40E-03	6.30E-03	
Biased Statistics								
Average Biased		6.22E-03	6.24E-03	6.24E-03	5.92E-03	5.42E-03	5.36E-03	5.40E-03
Std Dev Biased		1.10E-04	8.94E-05	8.94E-05	8.37E-05	8.37E-05	5.48E-05	1.00E-04
Ps90%/90% (+KTL) Biased		6.52E-03	6.49E-03	6.49E-03	6.15E-03	5.65E-03	5.51E-03	5.67E-03
Ps90%/90% (-KTL) Biased		5.92E-03	5.99E-03	5.99E-03	5.69E-03	5.19E-03	5.21E-03	5.13E-03
Un-Biased Statistics								
Average Un-Biased		6.18E-03	6.36E-03	6.30E-03	6.02E-03	5.62E-03	5.40E-03	5.34E-03
Std Dev Un-Biased		4.47E-05	5.48E-05	1.00E-04	4.47E-05	8.37E-05	7.07E-05	8.94E-05
Ps90%/90% (+KTL) Un-Biased		6.30E-03	6.51E-03	6.57E-03	6.14E-03	5.85E-03	5.59E-03	5.59E-03
Ps90%/90% (-KTL) Un-Biased		6.06E-03	6.21E-03	6.03E-03	5.90E-03	5.39E-03	5.21E-03	5.09E-03
Specification MAX		1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS

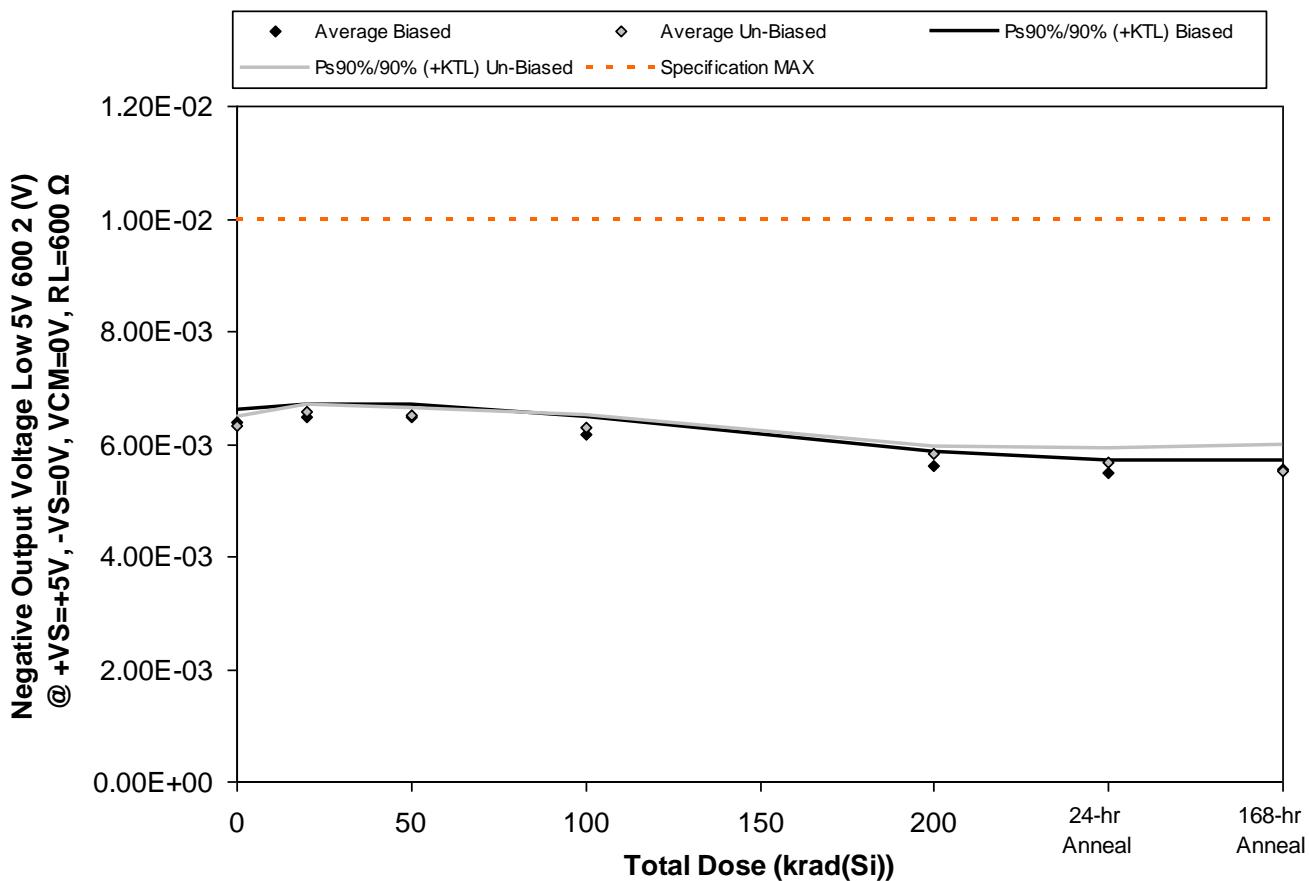


Figure 5.42. Plot of Negative Output Voltage Low 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.42. Raw data for Negative Output Voltage Low 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω		Total Dose (krad(Si))				24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200	
27	6.30E-03	6.50E-03	6.50E-03	6.10E-03	5.70E-03	5.50E-03	5.50E-03
28	6.50E-03	6.60E-03	6.60E-03	6.30E-03	5.70E-03	5.50E-03	5.60E-03
29	6.40E-03	6.40E-03	6.40E-03	6.00E-03	5.50E-03	5.40E-03	5.50E-03
30	6.40E-03	6.50E-03	6.50E-03	6.20E-03	5.60E-03	5.60E-03	5.50E-03
31	6.30E-03	6.40E-03	6.40E-03	6.20E-03	5.60E-03	5.50E-03	5.60E-03
32	6.30E-03	6.60E-03	6.50E-03	6.20E-03	5.80E-03	5.60E-03	5.40E-03
33	6.30E-03	6.50E-03	6.50E-03	6.20E-03	5.80E-03	5.70E-03	5.40E-03
34	6.40E-03	6.60E-03	6.60E-03	6.40E-03	5.80E-03	5.60E-03	5.40E-03
35	6.30E-03	6.60E-03	6.50E-03	6.30E-03	5.90E-03	5.70E-03	5.70E-03
36	6.40E-03	6.60E-03	6.50E-03	6.30E-03	5.80E-03	5.80E-03	5.70E-03
37	6.50E-03	6.70E-03	6.60E-03	6.60E-03	6.70E-03	6.60E-03	6.50E-03
38	6.50E-03	6.70E-03	6.60E-03	6.60E-03	6.60E-03	6.50E-03	6.50E-03
Biased Statistics							
Average Biased		6.38E-03	6.48E-03	6.48E-03	6.16E-03	5.62E-03	5.50E-03
Std Dev Biased		8.37E-05	8.37E-05	8.37E-05	1.14E-04	8.37E-05	7.07E-05
Ps90%/90% (+KTL) Biased		6.61E-03	6.71E-03	6.71E-03	6.47E-03	5.85E-03	5.69E-03
Ps90%/90% (-KTL) Biased		6.15E-03	6.25E-03	6.25E-03	5.85E-03	5.39E-03	5.31E-03
Un-Biased Statistics							
Average Un-Biased		6.34E-03	6.58E-03	6.52E-03	6.28E-03	5.82E-03	5.68E-03
Std Dev Un-Biased		5.48E-05	4.47E-05	4.47E-05	8.37E-05	4.47E-05	8.37E-05
Ps90%/90% (+KTL) Un-Biased		6.49E-03	6.70E-03	6.64E-03	6.51E-03	5.94E-03	5.91E-03
Ps90%/90% (-KTL) Un-Biased		6.19E-03	6.46E-03	6.40E-03	6.05E-03	5.70E-03	5.45E-03
Specification MAX		1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS

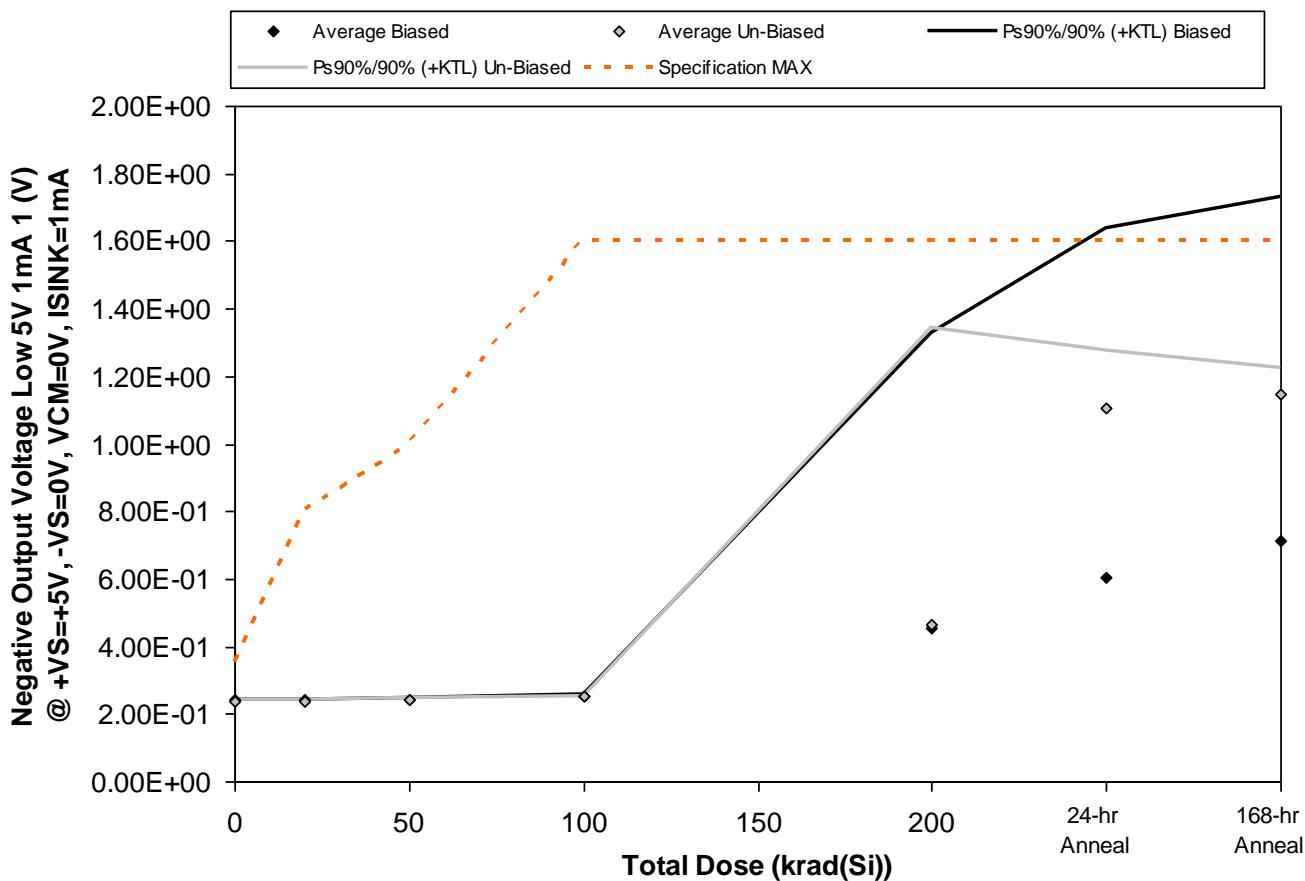


Figure 5.43. Plot of Negative Output Voltage Low 5V 1mA 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.43. Raw data for Negative Output Voltage Low 5V 1mA 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V 1mA 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	2.41E-01	2.41E-01	2.44E-01	2.57E-01	3.22E-01	9.97E-01	1.01E+00	
28	2.40E-01	2.41E-01	2.42E-01	2.53E-01	3.07E-01	3.29E-01	3.01E-01	
29	2.42E-01	2.42E-01	2.44E-01	2.56E-01	1.03E+00	1.03E+00	1.01E+00	
30	2.41E-01	2.41E-01	2.44E-01	2.53E-01	3.01E-01	3.15E-01	3.15E-01	
31	2.40E-01	2.40E-01	2.43E-01	2.53E-01	3.17E-01	3.38E-01	9.32E-01	
32	2.41E-01	2.40E-01	2.43E-01	2.53E-01	3.32E-01	1.13E+00	1.15E+00	
33	2.41E-01	2.39E-01	2.42E-01	2.52E-01	3.10E-01	1.07E+00	1.14E+00	
34	2.38E-01	2.37E-01	2.41E-01	2.51E-01	1.04E+00	1.19E+00	1.19E+00	
35	2.40E-01	2.41E-01	2.44E-01	2.54E-01	3.33E-01	1.11E+00	1.12E+00	
36	2.41E-01	2.39E-01	2.43E-01	2.53E-01	3.04E-01	1.03E+00	1.12E+00	
37	2.39E-01	2.39E-01	2.39E-01	2.39E-01	2.39E-01	2.40E-01	2.39E-01	
38	2.40E-01	2.41E-01	2.40E-01	2.40E-01	2.40E-01	2.41E-01	2.39E-01	
Biased Statistics								
Average Biased		2.41E-01	2.41E-01	2.43E-01	2.54E-01	4.55E-01	6.03E-01	7.14E-01
Std Dev Biased		8.37E-04	7.07E-04	8.94E-04	1.95E-03	3.20E-01	3.77E-01	3.72E-01
Ps90%/90% (+KTL) Biased		2.43E-01	2.43E-01	2.46E-01	2.60E-01	1.33E+00	1.64E+00	1.73E+00
Ps90%/90% (-KTL) Biased		2.39E-01	2.39E-01	2.41E-01	2.49E-01	-4.22E-01	-4.32E-01	-3.06E-01
Un-Biased Statistics								
Average Un-Biased		2.40E-01	2.39E-01	2.43E-01	2.53E-01	4.63E-01	1.10E+00	1.15E+00
Std Dev Un-Biased		1.30E-03	1.48E-03	1.14E-03	1.14E-03	3.21E-01	6.23E-02	2.86E-02
Ps90%/90% (+KTL) Un-Biased		2.44E-01	2.43E-01	2.46E-01	2.56E-01	1.34E+00	1.27E+00	1.22E+00
Ps90%/90% (-KTL) Un-Biased		2.37E-01	2.35E-01	2.39E-01	2.49E-01	-4.16E-01	9.33E-01	1.07E+00
Specification MAX		3.50E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00	1.60E+00
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS

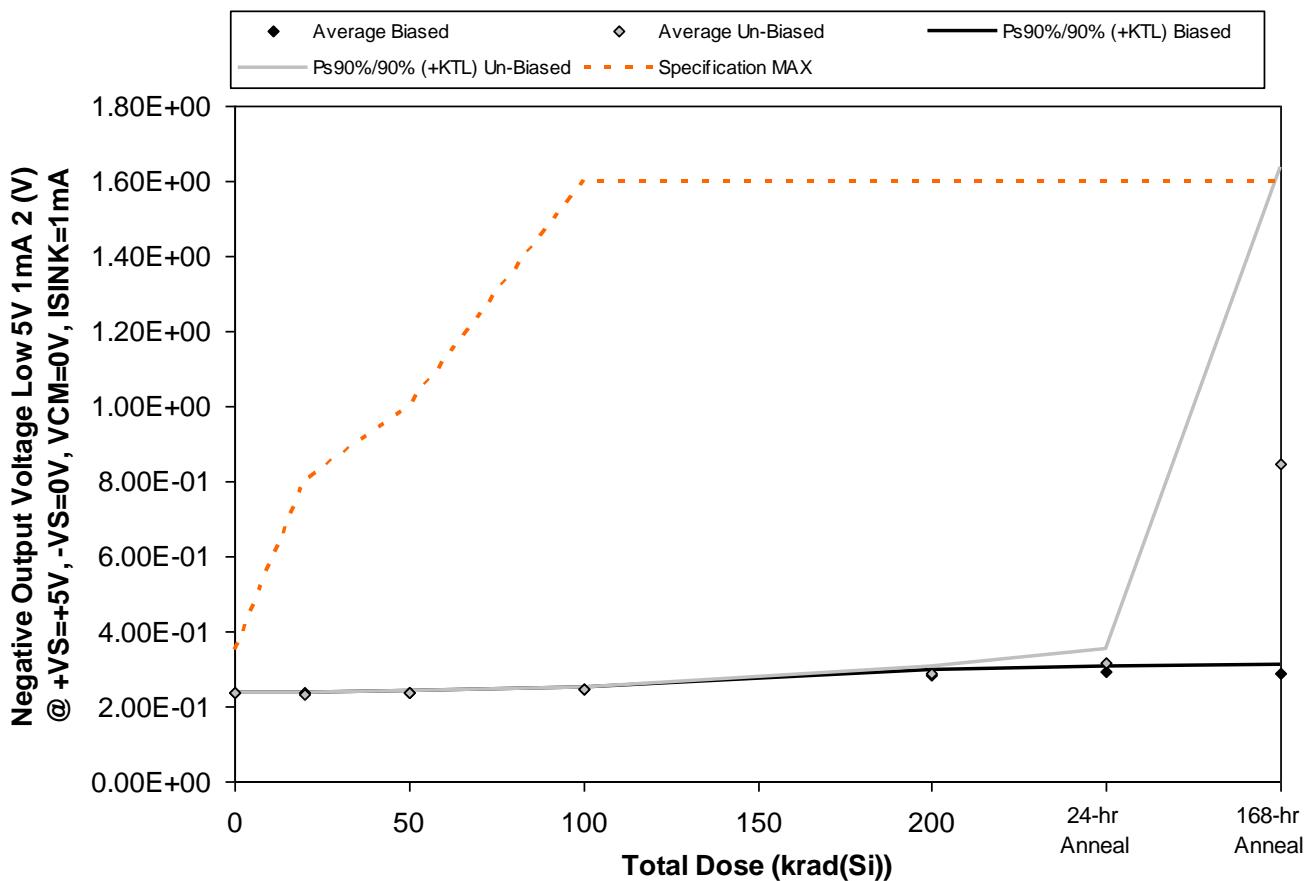


Figure 5.44. Plot of Negative Output Voltage Low 5V 1mA 2 (V) @ $+VS=+5V$, $-VS=0V$, $VCM=0V$, $ISINK=1mA$ versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.44. Raw data for Negative Output Voltage Low 5V 1mA 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Output Voltage Low 5V 1mA 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA		Total Dose (krad(Si))					24-hr Anneal	168-hr Anneal
Device		0	20	50	100	200		
27	2.36E-01	2.37E-01	2.38E-01	2.50E-01	2.88E-01	2.96E-01	2.97E-01	
28	2.35E-01	2.36E-01	2.37E-01	2.47E-01	2.82E-01	2.87E-01	2.77E-01	
29	2.36E-01	2.37E-01	2.40E-01	2.49E-01	2.92E-01	2.99E-01	2.93E-01	
30	2.36E-01	2.36E-01	2.39E-01	2.47E-01	2.80E-01	2.86E-01	2.84E-01	
31	2.35E-01	2.36E-01	2.38E-01	2.47E-01	2.84E-01	2.89E-01	2.91E-01	
32	2.36E-01	2.35E-01	2.38E-01	2.47E-01	2.87E-01	3.16E-01	9.72E-01	
33	2.36E-01	2.35E-01	2.39E-01	2.47E-01	2.85E-01	3.08E-01	9.90E-01	
34	2.34E-01	2.33E-01	2.36E-01	2.45E-01	2.96E-01	3.29E-01	9.81E-01	
35	2.36E-01	2.36E-01	2.39E-01	2.48E-01	2.92E-01	3.30E-01	9.62E-01	
36	2.35E-01	2.34E-01	2.37E-01	2.46E-01	2.80E-01	2.97E-01	3.34E-01	
37	2.35E-01	2.35E-01	2.35E-01	2.34E-01	2.34E-01	2.36E-01	2.34E-01	
38	2.35E-01	2.36E-01	2.35E-01	2.35E-01	2.35E-01	2.37E-01	2.34E-01	
Biased Statistics								
Average Biased		2.36E-01	2.36E-01	2.38E-01	2.48E-01	2.85E-01	2.91E-01	2.88E-01
Std Dev Biased		5.48E-04	5.48E-04	1.14E-03	1.41E-03	4.82E-03	5.77E-03	7.92E-03
Ps90%/90% (+KTL) Biased		2.37E-01	2.38E-01	2.42E-01	2.52E-01	2.98E-01	3.07E-01	3.10E-01
Ps90%/90% (-KTL) Biased		2.34E-01	2.35E-01	2.35E-01	2.44E-01	2.72E-01	2.76E-01	2.67E-01
Un-Biased Statistics								
Average Un-Biased		2.35E-01	2.35E-01	2.38E-01	2.47E-01	2.88E-01	3.16E-01	8.48E-01
Std Dev Un-Biased		8.94E-04	1.14E-03	1.30E-03	1.14E-03	6.20E-03	1.41E-02	2.87E-01
Ps90%/90% (+KTL) Un-Biased		2.38E-01	2.38E-01	2.41E-01	2.50E-01	3.05E-01	3.55E-01	1.64E+00
Ps90%/90% (-KTL) Un-Biased		2.33E-01	2.31E-01	2.34E-01	2.43E-01	2.71E-01	2.77E-01	5.97E-02
Specification MAX		3.50E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00	1.60E+00
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS



6.0. Summary / Conclusions

The total ionizing dose testing described in this final report was performed using the facilities at Aeroflex RAD's Longmire Laboratories in Colorado Springs, CO. The high dose rate total ionizing dose (TID) source is a JLSA 81-24 irradiator modified to provide a panoramic exposure. The Co-60 rods are held in the base of the irradiator heavily shielded by lead, during the radiation exposures the rod is raised by an electronic timer/controller and the exposure is performed in air. The dose rate for this irradiator in this configuration ranges from <1rad(Si)/s to a maximum of approximately 300rad(Si)/s, determined by the distance from the source.

The parametric data was obtained as "read and record" and all the raw data plus an attributes summary are contained in this report as well as in a separate Excel file. The attributes data contains the average, standard deviation and the average with the KTL values applied. The KTL value used in this work is 2.742 per MIL-HDBK-814 using one sided tolerance limits of 90/90 and a 5-piece sample size. The 90/90 KTL values were selected to match the statistical levels specified in the MIL-PRF-38535 sampling plan for the qualification of a radiation hardness assured (RHA) component. Note that the following criteria must be met for a device to pass the total ionizing dose test: following the radiation exposure each of the 5 pieces irradiated under electrical bias shall pass the specification value. The units irradiated without electrical bias and the KTL statistics are included in this report for reference only. If any of the 5 pieces irradiated under electrical bias exceed the device post radiation data sheet specification limits, then the lot could be logged as a failure.

Based on this criterion the RH1013MH Dual Precision Operational Amplifier (from the lot traceability information provided on the first page of this test report) the units-under-test:

- PASSED the total ionizing dose test to the 200krad(Si) dose level
- PASSED following 24-hour room temperature anneal
- PASSED following 168-hour 100°C anneal

Appendix A: Photograph of Packing Label and a Sample Unit-Under-Test to Show Part Traceability



Appendix B: Radiation Bias Connections and Absolute Maximum Ratings

TID Radiation Biased Conditions: Extracted from Linear Technology RH1013M Datasheet Revision E.

Pin	Function	Connection / Bias
1	OUT A	To Pin 2 via 10kΩ Resistor
2	-IN A	To Pin 1 via 10kΩ Resistor
3	+IN A	8V via 10kΩ Resistor
4	V- (Case)	-15V Decoupled to GND W/0.1μF
5	+IN B	8V via 10kΩ Resistor
6	-IN B	To Pin 7 via 10kΩ Resistor
7	OUT B	To Pin 6 via 10kΩ Resistor
8	V+	+15V Decoupled to GND W/0.1μF

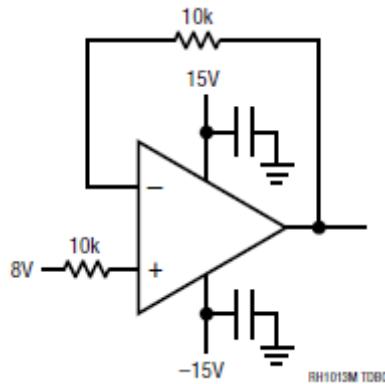


Figure B.1. Irradiation bias circuit. This figure was extracted from Linear Technology RH1013M Datasheet Revision E.

TID Radiation Unbiased Conditions: All pins grounded.

Pin	Function	Connection / Bias
1	OUT A	GND
2	-IN A	GND
3	+IN A	GND
4	V- (Case)	GND
5	+IN B	GND
6	-IN B	GND
7	OUT B	GND
8	V+	GND

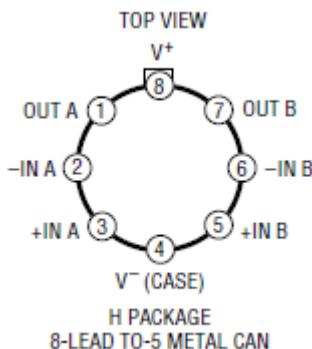


Figure B.2. H package drawing (for reference only). This figure was extracted from Linear Technology RH1013M Datasheet Revision E.

Absolute Maximum Ratings:

Parameter	Max Rating
Supply Voltage	$\pm 22V$
Differential Voltage	$\pm 30V$
Input Voltage	Equal to Positive Supply Voltage 5V Below Negative Supply Voltage
Output Short-Circuit Duration	Indefinite



Appendix C: Electrical Test Parameters and Conditions

The expected ranges of values as well as the measurement conditions are taken from Linear Technology RH1013M Datasheet Revision E. All electrical tests for this device are performed on one of Aeroflex RAD's LTS2020 Test Systems. The LTS2020 Test System is a programmable parametric tester that provides parameter measurements for a variety of digital, analog and mixed signal products including voltage regulators, voltage comparators, D to A and A to D converters. The LTS2020 Test System achieves accuracy and sensitivity through the use of software self-calibration and an internal relay matrix with separate family boards and custom personality adapter boards. The tester uses this relay matrix to connect the required test circuits, select the appropriate voltage / current sources and establish the needed measurement loops for all the tests performed. The measured parameters and test conditions are shown in Table C.1.

A listing of the measurement precision/resolution for each parameter is shown in Table C.2. The precision/resolution values were obtained from test data or from the DAC resolution of the LTS-2020 for the particular test shown, whichever is greater. To generate the precision/resolution shown in Table C.2, one of the units-under-test was tested repetitively (a total of 10-times with re-insertion between tests) to obtain the average test value and standard deviation. Using this test data MIL-HDBK-814 90/90 KTL statistics were applied to the measured standard deviation to generate the final measurement range. This value encompasses the precision/resolution of all aspects of the test system, including the LTS2020 mainframe, family board, socket assembly and DUT board as well as insertion error. In some cases, the measurement resolution is limited by the internal DACs, which results in a measured standard deviation of zero. In these instances the precision/resolution will be reported back as the LSB of the DAC.

Note that the testing and statistics used in this document are based on an “analysis of variables” technique, which relies on small sample sizes to qualify much larger lot sizes (see MIL-HDBK-814, p. 91 for a discussion of statistical treatments). Not all measured parameters are well suited to this approach due to inherent large variations. If necessary, larger samples sizes could be used to qualify these parameters using an “attributes” approach.



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table C.1. Measured parameters and test conditions for the RH1013MH Dual Precision Operational Amplifier.

Parameter	Symbol	Test Conditions
Positive Supply Current 15V (A)	+ICC_15V	VS=+/-15V, VCM=0V
Negative Supply Current 15V (A)	-IEE_15V	VS=+/-15V, VCM=0V
Input Offset Voltage 15V (V)	VOS_15V	VS=+/-15V, VCM=0V
Input Offset Current 15V (A)	IOS_15V	VS=+/-15V, VCM=0V
Positive Input Bias Current 15V (A)	+IB_15V	VS=+/-15V, VCM=0V
Negative Input Bias Current 15V (A)	-IB_15V	VS=+/-15V, VCM=0V
Common Mode Rejection Ratio 15V (dB)	CMRR_15V	VCM=+13V, -15V
Power Supply Rejection Ratio 15V (dB)	PSRR_15V	VS=+/-10V to +/-18V
Large-Signal Voltage Gain 15V (V/mV)	AVOL_15V	RL=10K, VO=+/-10V
Positive Output Voltage Swing 15V (V)	+VOUT_15V	VS=+/-15V, VCM=0V, RL=10k
Negative Output Voltage Swing 15V (V)	-VOUT_15V	VS=+/-15V, VCM=0V, RL=10k
Positive Slew Rate 15V (V/μs)	+SlewRate_15V	AV=1, VS=+/-15V, VCM=0V
Negative Slew Rate 15V (V/μs)	-SlewRate_15V	AV=1, VS=+/-15V, VCM=0V
Positive Supply Current 5V (A)	+ICC_5V	+VS=5V, -VS=0V, VCM=0V, VOUT=4V
Negative Supply Current 5V (A)	-IEE_5V	+VS=5V, -VS=0V, VCM=0V, VOUT=4V
Input Offset Voltage 5V (V)	VOS_5V	+VS=+5V, -VS=0V, VCM=0V, VOUT=4V
Input Offset Current 5V (A)	IOS_5V	+VS=+5V, -VS=0V, VCM=0V, VOUT=4V
Positive Input Bias Current 5V (A)	+IB_5V	+VS=+5V, -VS=0V, VCM=0V, VOUT=4V
Negative Input Bias Current 5V (A)	-IB_5V	+VS=+5V, -VS=0V, VCM=0V, VOUT=4V
Positive Output Voltage High 5V Open (V)	+VOUT_5V Open	+VS=+5V, -VS=0V, VCM=0V, No Load
Positive Output Voltage High 5V 600 (V)	+VOUT_5V 600	+VS=+5V, -VS=0V, VCM=0V, RL=600Ω
Negative Output Voltage Low 5V Open (V)	-VOUT_5V Open	+VS=+5V, -VS=0V, VCM=0V, No Load
Negative Output Voltage Low 5V 600 (V)	-VOUT_5V 600	+VS=+5V, -VS=0V, VCM=0V, RL=600Ω
Negative Output Voltage Low 5V 1mA (V)	-VOUT_5V 1mA	+VS=+5V, -VS=0V, VCM=0V, ISINK=1mA



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table C.2. Measured parameters, pre-irradiation specifications and measurement precision for the RH1013MH Dual Precision Operational Amplifier.

Parameter	Pre-Irradiation Specification		Measurement Precision/Resolution
	MIN	MAX	
Positive Supply Current 15V (A)		1.10E-03	±1.75E-06
Negative Supply Current 15V (A)	-1.10E-03		±2.05E-06
Input Offset Voltage 15V (V)	-3.00E-04	3.00E-04	±2.87E-06
Input Offset Current 15V (A)	-1.00E-08	1.00E-08	±2.73E-11
Positive Input Bias Current 15V (A)	-3.00E-08	3.00E-08	±2.34E-11
Negative Input Bias Current 15V (A)	-3.00E-08	3.00E-08	±3.20E-11
Common Mode Rejection Ratio 15V (dB)	9.70E+01		±6.95E-01
Power Supply Rejection Ratio 15V (dB)	1.00E+02		±4.07E+00
Large-Signal Voltage Gain 15V (V/mV)	1.20E+03		±4.72E+01%
Positive Output Voltage Swing 15V (V)	1.25E+01		±6.53E-04
Negative Output Voltage Swing 15V (V)		-1.25E+01	±8.71E-04
Positive Slew Rate 15V (V/µs)	2.00E-01		±3.02E-02
Negative Slew Rate 15V (V/µs)		-2.00E-01	±3.49E-02
Input Offset Voltage 5V (V)	-4.50E-04	4.50E-04	±9.65E-07
Input Offset Current 5V (A)	-1.00E-08	1.00E-08	±2.94E-11
Positive Input Bias Current 5V (A)	-5.00E-08	5.00E-08	±5.94E-11
Positive Input Bias Current 5V (A)	-5.00E-08	5.00E-08	±4.89E-11
Positive Output Voltage High 5V Open (V)	4.00E+00		±8.71E-04
Positive Output Voltage High 5V 600 (V)	3.40E+00		±9.97E-04
Negative Output Voltage Low 5V Open (V)		2.50E-02	±1.74E-04
Negative Output Voltage Low 5V 600 (V)		1.00E-02	±1.70E-04
Negative Output Voltage Low 5V 1mA (V)		3.50E-01	±6.53E-04

Appendix D: List of Figures Used in the Results Section (Section 5)

- 5.1. Positive Supply Current 15V (A) @ VS=+/-15V, VCM=0V
- 5.2. Negative Supply Current 15V (A) @ VS=+/-15V, VCM=0V
- 5.3. Input Offset Voltage1 15V (V) @ VS=+/-15V, VCM=0V
- 5.4. Input Offset Voltage2 15V (V) @ VS=+/-15V, VCM=0V
- 5.5. Input Offset Current1 15V (A) @ VS=+/-15V, VCM=0V
- 5.6. Input Offset Current2 15V (A) @ VS=+/-15V, VCM=0V
- 5.7. Positive Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V
- 5.8. Positive Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V
- 5.9. Negative Input Bias Current1 15V (A) @ VS=+/-15V, VCM=0V
- 5.10. Negative Input Bias Current2 15V (A) @ VS=+/-15V, VCM=0V
- 5.11. Common Mode Rejection Ratio1 15V (dB) @ VCM=+13V, -15V
- 5.12. Common Mode Rejection Ratio2 15V (dB) @ VCM=+13V, -15V
- 5.13. Power Supply Rejection Ratio1 15V (dB) @ VS=+/-10V to +/-18V
- 5.14. Power Supply Rejection Ratio2 15V (dB) @ VS=+/-10V to +/-18V
- 5.15. Large-Signal Voltage Gain1 15V (V/mV) @ RL=10K, VO=+/-10V
- 5.16. Large-Signal Voltage Gain2 15V (V/mV) @ RL=10K, VO=+/-10V
- 5.17. Positive Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
- 5.18. Positive Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
- 5.19. Negative Output Voltage Swing1 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
- 5.20. Negative Output Voltage Swing2 15V (V) @ VS=+/-15V, VCM=0V, RL=10k
- 5.21. Positive Slew Rate1 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V
- 5.22. Positive Slew Rate2 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V
- 5.23. Negative Slew Rate1 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V
- 5.24. Negative Slew Rate2 15V (V/ μ s) @ AV=1, VS=+/-15V, VCM=0V
- 5.25. Positive Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V
- 5.26. Negative Supply Current 5V (A) @ +VS=5V, -VS=0V, VCM=0V, VOUT=4V
- 5.27. Input Offset Voltage1 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.28. Input Offset Voltage2 5V (V) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.29. Input Offset Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.30. Input Offset Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.31. Positive Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.32. Positive Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.33. Negative Input Bias Current1 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.34. Negative Input Bias Current2 5V (A) @ +VS=+5V, -VS=0V, VCM=0V, VOUT=4V
- 5.35. Positive Output Voltage High 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
- 5.36. Positive Output Voltage High 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
- 5.37. Positive Output Voltage High 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600 Ω
- 5.38. Positive Output Voltage High 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600 Ω
- 5.39. Negative Output Voltage Low 5V Open 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load
- 5.40. Negative Output Voltage Low 5V Open 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, No Load



TID Report
14-0247 06/13/14 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

- 5.41. Negative Output Voltage Low 5V 600 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω
- 5.42. Negative Output Voltage Low 5V 600 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, RL=600Ω
- 5.43. Negative Output Voltage Low 5V 1mA 1 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA
- 5.44. Negative Output Voltage Low 5V 1mA 2 (V) @ +VS=+5V, -VS=0V, VCM=0V, ISINK=1mA