



Products contained in this shipment may be subject to ITAR regulations.

Warning:

The export of these commodity(ies), technology, or software are subject either to the U.S. Commerce Department Export Administration Regulations (E.A.R.), or to the U.S. State Department International Traffic In Arms Regulations (I.T.A.R.). Diversion, the shipment to unauthorized locations or entities, or the disclosure of related technical data or software to unauthorized foreign nationals is contrary to U.S. law and is prohibited. If export is authorized to a specific country or end-users, compliance with the U.S. export laws is required prior to transfer, transshipment on a non-continuous voyage, or disposal in any other country, or to any other end-user of these commodities, either in their original form or after being incorporated into other end-items.



Total Ionizing Dose (TID) Radiation Testing of the RH1014MW Quad Precision Operational Amplifier for Linear Technology

Customer: Linear Technology, PO# 74692L

RAD Job Number: 16-0066

Part Type Tested: RH1014MW Quad Precision Operational Amplifier, RH1014M Quad Precision Operational Amplifier Datasheet Revision G.

Traceability Information: Assembly Lot Number: 816078.1, Fab Lot Number: W1436449.1, Wafer Number: 23, Date Code: 1542A. See photograph of unit under test in Appendix A.

Quantity of Units: 11 units received, 5 units for biased irradiation, 5 units for unbiased irradiation and 1 unit for control. Serial numbers 259, 260, 326, 328 and 329 were biased during irradiation, serial numbers 330, 331, 334, 335 and 344 were unbiased during irradiation and serial number 346 was used as control. See Appendix B for the radiation bias connection table.

Radiation and Electrical Test Increments: 50rad(Si)/s ionizing radiation with electrical test increments: pre-irradiation, 10krad(Si), 20krad(Si), 30krad(Si), 50krad(Si) and 100krad(Si).

Pre-Irradiation Burn-In: Burn-In performed by Linear Technology prior to receipt by Cobham-RAD

Overtest and Post-Irradiation Anneal: No overtest. 24-hour room temperature anneal followed by a 168-hour 100°C anneal. Both anneals were performed in the same electrical bias condition as the irradiations. Electrical measurements were made following each anneal increment.

Radiation Test Standard: MIL-STD-883H TM1019 Condition A and Linear Technology RH1014M Quad Precision Operational Amplifier Datasheet Revision G.

Test Hardware and Software: LTS2020 Automated Tester, Entity ID TS04, Calibration Date: 5/28/2015, Calibration Due: 5/28/2016. LTS2101 Family Board, Entity ID FB02. LTS0600 Test Fixture, Entity ID TF01. BGSS-970312 RH1014 DUT Board. Test Program: RH1014LT.SRC

Facility and Radiation Source: Aeroflex RAD's, Colorado Springs, CO. Gamma rays provided by JLSA 81-24 Co60 source. Dosimetry performed by Air Ionization Chamber (AIC) traceable to NIST. Aeroflex RAD's dosimetry has been audited by DLA and Aeroflex RAD has been awarded Laboratory Suitability for MIL-STD-750 and MIL-STD-883H TM 1019.

Irradiation and Test Temperature: Room temperature controlled to 24°C±6°C per MIL-STD-883H.

High Dose Rate Test Result: PASSED the total ionizing dose test to the maximum tested dose level of 100krad(Si) with all parameters remaining within their datasheet specifications. Further the units do not exhibit ELDRS as defined in the current test method.



1.0. Overview and Background

It is well known that total dose ionizing radiation can cause parametric degradation and ultimately functional failure in electronic devices. The damage occurs via electron-hole pair production, transport and trapping in the dielectric and interface regions. In discrete devices the bulk of the damage is frequently manifested as a reduction in the gain and/or breakdown voltage of the device. The damage will usually anneal with time following the end of the radiation exposure. Due to this annealing, and to ensure a worst-case test condition MIL-STD-883H TM1019 calls out a dose rate of 50 to 300rad(Si)/s as Condition A and further specifies that the time from the end of an incremental radiation exposure and electrical testing shall be 1-hour or less and the total time from the end of one incremental irradiation to the beginning of the next incremental radiation step should be 2-hours or less. The work described in this report was performed to meet MIL-STD-883H TM1019 Condition A.

2.0. Radiation Test Apparatus

The total ionizing dose testing described in this final report was performed using the facilities at Aeroflex RAD's Longmire Laboratories in Colorado Springs, CO. The high dose rate total ionizing dose (TID) source is a JLSA 81-24 irradiator modified to provide a panoramic exposure. The Co-60 rods are held in the base of the irradiator heavily shielded by lead. During the radiation exposures the rod is raised by an electronic timer/controller and the exposure is performed in air. The dose rate for this irradiator in this configuration ranges from <1rad(Si)/s to a maximum of approximately 300rad(Si)/s, determined by the distance from the source. For high-dose rate experiments the bias boards are placed in a radial fashion equidistant from the raised Co-60 rods with the distance adjusted to provide the required dose rate. The irradiator calibration is maintained by Aeroflex RAD Longmire Laboratories using air ionization chamber (AIC) equipment calibrated with traceability to the National Institute of Standards and Technology (NIST). Figure 2.1 shows a photograph of the JLSA 81-24 Co-60 irradiator at Aeroflex RAD's Longmire Laboratory facility.

Aeroflex RAD is currently certified by the Defense Logistics Agency (DLA) for Laboratory Suitability under MIL STD 750 and MIL-STD-883H. Additional details regarding Aeroflex RAD dosimetry for TM1019 Condition A testing are available in Aeroflex RAD's report to DLA entitled: "Dose Rate Mapping of the J.L. Shepherd and Associates Model 81 Irradiator Installed by Radiation Assured Devices".



Figure 2.1. Aeroflex RAD's high dose rate Co-60 irradiator. The dose rate is obtained by positioning the device-under-test at a fixed distance from the gamma cell. The dose rate for this irradiator varies from approximately 300rad(Si)/s close to the rods down to 1rad(Si)/s at a distance of approximately 2-feet.



3.0. Radiation Test Conditions

The RH1014MW Quad Precision Operational Amplifier described in this final report were irradiated using 8V and split 15V supply and with all pins tied to ground, that is biased and unbiased. See the TID Bias Table in Appendix B for the full bias circuits. In our opinion, this bias circuit satisfies the requirements of MIL-STD-883H TM1019 Section 3.9.3 Bias and Loading Conditions which states "The bias applied to the test devices shall be selected to produce the greatest radiation induced damage or the worst-case damage for the intended application, if known. While maximum voltage is often worst case some bipolar linear device parameters (e.g. input bias current or maximum output load current) exhibit more degradation with 0 V bias."

The devices were irradiated to a maximum total ionizing dose level of 100krad(Si) with incremental readings at 10krad(Si), 20krad(Si), 30krad(Si) and 50krad(Si). Electrical testing occurred within one hour following the end of each irradiation segment. For intermediate irradiations, the parts were tested and returned to total dose exposure within two hours from the end of the previous radiation increment.

The TID bias board was positioned in the Co-60 cell to provide the required minimum of 50rad(Si)/s and was located inside a lead-aluminum enclosure. The lead-aluminum enclosure is required under MIL-STD-883H TM1019 Section 3.4 that reads as follows: "Lead/Aluminum (Pb/Al) container. Test specimens shall be enclosed in a Pb/Al container to minimize dose enhancement effects caused by low-energy, scattered radiation. A minimum of 1.5 mm Pb, surrounding an inner shield of at least 0.7 mm Al, is required. This Pb/Al container produces an approximate charged particle equilibrium for Si and for TLDs such as CaF₂. The radiation field intensity shall be measured inside the Pb/Al container (1) initially, (2) when the source is changed, or (3) when the orientation or configuration of the source, container, or test-fixture is changed. This measurement shall be performed by placing a dosimeter (e.g., a TLD) in the device-irradiation container at the approximate test-device position. If it can be demonstrated that low energy scattered radiation is small enough that it will not cause dosimetry errors due to dose enhancement, the Pb/Al container may be omitted."

The final dose rate within the high dose rate lead-aluminum enclosure was determined using calibration calculations based on air ionization chamber (AIC) dosimetry performed just prior to beginning the total dose irradiations. The final dose rate for this work was 61.4rad(Si)/s with a precision of $\pm 5\%$.



4.0. Tested Parameters

During the total ionizing dose characterization testing the following electrical parameters were measured pre- and post-irradiation:

1. Positive Supply Current 15V (A) @ VS= +/-15V, VCM= 0V
2. Negative Supply Current 15V (A) @ VS= +/-15V, VCM= 0V
3. Offset Voltage 15V 1 (V) @ VS= +/-15V, VCM= 0V
4. Offset Voltage 15V 2 (V) @ VS= +/-15V, VCM= 0V
5. Offset Voltage 15V 3 (V) @ VS= +/-15V, VCM= 0V
6. Offset Voltage 15V 4 (V) @ VS= +/-15V, VCM= 0V
7. Offset Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
8. Offset Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
9. Offset Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
10. Offset Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
11. Positive Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
12. Positive Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
13. Positive Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
14. Positive Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
15. Negative Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
16. Negative Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
17. Negative Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
18. Negative Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
19. Common Mode Rejection Ratio 1 (dB) @ VS= +/-15V, VCM= 13V to -15V
20. Common Mode Rejection Ratio 2 (dB) @ VS= +/-15V, VCM= 13V to -15V
21. Common Mode Rejection Ratio 3 (dB) @ VS= +/-15V, VCM= 13V to -15V
22. Common Mode Rejection Ratio 4 (dB) @ VS= +/-15V, VCM= 13V to -15V
23. Power Supply Rejection Ratio 1 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
24. Power Supply Rejection Ratio 2 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
25. Power Supply Rejection Ratio 3 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
26. Power Supply Rejection Ratio 4 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
27. Open Loop Gain 1 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
28. Open Loop Gain 2 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
29. Open Loop Gain 3 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
30. Open Loop Gain 4 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
31. Output Voltage High 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
32. Output Voltage High 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
33. Output Voltage High 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
34. Output Voltage High 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
35. Output Voltage Low 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
36. Output Voltage Low 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
37. Output Voltage Low 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K



38. Output Voltage Low 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
39. Positive Slew Rate 1 (V/us) @ VS= +/-15V
40. Positive Slew Rate 2 (V/us) @ VS= +/-15V
41. Positive Slew Rate 3 (V/us) @ VS= +/-15V
42. Positive Slew Rate 4 (V/us) @ VS= +/-15V
43. Negative Slew Rate 1 (V/us) @ VS= +/-15V
44. Negative Slew Rate 2 (V/us) @ VS= +/-15V
45. Negative Slew Rate 3 (V/us) @ VS= +/-15V
46. Negative Slew Rate 4 (V/us) @ VS= +/-15V
47. Positive Supply Current 5V (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
48. Negative Supply Current 5V (A) @ VS= +5V , VCM= 0V, VOUT= 1.4V
49. Offset Voltage 5V 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
50. Offset Voltage 5V 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
51. Offset Voltage 5V 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
52. Offset Voltage 5V 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
53. Offset Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
54. Offset Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
55. Offset Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
56. Offset Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
57. Positive Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
58. Positive Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
59. Positive Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
60. Positive Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
61. Negative Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
62. Negative Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
63. Negative Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
64. Negative Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
65. Output Voltage High 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
66. Output Voltage High 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
67. Output Voltage High 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
68. Output Voltage High 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
69. Output Voltage High 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
70. Output Voltage High 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
71. Output Voltage High 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
72. Output Voltage High 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
73. Output Voltage Low 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
74. Output Voltage Low 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
75. Output Voltage Low 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
76. Output Voltage Low 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
77. Output Voltage Low 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
78. Output Voltage Low 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
79. Output Voltage Low 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω

80. Output Voltage Low 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
81. Output Voltage Low 5V 1mA 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
82. Output Voltage Low 5V 1mA 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
83. Output Voltage Low 5V 1mA 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
84. Output Voltage Low 5V 1mA 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA

Appendix C details the measured parameters, test conditions, pre-irradiation specification and measurement resolution for each of the measurements.

The parametric data was obtained as "read and record" and all the raw data plus an attributes summary are contained in this report as well as in a separate Excel file. The attributes data contains the average, standard deviation and the average with the KTL values applied. The KTL value used in this work is 2.742 per MIL-HDBK-814 using one sided tolerance limits of 90/90 and a 5-piece sample size. The 90/90 KTL values were selected to match the statistical levels specified in the MIL-PRF-38535 sampling plan for the qualification of a radiation hardness assured (RHA) component. Note that the following criteria must be met for a device to pass the total ionizing dose test: following the radiation exposure each of the 5 pieces irradiated under electrical bias shall pass the specification value. The units irradiated without electrical bias and the KTL statistics are included in this report for reference only. If any of the 5 pieces irradiated under electrical bias exceed the device post radiation data sheet specification limits, then the lot could be logged as a failure.

Further, MIL-STD-883H, TM 1019 Section 3.13.1.1 Characterization test to determine if a part exhibits ELDRS' states the following: Select a minimum random sample of 21 devices from a population representative of recent production runs. Smaller sample sizes may be used if agreed upon between the parties to the test. All of the selected devices shall have undergone appropriate elevated temperature reliability screens, e.g. burn-in and high temperature storage life. Divide the samples into four groups of 5 each and use the remaining part for a control. Perform pre-irradiation electrical characterization on all parts assuring that they meet the Group A electrical tests. Irradiate 5 samples under a 0 volt bias and another 5 under the irradiation bias given in the acquisition specification at 50-300 rad(Si)/s and room temperature. Irradiate 5 samples under a 0 volt bias and another 5 under irradiation bias given in the acquisition specification at < 10mrad(Si)/s and room temperature. Irradiate all samples to the same dose levels, including 0.5 and 1.0 times the anticipated specification dose, and repeat the electrical characterization on each part at each dose level. Post irradiation electrical measurements shall be performed per paragraph 3.10 where the low dose rate test is considered Condition D. Calculate the radiation induced change in each electrical parameter (Δ para) for each sample at each radiation level. Calculate the ratio of the median Δ para at low dose rate to the median Δ para at high dose rate for each irradiation bias group at each total dose level. If this ratio exceeds 1.5 for any of the most sensitive parameters then the part is considered to be ELDRS susceptible. This test does not apply to parameters which exhibit changes that are within experimental error or whose values are below the pre-irradiation electrical specification limits at low dose rate at the specification dose.

Therefore, the data in this report can be analyzed along with the low dose rate report titled "Enhanced



Low Dose Rate Sensitivity (ELDRS) Radiation Testing of the RH1014MW Quad Precision Operational Amplifier for Linear Technology" to demonstrate that these parts do not exhibit ELDRS as defined in the current test method.

5.0. Total Ionizing Dose Test Results

Based on this criterion the RH1014MW Quad Precision Operational Amplifier (from the lot traceability information provided on the first page of this test report) PASSED the total ionizing dose test to the maximum tested dose level of 100krad(Si) with all parameters remaining within their datasheet specifications.

Figures 5.1 through 5.84 show plots of all the measured parameters versus total ionizing dose while Tables 5.1 - 5.84 show the corresponding raw data for each of these parameters. In the data plots the solid diamonds are the average of the measured data points for the sample irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the units irradiated with all pins tied to ground. The black lines (solid or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the sample irradiated in the biased condition while the shaded lines (solid or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the sample irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

The control units, as expected, show no significant changes to any of the parameters. Therefore we can conclude that the electrical testing remained in control throughout the duration of the tests and the observed degradation was due to the radiation exposure. Appendix D lists the figures used in this section to facilitate the location of a particular parameter.

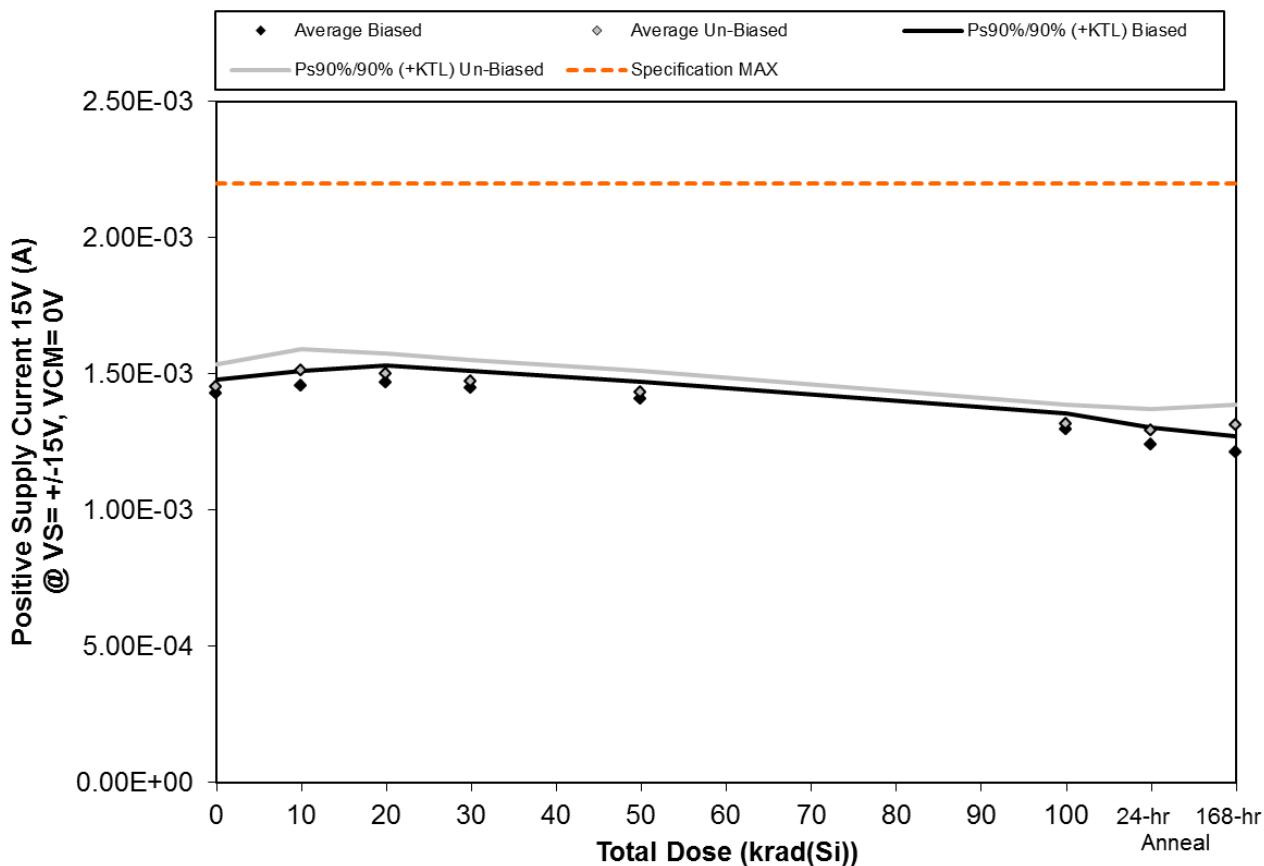


Figure 5.1. Plot of Positive Supply Current 15V (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.1. Raw data for Positive Supply Current 15V (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Supply Current 15V (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.42E-03	1.46E-03	1.47E-03	1.44E-03	1.41E-03	1.30E-03	1.23E-03	1.21E-03
260	1.43E-03	1.46E-03	1.47E-03	1.45E-03	1.41E-03	1.29E-03	1.24E-03	1.21E-03
326	1.40E-03	1.43E-03	1.44E-03	1.42E-03	1.38E-03	1.27E-03	1.22E-03	1.19E-03
328	1.46E-03	1.49E-03	1.50E-03	1.48E-03	1.44E-03	1.33E-03	1.28E-03	1.25E-03
329	1.43E-03	1.46E-03	1.47E-03	1.45E-03	1.41E-03	1.30E-03	1.25E-03	1.22E-03
330	1.48E-03	1.54E-03	1.52E-03	1.49E-03	1.46E-03	1.34E-03	1.32E-03	1.33E-03
331	1.49E-03	1.54E-03	1.53E-03	1.50E-03	1.47E-03	1.35E-03	1.33E-03	1.34E-03
334	1.43E-03	1.49E-03	1.48E-03	1.46E-03	1.41E-03	1.29E-03	1.27E-03	1.29E-03
335	1.42E-03	1.47E-03	1.46E-03	1.44E-03	1.40E-03	1.28E-03	1.26E-03	1.28E-03
344	1.46E-03	1.52E-03	1.51E-03	1.48E-03	1.44E-03	1.32E-03	1.30E-03	1.32E-03
346	1.45E-03	1.45E-03	1.45E-03	1.45E-03	1.45E-03	1.45E-03	1.45E-03	1.45E-03
Biased Statistics								
Average Biased	1.43E-03	1.46E-03	1.47E-03	1.45E-03	1.41E-03	1.30E-03	1.24E-03	1.21E-03
Std Dev Biased	1.92E-05	1.97E-05	2.30E-05	2.28E-05	2.16E-05	2.19E-05	2.15E-05	2.13E-05
Ps90%/90% (+KTL) Biased	1.48E-03	1.51E-03	1.53E-03	1.51E-03	1.47E-03	1.36E-03	1.30E-03	1.27E-03
Ps90%/90% (-KTL) Biased	1.37E-03	1.40E-03	1.41E-03	1.38E-03	1.35E-03	1.24E-03	1.18E-03	1.15E-03
Un-Biased Statistics								
Average Un-Biased	1.45E-03	1.51E-03	1.50E-03	1.47E-03	1.43E-03	1.32E-03	1.30E-03	1.31E-03
Std Dev Un-Biased	2.96E-05	2.85E-05	2.68E-05	2.73E-05	2.80E-05	2.66E-05	2.80E-05	2.83E-05
Ps90%/90% (+KTL) Un-Biased	1.54E-03	1.59E-03	1.57E-03	1.55E-03	1.51E-03	1.39E-03	1.37E-03	1.39E-03
Ps90%/90% (-KTL) Un-Biased	1.37E-03	1.43E-03	1.43E-03	1.40E-03	1.36E-03	1.24E-03	1.22E-03	1.23E-03
Specification MAX	2.20E-03	2.20E-03	2.20E-03	2.20E-03	2.20E-03	2.20E-03	2.20E-03	2.20E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

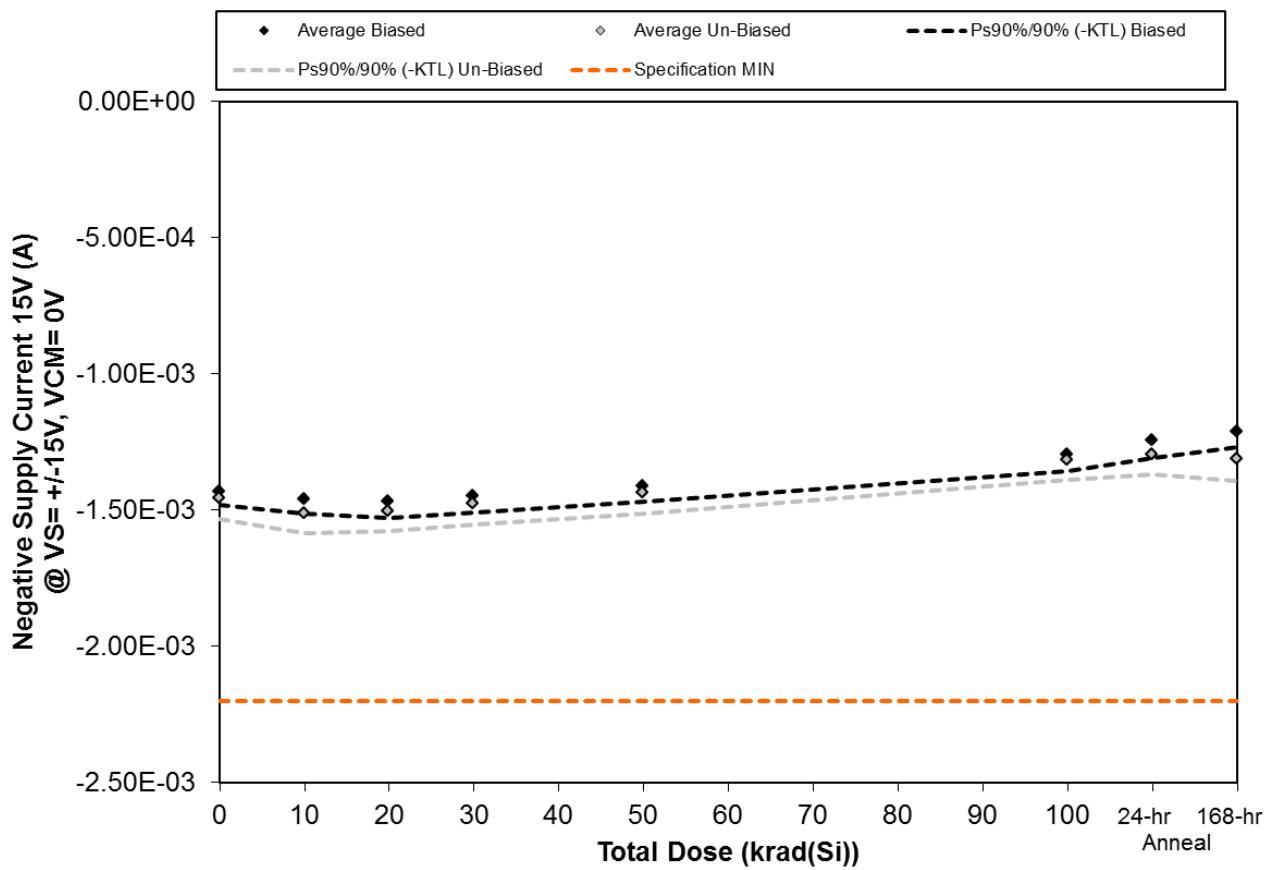


Figure 5.2. Plot of Negative Supply Current 15V (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.2. Raw data for Negative Supply Current 15V (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Supply Current 15V (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.42E-03	-1.46E-03	-1.47E-03	-1.44E-03	-1.41E-03	-1.30E-03	-1.24E-03	-1.21E-03
260	-1.43E-03	-1.46E-03	-1.47E-03	-1.45E-03	-1.41E-03	-1.29E-03	-1.24E-03	-1.21E-03
326	-1.41E-03	-1.43E-03	-1.44E-03	-1.42E-03	-1.38E-03	-1.27E-03	-1.22E-03	-1.19E-03
328	-1.46E-03	-1.49E-03	-1.50E-03	-1.48E-03	-1.44E-03	-1.33E-03	-1.28E-03	-1.24E-03
329	-1.43E-03	-1.47E-03	-1.47E-03	-1.45E-03	-1.41E-03	-1.30E-03	-1.25E-03	-1.22E-03
330	-1.48E-03	-1.53E-03	-1.53E-03	-1.50E-03	-1.46E-03	-1.34E-03	-1.32E-03	-1.33E-03
331	-1.49E-03	-1.54E-03	-1.53E-03	-1.51E-03	-1.47E-03	-1.35E-03	-1.33E-03	-1.35E-03
334	-1.45E-03	-1.49E-03	-1.48E-03	-1.46E-03	-1.42E-03	-1.30E-03	-1.27E-03	-1.29E-03
335	-1.42E-03	-1.47E-03	-1.46E-03	-1.44E-03	-1.40E-03	-1.29E-03	-1.26E-03	-1.28E-03
344	-1.46E-03	-1.52E-03	-1.51E-03	-1.48E-03	-1.44E-03	-1.32E-03	-1.30E-03	-1.32E-03
346	-1.45E-03	-1.45E-03	-1.45E-03	-1.45E-03	-1.45E-03	-1.45E-03	-1.45E-03	-1.45E-03
Biased Statistics								
Average Biased	-1.43E-03	-1.46E-03	-1.47E-03	-1.45E-03	-1.41E-03	-1.30E-03	-1.24E-03	-1.21E-03
Std Dev Biased	1.92E-05	2.01E-05	2.23E-05	2.24E-05	2.16E-05	2.12E-05	2.30E-05	2.07E-05
Ps90%/90% (+KTL) Biased	-1.38E-03	-1.40E-03	-1.41E-03	-1.39E-03	-1.35E-03	-1.24E-03	-1.18E-03	-1.16E-03
Ps90%/90% (-KTL) Biased	-1.48E-03	-1.51E-03	-1.53E-03	-1.51E-03	-1.47E-03	-1.35E-03	-1.31E-03	-1.27E-03
Un-Biased Statistics								
Average Un-Biased	-1.46E-03	-1.51E-03	-1.50E-03	-1.48E-03	-1.44E-03	-1.32E-03	-1.30E-03	-1.31E-03
Std Dev Un-Biased	2.72E-05	2.74E-05	2.73E-05	2.76E-05	2.77E-05	2.59E-05	2.74E-05	2.91E-05
Ps90%/90% (+KTL) Un-Biased	-1.38E-03	-1.44E-03	-1.43E-03	-1.40E-03	-1.36E-03	-1.25E-03	-1.22E-03	-1.23E-03
Ps90%/90% (-KTL) Un-Biased	-1.53E-03	-1.59E-03	-1.58E-03	-1.55E-03	-1.51E-03	-1.39E-03	-1.37E-03	-1.39E-03
Specification MIN	-2.20E-03	-2.20E-03	-2.20E-03	-2.20E-03	-2.20E-03	-2.20E-03	-2.20E-03	-2.20E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

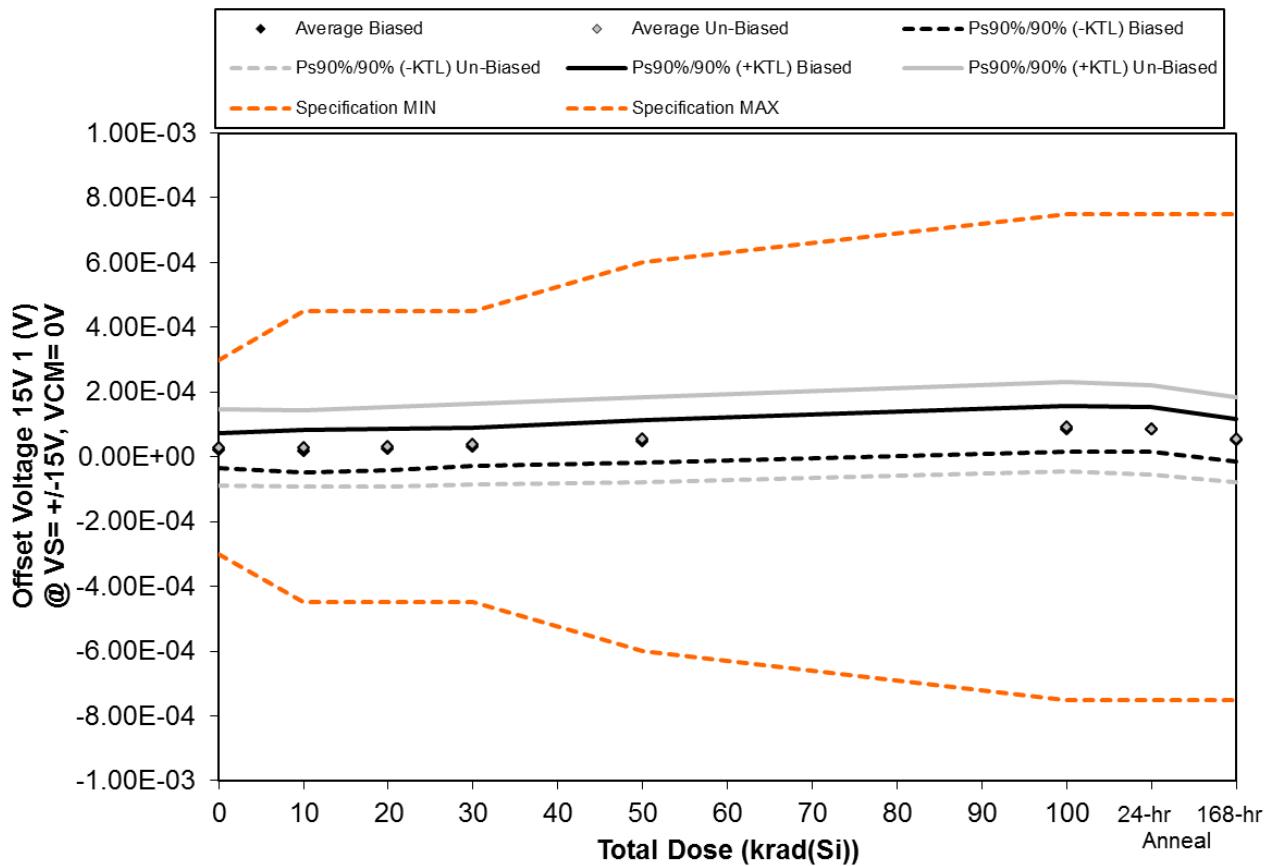


Figure 5.3. Plot of Offset Voltage 15V 1 (V) @ VS = +/-15V, VCM = 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.3. Raw data for Offset Voltage 15V 1 (V) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 15V 1 (V) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	4.34E-06	-1.29E-06	2.53E-06	1.03E-05	2.31E-05	5.30E-05	5.71E-05	2.77E-05
260	4.80E-05	4.83E-05	5.32E-05	6.03E-05	7.99E-05	1.23E-04	1.21E-04	8.68E-05
326	5.28E-06	-8.30E-06	1.11E-06	1.22E-05	2.63E-05	7.57E-05	6.50E-05	3.10E-05
328	9.52E-06	1.26E-05	1.97E-05	2.74E-05	4.61E-05	8.76E-05	8.71E-05	5.30E-05
329	3.43E-05	3.34E-05	4.02E-05	4.64E-05	6.09E-05	9.28E-05	9.24E-05	6.08E-05
330	6.45E-05	5.96E-05	6.69E-05	7.53E-05	9.15E-05	1.38E-04	1.33E-04	9.03E-05
331	-1.86E-05	-2.12E-05	-1.86E-05	-1.42E-05	-2.23E-06	3.38E-05	2.37E-05	-4.24E-06
334	-2.78E-06	-6.67E-06	-4.65E-06	1.92E-06	1.30E-05	5.33E-05	4.13E-05	1.94E-05
335	1.79E-05	2.21E-05	3.03E-05	4.12E-05	5.62E-05	9.41E-05	8.99E-05	5.27E-05
344	8.14E-05	8.07E-05	8.54E-05	9.26E-05	1.07E-04	1.47E-04	1.30E-04	1.11E-04
346	-1.40E-05	-1.41E-05	-1.39E-05	-1.43E-05	-1.36E-05	-1.34E-05	-1.36E-05	-1.39E-05
Biased Statistics								
Average Biased	2.03E-05	1.69E-05	2.34E-05	3.13E-05	4.72E-05	8.64E-05	8.45E-05	5.19E-05
Std Dev Biased	1.98E-05	2.37E-05	2.30E-05	2.17E-05	2.39E-05	2.55E-05	2.52E-05	2.41E-05
Ps90%/90% (+KTL) Biased	7.45E-05	8.19E-05	8.65E-05	9.09E-05	1.13E-04	1.56E-04	1.54E-04	1.18E-04
Ps90%/90% (-KTL) Biased	-3.39E-05	-4.80E-05	-3.97E-05	-2.83E-05	-1.82E-05	1.65E-05	1.55E-05	-1.42E-05
Un-Biased Statistics								
Average Un-Biased	2.85E-05	2.69E-05	3.18E-05	3.94E-05	5.31E-05	9.32E-05	8.35E-05	5.38E-05
Std Dev Un-Biased	4.30E-05	4.31E-05	4.46E-05	4.58E-05	4.75E-05	5.00E-05	4.99E-05	4.79E-05
Ps90%/90% (+KTL) Un-Biased	1.46E-04	1.45E-04	1.54E-04	1.65E-04	1.83E-04	2.30E-04	2.20E-04	1.85E-04
Ps90%/90% (-KTL) Un-Biased	-8.95E-05	-9.12E-05	-9.05E-05	-8.63E-05	-7.73E-05	-4.40E-05	-5.34E-05	-7.74E-05
Specification MIN	-3.00E-04	-4.50E-04	-4.50E-04	-4.50E-04	-6.00E-04	-7.50E-04	-7.50E-04	-7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-04	4.50E-04	4.50E-04	4.50E-04	6.00E-04	7.50E-04	7.50E-04	7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

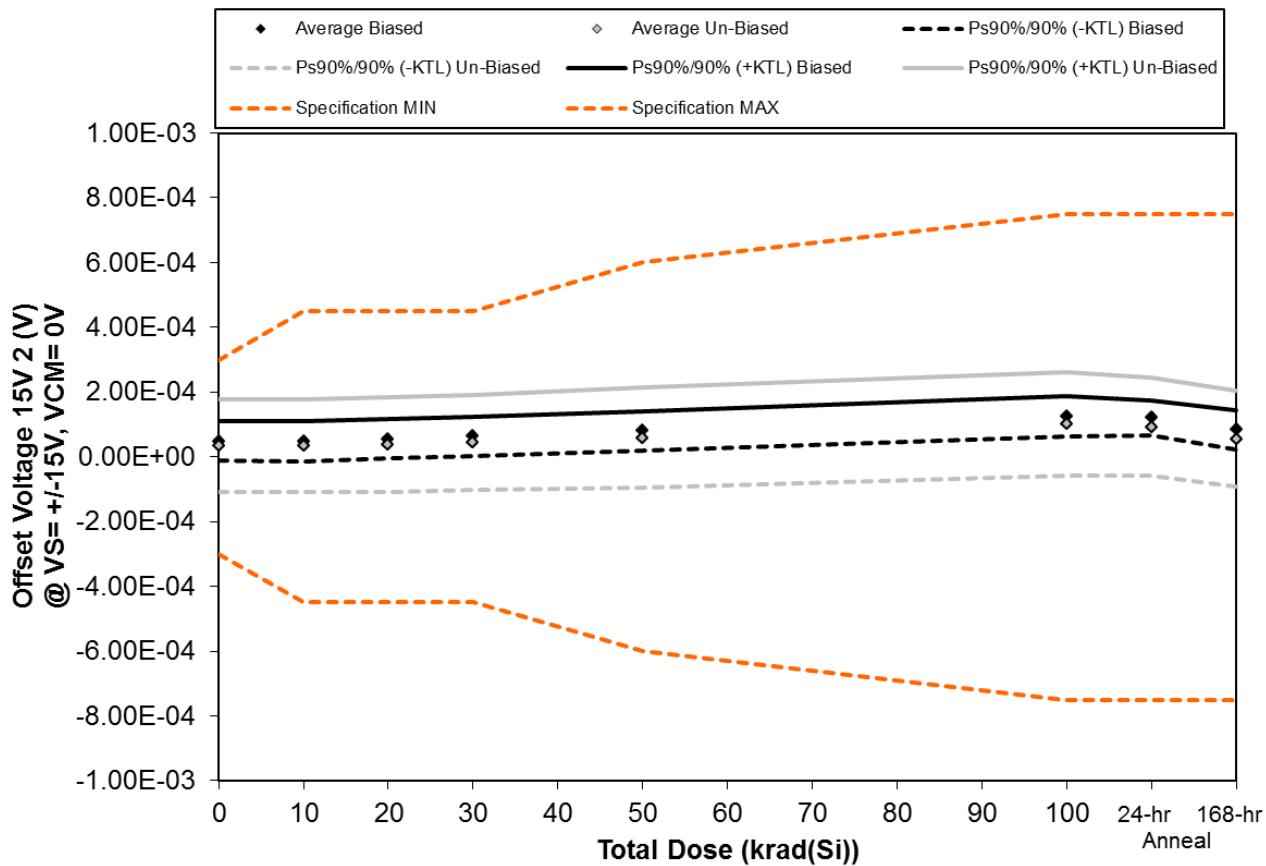


Figure 5.4. Plot of Offset Voltage 15V 2 (V) @ VS = +/-15V, VCM = 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.4. Raw data for Offset Voltage 15V 2 (V) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 15V 2 (V) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	3.73E-05	3.71E-05	4.56E-05	5.59E-05	7.43E-05	1.17E-04	1.19E-04	8.23E-05
260	7.97E-05	8.18E-05	9.03E-05	9.60E-05	1.17E-04	1.64E-04	1.53E-04	1.17E-04
326	3.14E-05	3.02E-05	3.81E-05	4.45E-05	5.95E-05	1.04E-04	9.87E-05	5.61E-05
328	6.52E-05	5.91E-05	6.42E-05	7.33E-05	8.26E-05	1.18E-04	1.21E-04	8.71E-05
329	3.30E-05	2.91E-05	3.93E-05	4.58E-05	6.63E-05	1.21E-04	1.11E-04	7.67E-05
330	4.06E-05	4.33E-05	4.99E-05	5.66E-05	7.31E-05	1.19E-04	1.05E-04	6.92E-05
331	9.91E-05	1.01E-04	1.05E-04	1.13E-04	1.30E-04	1.76E-04	1.62E-04	1.28E-04
334	-4.21E-05	-3.98E-05	-3.86E-05	-3.25E-05	-2.18E-05	2.22E-05	1.87E-05	-2.02E-05
335	5.66E-05	5.24E-05	5.71E-05	6.38E-05	7.77E-05	1.25E-04	1.17E-04	6.72E-05
344	1.93E-05	1.46E-05	1.78E-05	2.33E-05	3.41E-05	7.00E-05	6.08E-05	3.55E-05
346	4.35E-05	4.32E-05	4.49E-05	4.33E-05	4.34E-05	4.34E-05	4.36E-05	4.29E-05
Biased Statistics								
Average Biased	4.93E-05	4.74E-05	5.55E-05	6.31E-05	7.99E-05	1.25E-04	1.21E-04	8.38E-05
Std Dev Biased	2.19E-05	2.27E-05	2.21E-05	2.17E-05	2.23E-05	2.30E-05	2.01E-05	2.21E-05
Ps90%/90% (+KTL) Biased	1.09E-04	1.10E-04	1.16E-04	1.23E-04	1.41E-04	1.88E-04	1.76E-04	1.44E-04
Ps90%/90% (-KTL) Biased	-1.06E-05	-1.47E-05	-5.06E-06	3.59E-06	1.87E-05	6.17E-05	6.55E-05	2.34E-05
Un-Biased Statistics								
Average Un-Biased	3.47E-05	3.42E-05	3.82E-05	4.48E-05	5.86E-05	1.02E-04	9.28E-05	5.60E-05
Std Dev Un-Biased	5.19E-05	5.18E-05	5.30E-05	5.38E-05	5.65E-05	5.86E-05	5.49E-05	5.42E-05
Ps90%/90% (+KTL) Un-Biased	1.77E-04	1.76E-04	1.84E-04	1.92E-04	2.13E-04	2.63E-04	2.43E-04	2.05E-04
Ps90%/90% (-KTL) Un-Biased	-1.08E-04	-1.08E-04	-1.07E-04	-1.03E-04	-9.62E-05	-5.82E-05	-5.77E-05	-9.26E-05
Specification MIN	-3.00E-04	-4.50E-04	-4.50E-04	-4.50E-04	-6.00E-04	-7.50E-04	-7.50E-04	-7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-04	4.50E-04	4.50E-04	4.50E-04	6.00E-04	7.50E-04	7.50E-04	7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

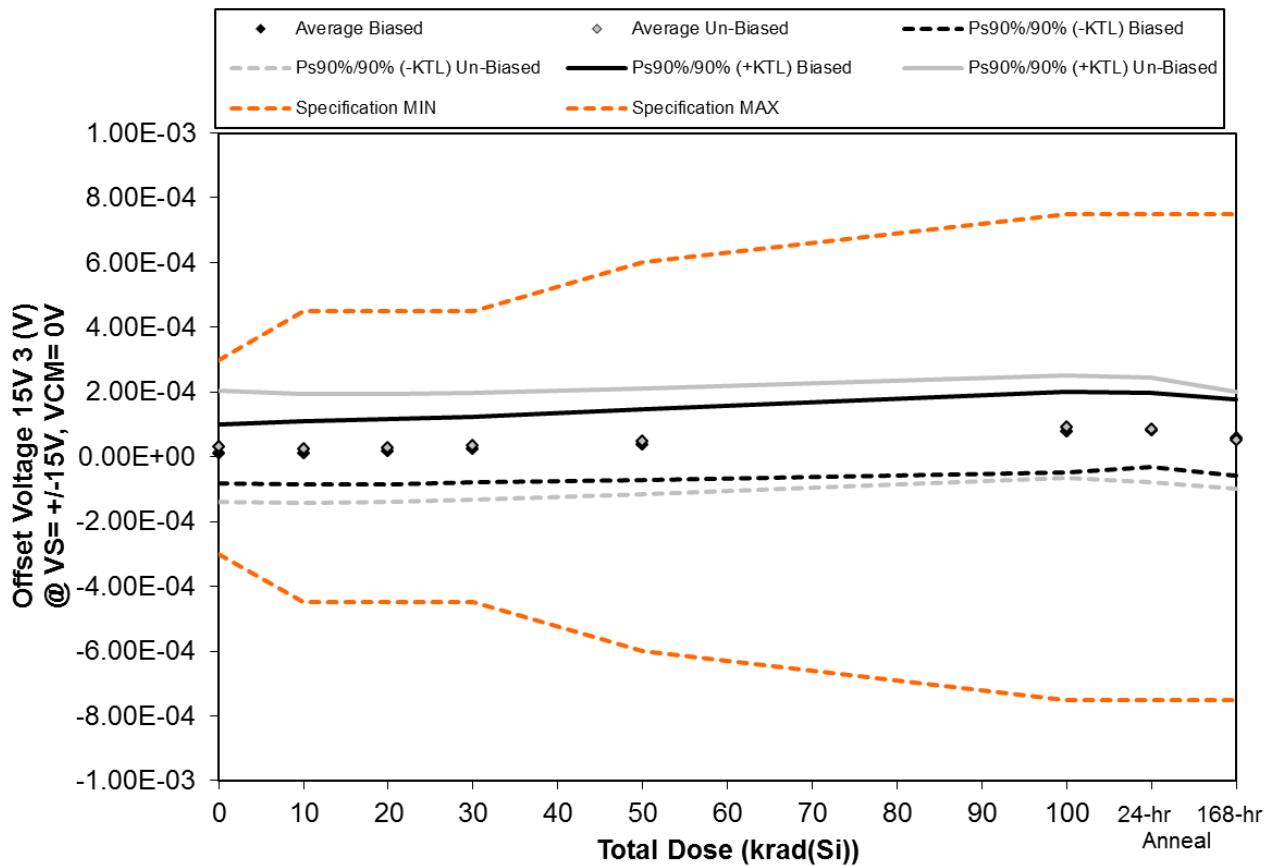


Figure 5.5. Plot of Offset Voltage 15V 3 (V) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.5. Raw data for Offset Voltage 15V 3 (V) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 15V 3 (V) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	4.48E-05	4.53E-05	5.03E-05	5.65E-05	6.95E-05	1.07E-04	1.12E-04	9.40E-05
260	4.01E-05	4.10E-05	5.00E-05	5.49E-05	6.92E-05	1.13E-04	1.12E-04	9.86E-05
326	1.20E-05	2.33E-05	2.66E-05	3.53E-05	5.83E-05	1.06E-04	1.10E-04	7.47E-05
328	-3.08E-05	-3.38E-05	-3.11E-05	-2.71E-05	-2.06E-05	9.41E-06	2.16E-05	5.35E-06
329	-1.56E-05	-1.68E-05	-1.20E-05	-2.43E-06	1.22E-05	5.30E-05	5.54E-05	2.23E-05
330	8.71E-05	6.81E-05	6.80E-05	7.22E-05	8.38E-05	1.25E-04	1.09E-04	7.25E-05
331	-4.84E-05	-5.27E-05	-4.98E-05	-4.15E-05	-2.72E-05	2.09E-05	9.43E-06	-1.88E-05
334	-1.95E-05	-2.76E-05	-2.20E-05	-1.88E-05	-3.65E-06	4.67E-05	3.66E-05	7.28E-06
335	8.52E-05	8.35E-05	8.86E-05	9.39E-05	1.11E-04	1.61E-04	1.54E-04	1.16E-04
344	5.59E-05	5.48E-05	5.91E-05	6.25E-05	7.77E-05	1.11E-04	1.09E-04	7.33E-05
346	8.32E-05	8.24E-05	8.32E-05	8.28E-05	8.35E-05	8.36E-05	8.34E-05	8.30E-05
Biased Statistics								
Average Biased	1.01E-05	1.18E-05	1.67E-05	2.34E-05	3.77E-05	7.77E-05	8.22E-05	5.90E-05
Std Dev Biased	3.33E-05	3.54E-05	3.69E-05	3.69E-05	4.03E-05	4.52E-05	4.16E-05	4.26E-05
Ps90%/90% (+KTL) Biased	1.01E-04	1.09E-04	1.18E-04	1.25E-04	1.48E-04	2.02E-04	1.96E-04	1.76E-04
Ps90%/90% (-KTL) Biased	-8.13E-05	-8.52E-05	-8.44E-05	-7.77E-05	-7.26E-05	-4.63E-05	-3.20E-05	-5.78E-05
Un-Biased Statistics								
Average Un-Biased	3.20E-05	2.52E-05	2.88E-05	3.36E-05	4.82E-05	9.29E-05	8.37E-05	5.01E-05
Std Dev Un-Biased	6.23E-05	6.12E-05	6.08E-05	5.99E-05	6.00E-05	5.76E-05	5.91E-05	5.47E-05
Ps90%/90% (+KTL) Un-Biased	2.03E-04	1.93E-04	1.95E-04	1.98E-04	2.13E-04	2.51E-04	2.46E-04	2.00E-04
Ps90%/90% (-KTL) Un-Biased	-1.39E-04	-1.43E-04	-1.38E-04	-1.31E-04	-1.16E-04	-6.52E-05	-7.84E-05	-9.99E-05
Specification MIN	-3.00E-04	-4.50E-04	-4.50E-04	-4.50E-04	-6.00E-04	-7.50E-04	-7.50E-04	-7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-04	4.50E-04	4.50E-04	4.50E-04	6.00E-04	7.50E-04	7.50E-04	7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

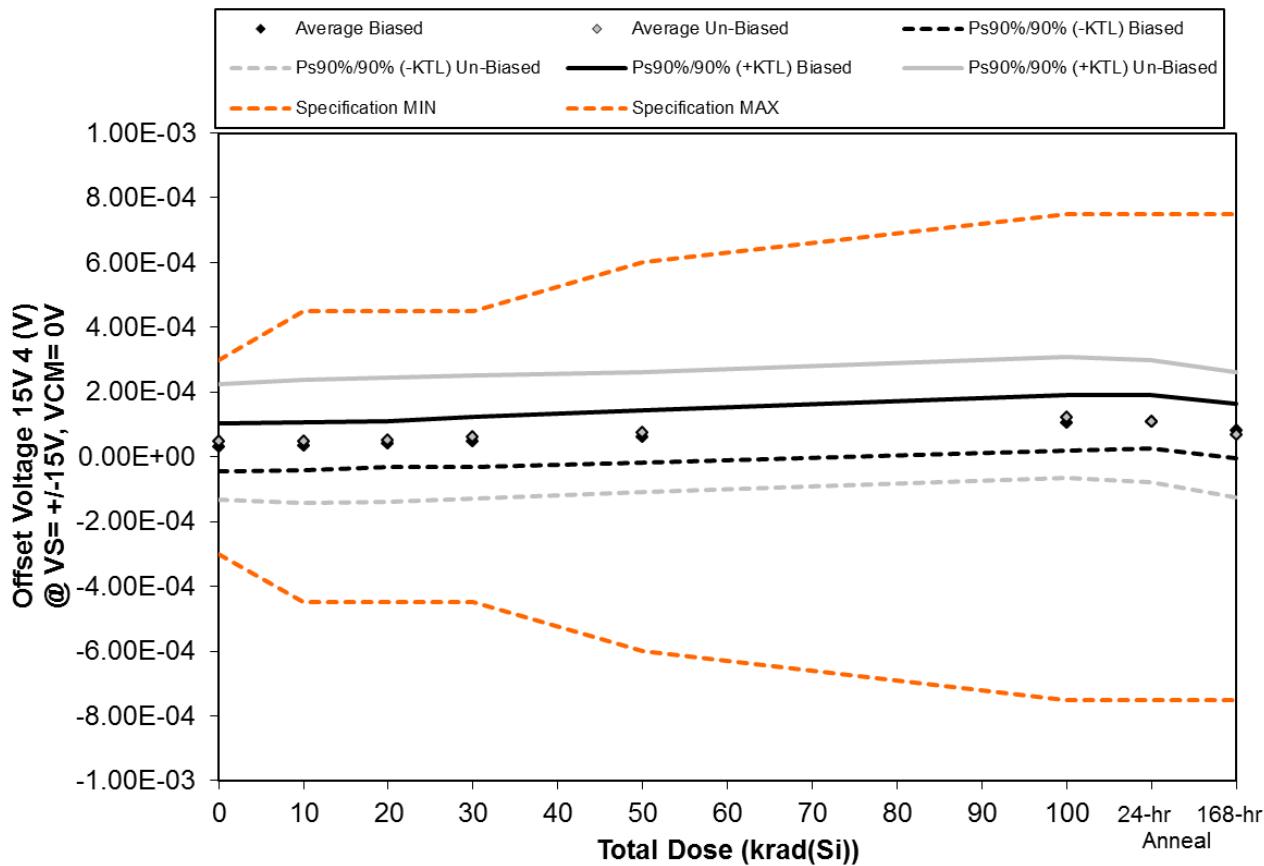


Figure 5.6. Plot of Offset Voltage 15V 4 (V) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.6. Raw data for Offset Voltage 15V 4 (V) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 15V 4 (V) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	4.21E-05	4.13E-05	4.83E-05	5.71E-05	7.37E-05	1.17E-04	1.21E-04	9.18E-05
260	2.00E-05	1.97E-05	2.65E-05	3.49E-05	4.97E-05	8.93E-05	8.69E-05	6.70E-05
326	-2.76E-06	5.48E-06	1.34E-05	2.06E-05	3.76E-05	8.92E-05	8.97E-05	5.65E-05
328	6.88E-05	7.63E-05	8.07E-05	9.21E-05	1.09E-04	1.57E-04	1.57E-04	1.28E-04
329	2.01E-05	2.21E-05	2.87E-05	3.34E-05	4.47E-05	8.05E-05	9.10E-05	5.79E-05
330	2.12E-05	2.08E-05	2.77E-05	3.81E-05	5.55E-05	1.06E-04	9.48E-05	4.25E-05
331	8.88E-05	8.76E-05	9.13E-05	9.68E-05	1.10E-04	1.50E-04	1.34E-04	1.12E-04
334	6.44E-05	6.27E-05	6.80E-05	7.13E-05	8.35E-05	1.24E-04	1.15E-04	8.22E-05
335	1.12E-04	1.20E-04	1.30E-04	1.41E-04	1.58E-04	2.09E-04	1.98E-04	1.46E-04
344	-5.24E-05	-5.94E-05	-5.30E-05	-4.35E-05	-2.46E-05	2.16E-05	8.51E-06	-3.68E-05
346	4.60E-07	1.44E-06	1.32E-06	1.27E-06	1.42E-06	1.33E-06	1.70E-06	1.54E-06
Biased Statistics								
Average Biased	2.97E-05	3.30E-05	3.95E-05	4.76E-05	6.29E-05	1.06E-04	1.09E-04	8.02E-05
Std Dev Biased	2.70E-05	2.74E-05	2.62E-05	2.81E-05	2.91E-05	3.12E-05	3.00E-05	3.02E-05
Ps90%/90% (+KTL) Biased	1.04E-04	1.08E-04	1.11E-04	1.25E-04	1.43E-04	1.92E-04	1.91E-04	1.63E-04
Ps90%/90% (-KTL) Biased	-4.45E-05	-4.21E-05	-3.22E-05	-2.95E-05	-1.69E-05	2.09E-05	2.66E-05	-2.62E-06
Un-Biased Statistics								
Average Un-Biased	4.69E-05	4.64E-05	5.27E-05	6.08E-05	7.64E-05	1.22E-04	1.10E-04	6.92E-05
Std Dev Un-Biased	6.50E-05	6.93E-05	6.97E-05	6.94E-05	6.79E-05	6.85E-05	6.86E-05	7.05E-05
Ps90%/90% (+KTL) Un-Biased	2.25E-04	2.37E-04	2.44E-04	2.51E-04	2.63E-04	3.10E-04	2.98E-04	2.62E-04
Ps90%/90% (-KTL) Un-Biased	-1.31E-04	-1.44E-04	-1.38E-04	-1.30E-04	-1.10E-04	-6.55E-05	-7.81E-05	-1.24E-04
Specification MIN	-3.00E-04	-4.50E-04	-4.50E-04	-4.50E-04	-6.00E-04	-7.50E-04	-7.50E-04	-7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-04	4.50E-04	4.50E-04	4.50E-04	6.00E-04	7.50E-04	7.50E-04	7.50E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

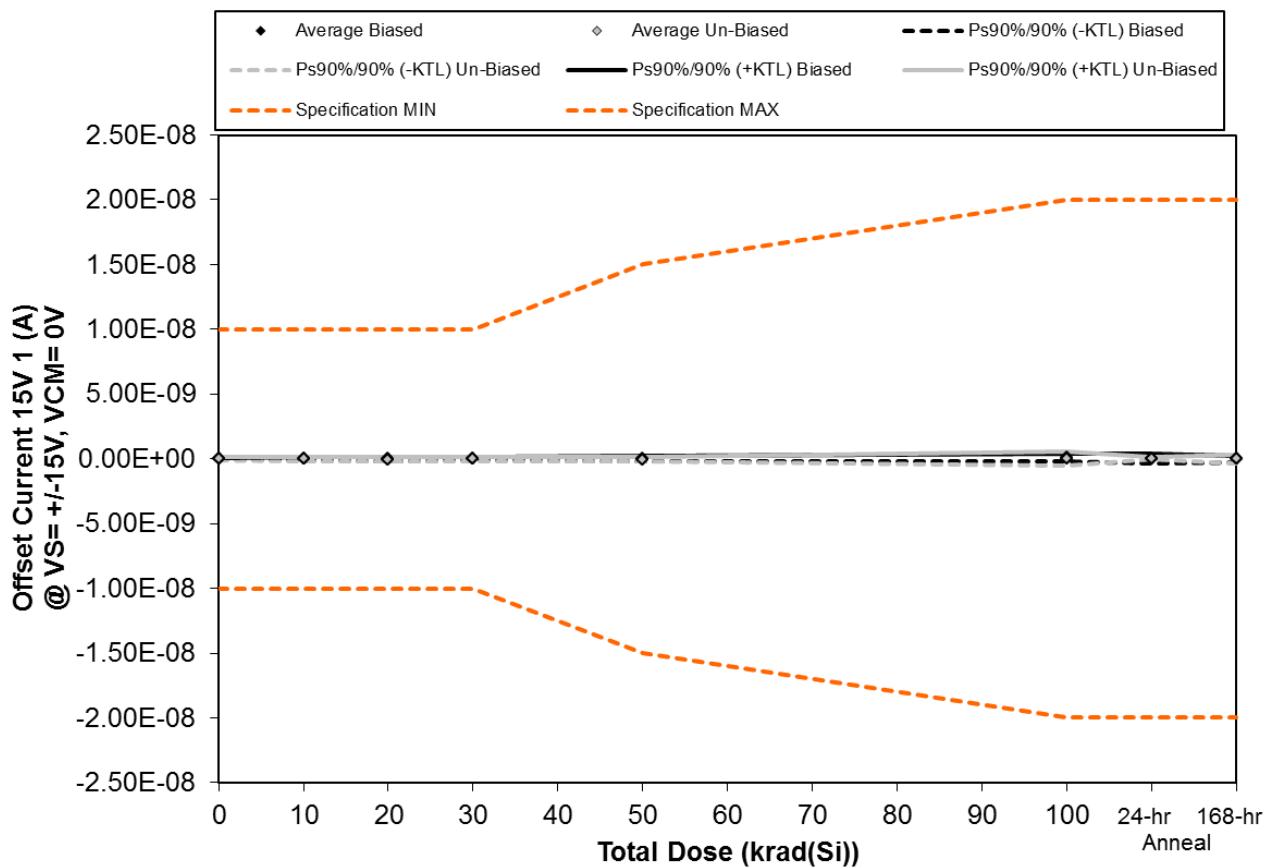


Figure 5.7. Plot of Offset Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.7. Raw data for Offset Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 15V 1 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	4.20E-11	5.70E-11	3.10E-11	2.10E-11	1.40E-11	1.45E-10	1.80E-11	0.00E+00
260	1.90E-11	2.10E-11	9.40E-11	-3.20E-11	-1.70E-11	3.70E-11	6.00E-11	7.80E-11
326	3.50E-11	5.60E-11	0.00E+00	1.01E-10	1.34E-10	1.99E-10	2.69E-10	4.90E-11
328	7.00E-12	-2.80E-11	-6.90E-11	-1.00E-11	6.90E-11	1.09E-10	-1.09E-10	-1.41E-10
329	-1.90E-11	2.60E-11	-2.60E-11	-1.70E-11	-9.20E-11	-8.00E-11	-6.00E-11	7.30E-11
330	-3.30E-11	-2.20E-11	-3.90E-11	-5.30E-11	-2.20E-11	2.49E-10	4.20E-11	1.30E-10
331	8.60E-11	6.00E-11	2.00E-11	4.90E-11	2.80E-11	1.57E-10	7.90E-11	-8.60E-11
334	2.20E-11	-8.60E-11	-1.44E-10	-8.60E-11	-1.06E-10	-1.70E-10	5.60E-11	-1.52E-10
335	-1.10E-11	-3.90E-11	0.00E+00	-3.60E-11	5.00E-12	-6.30E-11	1.80E-11	5.40E-11
344	9.10E-11	2.60E-11	1.60E-11	6.20E-11	-7.20E-11	-1.60E-10	1.60E-11	9.40E-11
346	-4.50E-11	-2.00E-11	-5.10E-11	-5.50E-11	-5.30E-11	-5.40E-11	-6.40E-11	-7.50E-11
Biased Statistics								
Average Biased	1.68E-11	2.64E-11	6.00E-12	1.26E-11	2.16E-11	8.20E-11	3.56E-11	1.18E-11
Std Dev Biased	2.42E-11	3.46E-11	6.13E-11	5.31E-11	8.56E-11	1.08E-10	1.46E-10	9.08E-11
Ps90%/90% (+KTL) Biased	8.32E-11	1.21E-10	1.74E-10	1.58E-10	2.56E-10	3.78E-10	4.36E-10	2.61E-10
Ps90%/90% (-KTL) Biased	-4.96E-11	-6.86E-11	-1.62E-10	-1.33E-10	-2.13E-10	-2.14E-10	-3.65E-10	-2.37E-10
Un-Biased Statistics								
Average Un-Biased	3.10E-11	-1.22E-11	-2.94E-11	-1.28E-11	-3.34E-11	2.60E-12	4.22E-11	8.00E-12
Std Dev Un-Biased	5.60E-11	5.69E-11	6.82E-11	6.51E-11	5.51E-11	1.90E-10	2.65E-11	1.21E-10
Ps90%/90% (+KTL) Un-Biased	1.85E-10	1.44E-10	1.58E-10	1.66E-10	1.18E-10	5.25E-10	1.15E-10	3.41E-10
Ps90%/90% (-KTL) Un-Biased	-1.23E-10	-1.68E-10	-2.16E-10	-1.91E-10	-1.84E-10	-5.20E-10	-3.06E-11	-3.25E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

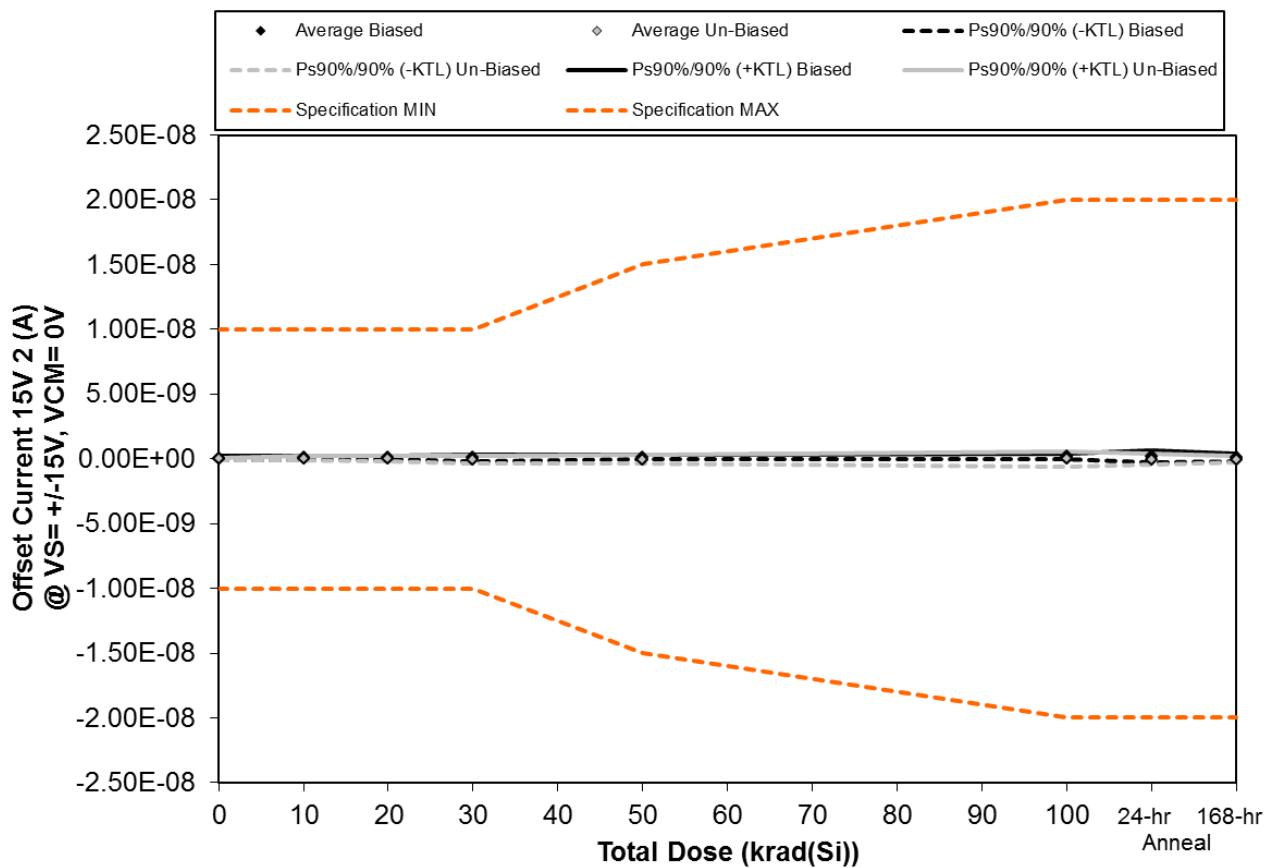


Figure 5.8. Plot of Offset Current 15V 2 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.8. Raw data for Offset Current 15V 2 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 15V 2 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.26E-10	1.07E-10	3.60E-11	-8.00E-11	9.90E-11	1.47E-10	2.11E-10	2.00E-12
260	-1.90E-11	-2.00E-11	7.10E-11	1.18E-10	1.70E-10	3.33E-10	4.41E-10	2.28E-10
326	9.00E-12	1.42E-10	1.00E-10	5.40E-11	7.70E-11	1.60E-10	1.25E-10	7.90E-11
328	6.00E-11	7.80E-11	1.60E-10	1.16E-10	1.48E-10	1.08E-10	5.60E-11	2.20E-10
329	7.00E-12	6.40E-11	3.40E-11	1.47E-10	2.07E-10	1.59E-10	2.90E-11	3.00E-12
330	5.60E-11	9.40E-11	0.00E+00	-1.04E-10	-1.80E-10	-3.28E-10	-3.18E-10	-1.10E-11
331	-4.00E-12	-3.50E-11	-5.90E-11	-1.56E-10	-1.10E-11	-6.40E-11	-2.60E-11	-1.01E-10
334	-3.10E-11	5.00E-11	1.00E-10	-6.60E-11	4.20E-11	9.30E-11	1.50E-11	-1.18E-10
335	2.00E-12	3.90E-11	-3.50E-11	-3.70E-11	-1.24E-10	-4.50E-11	-3.10E-11	2.80E-11
344	3.00E-12	1.21E-10	1.38E-10	1.04E-10	1.48E-10	2.46E-10	9.70E-11	7.20E-11
346	2.50E-11	0.00E+00	-1.80E-11	4.00E-12	-4.00E-12	2.50E-11	2.00E-12	1.20E-11
Biased Statistics								
Average Biased	3.66E-11	7.42E-11	8.02E-11	7.10E-11	1.40E-10	1.81E-10	1.72E-10	1.06E-10
Std Dev Biased	5.76E-11	6.05E-11	5.23E-11	9.10E-11	5.27E-11	8.73E-11	1.66E-10	1.12E-10
Ps90%/90% (+KTL) Biased	1.95E-10	2.40E-10	2.24E-10	3.20E-10	2.85E-10	4.21E-10	6.27E-10	4.13E-10
Ps90%/90% (-KTL) Biased	-1.21E-10	-9.18E-11	-6.32E-11	-1.78E-10	-4.26E-12	-5.81E-11	-2.82E-10	-2.00E-10
Un-Biased Statistics								
Average Un-Biased	5.20E-12	5.38E-11	2.88E-11	-5.18E-11	-2.50E-11	-1.96E-11	-5.26E-11	-2.60E-11
Std Dev Un-Biased	3.16E-11	5.97E-11	8.60E-11	9.78E-11	1.31E-10	2.13E-10	1.57E-10	8.19E-11
Ps90%/90% (+KTL) Un-Biased	9.18E-11	2.17E-10	2.65E-10	2.16E-10	3.34E-10	5.64E-10	3.78E-10	1.99E-10
Ps90%/90% (-KTL) Un-Biased	-8.14E-11	-1.10E-10	-2.07E-10	-3.20E-10	-3.84E-10	-6.03E-10	-4.83E-10	-2.51E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

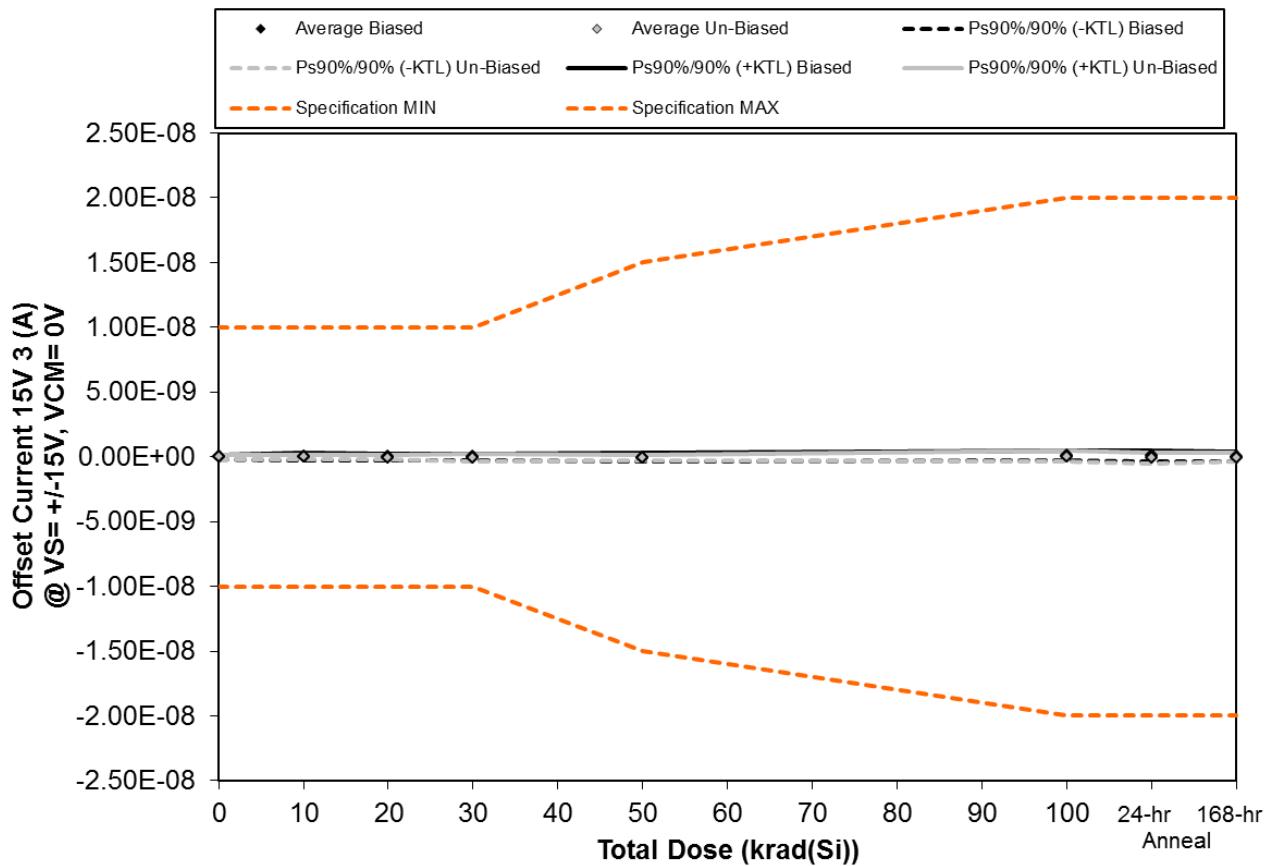


Figure 5.9. Plot of Offset Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.9. Raw data for Offset Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 15V 3 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.60E-11	4.00E-12	-4.80E-11	-1.34E-10	-1.23E-10	1.80E-11	8.50E-11	-1.93E-10
260	5.40E-11	1.04E-10	1.05E-10	9.80E-11	-9.20E-11	-1.50E-11	1.22E-10	2.50E-11
326	-4.20E-11	-9.20E-11	-1.18E-10	-8.20E-11	-1.35E-10	-7.50E-11	-1.28E-10	8.30E-11
328	6.70E-11	1.18E-10	4.40E-11	7.70E-11	1.81E-10	2.73E-10	2.67E-10	1.76E-10
329	-6.30E-11	-8.20E-11	-4.10E-11	-2.20E-11	-5.10E-11	1.55E-10	-2.90E-11	1.80E-11
330	2.80E-11	-4.50E-11	-3.80E-11	-1.36E-10	-6.80E-11	4.90E-11	-1.03E-10	1.48E-10
331	-2.00E-11	1.70E-11	-4.30E-11	-4.70E-11	1.90E-11	1.55E-10	5.60E-11	2.50E-11
334	-7.10E-11	-4.70E-11	-1.39E-10	-1.96E-10	-1.70E-10	-1.89E-10	-3.12E-10	-1.51E-10
335	8.70E-11	1.00E-10	3.70E-11	6.00E-11	3.90E-11	2.18E-10	2.70E-11	-1.31E-10
344	-4.00E-12	2.90E-11	5.00E-12	-1.70E-11	-8.70E-11	5.80E-11	-1.11E-10	-2.50E-11
346	1.90E-11	2.40E-11	-4.00E-12	1.90E-11	-8.00E-12	2.00E-11	0.00E+00	1.30E-11
Biased Statistics								
Average Biased	0.00E+00	1.04E-11	-1.16E-11	-1.26E-11	-4.40E-11	7.12E-11	6.34E-11	2.18E-11
Std Dev Biased	5.79E-11	9.93E-11	8.69E-11	9.99E-11	1.30E-10	1.41E-10	1.50E-10	1.36E-10
Ps90%/90% (+KTL) Biased	1.59E-10	2.83E-10	2.27E-10	2.61E-10	3.12E-10	4.57E-10	4.76E-10	3.94E-10
Ps90%/90% (-KTL) Biased	-1.59E-10	-2.62E-10	-2.50E-10	-2.86E-10	-4.00E-10	-3.15E-10	-3.49E-10	-3.50E-10
Un-Biased Statistics								
Average Un-Biased	4.00E-12	1.08E-11	-3.56E-11	-6.72E-11	-5.34E-11	5.82E-11	-8.86E-11	-2.68E-11
Std Dev Un-Biased	5.86E-11	6.08E-11	6.65E-11	1.01E-10	8.47E-11	1.55E-10	1.46E-10	1.22E-10
Ps90%/90% (+KTL) Un-Biased	1.65E-10	1.77E-10	1.47E-10	2.08E-10	1.79E-10	4.83E-10	3.11E-10	3.08E-10
Ps90%/90% (-KTL) Un-Biased	-1.57E-10	-1.56E-10	-2.18E-10	-3.43E-10	-2.86E-10	-3.67E-10	-4.88E-10	-3.61E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

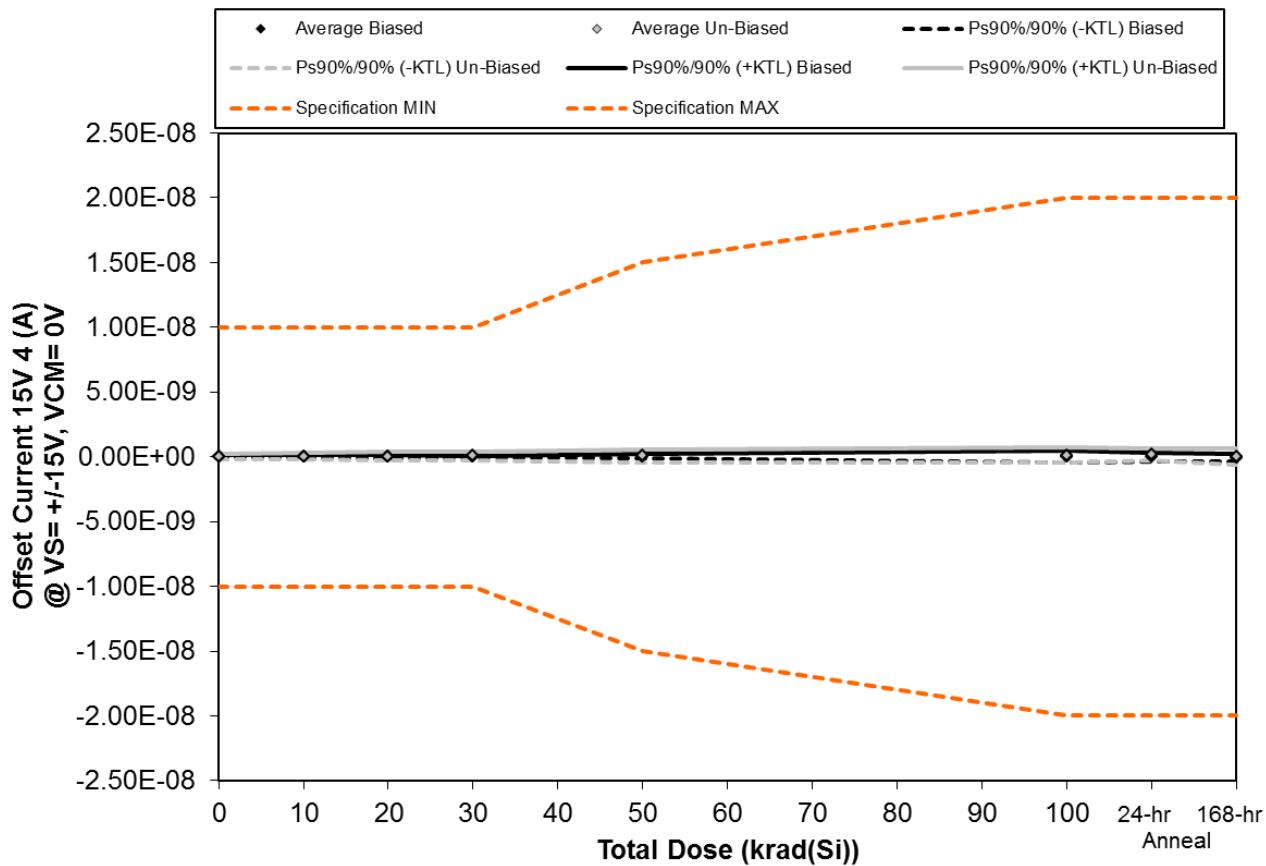


Figure 5.10. Plot of Offset Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.10. Raw data for Offset Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 15V 4 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.40E-11	6.90E-11	7.90E-11	2.80E-11	-1.60E-11	1.40E-10	-2.00E-12	-1.00E-10
260	5.70E-11	9.00E-12	-2.80E-11	2.50E-11	4.00E-12	-1.23E-10	-2.09E-10	-2.44E-10
326	-2.90E-11	-5.30E-11	-2.30E-11	5.30E-11	1.33E-10	-8.50E-11	2.70E-11	-3.00E-12
328	2.40E-11	-4.00E-11	3.40E-11	-1.70E-11	6.10E-11	5.30E-11	1.04E-10	-6.10E-11
329	3.10E-11	-1.10E-11	-7.00E-12	4.40E-11	1.01E-10	2.82E-10	9.90E-11	6.50E-11
330	4.30E-11	1.73E-10	1.91E-10	2.42E-10	2.48E-10	2.24E-10	2.50E-10	5.00E-11
331	-3.80E-11	-3.00E-11	-1.60E-11	2.80E-11	-1.60E-10	1.50E-10	1.61E-10	-6.30E-11
334	4.60E-11	9.00E-12	-3.50E-11	7.90E-11	6.20E-11	3.39E-10	1.77E-10	1.46E-10
335	1.15E-10	1.16E-10	1.93E-10	9.60E-11	2.65E-10	2.32E-10	2.98E-10	3.06E-10
344	-5.00E-11	-4.60E-11	-2.80E-11	-8.40E-11	-6.20E-11	-2.24E-10	-1.35E-10	-2.95E-10
346	-1.00E-10	-8.80E-11	-8.10E-11	-5.20E-11	-7.20E-11	-1.19E-10	-6.00E-11	-5.10E-11
Biased Statistics								
Average Biased	2.14E-11	-5.20E-12	1.10E-11	2.66E-11	5.66E-11	5.34E-11	3.80E-12	-6.86E-11
Std Dev Biased	3.13E-11	4.81E-11	4.51E-11	2.69E-11	6.30E-11	1.66E-10	1.27E-10	1.16E-10
Ps90%/90% (+KTL) Biased	1.07E-10	1.27E-10	1.35E-10	1.00E-10	2.29E-10	5.08E-10	3.53E-10	2.50E-10
Ps90%/90% (-KTL) Biased	-6.44E-11	-1.37E-10	-1.13E-10	-4.73E-11	-1.16E-10	-4.01E-10	-3.46E-10	-3.87E-10
Un-Biased Statistics								
Average Un-Biased	2.32E-11	4.44E-11	6.10E-11	7.22E-11	7.06E-11	1.44E-10	1.50E-10	2.88E-11
Std Dev Un-Biased	6.79E-11	9.57E-11	1.20E-10	1.18E-10	1.87E-10	2.17E-10	1.69E-10	2.26E-10
Ps90%/90% (+KTL) Un-Biased	2.09E-10	3.07E-10	3.89E-10	3.96E-10	5.84E-10	7.38E-10	6.13E-10	6.48E-10
Ps90%/90% (-KTL) Un-Biased	-1.63E-10	-2.18E-10	-2.67E-10	-2.52E-10	-4.43E-10	-4.50E-10	-3.13E-10	-5.91E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

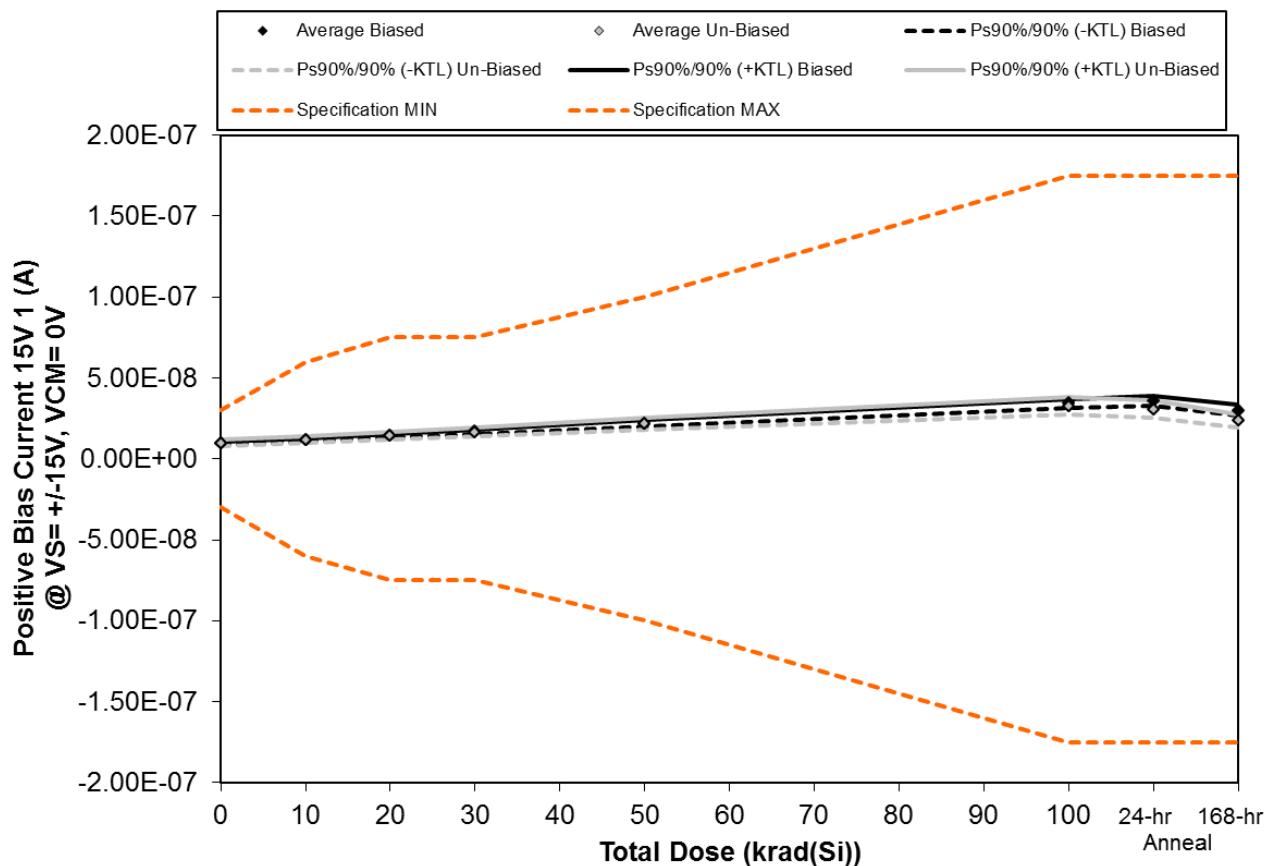


Figure 5.11. Plot of Positive Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.11. Raw data for Positive Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	9.65E-09	1.16E-08	1.41E-08	1.68E-08	2.21E-08	3.46E-08	3.66E-08	3.00E-08
260	1.02E-08	1.21E-08	1.44E-08	1.74E-08	2.27E-08	3.55E-08	3.73E-08	3.13E-08
326	1.02E-08	1.21E-08	1.45E-08	1.72E-08	2.23E-08	3.47E-08	3.65E-08	3.11E-08
328	9.81E-09	1.16E-08	1.38E-08	1.65E-08	2.14E-08	3.30E-08	3.49E-08	2.95E-08
329	9.24E-09	1.11E-08	1.35E-08	1.61E-08	2.12E-08	3.33E-08	3.49E-08	2.85E-08
330	1.07E-08	1.27E-08	1.51E-08	1.79E-08	2.29E-08	3.45E-08	3.30E-08	2.53E-08
331	1.04E-08	1.23E-08	1.49E-08	1.77E-08	2.28E-08	3.48E-08	3.28E-08	2.52E-08
334	9.27E-09	1.12E-08	1.33E-08	1.58E-08	2.03E-08	3.11E-08	2.90E-08	2.24E-08
335	9.74E-09	1.15E-08	1.37E-08	1.62E-08	2.09E-08	3.17E-08	2.98E-08	2.29E-08
344	9.34E-09	1.11E-08	1.32E-08	1.56E-08	2.02E-08	3.08E-08	2.90E-08	2.22E-08
346	1.05E-08	1.04E-08	1.05E-08	1.05E-08	1.05E-08	1.04E-08	1.05E-08	1.05E-08
Biased Statistics								
Average Biased	9.81E-09	1.17E-08	1.41E-08	1.68E-08	2.19E-08	3.42E-08	3.60E-08	3.01E-08
Std Dev Biased	3.93E-10	4.22E-10	4.03E-10	5.18E-10	6.53E-10	1.07E-09	1.10E-09	1.16E-09
Ps90%/90% (+KTL) Biased	1.09E-08	1.28E-08	1.52E-08	1.82E-08	2.37E-08	3.71E-08	3.90E-08	3.33E-08
Ps90%/90% (-KTL) Biased	8.73E-09	1.05E-08	1.30E-08	1.54E-08	2.01E-08	3.13E-08	3.30E-08	2.69E-08
Un-Biased Statistics								
Average Un-Biased	9.89E-09	1.18E-08	1.40E-08	1.66E-08	2.14E-08	3.26E-08	3.07E-08	2.36E-08
Std Dev Un-Biased	6.43E-10	7.32E-10	8.88E-10	1.09E-09	1.34E-09	1.92E-09	2.02E-09	1.52E-09
Ps90%/90% (+KTL) Un-Biased	1.17E-08	1.38E-08	1.65E-08	1.96E-08	2.51E-08	3.78E-08	3.62E-08	2.77E-08
Ps90%/90% (-KTL) Un-Biased	8.13E-09	9.77E-09	1.16E-08	1.37E-08	1.77E-08	2.73E-08	2.52E-08	1.94E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

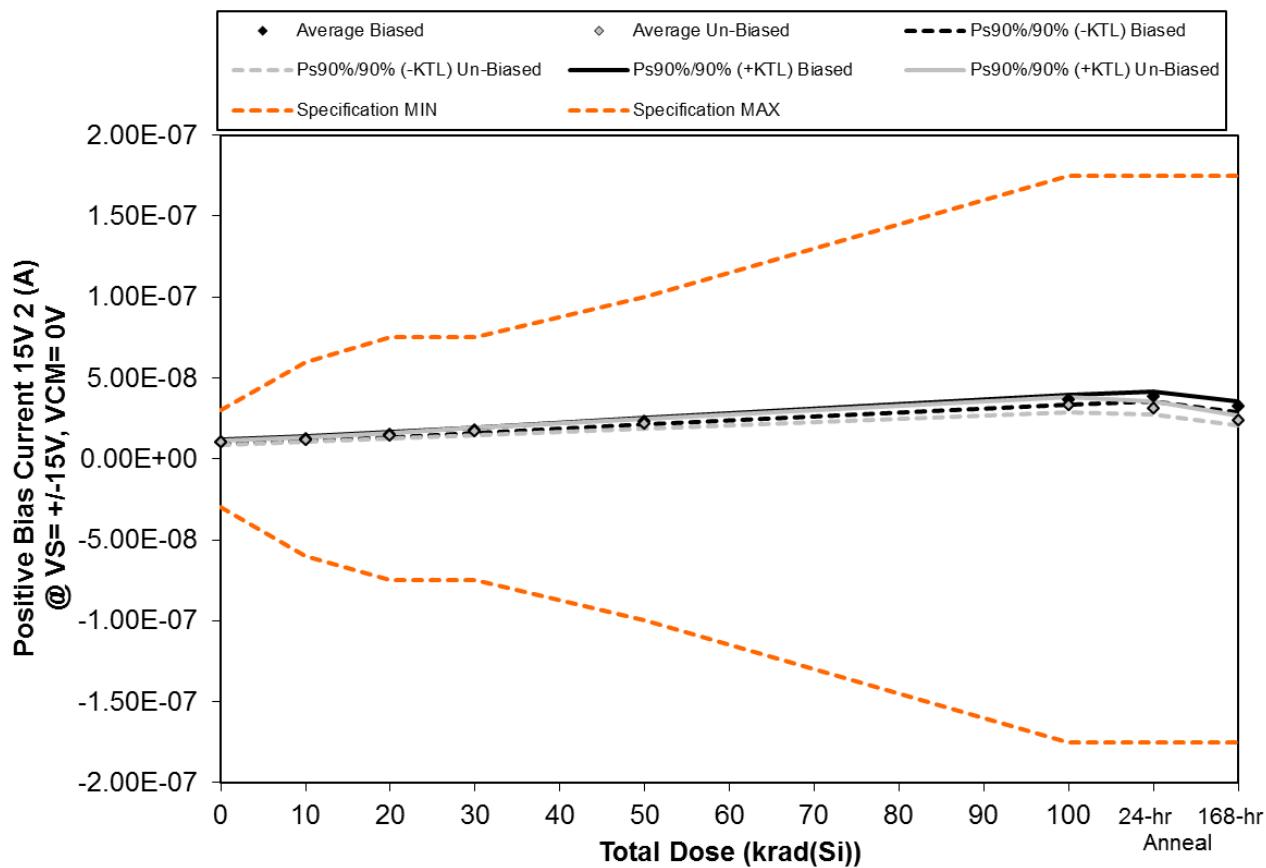


Figure 5.12. Plot of Positive Bias Current 15V 2 (A) @ VS = +/-15V, VCM = 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.12. Raw data for Positive Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.01E-08	1.23E-08	1.48E-08	1.78E-08	2.32E-08	3.63E-08	3.82E-08	3.15E-08
260	1.09E-08	1.30E-08	1.56E-08	1.87E-08	2.41E-08	3.79E-08	3.98E-08	3.35E-08
326	1.04E-08	1.24E-08	1.47E-08	1.74E-08	2.25E-08	3.51E-08	3.72E-08	3.15E-08
328	9.83E-09	1.20E-08	1.44E-08	1.73E-08	2.26E-08	3.57E-08	3.73E-08	3.10E-08
329	1.11E-08	1.31E-08	1.57E-08	1.85E-08	2.41E-08	3.73E-08	3.94E-08	3.33E-08
330	9.54E-09	1.14E-08	1.37E-08	1.62E-08	2.10E-08	3.16E-08	3.01E-08	2.30E-08
331	1.07E-08	1.27E-08	1.53E-08	1.82E-08	2.33E-08	3.58E-08	3.37E-08	2.57E-08
334	9.62E-09	1.16E-08	1.35E-08	1.62E-08	2.08E-08	3.17E-08	2.98E-08	2.28E-08
335	1.02E-08	1.20E-08	1.44E-08	1.69E-08	2.19E-08	3.31E-08	3.13E-08	2.39E-08
344	9.87E-09	1.17E-08	1.42E-08	1.69E-08	2.20E-08	3.38E-08	3.18E-08	2.42E-08
346	1.05E-08	1.04E-08	1.05E-08	1.06E-08	1.06E-08	1.05E-08	1.06E-08	1.06E-08
Biased Statistics								
Average Biased	1.05E-08	1.26E-08	1.50E-08	1.79E-08	2.33E-08	3.65E-08	3.84E-08	3.22E-08
Std Dev Biased	5.45E-10	4.78E-10	5.44E-10	6.23E-10	7.63E-10	1.16E-09	1.17E-09	1.14E-09
Ps90%/90% (+KTL) Biased	1.20E-08	1.39E-08	1.65E-08	1.96E-08	2.54E-08	3.96E-08	4.16E-08	3.53E-08
Ps90%/90% (-KTL) Biased	8.98E-09	1.13E-08	1.36E-08	1.62E-08	2.12E-08	3.33E-08	3.52E-08	2.90E-08
Un-Biased Statistics								
Average Un-Biased	9.98E-09	1.19E-08	1.42E-08	1.69E-08	2.18E-08	3.32E-08	3.13E-08	2.39E-08
Std Dev Un-Biased	4.59E-10	5.21E-10	6.81E-10	8.01E-10	1.02E-09	1.72E-09	1.53E-09	1.13E-09
Ps90%/90% (+KTL) Un-Biased	1.12E-08	1.33E-08	1.61E-08	1.91E-08	2.46E-08	3.79E-08	3.55E-08	2.70E-08
Ps90%/90% (-KTL) Un-Biased	8.72E-09	1.05E-08	1.23E-08	1.47E-08	1.90E-08	2.85E-08	2.71E-08	2.08E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

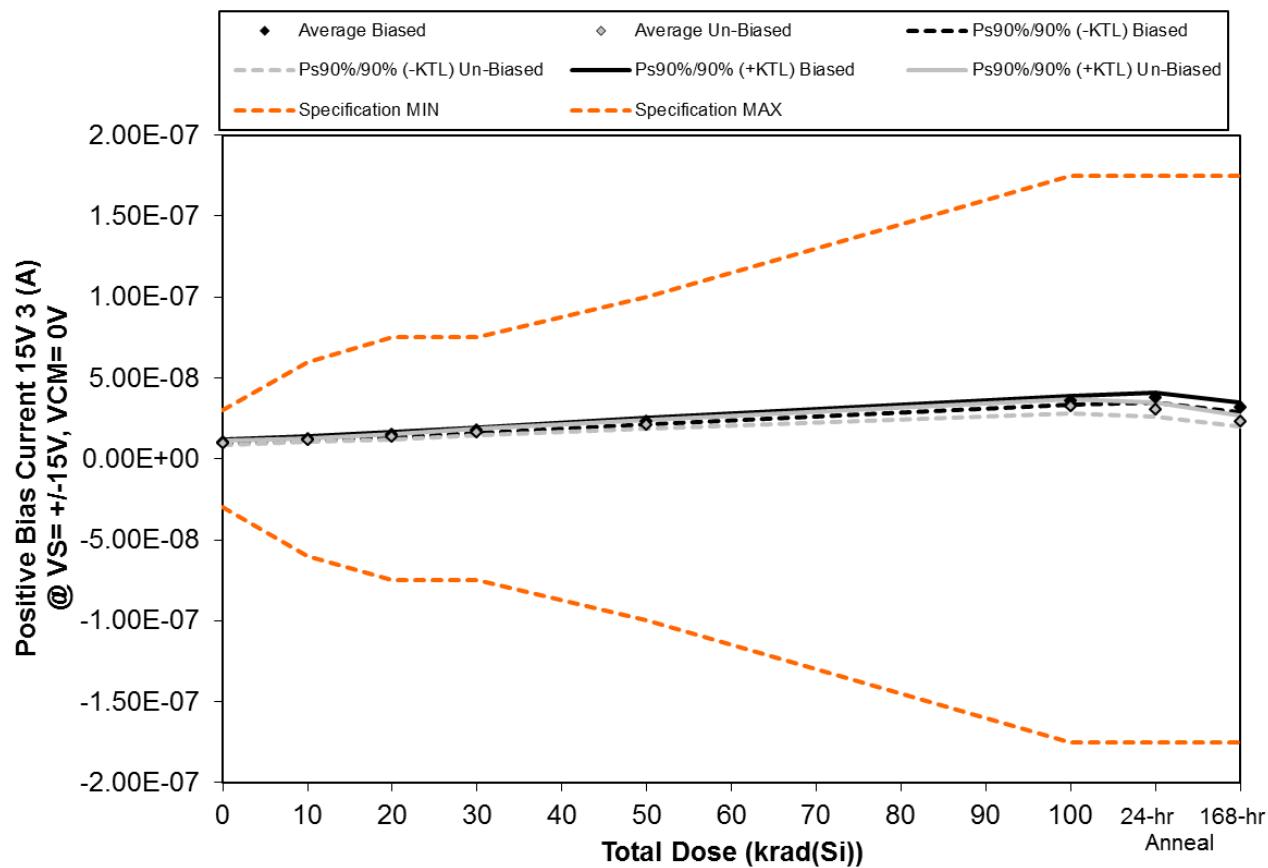


Figure 5.13. Plot of Positive Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.13. Raw data for Positive Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	9.89E-09	1.21E-08	1.45E-08	1.75E-08	2.27E-08	3.56E-08	3.72E-08	3.09E-08
260	1.05E-08	1.26E-08	1.51E-08	1.82E-08	2.38E-08	3.71E-08	3.90E-08	3.27E-08
326	1.06E-08	1.27E-08	1.52E-08	1.80E-08	2.32E-08	3.61E-08	3.80E-08	3.22E-08
328	9.69E-09	1.16E-08	1.41E-08	1.69E-08	2.21E-08	3.47E-08	3.65E-08	3.01E-08
329	1.08E-08	1.29E-08	1.54E-08	1.83E-08	2.38E-08	3.67E-08	3.86E-08	3.28E-08
330	9.35E-09	1.13E-08	1.34E-08	1.60E-08	2.06E-08	3.11E-08	2.96E-08	2.25E-08
331	1.05E-08	1.23E-08	1.48E-08	1.76E-08	2.26E-08	3.47E-08	3.27E-08	2.50E-08
334	9.19E-09	1.11E-08	1.31E-08	1.56E-08	2.00E-08	3.05E-08	2.87E-08	2.20E-08
335	9.86E-09	1.16E-08	1.40E-08	1.65E-08	2.14E-08	3.23E-08	3.07E-08	2.34E-08
344	9.57E-09	1.16E-08	1.39E-08	1.66E-08	2.16E-08	3.29E-08	3.12E-08	2.37E-08
346	9.82E-09	9.77E-09	9.73E-09	9.78E-09	9.88E-09	9.81E-09	9.78E-09	9.78E-09
Biased Statistics								
Average Biased	1.03E-08	1.24E-08	1.49E-08	1.78E-08	2.31E-08	3.60E-08	3.79E-08	3.17E-08
Std Dev Biased	4.88E-10	5.31E-10	5.53E-10	5.69E-10	7.36E-10	9.25E-10	1.03E-09	1.20E-09
Ps90%/90% (+KTL) Biased	1.16E-08	1.38E-08	1.64E-08	1.93E-08	2.51E-08	3.86E-08	4.07E-08	3.50E-08
Ps90%/90% (-KTL) Biased	8.96E-09	1.09E-08	1.33E-08	1.62E-08	2.11E-08	3.35E-08	3.50E-08	2.85E-08
Un-Biased Statistics								
Average Un-Biased	9.69E-09	1.16E-08	1.38E-08	1.65E-08	2.12E-08	3.23E-08	3.06E-08	2.33E-08
Std Dev Un-Biased	5.05E-10	4.60E-10	6.40E-10	7.71E-10	9.84E-10	1.62E-09	1.54E-09	1.15E-09
Ps90%/90% (+KTL) Un-Biased	1.11E-08	1.28E-08	1.56E-08	1.86E-08	2.39E-08	3.68E-08	3.48E-08	2.65E-08
Ps90%/90% (-KTL) Un-Biased	8.30E-09	1.03E-08	1.21E-08	1.43E-08	1.85E-08	2.78E-08	2.63E-08	2.02E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

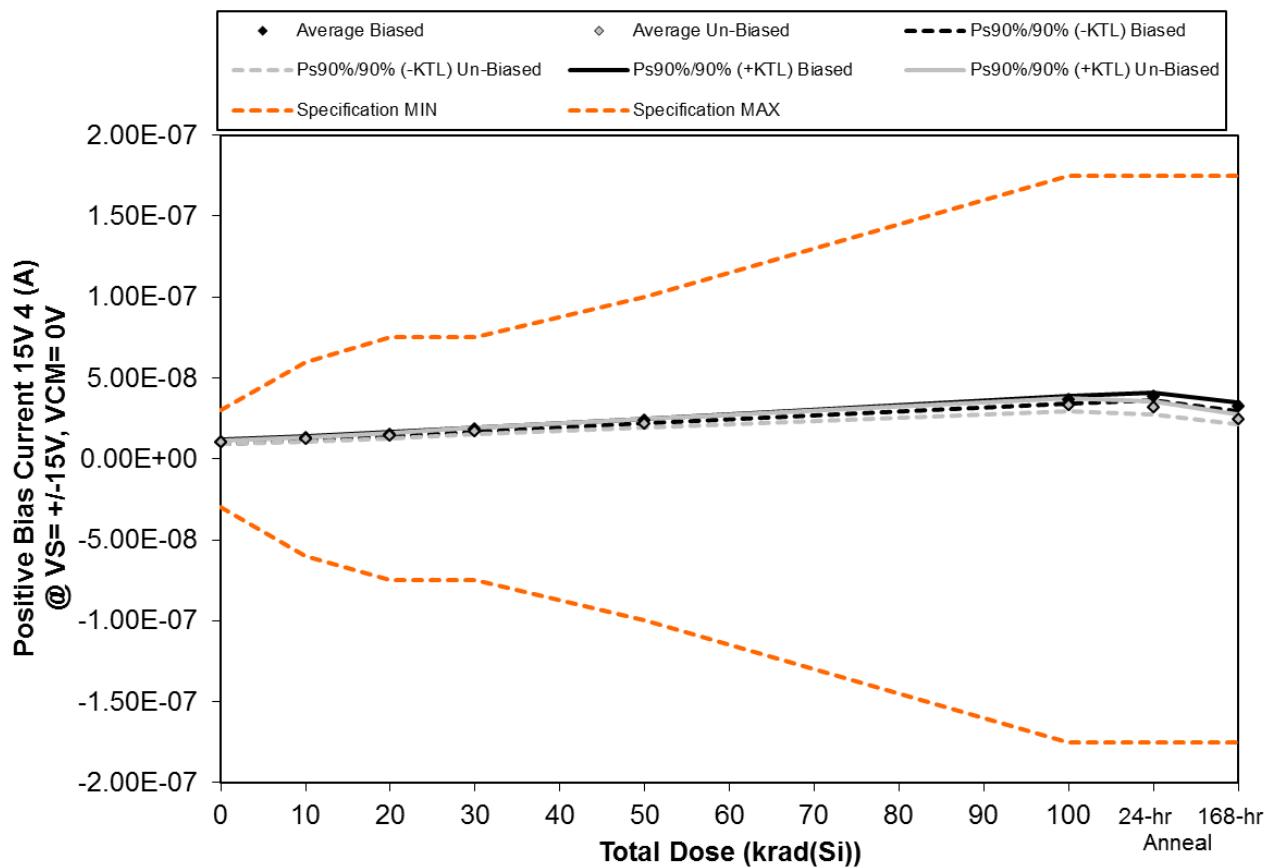


Figure 5.14. Plot of Positive Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.14. Raw data for Positive Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.05E-08	1.27E-08	1.52E-08	1.83E-08	2.37E-08	3.70E-08	3.90E-08	3.24E-08
260	1.04E-08	1.24E-08	1.48E-08	1.78E-08	2.34E-08	3.66E-08	3.85E-08	3.23E-08
326	1.12E-08	1.33E-08	1.59E-08	1.89E-08	2.42E-08	3.73E-08	3.94E-08	3.38E-08
328	1.06E-08	1.25E-08	1.50E-08	1.80E-08	2.31E-08	3.57E-08	3.77E-08	3.21E-08
329	1.01E-08	1.21E-08	1.47E-08	1.75E-08	2.29E-08	3.56E-08	3.74E-08	3.10E-08
330	1.08E-08	1.30E-08	1.54E-08	1.81E-08	2.33E-08	3.53E-08	3.36E-08	2.59E-08
331	1.01E-08	1.21E-08	1.46E-08	1.73E-08	2.24E-08	3.43E-08	3.22E-08	2.47E-08
334	9.64E-09	1.16E-08	1.37E-08	1.62E-08	2.09E-08	3.18E-08	2.97E-08	2.29E-08
335	9.88E-09	1.18E-08	1.40E-08	1.66E-08	2.14E-08	3.25E-08	3.07E-08	2.36E-08
344	1.02E-08	1.21E-08	1.44E-08	1.71E-08	2.19E-08	3.32E-08	3.15E-08	2.42E-08
346	1.08E-08	1.08E-08	1.08E-08	1.08E-08	1.08E-08	1.08E-08	1.08E-08	1.08E-08
Biased Statistics								
Average Biased	1.06E-08	1.26E-08	1.51E-08	1.81E-08	2.35E-08	3.64E-08	3.84E-08	3.23E-08
Std Dev Biased	3.91E-10	4.38E-10	4.59E-10	5.12E-10	5.22E-10	7.92E-10	8.47E-10	1.00E-09
Ps90%/90% (+KTL) Biased	1.16E-08	1.38E-08	1.64E-08	1.95E-08	2.49E-08	3.86E-08	4.07E-08	3.51E-08
Ps90%/90% (-KTL) Biased	9.48E-09	1.14E-08	1.39E-08	1.67E-08	2.20E-08	3.43E-08	3.61E-08	2.96E-08
Un-Biased Statistics								
Average Un-Biased	1.01E-08	1.21E-08	1.44E-08	1.71E-08	2.20E-08	3.34E-08	3.15E-08	2.43E-08
Std Dev Un-Biased	4.41E-10	5.29E-10	6.46E-10	7.32E-10	9.20E-10	1.38E-09	1.44E-09	1.15E-09
Ps90%/90% (+KTL) Un-Biased	1.13E-08	1.36E-08	1.62E-08	1.91E-08	2.45E-08	3.72E-08	3.55E-08	2.74E-08
Ps90%/90% (-KTL) Un-Biased	8.92E-09	1.07E-08	1.26E-08	1.51E-08	1.94E-08	2.96E-08	2.76E-08	2.11E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

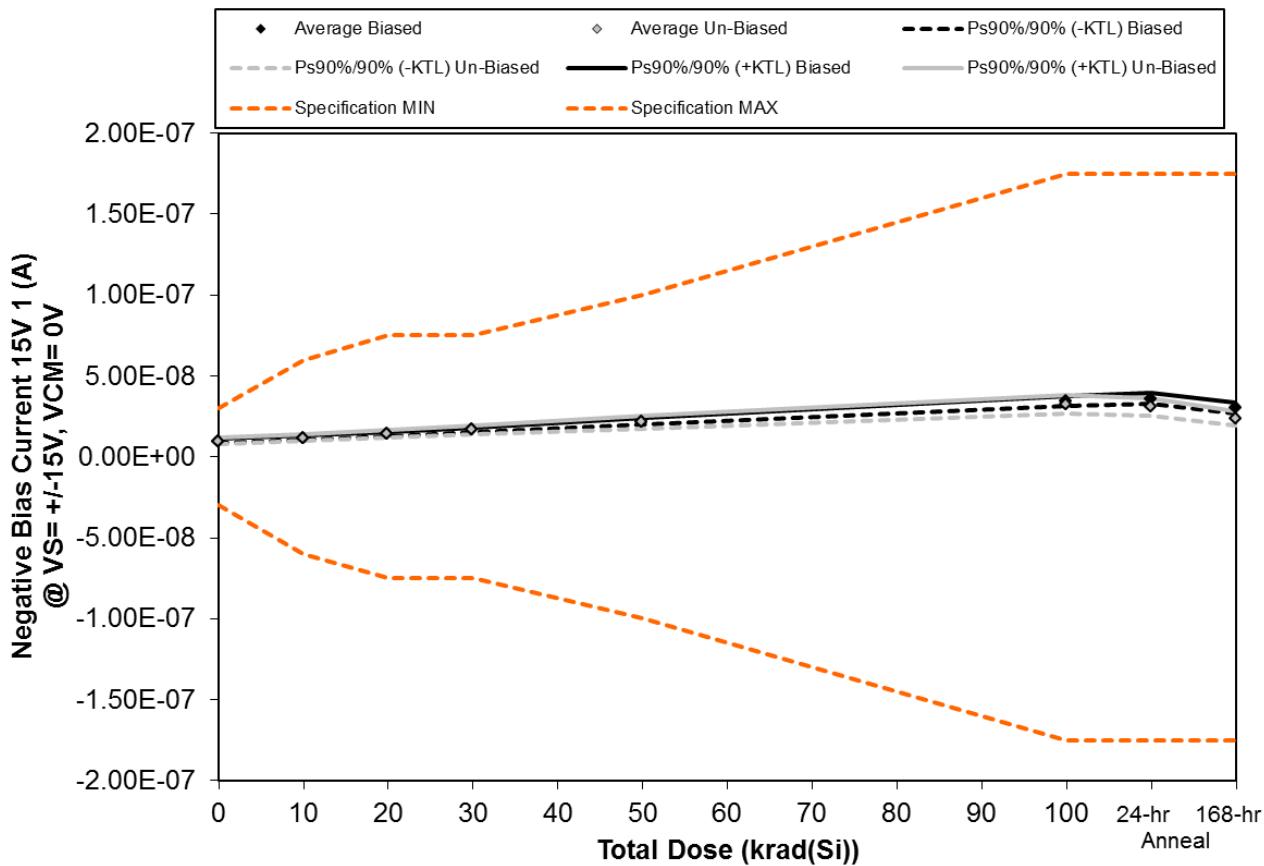


Figure 5.15. Plot of Negative Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.15. Raw data for Negative Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	9.56E-09	1.17E-08	1.40E-08	1.68E-08	2.22E-08	3.48E-08	3.66E-08	3.00E-08
260	1.01E-08	1.20E-08	1.46E-08	1.75E-08	2.26E-08	3.56E-08	3.75E-08	3.14E-08
326	1.03E-08	1.23E-08	1.45E-08	1.73E-08	2.24E-08	3.49E-08	3.68E-08	3.12E-08
328	9.87E-09	1.16E-08	1.39E-08	1.64E-08	2.13E-08	3.32E-08	3.48E-08	2.94E-08
329	9.19E-09	1.11E-08	1.35E-08	1.62E-08	2.10E-08	3.33E-08	3.50E-08	2.86E-08
330	1.08E-08	1.27E-08	1.51E-08	1.79E-08	2.29E-08	3.46E-08	3.32E-08	2.55E-08
331	1.04E-08	1.24E-08	1.48E-08	1.78E-08	2.29E-08	3.50E-08	3.30E-08	2.51E-08
334	9.23E-09	1.10E-08	1.32E-08	1.57E-08	2.02E-08	3.09E-08	2.92E-08	2.21E-08
335	9.67E-09	1.16E-08	1.37E-08	1.63E-08	2.09E-08	3.16E-08	3.00E-08	2.30E-08
344	9.37E-09	1.13E-08	1.34E-08	1.58E-08	2.02E-08	3.07E-08	2.91E-08	2.24E-08
346	1.04E-08	1.04E-08	1.04E-08	1.03E-08	1.04E-08	1.04E-08	1.04E-08	1.04E-08
Biased Statistics								
Average Biased	9.80E-09	1.18E-08	1.41E-08	1.68E-08	2.19E-08	3.44E-08	3.61E-08	3.01E-08
Std Dev Biased	4.39E-10	4.66E-10	4.64E-10	5.45E-10	7.14E-10	1.08E-09	1.19E-09	1.19E-09
Ps90%/90% (+KTL) Biased	1.10E-08	1.30E-08	1.54E-08	1.83E-08	2.39E-08	3.73E-08	3.94E-08	3.34E-08
Ps90%/90% (-KTL) Biased	8.60E-09	1.05E-08	1.28E-08	1.53E-08	1.99E-08	3.14E-08	3.29E-08	2.69E-08
Un-Biased Statistics								
Average Un-Biased	9.89E-09	1.18E-08	1.41E-08	1.67E-08	2.14E-08	3.26E-08	3.09E-08	2.36E-08
Std Dev Un-Biased	6.68E-10	7.38E-10	8.85E-10	1.08E-09	1.37E-09	2.07E-09	2.04E-09	1.57E-09
Ps90%/90% (+KTL) Un-Biased	1.17E-08	1.38E-08	1.65E-08	1.96E-08	2.52E-08	3.83E-08	3.65E-08	2.79E-08
Ps90%/90% (-KTL) Un-Biased	8.06E-09	9.78E-09	1.16E-08	1.37E-08	1.77E-08	2.69E-08	2.53E-08	1.93E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

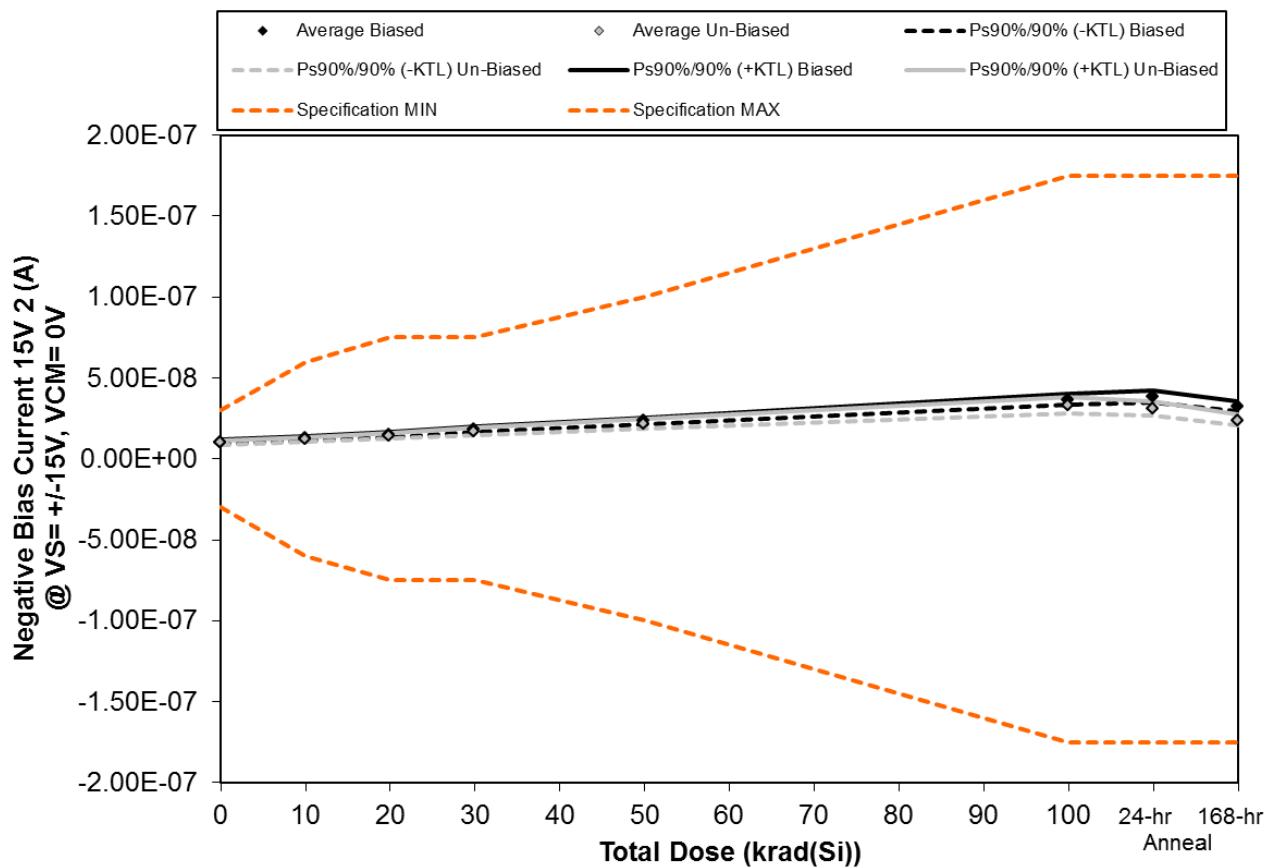


Figure 5.16. Plot of Negative Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.16. Raw data for Negative Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.01E-08	1.24E-08	1.48E-08	1.78E-08	2.32E-08	3.65E-08	3.84E-08	3.16E-08
260	1.08E-08	1.29E-08	1.56E-08	1.87E-08	2.44E-08	3.82E-08	4.04E-08	3.38E-08
326	1.05E-08	1.26E-08	1.48E-08	1.76E-08	2.26E-08	3.55E-08	3.73E-08	3.18E-08
328	1.00E-08	1.21E-08	1.45E-08	1.74E-08	2.27E-08	3.58E-08	3.76E-08	3.12E-08
329	1.10E-08	1.33E-08	1.58E-08	1.87E-08	2.43E-08	3.76E-08	3.94E-08	3.35E-08
330	9.71E-09	1.17E-08	1.38E-08	1.62E-08	2.07E-08	3.13E-08	2.99E-08	2.31E-08
331	1.08E-08	1.28E-08	1.52E-08	1.81E-08	2.34E-08	3.57E-08	3.38E-08	2.57E-08
334	9.51E-09	1.15E-08	1.38E-08	1.60E-08	2.07E-08	3.18E-08	2.99E-08	2.27E-08
335	1.01E-08	1.21E-08	1.44E-08	1.70E-08	2.17E-08	3.31E-08	3.12E-08	2.39E-08
344	9.77E-09	1.20E-08	1.44E-08	1.72E-08	2.21E-08	3.40E-08	3.19E-08	2.44E-08
346	1.05E-08	1.06E-08	1.05E-08	1.04E-08	1.05E-08	1.06E-08	1.05E-08	1.05E-08
Biased Statistics								
Average Biased	1.05E-08	1.27E-08	1.51E-08	1.81E-08	2.34E-08	3.67E-08	3.86E-08	3.24E-08
Std Dev Biased	4.32E-10	4.77E-10	5.51E-10	6.30E-10	8.28E-10	1.18E-09	1.30E-09	1.19E-09
Ps90%/90% (+KTL) Biased	1.17E-08	1.40E-08	1.66E-08	1.98E-08	2.57E-08	4.00E-08	4.22E-08	3.56E-08
Ps90%/90% (-KTL) Biased	9.30E-09	1.14E-08	1.36E-08	1.63E-08	2.12E-08	3.35E-08	3.51E-08	2.91E-08
Un-Biased Statistics								
Average Un-Biased	9.98E-09	1.20E-08	1.43E-08	1.69E-08	2.18E-08	3.32E-08	3.13E-08	2.40E-08
Std Dev Un-Biased	4.96E-10	4.98E-10	5.65E-10	8.47E-10	1.10E-09	1.76E-09	1.61E-09	1.18E-09
Ps90%/90% (+KTL) Un-Biased	1.13E-08	1.34E-08	1.58E-08	1.92E-08	2.48E-08	3.80E-08	3.58E-08	2.72E-08
Ps90%/90% (-KTL) Un-Biased	8.62E-09	1.06E-08	1.27E-08	1.46E-08	1.87E-08	2.84E-08	2.69E-08	2.07E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

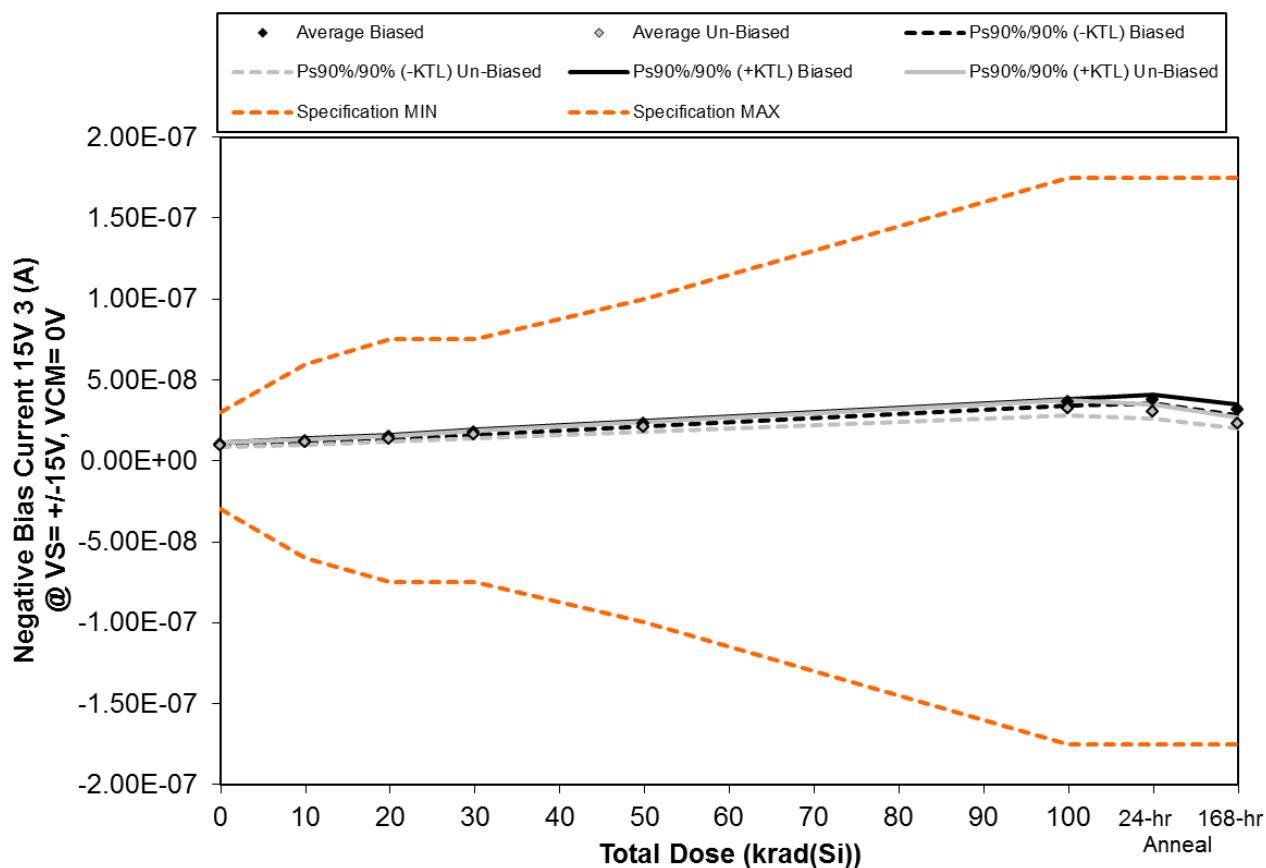


Figure 5.17. Plot of Negative Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.17. Raw data for Negative Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	9.83E-09	1.19E-08	1.45E-08	1.73E-08	2.27E-08	3.58E-08	3.74E-08	3.08E-08
260	1.05E-08	1.27E-08	1.53E-08	1.83E-08	2.37E-08	3.71E-08	3.92E-08	3.28E-08
326	1.06E-08	1.27E-08	1.50E-08	1.78E-08	2.31E-08	3.60E-08	3.79E-08	3.22E-08
328	9.71E-09	1.18E-08	1.42E-08	1.70E-08	2.22E-08	3.51E-08	3.68E-08	3.02E-08
329	1.07E-08	1.29E-08	1.54E-08	1.84E-08	2.38E-08	3.69E-08	3.87E-08	3.29E-08
330	9.32E-09	1.12E-08	1.34E-08	1.59E-08	2.05E-08	3.13E-08	2.96E-08	2.27E-08
331	1.03E-08	1.24E-08	1.48E-08	1.76E-08	2.26E-08	3.49E-08	3.29E-08	2.50E-08
334	9.15E-09	1.11E-08	1.31E-08	1.53E-08	1.98E-08	3.04E-08	2.86E-08	2.18E-08
335	9.89E-09	1.17E-08	1.41E-08	1.66E-08	2.14E-08	3.26E-08	3.08E-08	2.34E-08
344	9.61E-09	1.16E-08	1.39E-08	1.65E-08	2.16E-08	3.32E-08	3.12E-08	2.37E-08
346	9.80E-09	9.85E-09	9.76E-09	9.76E-09	9.78E-09	9.88E-09	9.79E-09	9.82E-09
Biased Statistics								
Average Biased	1.03E-08	1.24E-08	1.49E-08	1.78E-08	2.31E-08	3.62E-08	3.80E-08	3.18E-08
Std Dev Biased	4.76E-10	5.00E-10	5.16E-10	5.95E-10	6.81E-10	8.21E-10	9.61E-10	1.23E-09
Ps90%/90% (+KTL) Biased	1.16E-08	1.38E-08	1.63E-08	1.94E-08	2.50E-08	3.84E-08	4.06E-08	3.51E-08
Ps90%/90% (-KTL) Biased	8.97E-09	1.10E-08	1.34E-08	1.61E-08	2.12E-08	3.39E-08	3.54E-08	2.84E-08
Un-Biased Statistics								
Average Un-Biased	9.66E-09	1.16E-08	1.38E-08	1.64E-08	2.12E-08	3.25E-08	3.06E-08	2.33E-08
Std Dev Un-Biased	4.71E-10	5.00E-10	6.52E-10	8.68E-10	1.09E-09	1.72E-09	1.64E-09	1.18E-09
Ps90%/90% (+KTL) Un-Biased	1.10E-08	1.30E-08	1.56E-08	1.88E-08	2.41E-08	3.72E-08	3.51E-08	2.65E-08
Ps90%/90% (-KTL) Un-Biased	8.37E-09	1.02E-08	1.20E-08	1.40E-08	1.82E-08	2.78E-08	2.61E-08	2.01E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

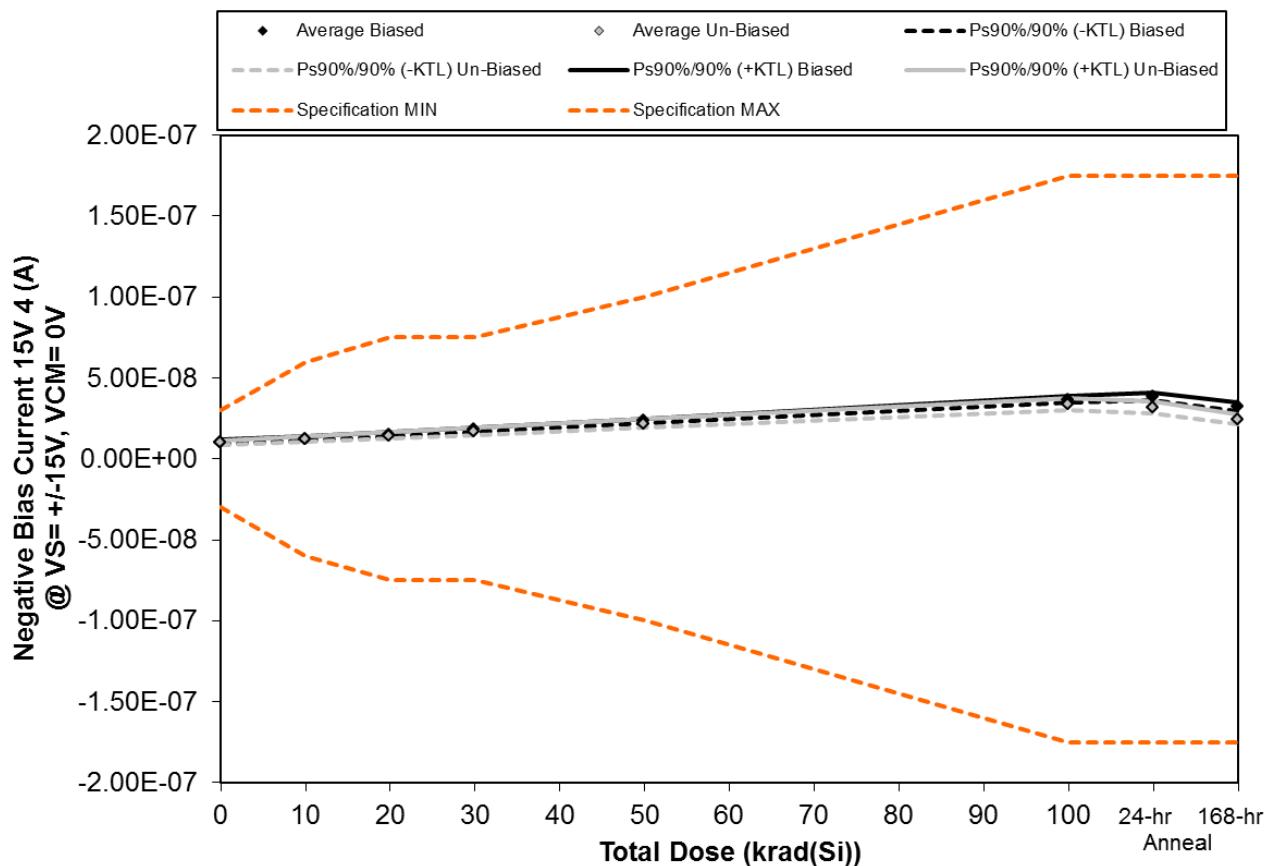


Figure 5.18. Plot of Negative Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.18. Raw data for Negative Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.04E-08	1.26E-08	1.52E-08	1.83E-08	2.38E-08	3.73E-08	3.91E-08	3.24E-08
260	1.04E-08	1.23E-08	1.49E-08	1.80E-08	2.34E-08	3.65E-08	3.83E-08	3.21E-08
326	1.12E-08	1.34E-08	1.58E-08	1.89E-08	2.43E-08	3.74E-08	3.94E-08	3.38E-08
328	1.07E-08	1.26E-08	1.51E-08	1.79E-08	2.31E-08	3.59E-08	3.77E-08	3.20E-08
329	1.00E-08	1.21E-08	1.46E-08	1.76E-08	2.30E-08	3.60E-08	3.76E-08	3.10E-08
330	1.09E-08	1.31E-08	1.57E-08	1.85E-08	2.34E-08	3.55E-08	3.39E-08	2.61E-08
331	1.01E-08	1.21E-08	1.45E-08	1.73E-08	2.23E-08	3.44E-08	3.24E-08	2.46E-08
334	9.61E-09	1.15E-08	1.37E-08	1.62E-08	2.08E-08	3.21E-08	3.01E-08	2.30E-08
335	9.97E-09	1.19E-08	1.42E-08	1.68E-08	2.16E-08	3.28E-08	3.10E-08	2.39E-08
344	1.02E-08	1.22E-08	1.45E-08	1.70E-08	2.20E-08	3.32E-08	3.14E-08	2.39E-08
346	1.07E-08	1.07E-08	1.07E-08	1.07E-08	1.06E-08	1.07E-08	1.07E-08	1.08E-08
Biased Statistics								
Average Biased	1.05E-08	1.26E-08	1.51E-08	1.81E-08	2.35E-08	3.66E-08	3.84E-08	3.23E-08
Std Dev Biased	4.51E-10	4.73E-10	4.47E-10	4.76E-10	5.41E-10	7.40E-10	7.85E-10	1.02E-09
Ps90%/90% (+KTL) Biased	1.18E-08	1.39E-08	1.64E-08	1.94E-08	2.50E-08	3.86E-08	4.06E-08	3.51E-08
Ps90%/90% (-KTL) Biased	9.31E-09	1.13E-08	1.39E-08	1.68E-08	2.20E-08	3.46E-08	3.63E-08	2.95E-08
Un-Biased Statistics								
Average Un-Biased	1.01E-08	1.22E-08	1.45E-08	1.72E-08	2.20E-08	3.36E-08	3.18E-08	2.43E-08
Std Dev Un-Biased	4.61E-10	5.77E-10	7.20E-10	8.46E-10	9.51E-10	1.36E-09	1.47E-09	1.15E-09
Ps90%/90% (+KTL) Un-Biased	1.14E-08	1.37E-08	1.65E-08	1.95E-08	2.46E-08	3.73E-08	3.58E-08	2.74E-08
Ps90%/90% (-KTL) Un-Biased	8.88E-09	1.06E-08	1.25E-08	1.48E-08	1.94E-08	2.99E-08	2.78E-08	2.11E-08
Specification MIN	-3.00E-08	-6.00E-08	-7.50E-08	-7.50E-08	-1.00E-07	-1.75E-07	-1.75E-07	-1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	3.00E-08	6.00E-08	7.50E-08	7.50E-08	1.00E-07	1.75E-07	1.75E-07	1.75E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

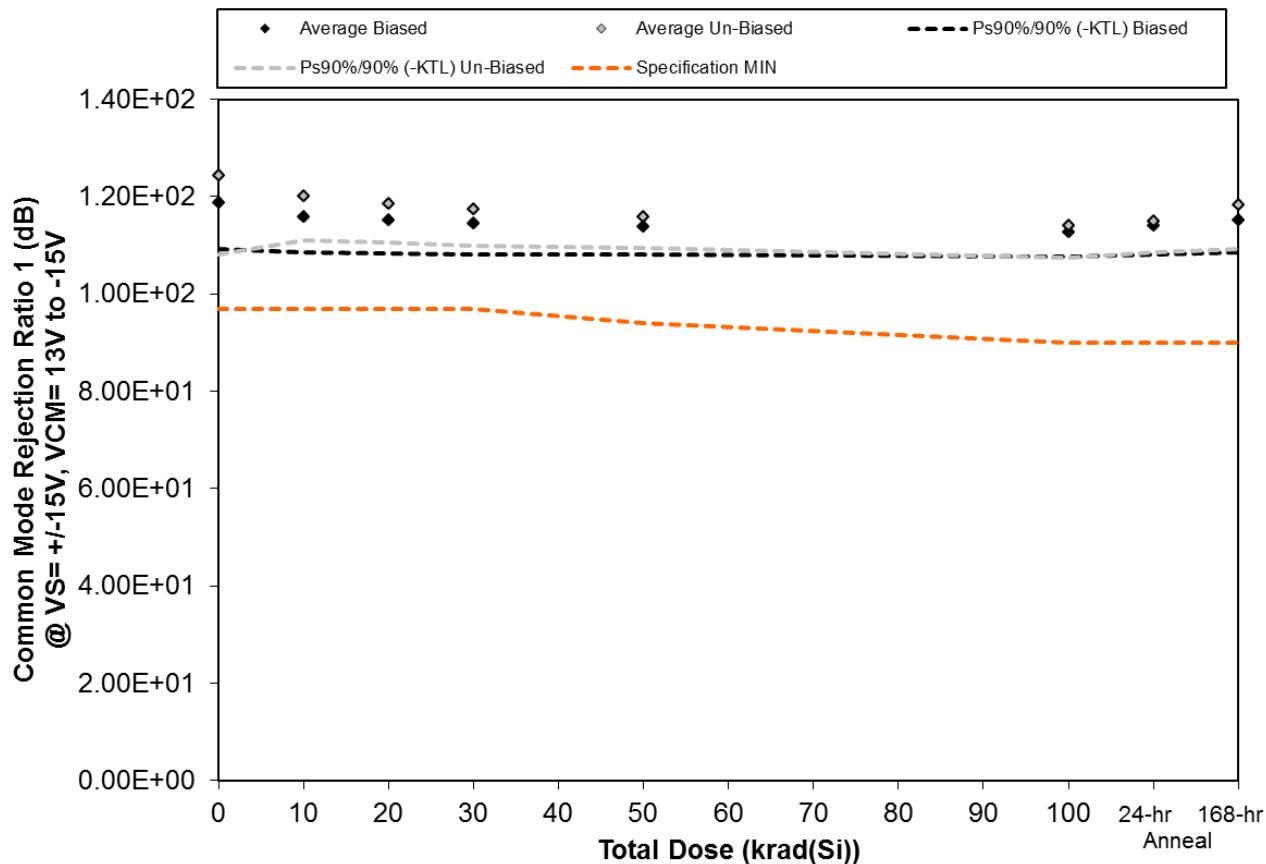


Figure 5.19. Plot of Common Mode Rejection Ratio 1 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.19. Raw data for Common Mode Rejection Ratio 1 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio 1 (dB) @ VS= +/-15V, VCM= 13V to -15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.22E+02	1.18E+02	1.18E+02	1.17E+02	1.16E+02	1.15E+02	1.17E+02	1.18E+02
260	1.21E+02	1.17E+02	1.17E+02	1.16E+02	1.15E+02	1.13E+02	1.15E+02	1.16E+02
326	1.20E+02	1.17E+02	1.16E+02	1.15E+02	1.15E+02	1.13E+02	1.15E+02	1.16E+02
328	1.14E+02	1.12E+02	1.11E+02	1.11E+02	1.11E+02	1.10E+02	1.11E+02	1.12E+02
329	1.16E+02	1.14E+02	1.14E+02	1.13E+02	1.13E+02	1.12E+02	1.13E+02	1.14E+02
330	1.18E+02	1.16E+02	1.15E+02	1.14E+02	1.13E+02	1.11E+02	1.11E+02	1.14E+02
331	1.23E+02	1.19E+02	1.18E+02	1.17E+02	1.16E+02	1.14E+02	1.15E+02	1.18E+02
334	1.27E+02	1.22E+02	1.20E+02	1.19E+02	1.17E+02	1.15E+02	1.16E+02	1.20E+02
335	1.21E+02	1.19E+02	1.17E+02	1.16E+02	1.15E+02	1.14E+02	1.14E+02	1.17E+02
344	1.33E+02	1.25E+02	1.22E+02	1.21E+02	1.19E+02	1.17E+02	1.18E+02	1.23E+02
346	1.20E+02	1.20E+02	1.20E+02	1.20E+02	1.20E+02	1.20E+02	1.20E+02	1.20E+02
Biased Statistics								
Average Biased	1.19E+02	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.13E+02	1.14E+02	1.15E+02
Std Dev Biased	3.46E+00	2.60E+00	2.43E+00	2.34E+00	2.09E+00	1.83E+00	2.18E+00	2.38E+00
Ps90%/90% (+KTL) Biased	1.28E+02	1.23E+02	1.22E+02	1.21E+02	1.20E+02	1.18E+02	1.20E+02	1.22E+02
Ps90%/90% (-KTL) Biased	1.09E+02	1.09E+02	1.08E+02	1.08E+02	1.08E+02	1.08E+02	1.08E+02	1.09E+02
Un-Biased Statistics								
Average Un-Biased	1.24E+02	1.20E+02	1.18E+02	1.17E+02	1.16E+02	1.14E+02	1.15E+02	1.18E+02
Std Dev Un-Biased	5.95E+00	3.29E+00	2.90E+00	2.77E+00	2.33E+00	2.38E+00	2.32E+00	3.24E+00
Ps90%/90% (+KTL) Un-Biased	1.41E+02	1.29E+02	1.26E+02	1.25E+02	1.22E+02	1.21E+02	1.21E+02	1.27E+02
Ps90%/90% (-KTL) Un-Biased	1.08E+02	1.11E+02	1.11E+02	1.10E+02	1.10E+02	1.08E+02	1.09E+02	1.09E+02
Specification MIN	9.70E+01	9.70E+01	9.70E+01	9.70E+01	9.40E+01	9.00E+01	9.00E+01	9.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

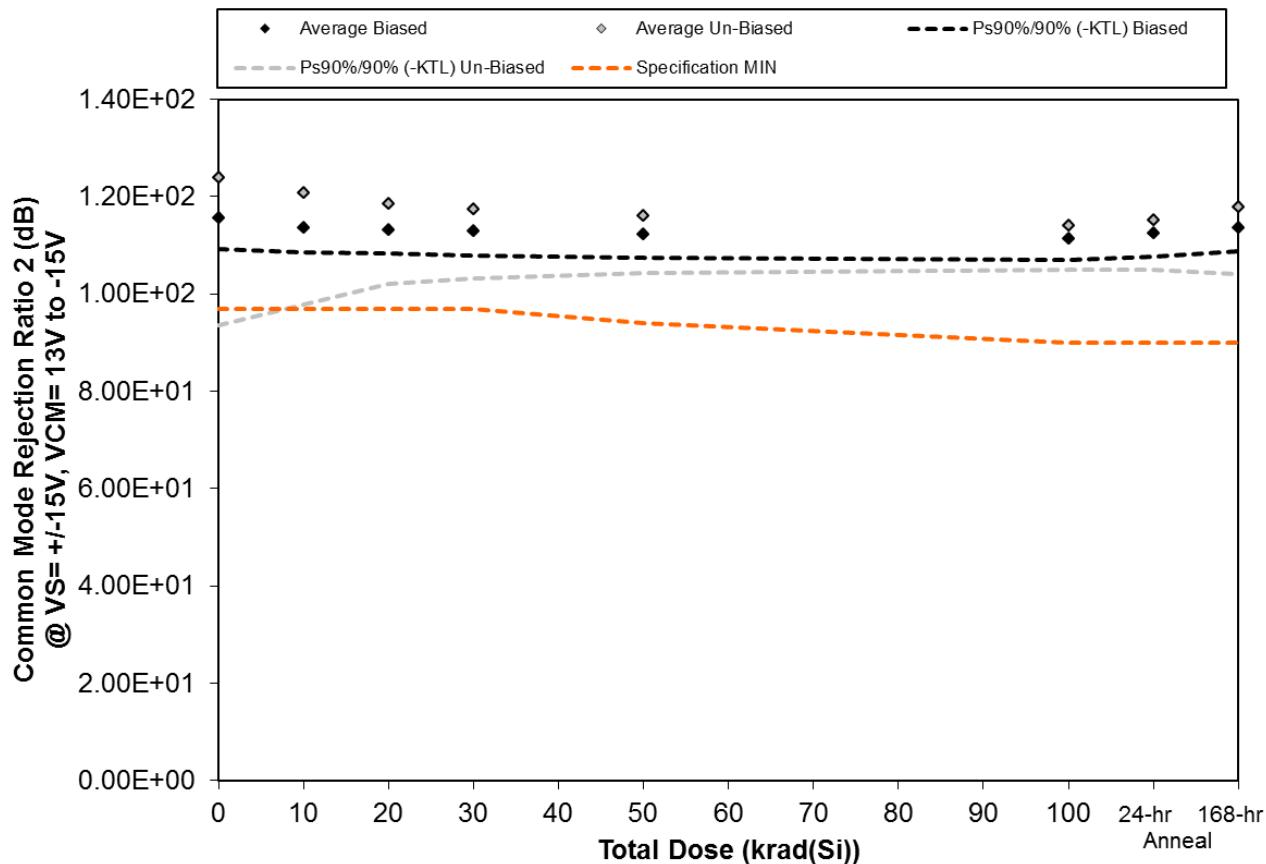


Figure 5.20. Plot of Common Mode Rejection Ratio 2 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.20. Raw data for Common Mode Rejection Ratio 2 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio 2 (dB) @ VS= +/-15V, VCM= 13V to -15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.18E+02	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.13E+02	1.15E+02	1.16E+02
260	1.18E+02	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.13E+02	1.14E+02	1.15E+02
326	1.13E+02	1.12E+02	1.11E+02	1.11E+02	1.11E+02	1.10E+02	1.11E+02	1.12E+02
328	1.13E+02	1.12E+02	1.12E+02	1.11E+02	1.11E+02	1.10E+02	1.11E+02	1.12E+02
329	1.15E+02	1.13E+02	1.13E+02	1.13E+02	1.12E+02	1.11E+02	1.12E+02	1.13E+02
330	1.16E+02	1.14E+02	1.14E+02	1.13E+02	1.12E+02	1.11E+02	1.12E+02	1.13E+02
331	1.26E+02	1.23E+02	1.21E+02	1.19E+02	1.18E+02	1.15E+02	1.16E+02	1.21E+02
334	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.13E+02	1.12E+02	1.13E+02	1.15E+02
335	1.42E+02	1.34E+02	1.28E+02	1.26E+02	1.23E+02	1.19E+02	1.21E+02	1.25E+02
344	1.19E+02	1.17E+02	1.16E+02	1.15E+02	1.14E+02	1.12E+02	1.13E+02	1.15E+02
346	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02	1.17E+02
Biased Statistics								
Average Biased	1.16E+02	1.14E+02	1.13E+02	1.13E+02	1.12E+02	1.11E+02	1.13E+02	1.14E+02
Std Dev Biased	2.33E+00	1.89E+00	1.83E+00	1.80E+00	1.76E+00	1.57E+00	1.79E+00	1.76E+00
Ps90%/90% (+KTL) Biased	1.22E+02	1.19E+02	1.18E+02	1.18E+02	1.17E+02	1.16E+02	1.17E+02	1.19E+02
Ps90%/90% (-KTL) Biased	1.09E+02	1.08E+02	1.08E+02	1.08E+02	1.08E+02	1.07E+02	1.08E+02	1.09E+02
Un-Biased Statistics								
Average Un-Biased	1.24E+02	1.21E+02	1.19E+02	1.18E+02	1.16E+02	1.14E+02	1.15E+02	1.18E+02
Std Dev Un-Biased	1.10E+01	8.31E+00	6.04E+00	5.25E+00	4.26E+00	3.30E+00	3.71E+00	4.97E+00
Ps90%/90% (+KTL) Un-Biased	1.54E+02	1.43E+02	1.35E+02	1.32E+02	1.28E+02	1.23E+02	1.25E+02	1.31E+02
Ps90%/90% (-KTL) Un-Biased	9.36E+01	9.79E+01	1.02E+02	1.03E+02	1.04E+02	1.05E+02	1.05E+02	1.04E+02
Specification MIN	9.70E+01	9.70E+01	9.70E+01	9.70E+01	9.40E+01	9.00E+01	9.00E+01	9.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

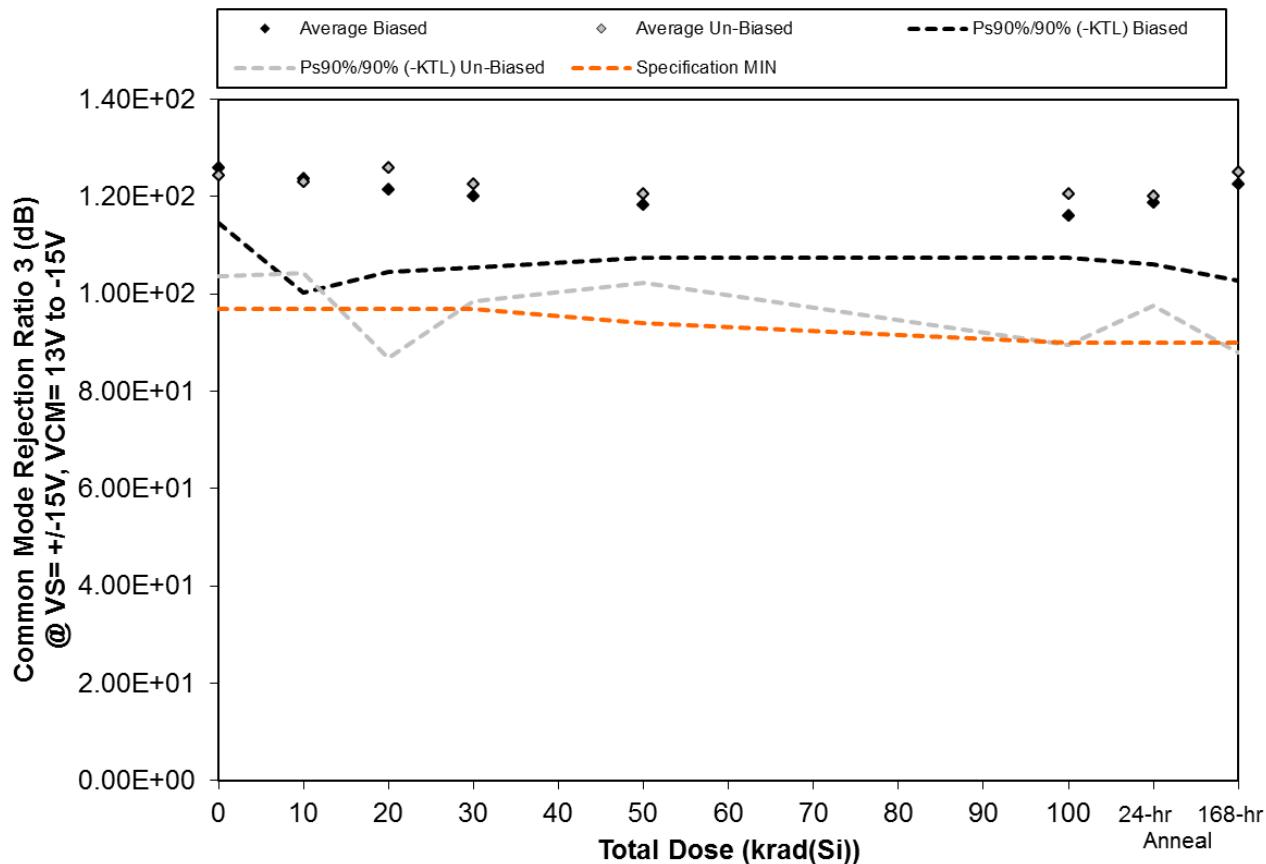


Figure 5.21. Plot of Common Mode Rejection Ratio 3 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.21. Raw data for Common Mode Rejection Ratio 3 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio 3 (dB) @ VS= +/-15V, VCM= 13V to -15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.32E+02	1.39E+02	1.32E+02	1.29E+02	1.25E+02	1.21E+02	1.27E+02	1.35E+02
260	1.24E+02	1.20E+02	1.19E+02	1.18E+02	1.17E+02	1.15E+02	1.17E+02	1.20E+02
326	1.26E+02	1.21E+02	1.19E+02	1.18E+02	1.17E+02	1.15E+02	1.17E+02	1.19E+02
328	1.28E+02	1.21E+02	1.20E+02	1.19E+02	1.18E+02	1.16E+02	1.18E+02	1.22E+02
329	1.21E+02	1.18E+02	1.17E+02	1.16E+02	1.15E+02	1.13E+02	1.15E+02	1.17E+02
330	1.16E+02	1.14E+02	1.14E+02	1.13E+02	1.12E+02	1.10E+02	1.11E+02	1.13E+02
331	1.34E+02	1.25E+02	1.23E+02	1.20E+02	1.19E+02	1.16E+02	1.17E+02	1.21E+02
334	1.30E+02	1.23E+02	1.22E+02	1.20E+02	1.18E+02	1.15E+02	1.17E+02	1.20E+02
335	1.17E+02	1.19E+02	1.21E+02	1.23E+02	1.27E+02	1.39E+02	1.32E+02	1.23E+02
344	1.26E+02	1.33E+02	1.51E+02	1.37E+02	1.28E+02	1.22E+02	1.24E+02	1.48E+02
346	1.25E+02	1.26E+02	1.26E+02	1.25E+02	1.25E+02	1.25E+02	1.25E+02	1.26E+02
Biased Statistics								
Average Biased	1.26E+02	1.24E+02	1.22E+02	1.20E+02	1.18E+02	1.16E+02	1.19E+02	1.23E+02
Std Dev Biased	4.09E+00	8.58E+00	6.16E+00	5.34E+00	3.94E+00	3.12E+00	4.60E+00	7.22E+00
Ps90%/90% (+KTL) Biased	1.37E+02	1.47E+02	1.38E+02	1.35E+02	1.29E+02	1.25E+02	1.31E+02	1.42E+02
Ps90%/90% (-KTL) Biased	1.15E+02	1.00E+02	1.05E+02	1.05E+02	1.07E+02	1.08E+02	1.06E+02	1.03E+02
Un-Biased Statistics								
Average Un-Biased	1.24E+02	1.23E+02	1.26E+02	1.23E+02	1.21E+02	1.21E+02	1.20E+02	1.25E+02
Std Dev Un-Biased	7.60E+00	6.79E+00	1.43E+01	8.75E+00	6.68E+00	1.13E+01	8.24E+00	1.35E+01
Ps90%/90% (+KTL) Un-Biased	1.45E+02	1.42E+02	1.65E+02	1.47E+02	1.39E+02	1.51E+02	1.43E+02	1.62E+02
Ps90%/90% (-KTL) Un-Biased	1.04E+02	1.04E+02	8.68E+01	9.86E+01	1.02E+02	8.96E+01	9.76E+01	8.80E+01
Specification MIN	9.70E+01	9.70E+01	9.70E+01	9.70E+01	9.40E+01	9.00E+01	9.00E+01	9.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

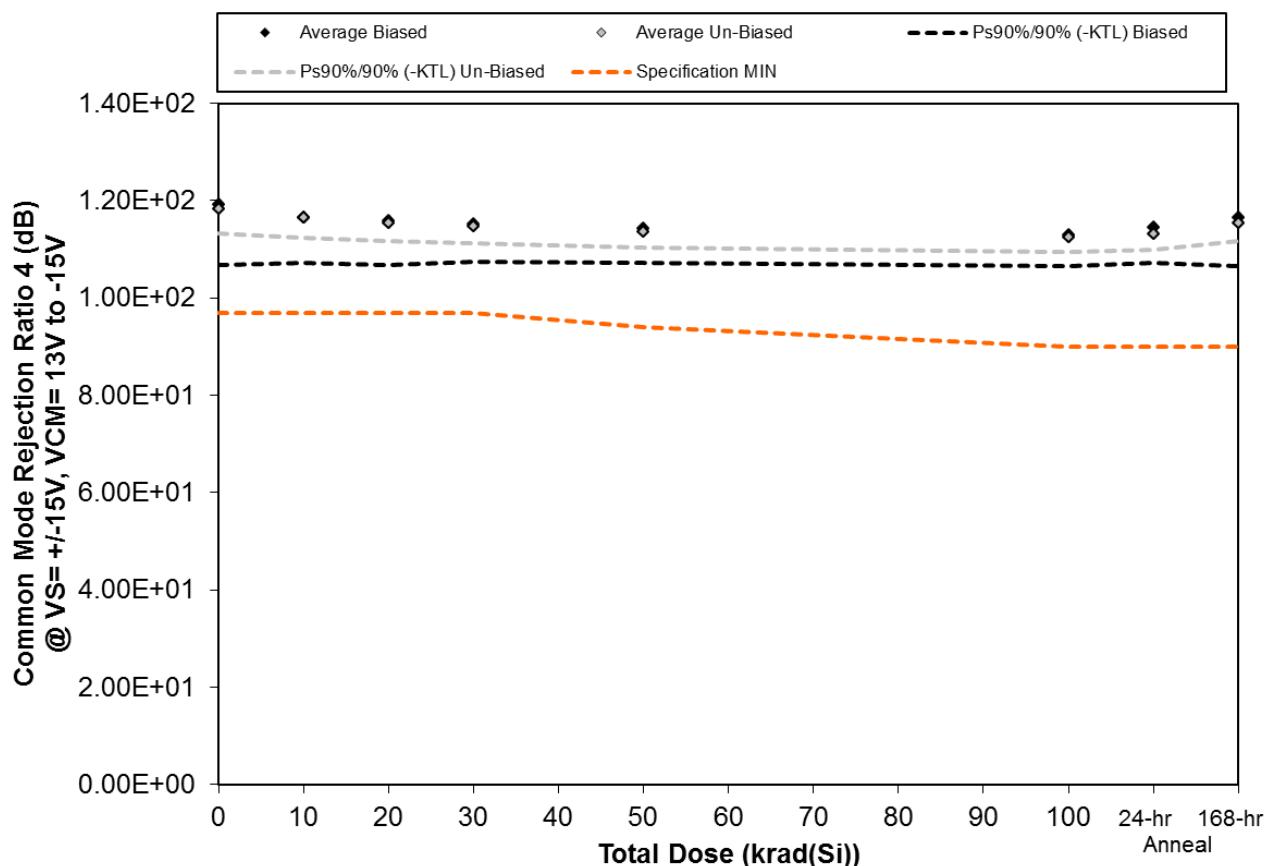


Figure 5.22. Plot of Common Mode Rejection Ratio 4 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.22. Raw data for Common Mode Rejection Ratio 4 (dB) @ VS= +/-15V, VCM= 13V to -15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Common Mode Rejection Ratio 4 (dB) @ VS= +/-15V, VCM= 13V to -15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.16E+02	1.14E+02	1.14E+02	1.13E+02	1.12E+02	1.11E+02	1.13E+02	1.14E+02
260	1.15E+02	1.13E+02	1.13E+02	1.13E+02	1.12E+02	1.11E+02	1.12E+02	1.13E+02
326	1.17E+02	1.16E+02	1.15E+02	1.14E+02	1.14E+02	1.12E+02	1.14E+02	1.15E+02
328	1.22E+02	1.18E+02	1.17E+02	1.16E+02	1.16E+02	1.14E+02	1.16E+02	1.19E+02
329	1.26E+02	1.22E+02	1.21E+02	1.20E+02	1.18E+02	1.17E+02	1.18E+02	1.22E+02
330	1.20E+02	1.18E+02	1.17E+02	1.16E+02	1.14E+02	1.12E+02	1.13E+02	1.16E+02
331	1.15E+02	1.14E+02	1.13E+02	1.13E+02	1.12E+02	1.11E+02	1.11E+02	1.13E+02
334	1.19E+02	1.17E+02	1.16E+02	1.15E+02	1.14E+02	1.13E+02	1.14E+02	1.16E+02
335	1.19E+02	1.18E+02	1.16E+02	1.16E+02	1.15E+02	1.14E+02	1.14E+02	1.17E+02
344	1.19E+02	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.13E+02	1.13E+02	1.15E+02
346	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02	1.14E+02
Biased Statistics								
Average Biased	1.19E+02	1.17E+02	1.16E+02	1.15E+02	1.14E+02	1.13E+02	1.14E+02	1.16E+02
Std Dev Biased	4.57E+00	3.47E+00	3.38E+00	2.83E+00	2.63E+00	2.37E+00	2.64E+00	3.66E+00
Ps90%/90% (+KTL) Biased	1.32E+02	1.26E+02	1.25E+02	1.23E+02	1.22E+02	1.19E+02	1.22E+02	1.27E+02
Ps90%/90% (-KTL) Biased	1.07E+02	1.07E+02	1.07E+02	1.07E+02	1.07E+02	1.06E+02	1.07E+02	1.06E+02
Un-Biased Statistics								
Average Un-Biased	1.18E+02	1.16E+02	1.15E+02	1.15E+02	1.14E+02	1.12E+02	1.13E+02	1.15E+02
Std Dev Un-Biased	1.88E+00	1.50E+00	1.36E+00	1.30E+00	1.20E+00	1.06E+00	1.14E+00	1.31E+00
Ps90%/90% (+KTL) Un-Biased	1.23E+02	1.21E+02	1.19E+02	1.18E+02	1.17E+02	1.15E+02	1.16E+02	1.19E+02
Ps90%/90% (-KTL) Un-Biased	1.13E+02	1.12E+02	1.12E+02	1.11E+02	1.10E+02	1.09E+02	1.10E+02	1.12E+02
Specification MIN	9.70E+01	9.70E+01	9.70E+01	9.70E+01	9.40E+01	9.00E+01	9.00E+01	9.00E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

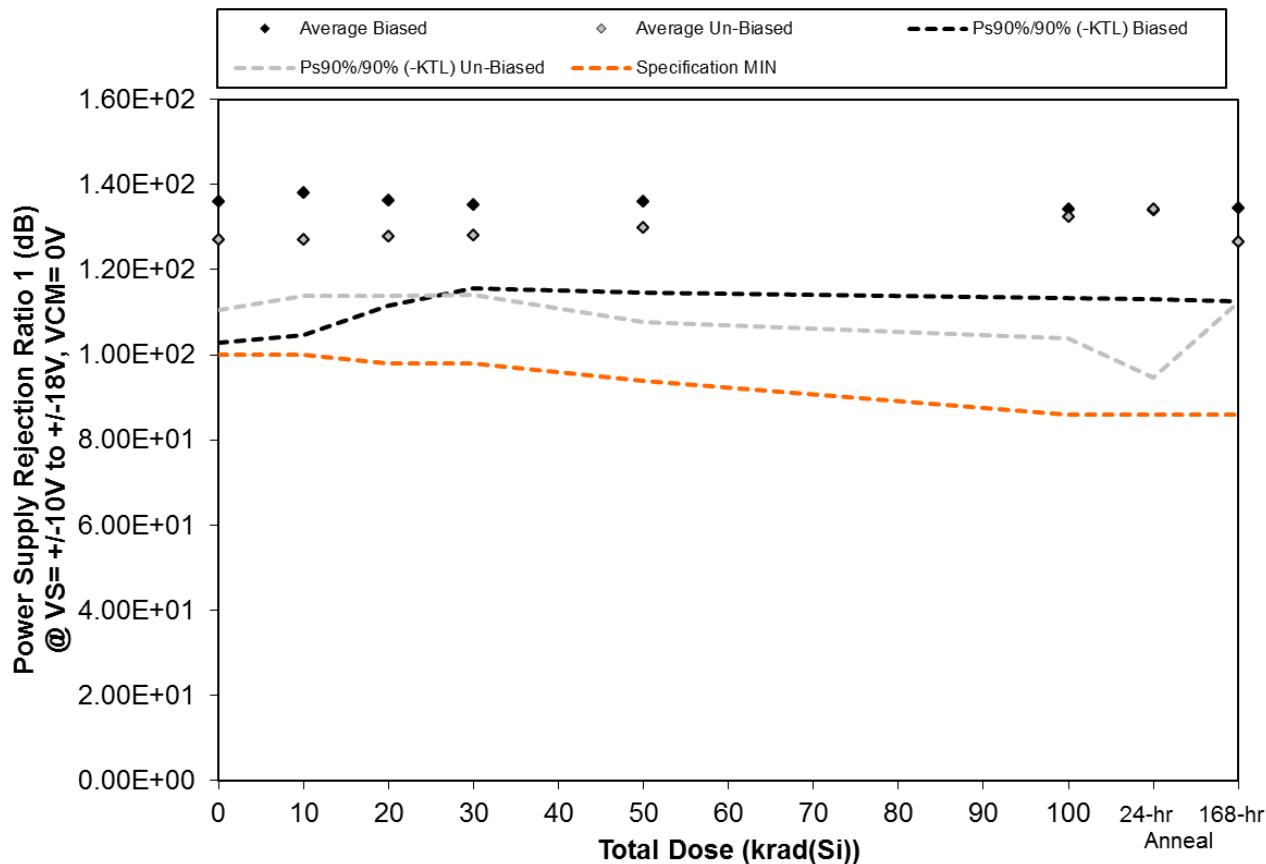


Figure 5.23. Plot of Power Supply Rejection Ratio 1 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.23. Raw data for Power Supply Rejection Ratio 1 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio 1 (dB) @ VS= +/-10V to +/-18V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.22E+02	1.23E+02	1.24E+02	1.24E+02	1.24E+02	1.26E+02	1.26E+02	1.22E+02
260	1.32E+02	1.36E+02	1.38E+02	1.38E+02	1.46E+02	1.39E+02	1.46E+02	1.38E+02
326	1.46E+02	1.54E+02	1.47E+02	1.42E+02	1.40E+02	1.30E+02	1.31E+02	1.40E+02
328	1.51E+02	1.46E+02	1.41E+02	1.40E+02	1.36E+02	1.30E+02	1.31E+02	1.41E+02
329	1.29E+02	1.31E+02	1.32E+02	1.32E+02	1.34E+02	1.45E+02	1.36E+02	1.31E+02
330	1.35E+02	1.32E+02	1.31E+02	1.29E+02	1.27E+02	1.23E+02	1.23E+02	1.28E+02
331	1.28E+02	1.29E+02	1.30E+02	1.31E+02	1.33E+02	1.48E+02	1.42E+02	1.28E+02
334	1.21E+02	1.23E+02	1.23E+02	1.23E+02	1.24E+02	1.28E+02	1.25E+02	1.22E+02
335	1.31E+02	1.31E+02	1.33E+02	1.34E+02	1.43E+02	1.37E+02	1.56E+02	1.34E+02
344	1.21E+02	1.21E+02	1.22E+02	1.22E+02	1.23E+02	1.25E+02	1.24E+02	1.21E+02
346	1.34E+02	1.34E+02	1.35E+02	1.35E+02	1.34E+02	1.34E+02	1.35E+02	1.34E+02
Biased Statistics								
Average Biased	1.36E+02	1.38E+02	1.36E+02	1.35E+02	1.36E+02	1.34E+02	1.34E+02	1.34E+02
Std Dev Biased	1.21E+01	1.22E+01	8.98E+00	7.18E+00	7.81E+00	7.56E+00	7.56E+00	7.93E+00
Ps90%/90% (+KTL) Biased	1.69E+02	1.72E+02	1.61E+02	1.55E+02	1.57E+02	1.55E+02	1.55E+02	1.56E+02
Ps90%/90% (-KTL) Biased	1.03E+02	1.05E+02	1.12E+02	1.16E+02	1.15E+02	1.13E+02	1.13E+02	1.13E+02
Un-Biased Statistics								
Average Un-Biased	1.27E+02	1.27E+02	1.28E+02	1.28E+02	1.30E+02	1.32E+02	1.34E+02	1.27E+02
Std Dev Un-Biased	6.01E+00	4.88E+00	5.14E+00	5.03E+00	8.14E+00	1.04E+01	1.44E+01	5.26E+00
Ps90%/90% (+KTL) Un-Biased	1.43E+02	1.41E+02	1.42E+02	1.42E+02	1.52E+02	1.61E+02	1.73E+02	1.41E+02
Ps90%/90% (-KTL) Un-Biased	1.11E+02	1.14E+02	1.14E+02	1.14E+02	1.08E+02	1.04E+02	9.46E+01	1.12E+02
Specification MIN	1.00E+02	1.00E+02	9.80E+01	9.80E+01	9.40E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

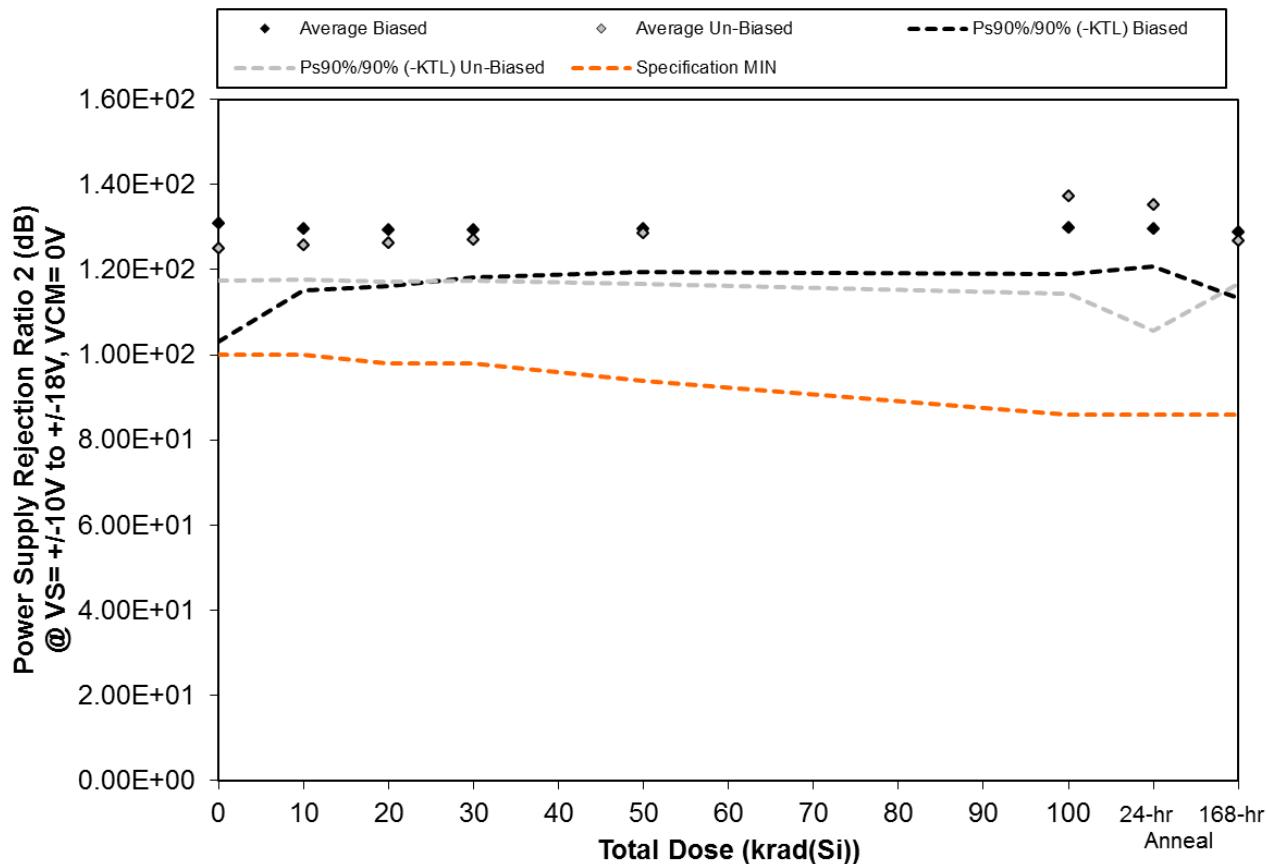


Figure 5.24. Plot of Power Supply Rejection Ratio 2 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.24. Raw data for Power Supply Rejection Ratio 2 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio 2 (dB) @ VS= +/-10V to +/-18V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.26E+02	1.27E+02	1.27E+02	1.28E+02	1.29E+02	1.35E+02	1.33E+02	1.28E+02
260	1.25E+02	1.26E+02	1.26E+02	1.26E+02	1.28E+02	1.31E+02	1.29E+02	1.25E+02
326	1.25E+02	1.27E+02	1.27E+02	1.27E+02	1.28E+02	1.31E+02	1.30E+02	1.25E+02
328	1.48E+02	1.39E+02	1.38E+02	1.36E+02	1.36E+02	1.29E+02	1.31E+02	1.39E+02
329	1.31E+02	1.30E+02	1.29E+02	1.29E+02	1.27E+02	1.24E+02	1.24E+02	1.27E+02
330	1.25E+02	1.26E+02	1.26E+02	1.28E+02	1.29E+02	1.37E+02	1.32E+02	1.27E+02
331	1.29E+02	1.29E+02	1.31E+02	1.31E+02	1.33E+02	1.45E+02	1.52E+02	1.32E+02
334	1.27E+02	1.27E+02	1.29E+02	1.29E+02	1.33E+02	1.46E+02	1.39E+02	1.28E+02
335	1.23E+02	1.23E+02	1.24E+02	1.24E+02	1.25E+02	1.32E+02	1.29E+02	1.26E+02
344	1.22E+02	1.22E+02	1.22E+02	1.23E+02	1.23E+02	1.26E+02	1.24E+02	1.22E+02
346	1.29E+02	1.28E+02	1.28E+02	1.29E+02	1.28E+02	1.28E+02	1.28E+02	1.28E+02
Biased Statistics								
Average Biased	1.31E+02	1.30E+02	1.29E+02	1.29E+02	1.30E+02	1.30E+02	1.30E+02	1.29E+02
Std Dev Biased	1.01E+01	5.35E+00	4.82E+00	4.06E+00	3.74E+00	3.97E+00	3.21E+00	5.62E+00
Ps90%/90% (+KTL) Biased	1.59E+02	1.44E+02	1.43E+02	1.40E+02	1.40E+02	1.41E+02	1.38E+02	1.44E+02
Ps90%/90% (-KTL) Biased	1.03E+02	1.15E+02	1.16E+02	1.18E+02	1.19E+02	1.19E+02	1.21E+02	1.13E+02
Un-Biased Statistics								
Average Un-Biased	1.25E+02	1.26E+02	1.26E+02	1.27E+02	1.29E+02	1.37E+02	1.35E+02	1.27E+02
Std Dev Un-Biased	2.79E+00	2.93E+00	3.37E+00	3.52E+00	4.37E+00	8.35E+00	1.08E+01	3.67E+00
Ps90%/90% (+KTL) Un-Biased	1.33E+02	1.34E+02	1.36E+02	1.37E+02	1.41E+02	1.60E+02	1.65E+02	1.37E+02
Ps90%/90% (-KTL) Un-Biased	1.17E+02	1.18E+02	1.17E+02	1.17E+02	1.17E+02	1.14E+02	1.06E+02	1.17E+02
Specification MIN	1.00E+02	1.00E+02	9.80E+01	9.80E+01	9.40E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

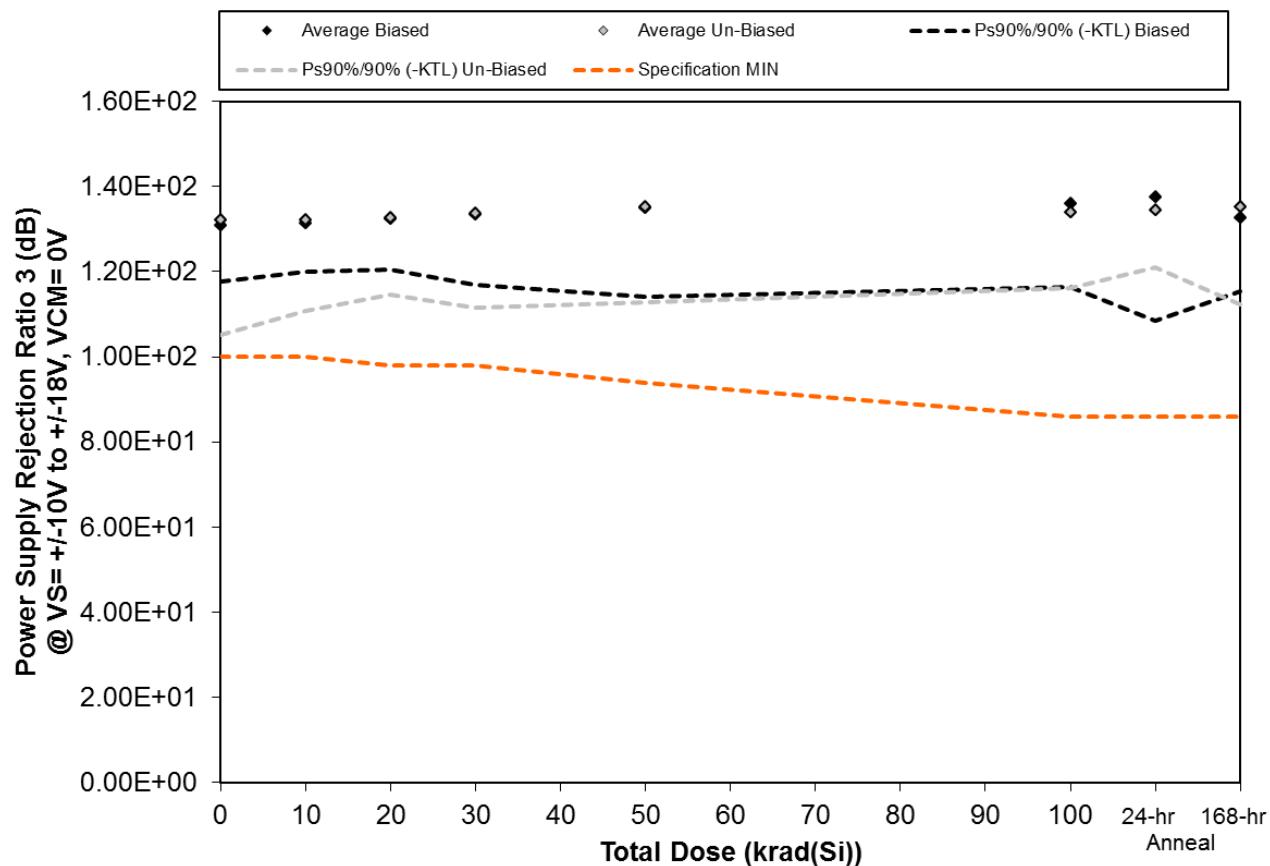


Figure 5.25. Plot of Power Supply Rejection Ratio 3 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.25. Raw data for Power Supply Rejection Ratio 3 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio 3 (dB) @ VS= +/-10V to +/-18V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.26E+02	1.27E+02	1.28E+02	1.29E+02	1.30E+02	1.37E+02	1.33E+02	1.27E+02
260	1.26E+02	1.27E+02	1.28E+02	1.28E+02	1.30E+02	1.36E+02	1.33E+02	1.27E+02
326	1.38E+02	1.35E+02	1.34E+02	1.32E+02	1.30E+02	1.25E+02	1.26E+02	1.31E+02
328	1.32E+02	1.32E+02	1.34E+02	1.36E+02	1.39E+02	1.45E+02	1.54E+02	1.35E+02
329	1.33E+02	1.36E+02	1.38E+02	1.43E+02	1.47E+02	1.37E+02	1.41E+02	1.42E+02
330	1.33E+02	1.37E+02	1.41E+02	1.46E+02	1.46E+02	1.31E+02	1.35E+02	1.48E+02
331	1.49E+02	1.43E+02	1.37E+02	1.35E+02	1.31E+02	1.25E+02	1.26E+02	1.35E+02
334	1.30E+02	1.31E+02	1.33E+02	1.33E+02	1.42E+02	1.35E+02	1.39E+02	1.36E+02
335	1.25E+02	1.25E+02	1.26E+02	1.27E+02	1.29E+02	1.43E+02	1.37E+02	1.30E+02
344	1.25E+02	1.25E+02	1.26E+02	1.27E+02	1.28E+02	1.37E+02	1.35E+02	1.27E+02
346	1.24E+02	1.24E+02	1.24E+02	1.24E+02	1.24E+02	1.24E+02	1.24E+02	1.24E+02
Biased Statistics								
Average Biased	1.31E+02	1.31E+02	1.32E+02	1.34E+02	1.35E+02	1.36E+02	1.37E+02	1.33E+02
Std Dev Biased	4.81E+00	4.22E+00	4.36E+00	6.09E+00	7.62E+00	7.13E+00	1.06E+01	6.24E+00
Ps90%/90% (+KTL) Biased	1.44E+02	1.43E+02	1.44E+02	1.50E+02	1.56E+02	1.56E+02	1.66E+02	1.50E+02
Ps90%/90% (-KTL) Biased	1.18E+02	1.20E+02	1.20E+02	1.17E+02	1.14E+02	1.16E+02	1.08E+02	1.15E+02
Un-Biased Statistics								
Average Un-Biased	1.32E+02	1.32E+02	1.33E+02	1.34E+02	1.35E+02	1.34E+02	1.35E+02	1.35E+02
Std Dev Un-Biased	9.88E+00	7.78E+00	6.56E+00	8.06E+00	8.21E+00	6.55E+00	4.92E+00	8.32E+00
Ps90%/90% (+KTL) Un-Biased	1.59E+02	1.54E+02	1.51E+02	1.56E+02	1.58E+02	1.52E+02	1.48E+02	1.58E+02
Ps90%/90% (-KTL) Un-Biased	1.05E+02	1.11E+02	1.15E+02	1.11E+02	1.13E+02	1.16E+02	1.21E+02	1.12E+02
Specification MIN	1.00E+02	1.00E+02	9.80E+01	9.80E+01	9.40E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

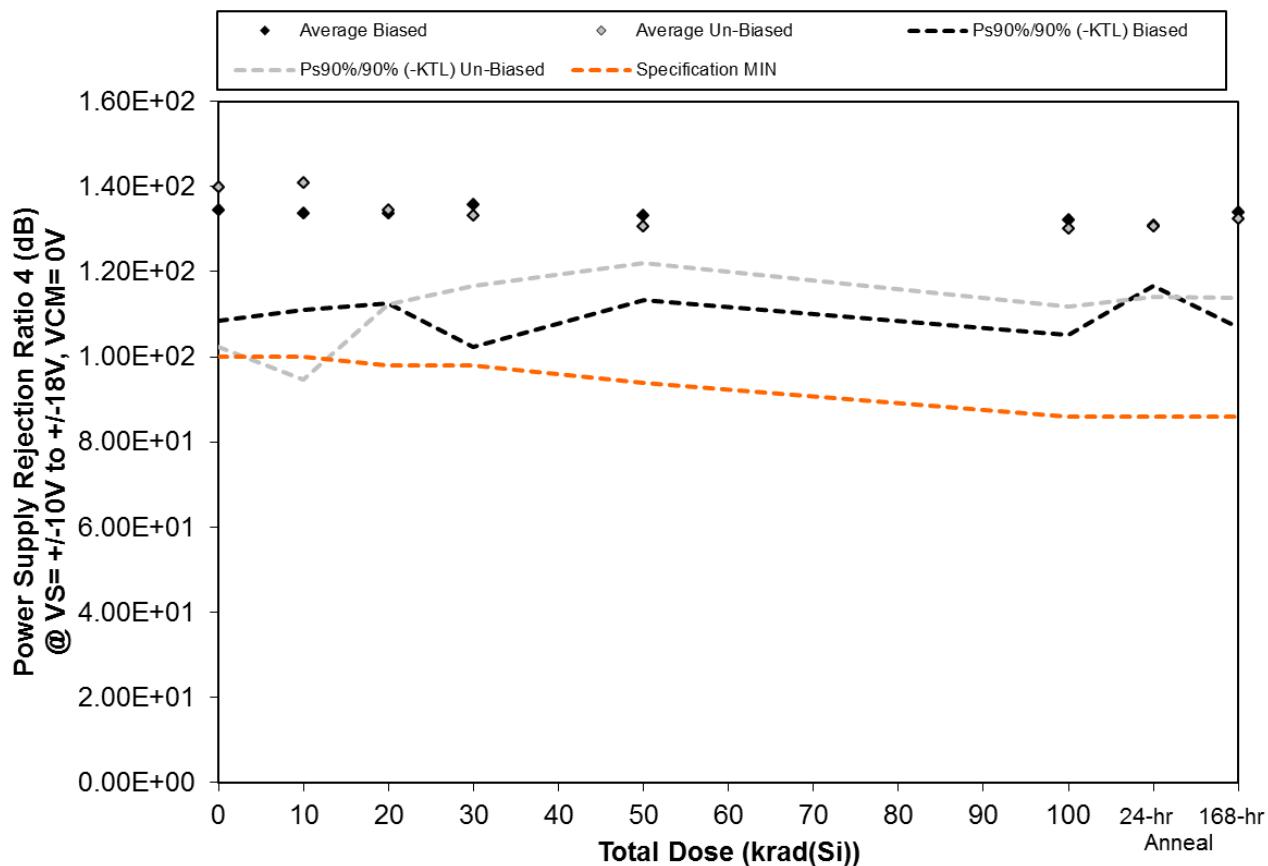


Figure 5.26. Plot of Power Supply Rejection Ratio 4 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.26. Raw data for Power Supply Rejection Ratio 4 (dB) @ VS= +/-10V to +/-18V, VCM= 0V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Power Supply Rejection Ratio 4 (dB) @ VS= +/-10V to +/-18V, VCM= 0V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.47E+02	1.38E+02	1.37E+02	1.35E+02	1.33E+02	1.28E+02	1.30E+02	1.38E+02
260	1.28E+02	1.29E+02	1.31E+02	1.31E+02	1.35E+02	1.49E+02	1.38E+02	1.29E+02
326	1.37E+02	1.33E+02	1.33E+02	1.32E+02	1.30E+02	1.25E+02	1.26E+02	1.30E+02
328	1.38E+02	1.45E+02	1.44E+02	1.56E+02	1.44E+02	1.31E+02	1.34E+02	1.49E+02
329	1.23E+02	1.23E+02	1.24E+02	1.24E+02	1.24E+02	1.27E+02	1.26E+02	1.24E+02
330	1.49E+02	1.66E+02	1.42E+02	1.39E+02	1.33E+02	1.28E+02	1.28E+02	1.36E+02
331	1.47E+02	1.41E+02	1.36E+02	1.35E+02	1.31E+02	1.27E+02	1.29E+02	1.38E+02
334	1.23E+02	1.23E+02	1.24E+02	1.24E+02	1.25E+02	1.29E+02	1.26E+02	1.22E+02
335	1.28E+02	1.28E+02	1.29E+02	1.30E+02	1.31E+02	1.42E+02	1.41E+02	1.28E+02
344	1.53E+02	1.46E+02	1.42E+02	1.37E+02	1.33E+02	1.25E+02	1.29E+02	1.36E+02
346	1.26E+02	1.26E+02	1.27E+02	1.27E+02	1.27E+02	1.26E+02	1.27E+02	1.26E+02
Biased Statistics								
Average Biased	1.35E+02	1.34E+02	1.34E+02	1.36E+02	1.33E+02	1.32E+02	1.31E+02	1.34E+02
Std Dev Biased	9.48E+00	8.25E+00	7.66E+00	1.21E+01	7.24E+00	9.78E+00	5.17E+00	9.85E+00
Ps90%/90% (+KTL) Biased	1.61E+02	1.56E+02	1.55E+02	1.69E+02	1.53E+02	1.59E+02	1.45E+02	1.61E+02
Ps90%/90% (-KTL) Biased	1.09E+02	1.11E+02	1.13E+02	1.02E+02	1.13E+02	1.05E+02	1.17E+02	1.07E+02
Un-Biased Statistics								
Average Un-Biased	1.40E+02	1.41E+02	1.34E+02	1.33E+02	1.31E+02	1.30E+02	1.31E+02	1.32E+02
Std Dev Un-Biased	1.37E+01	1.68E+01	8.06E+00	6.03E+00	3.11E+00	6.64E+00	6.05E+00	6.76E+00
Ps90%/90% (+KTL) Un-Biased	1.77E+02	1.87E+02	1.57E+02	1.50E+02	1.39E+02	1.48E+02	1.47E+02	1.51E+02
Ps90%/90% (-KTL) Un-Biased	1.02E+02	9.47E+01	1.12E+02	1.17E+02	1.22E+02	1.12E+02	1.14E+02	1.14E+02
Specification MIN	1.00E+02	1.00E+02	9.80E+01	9.80E+01	9.40E+01	8.60E+01	8.60E+01	8.60E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

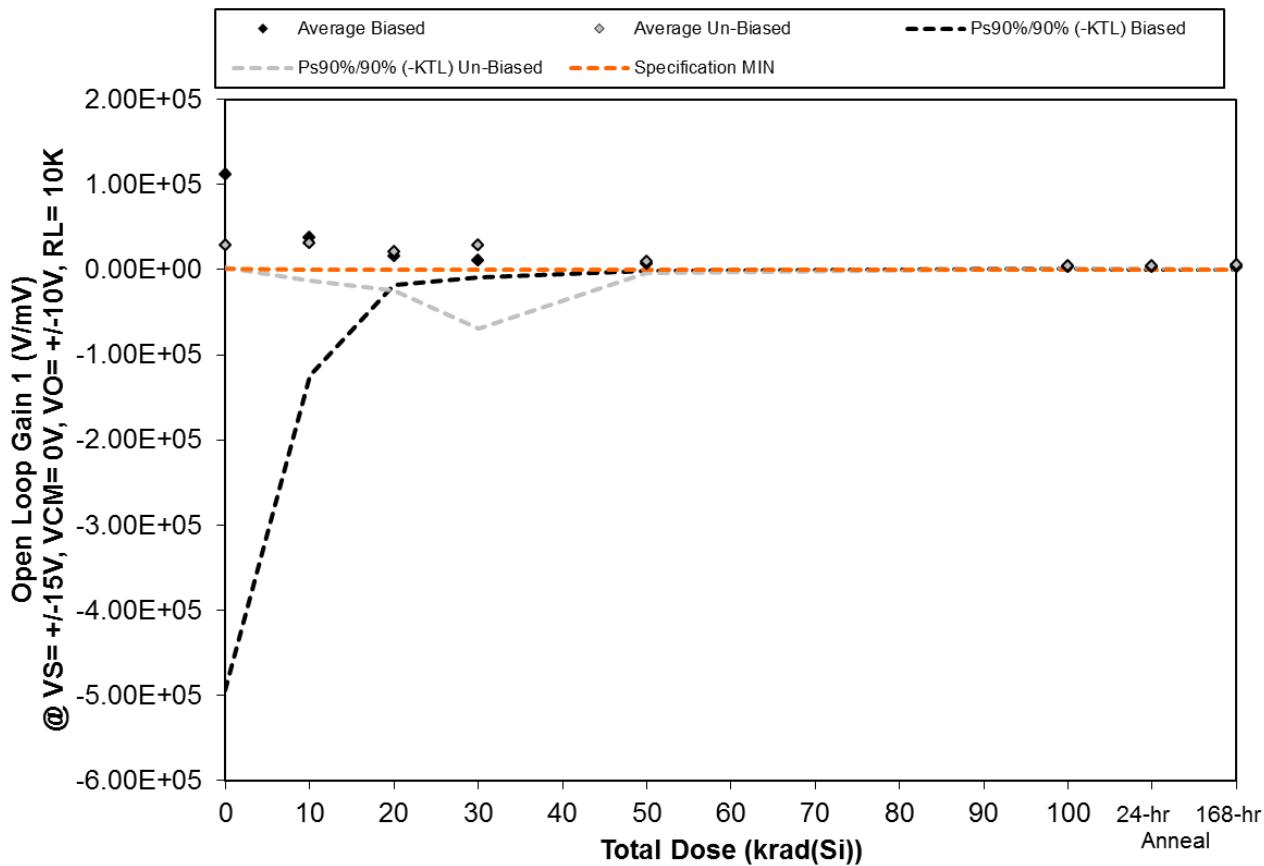


Figure 5.27. Plot of Open Loop Gain 1 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.27. Raw data for Open Loop Gain 1 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Open Loop Gain 1 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	2.02E+04	1.64E+04	1.58E+04	8.29E+03	6.30E+03	3.59E+03	3.09E+03	2.92E+03	
260	1.34E+04	1.17E+04	1.17E+04	7.06E+03	5.52E+03	3.10E+03	2.46E+03	2.56E+03	
326	8.87E+03	8.75E+03	7.06E+03	6.40E+03	4.62E+03	2.49E+03	2.30E+03	2.22E+03	
328	1.10E+04	9.46E+03	9.53E+03	7.17E+03	6.03E+03	3.09E+03	2.59E+03	2.44E+03	
329	5.08E+05	1.43E+05	3.79E+04	2.33E+04	1.24E+04	4.51E+03	4.46E+03	4.38E+03	
330	1.36E+04	1.26E+04	8.61E+03	8.09E+03	7.11E+03	2.60E+03	2.95E+03	3.31E+03	
331	2.88E+04	3.30E+04	1.62E+04	2.01E+04	9.58E+03	3.61E+03	3.82E+03	4.36E+03	
334	3.72E+04	5.61E+04	5.07E+04	9.30E+04	1.89E+04	5.58E+03	5.43E+03	7.89E+03	
335	3.72E+04	2.90E+04	1.51E+04	1.56E+04	7.78E+03	4.51E+03	4.80E+03	5.47E+03	
344	2.64E+04	2.30E+04	1.61E+04	9.39E+03	7.33E+03	4.09E+03	4.22E+03	5.04E+03	
346	1.71E+04	1.40E+04	1.69E+04	1.48E+04	1.49E+04	1.51E+04	1.41E+04	1.37E+04	
Biased Statistics									
Average Biased		1.12E+05	3.79E+04	1.64E+04	1.04E+04	6.98E+03	3.36E+03	2.98E+03	2.91E+03
Std Dev Biased		2.21E+05	5.89E+04	1.25E+04	7.23E+03	3.11E+03	7.53E+02	8.82E+02	8.63E+02
Ps90%/90% (+KTL) Biased		7.19E+05	1.99E+05	5.05E+04	3.03E+04	1.55E+04	5.42E+03	5.40E+03	5.27E+03
Ps90%/90% (-KTL) Biased		-4.94E+05	-1.24E+05	-1.78E+04	-9.37E+03	-1.56E+03	1.29E+03	5.61E+02	5.41E+02
Un-Biased Statistics									
Average Un-Biased		2.86E+04	3.08E+04	2.14E+04	2.92E+04	1.01E+04	4.08E+03	4.24E+03	5.22E+03
Std Dev Un-Biased		9.71E+03	1.61E+04	1.67E+04	3.60E+04	4.99E+03	1.10E+03	9.43E+02	1.71E+03
Ps90%/90% (+KTL) Un-Biased		5.52E+04	7.50E+04	6.72E+04	1.28E+05	2.38E+04	7.10E+03	6.83E+03	9.89E+03
Ps90%/90% (-KTL) Un-Biased		1.99E+03	-1.34E+04	-2.45E+04	-6.94E+04	-3.53E+03	1.05E+03	1.66E+03	5.37E+02
Specification MIN		1.20E+03	5.00E+02	2.00E+02	2.00E+02	1.00E+02	5.00E+01	5.00E+01	5.00E+01
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

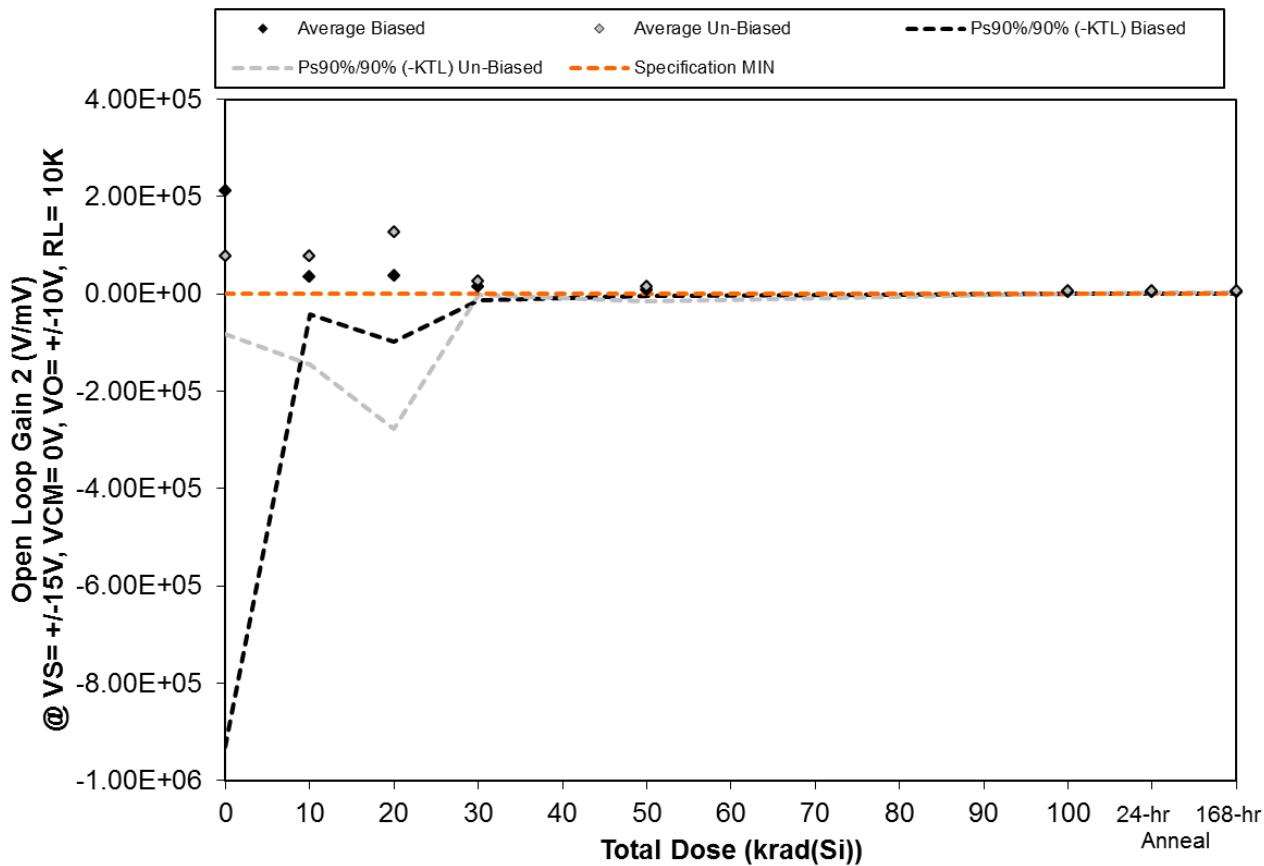


Figure 5.28. Plot of Open Loop Gain 2 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.28. Raw data for Open Loop Gain 2 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Open Loop Gain 2 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	9.58E+05	8.18E+04	1.25E+05	3.13E+04	1.50E+04	5.18E+03	4.20E+03	4.30E+03	
260	2.28E+04	2.52E+04	1.93E+04	1.15E+04	5.73E+03	3.02E+03	2.87E+03	2.81E+03	
326	1.09E+04	9.63E+03	7.32E+03	6.09E+03	4.69E+03	2.44E+03	2.43E+03	2.39E+03	
328	5.12E+04	3.37E+04	1.98E+04	1.37E+04	8.58E+03	4.81E+03	4.56E+03	4.41E+03	
329	1.89E+04	2.26E+04	1.34E+04	1.06E+04	5.85E+03	3.00E+03	2.74E+03	2.71E+03	
330	2.32E+04	2.65E+04	1.93E+04	1.18E+04	6.58E+03	3.20E+03	4.02E+03	5.29E+03	
331	1.46E+05	3.91E+04	3.28E+04	1.92E+04	9.19E+03	4.05E+03	4.58E+03	7.25E+03	
334	4.54E+04	7.34E+04	1.60E+05	3.81E+04	1.59E+04	6.47E+03	7.18E+03	8.29E+03	
335	1.37E+05	2.20E+05	4.88E+04	2.67E+04	1.15E+04	6.14E+03	5.45E+03	6.94E+03	
344	3.94E+04	3.07E+04	3.70E+05	3.10E+04	3.46E+04	5.72E+03	5.05E+03	8.27E+03	
346	4.66E+04	3.77E+04	4.58E+04	4.00E+04	6.13E+04	4.37E+04	3.93E+04	6.07E+04	
Biased Statistics									
Average Biased		2.12E+05	3.46E+04	3.69E+04	1.46E+04	7.96E+03	3.69E+03	3.36E+03	3.32E+03
Std Dev Biased		4.17E+05	2.78E+04	4.93E+04	9.73E+03	4.17E+03	1.22E+03	9.53E+02	9.55E+02
Ps90%/90% (+KTL) Biased		1.36E+06	1.11E+05	1.72E+05	4.13E+04	1.94E+04	7.03E+03	5.97E+03	5.94E+03
Ps90%/90% (-KTL) Biased		-9.31E+05	-4.16E+04	-9.82E+04	-1.20E+04	-3.46E+03	3.41E+02	7.45E+02	7.04E+02
Un-Biased Statistics									
Average Un-Biased		7.82E+04	7.80E+04	1.26E+05	2.54E+04	1.55E+04	5.11E+03	5.26E+03	7.21E+03
Std Dev Un-Biased		5.84E+04	8.17E+04	1.47E+05	1.02E+04	1.12E+04	1.42E+03	1.20E+03	1.23E+03
Ps90%/90% (+KTL) Un-Biased		2.38E+05	3.02E+05	5.30E+05	5.34E+04	4.63E+04	9.00E+03	8.55E+03	1.06E+04
Ps90%/90% (-KTL) Un-Biased		-8.20E+04	-1.46E+05	-2.78E+05	-2.71E+03	-1.52E+04	1.23E+03	1.96E+03	3.84E+03
Specification MIN		1.20E+03	5.00E+02	2.00E+02	2.00E+02	1.00E+02	5.00E+01	5.00E+01	5.00E+01
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

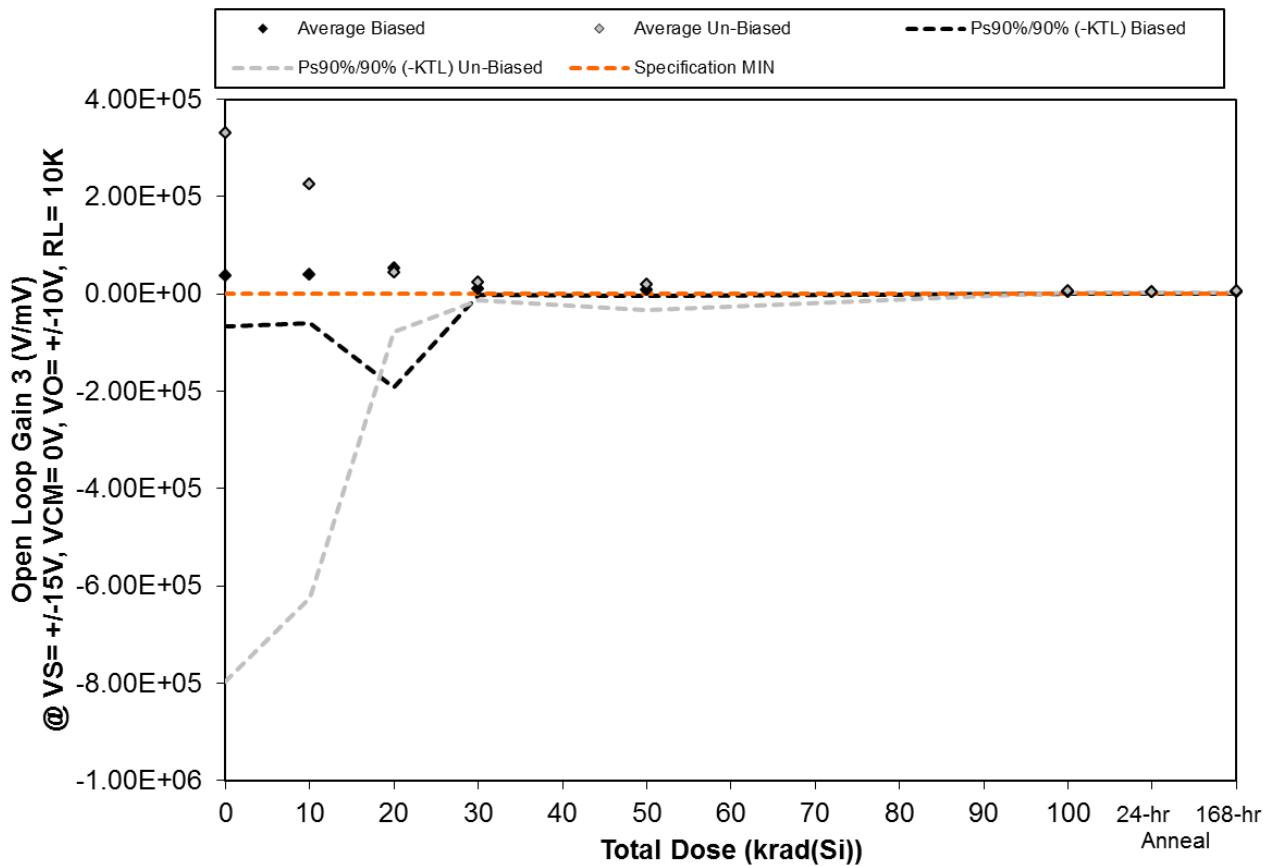


Figure 5.29. Plot of Open Loop Gain 3 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.29. Raw data for Open Loop Gain 3 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Open Loop Gain 3 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	9.95E+04	8.70E+04	2.13E+05	1.78E+04	1.32E+04	4.47E+03	4.02E+03	4.21E+03	
260	1.64E+04	1.62E+04	1.29E+04	7.99E+03	5.35E+03	2.82E+03	2.74E+03	2.69E+03	
326	1.31E+04	1.47E+04	1.20E+04	8.87E+03	5.23E+03	2.73E+03	2.44E+03	2.36E+03	
328	5.32E+04	7.13E+04	2.14E+04	1.68E+04	1.22E+04	4.22E+03	3.92E+03	4.46E+03	
329	1.08E+04	1.11E+04	9.58E+03	7.30E+03	5.31E+03	2.84E+03	2.32E+03	2.31E+03	
330	2.66E+04	1.59E+04	1.41E+04	1.07E+04	6.84E+03	4.23E+03	3.76E+03	4.35E+03	
331	6.88E+04	3.41E+04	1.80E+04	1.89E+04	9.54E+03	4.33E+03	3.97E+03	5.67E+03	
334	5.75E+05	2.03E+05	2.97E+04	2.68E+04	1.63E+04	6.15E+03	5.60E+03	6.73E+03	
335	9.41E+05	7.63E+05	3.83E+04	1.60E+04	1.06E+04	5.34E+03	5.16E+03	6.55E+03	
344	4.16E+04	1.10E+05	1.23E+05	4.57E+04	5.17E+04	5.48E+03	4.27E+03	7.39E+03	
346	1.65E+04	1.80E+04	1.79E+04	1.81E+04	1.72E+04	1.69E+04	1.84E+04	1.81E+04	
Biased Statistics									
Average Biased		3.86E+04	4.01E+04	5.38E+04	1.18E+04	8.26E+03	3.42E+03	3.09E+03	3.20E+03
Std Dev Biased		3.82E+04	3.62E+04	8.92E+04	5.13E+03	4.08E+03	8.54E+02	8.18E+02	1.04E+03
Ps90%/90% (+KTL) Biased		1.43E+05	1.39E+05	2.99E+05	2.58E+04	1.94E+04	5.76E+03	5.33E+03	6.06E+03
Ps90%/90% (-KTL) Biased		-6.61E+04	-5.92E+04	-1.91E+05	-2.29E+03	-2.92E+03	1.08E+03	8.45E+02	3.41E+02
Un-Biased Statistics									
Average Un-Biased		3.31E+05	2.25E+05	4.47E+04	2.36E+04	1.90E+04	5.11E+03	4.55E+03	6.14E+03
Std Dev Un-Biased		4.11E+05	3.10E+05	4.50E+04	1.36E+04	1.86E+04	8.16E+02	7.92E+02	1.17E+03
Ps90%/90% (+KTL) Un-Biased		1.46E+06	1.07E+06	1.68E+05	6.10E+04	7.00E+04	7.35E+03	6.72E+03	9.35E+03
Ps90%/90% (-KTL) Un-Biased		-7.97E+05	-6.24E+05	-7.87E+04	-1.38E+04	-3.20E+04	2.87E+03	2.38E+03	2.92E+03
Specification MIN		1.20E+03	5.00E+02	2.00E+02	2.00E+02	1.00E+02	5.00E+01	5.00E+01	5.00E+01
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

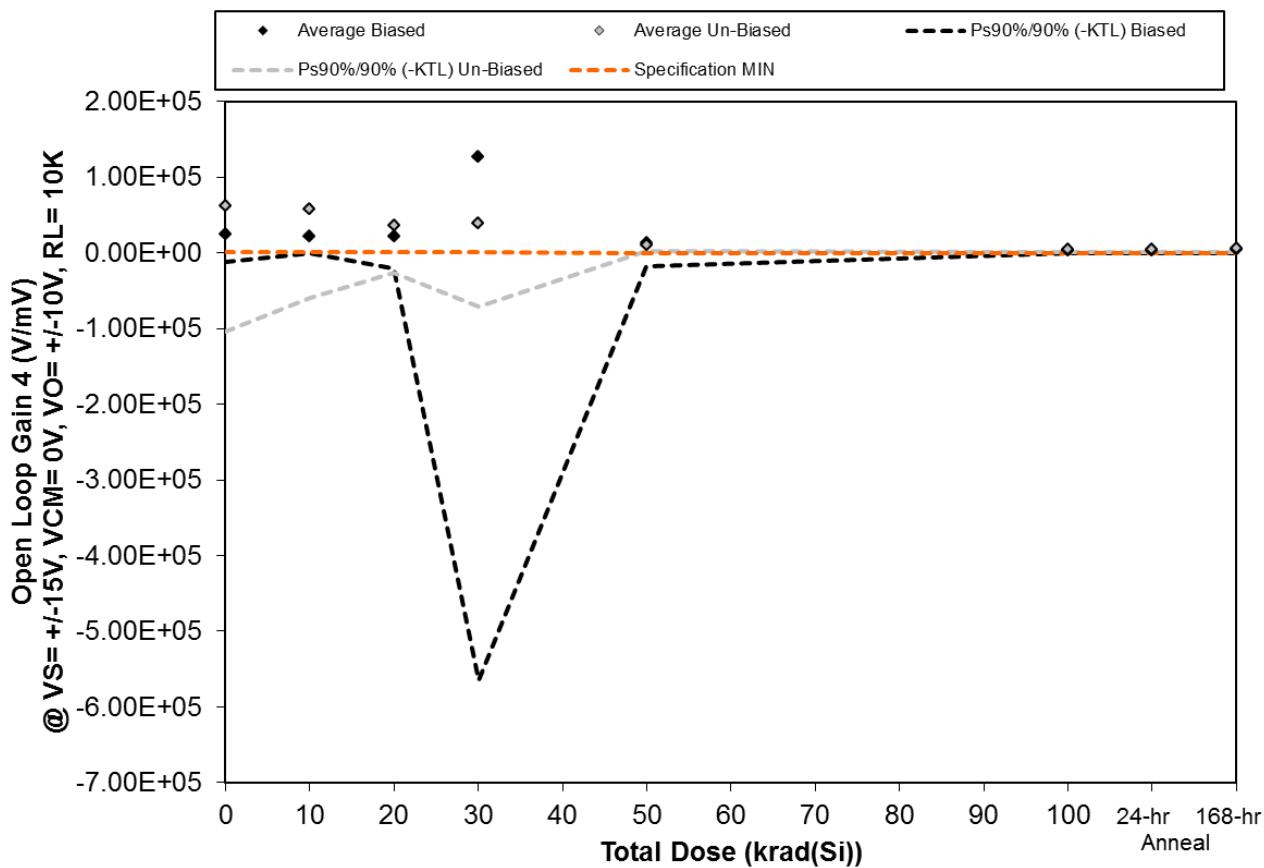


Figure 5.30. Plot of Open Loop Gain 4 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.30. Raw data for Open Loop Gain 4 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Open Loop Gain 4 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	4.78E+04	3.34E+04	2.36E+04	1.73E+04	1.13E+04	4.16E+03	3.70E+03	3.84E+03	
260	1.33E+04	1.19E+04	9.78E+03	9.67E+03	5.39E+03	2.94E+03	2.73E+03	2.78E+03	
326	1.74E+04	2.40E+04	1.29E+04	1.12E+04	7.05E+03	2.55E+03	2.65E+03	2.72E+03	
328	2.03E+04	1.72E+04	1.27E+04	1.56E+04	7.06E+03	2.99E+03	3.08E+03	2.92E+03	
329	2.49E+04	2.31E+04	4.66E+04	5.78E+05	3.17E+04	5.74E+03	5.71E+03	6.38E+03	
330	1.80E+04	1.64E+04	1.33E+04	8.27E+03	8.02E+03	3.35E+03	3.31E+03	3.84E+03	
331	2.12E+04	3.71E+04	1.09E+04	1.19E+04	7.61E+03	3.39E+03	3.79E+03	5.77E+03	
334	5.25E+04	4.85E+04	5.18E+04	1.07E+05	1.50E+04	6.48E+03	5.70E+03	9.67E+03	
335	1.66E+05	1.29E+05	6.19E+04	2.66E+04	1.19E+04	4.94E+03	6.27E+03	6.66E+03	
344	5.19E+04	5.56E+04	4.03E+04	4.02E+04	1.04E+04	6.10E+03	5.72E+03	6.32E+03	
346	1.92E+04	1.80E+04	2.10E+04	2.03E+04	1.82E+04	1.89E+04	1.97E+04	2.18E+04	
Biased Statistics									
Average Biased		2.48E+04	2.19E+04	2.11E+04	1.26E+05	1.25E+04	3.68E+03	3.57E+03	3.73E+03
Std Dev Biased		1.35E+04	8.06E+03	1.52E+04	2.52E+05	1.09E+04	1.30E+03	1.26E+03	1.55E+03
Ps90%/90% (+KTL) Biased		6.19E+04	4.40E+04	6.28E+04	8.18E+05	4.25E+04	7.25E+03	7.04E+03	7.98E+03
Ps90%/90% (-KTL) Biased		-1.24E+04	-1.64E+02	-2.05E+04	-5.65E+05	-1.75E+04	9.98E+01	1.04E+02	-5.26E+02
Un-Biased Statistics									
Average Un-Biased		6.20E+04	5.73E+04	3.56E+04	3.87E+04	1.06E+04	4.85E+03	4.96E+03	6.45E+03
Std Dev Un-Biased		6.05E+04	4.26E+04	2.28E+04	4.00E+04	3.03E+03	1.47E+03	1.32E+03	2.11E+03
Ps90%/90% (+KTL) Un-Biased		2.28E+05	1.74E+05	9.82E+04	1.48E+05	1.89E+04	8.88E+03	8.57E+03	1.22E+04
Ps90%/90% (-KTL) Un-Biased		-1.04E+05	-5.96E+04	-2.70E+04	-7.09E+04	2.29E+03	8.26E+02	1.35E+03	6.75E+02
Specification MIN		1.20E+03	5.00E+02	2.00E+02	2.00E+02	1.00E+02	5.00E+01	5.00E+01	5.00E+01
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

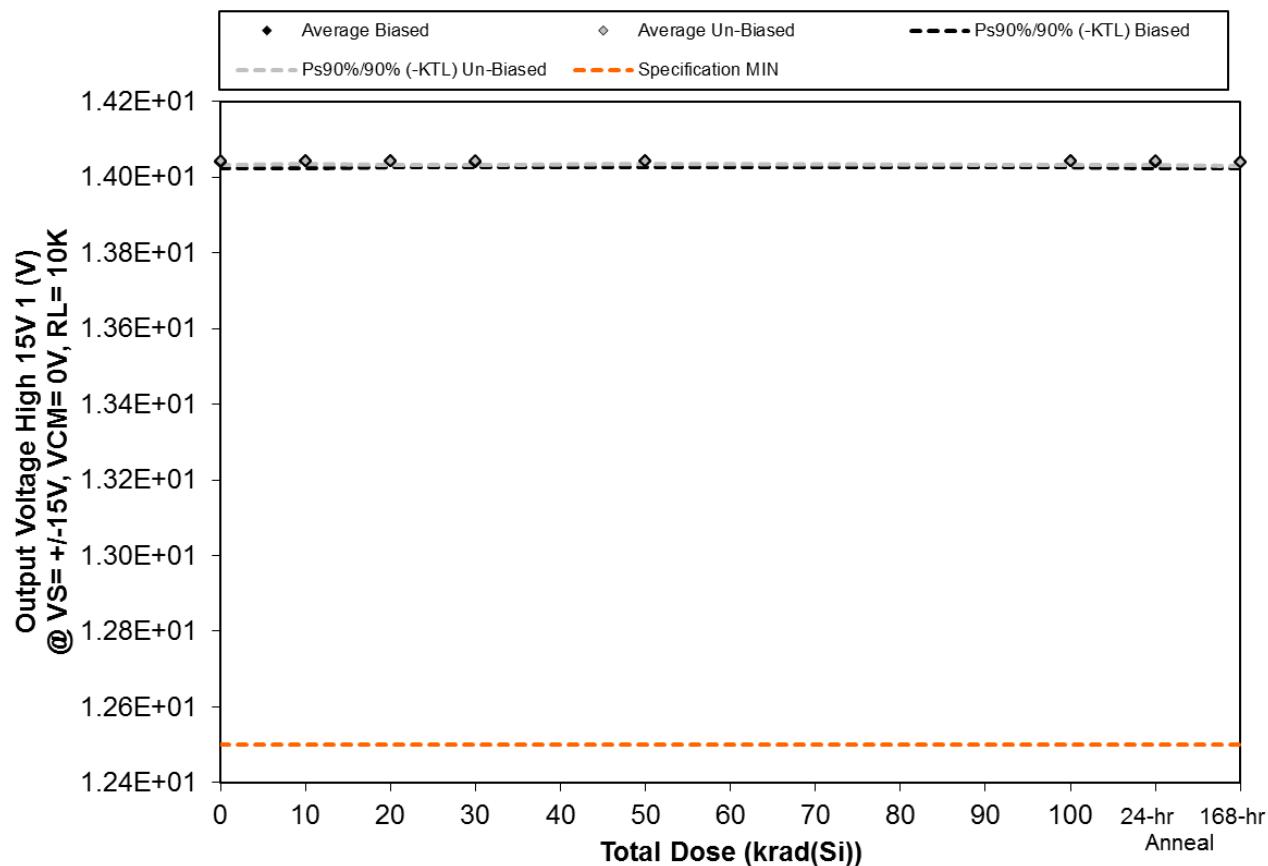


Figure 5.31. Plot of Output Voltage High 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.31. Raw data for Output Voltage High 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
260	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
326	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
328	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
329	1.40E+01	1.41E+01	1.40E+01	1.40E+01	1.41E+01	1.40E+01	1.40E+01	1.40E+01
330	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
331	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
334	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
335	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
344	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
346	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Biased Statistics								
Average Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Biased	5.59E-03	6.22E-03	5.46E-03	5.18E-03	5.90E-03	5.93E-03	5.93E-03	5.73E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Un-Biased Statistics								
Average Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Un-Biased	3.29E-03	2.92E-03	3.51E-03	3.49E-03	3.29E-03	3.74E-03	3.51E-03	3.77E-03
Ps90%/90% (+KTL) Un-Biased	1.40E+01	1.40E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
Ps90%/90% (-KTL) Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

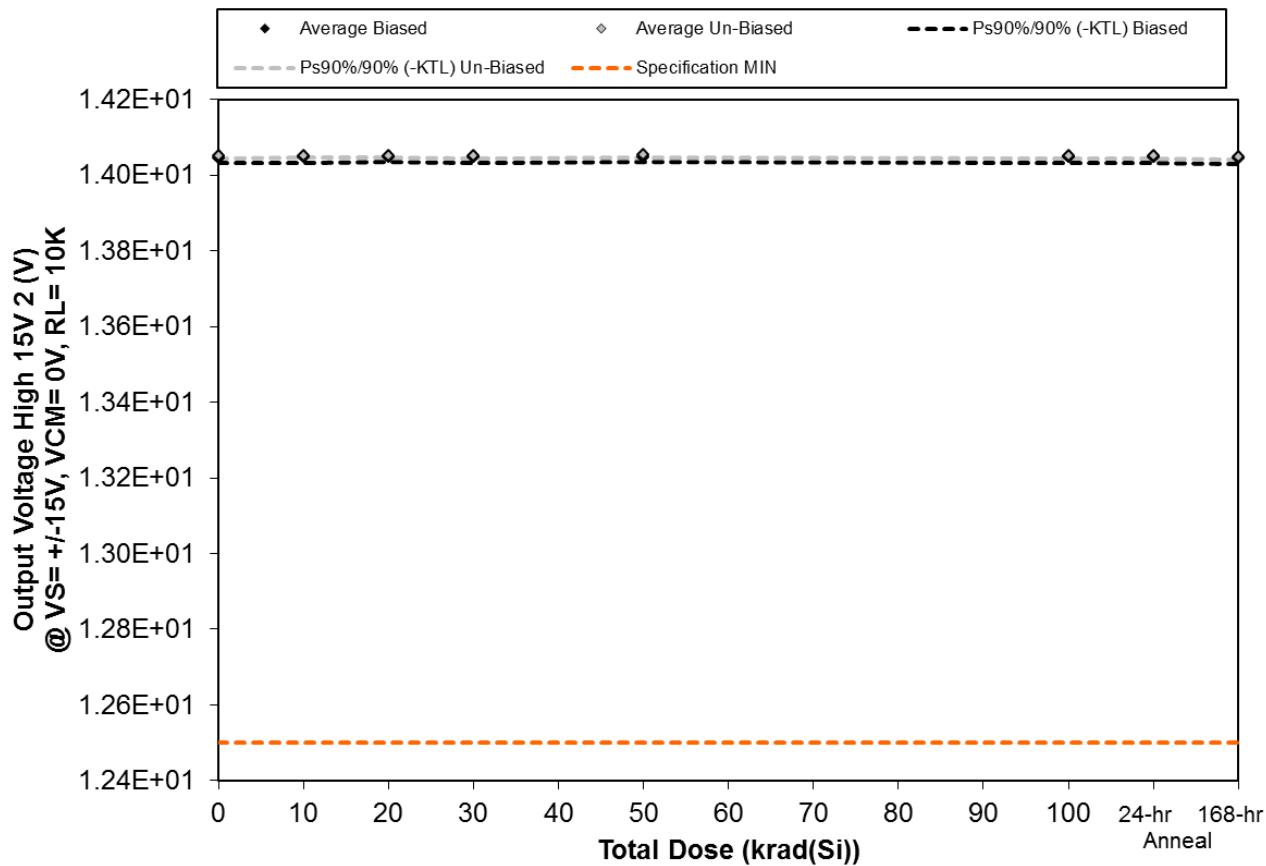


Figure 5.32. Plot of Output Voltage High 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.32. Raw data for Output Voltage High 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
260	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
326	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
328	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
329	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
330	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
331	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
334	1.40E+01	1.41E+01	1.41E+01	1.40E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
335	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
344	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
346	1.40E+01	1.41E+01	1.41E+01	1.40E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
Biased Statistics								
Average Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Biased	5.05E-03	5.17E-03	5.13E-03	4.88E-03	5.13E-03	5.27E-03	5.18E-03	5.40E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Un-Biased Statistics								
Average Un-Biased	1.40E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
Std Dev Un-Biased	2.59E-03	2.28E-03	2.19E-03	2.61E-03	2.28E-03	2.30E-03	2.59E-03	2.92E-03
Ps90%/90% (+KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

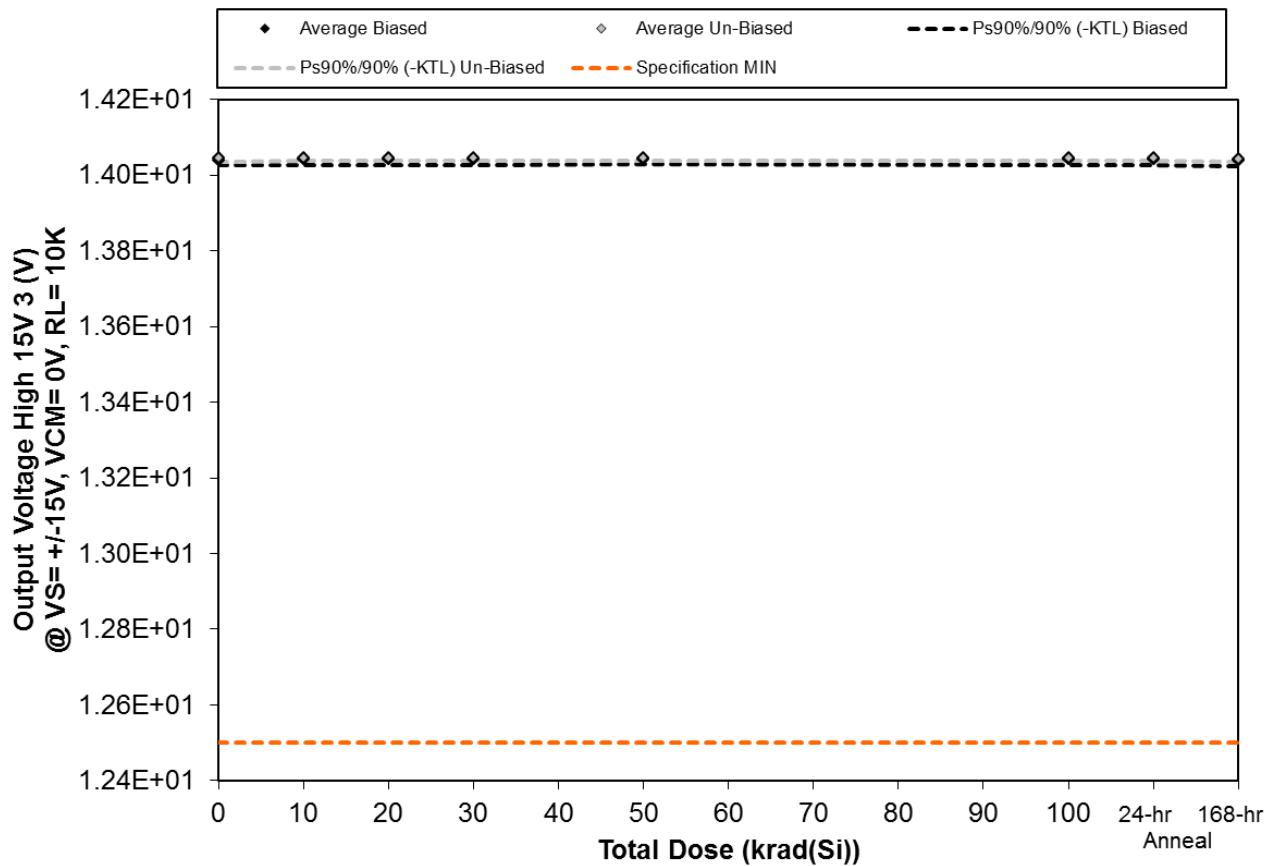


Figure 5.33. Plot of Output Voltage High 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.33. Raw data for Output Voltage High 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
260	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
326	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
328	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
329	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
330	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
331	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
334	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
335	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
344	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
346	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Biased Statistics								
Average Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Biased	5.02E-03	5.63E-03	5.29E-03	4.92E-03	5.32E-03	5.27E-03	5.12E-03	5.18E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Un-Biased Statistics								
Average Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Un-Biased	2.97E-03	2.59E-03	2.65E-03	2.65E-03	2.97E-03	2.59E-03	2.28E-03	2.28E-03
Ps90%/90% (+KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
Ps90%/90% (-KTL) Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

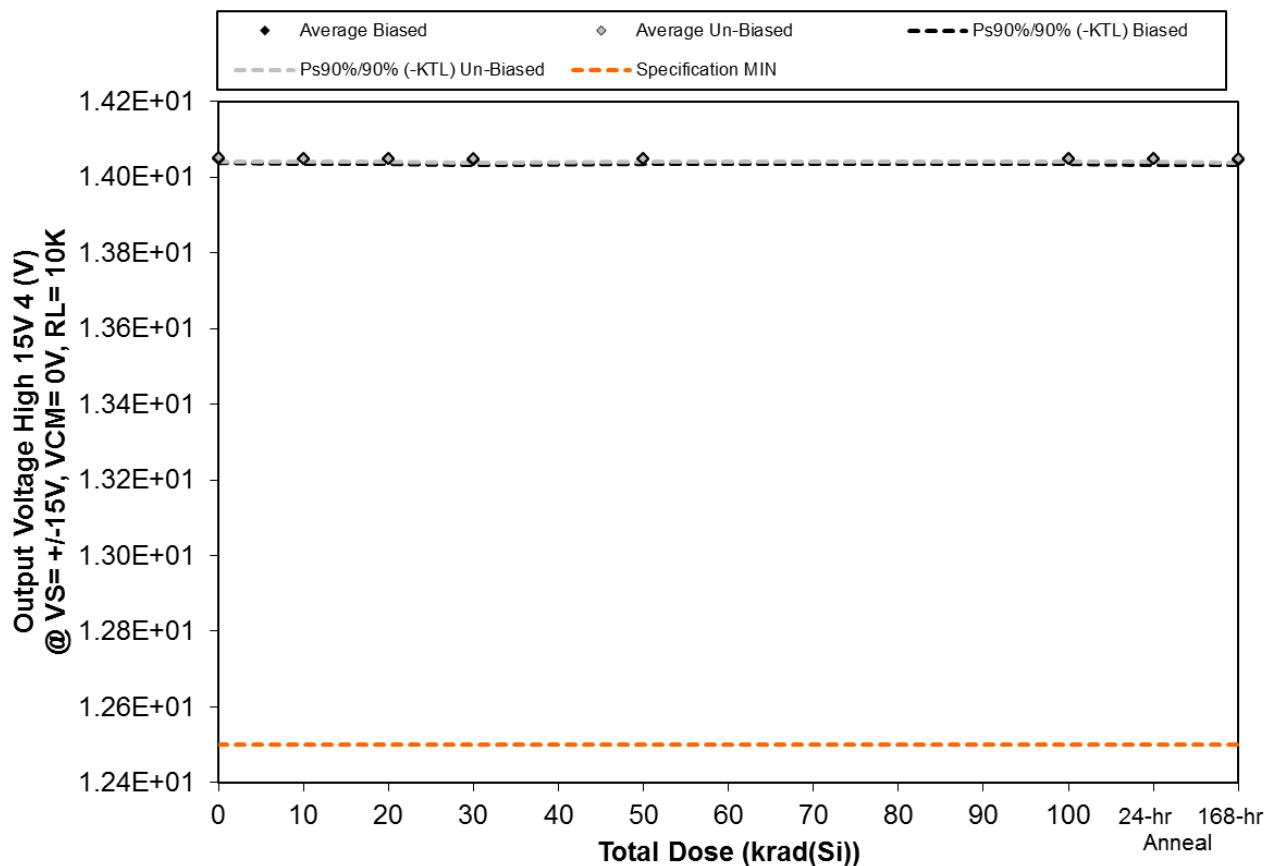


Figure 5.34. Plot of Output Voltage High 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.34. Raw data for Output Voltage High 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.41E+01	1.40E+01	1.41E+01	1.40E+01	1.41E+01	1.41E+01	1.40E+01	1.40E+01
260	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
326	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
328	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
329	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
330	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
331	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
334	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.40E+01
335	1.41E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
344	1.41E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
346	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Biased Statistics								
Average Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Biased	4.64E-03	4.71E-03	4.76E-03	5.02E-03	4.82E-03	4.72E-03	5.13E-03	4.93E-03
Ps90%/90% (+KTL) Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Un-Biased Statistics								
Average Un-Biased	1.41E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Std Dev Un-Biased	3.74E-03	3.11E-03	2.88E-03	3.51E-03	2.86E-03	3.29E-03	3.29E-03	3.13E-03
Ps90%/90% (+KTL) Un-Biased	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01	1.41E+01
Ps90%/90% (-KTL) Un-Biased	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01	1.40E+01
Specification MIN	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01	1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

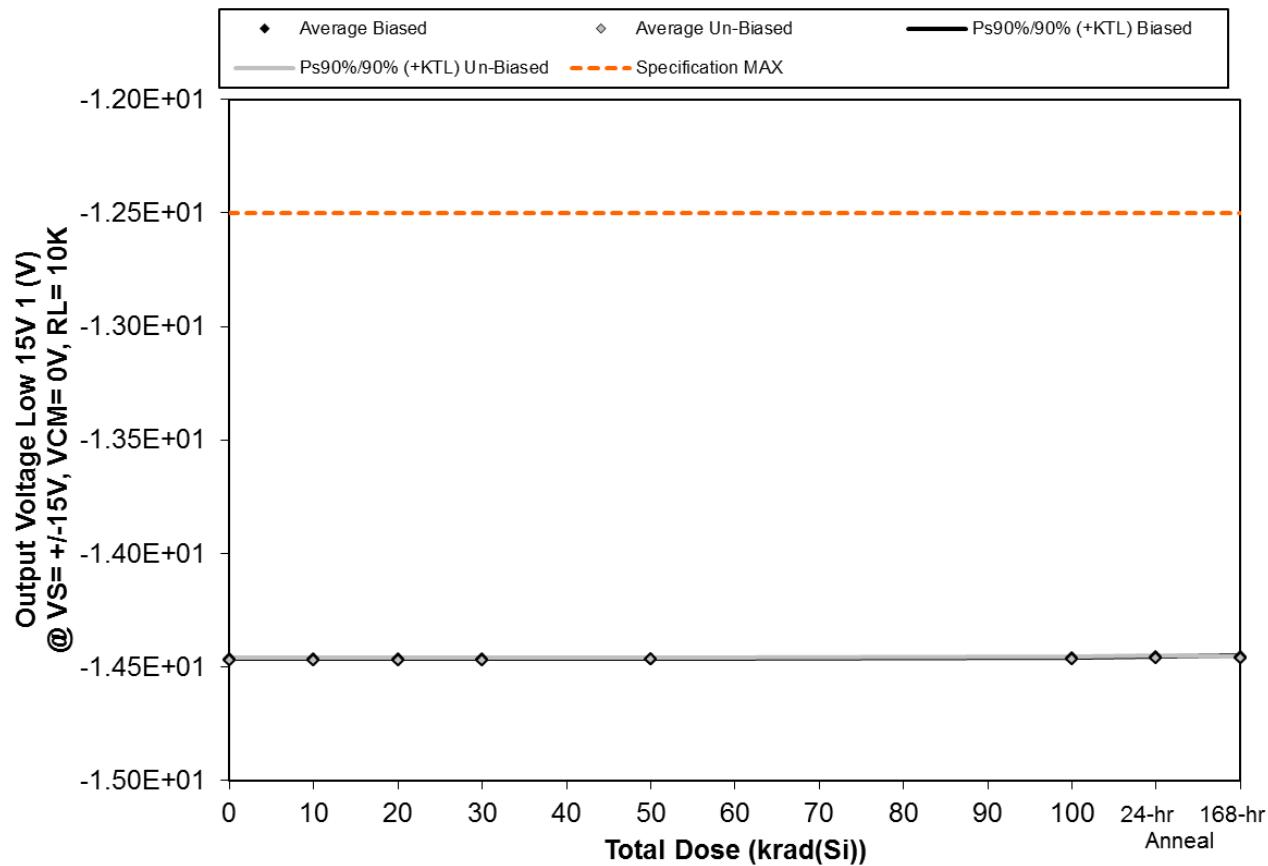


Figure 5.35. Plot of Output Voltage Low 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.35. Raw data for Output Voltage Low 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
260	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
326	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
328	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
329	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
330	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
331	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
334	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
335	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
344	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
346	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Biased Statistics								
Average Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Biased	1.34E-03	1.14E-03	1.30E-03	1.14E-03	8.94E-04	1.41E-03	1.14E-03	1.67E-03
Ps90%/90% (+KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Un-Biased Statistics								
Average Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Un-Biased	3.58E-03	3.90E-03	4.10E-03	4.32E-03	3.90E-03	4.10E-03	4.62E-03	4.18E-03
Ps90%/90% (+KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.44E+01	-1.45E+01
Ps90%/90% (-KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Specification MAX	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

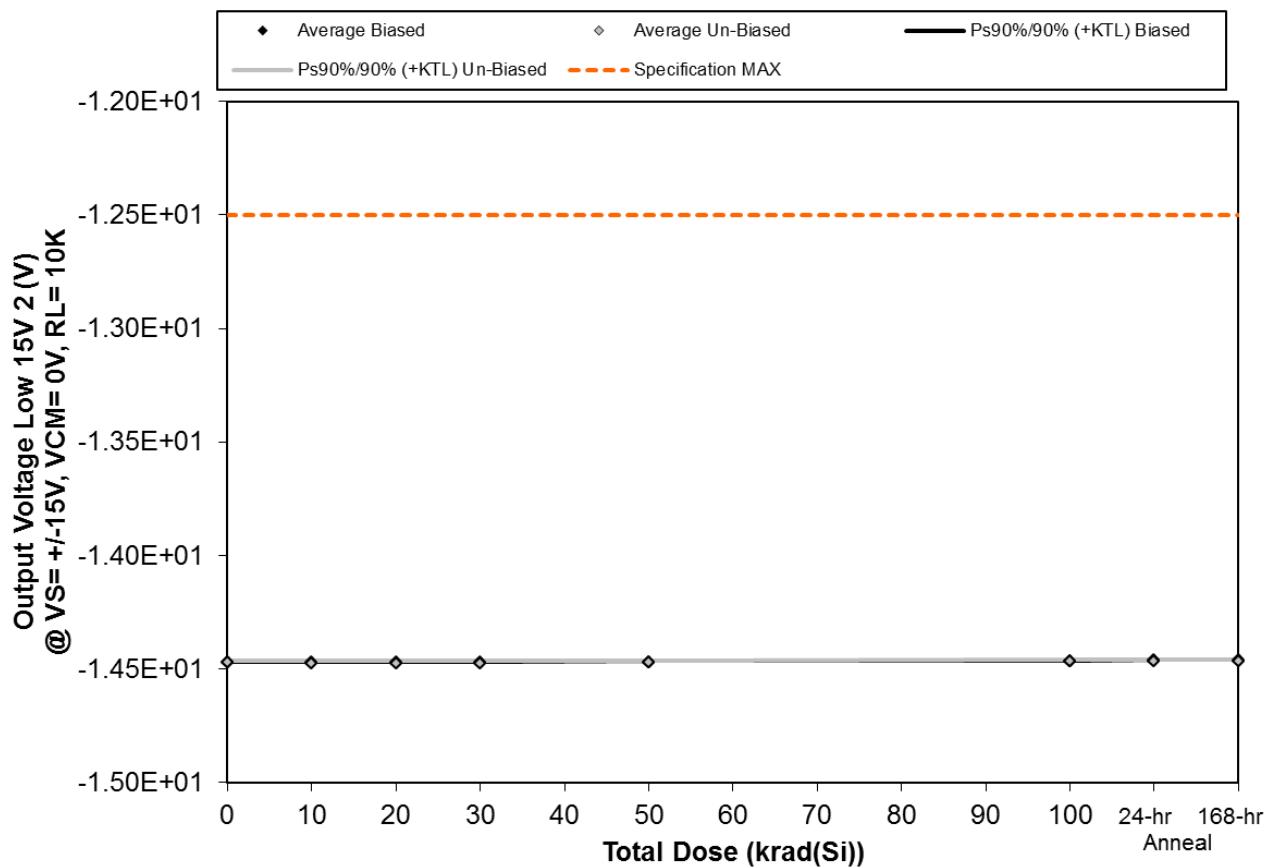


Figure 5.36. Plot of Output Voltage Low 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.36. Raw data for Output Voltage Low 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
260	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
326	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
328	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
329	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
330	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
331	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
334	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
335	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
344	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
346	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Biased Statistics								
Average Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Biased	4.47E-04	5.48E-04	4.47E-04	1.00E-03	1.10E-03	1.14E-03	8.37E-04	8.94E-04
Ps90%/90% (+KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Un-Biased Statistics								
Average Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Un-Biased	2.61E-03	3.00E-03	3.00E-03	3.27E-03	2.79E-03	2.79E-03	2.79E-03	2.77E-03
Ps90%/90% (+KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Specification MAX	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

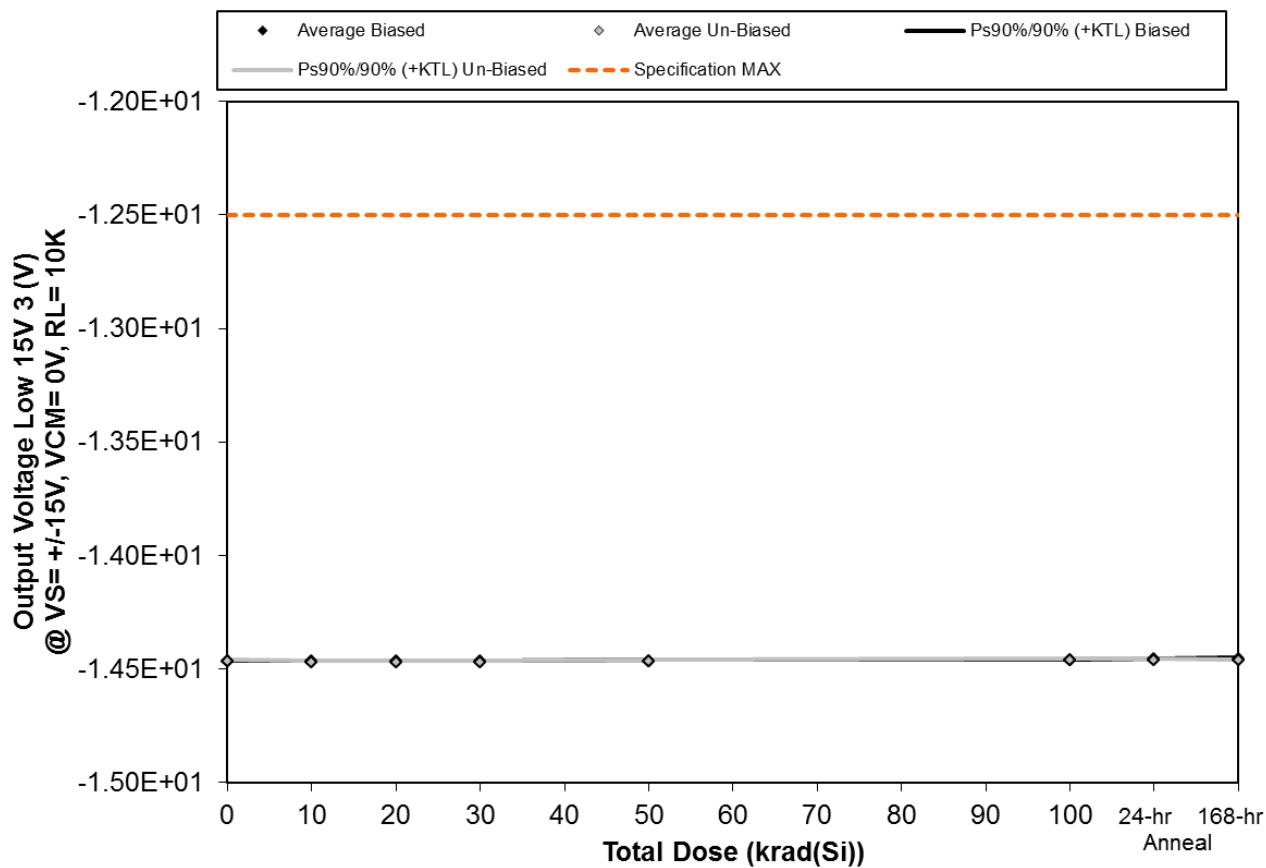


Figure 5.37. Plot of Output Voltage Low 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.37. Raw data for Output Voltage Low 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
260	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
326	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
328	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
329	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
330	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
331	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
334	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
335	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
344	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
346	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Biased Statistics								
Average Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Biased	1.10E-03	1.22E-03	1.14E-03	1.10E-03	1.30E-03	1.30E-03	1.30E-03	1.67E-03
Ps90%/90% (+KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Un-Biased Statistics								
Average Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Un-Biased	2.97E-03	3.05E-03	3.00E-03	2.77E-03	2.77E-03	3.00E-03	2.00E-03	2.55E-03
Ps90%/90% (+KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Specification MAX	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

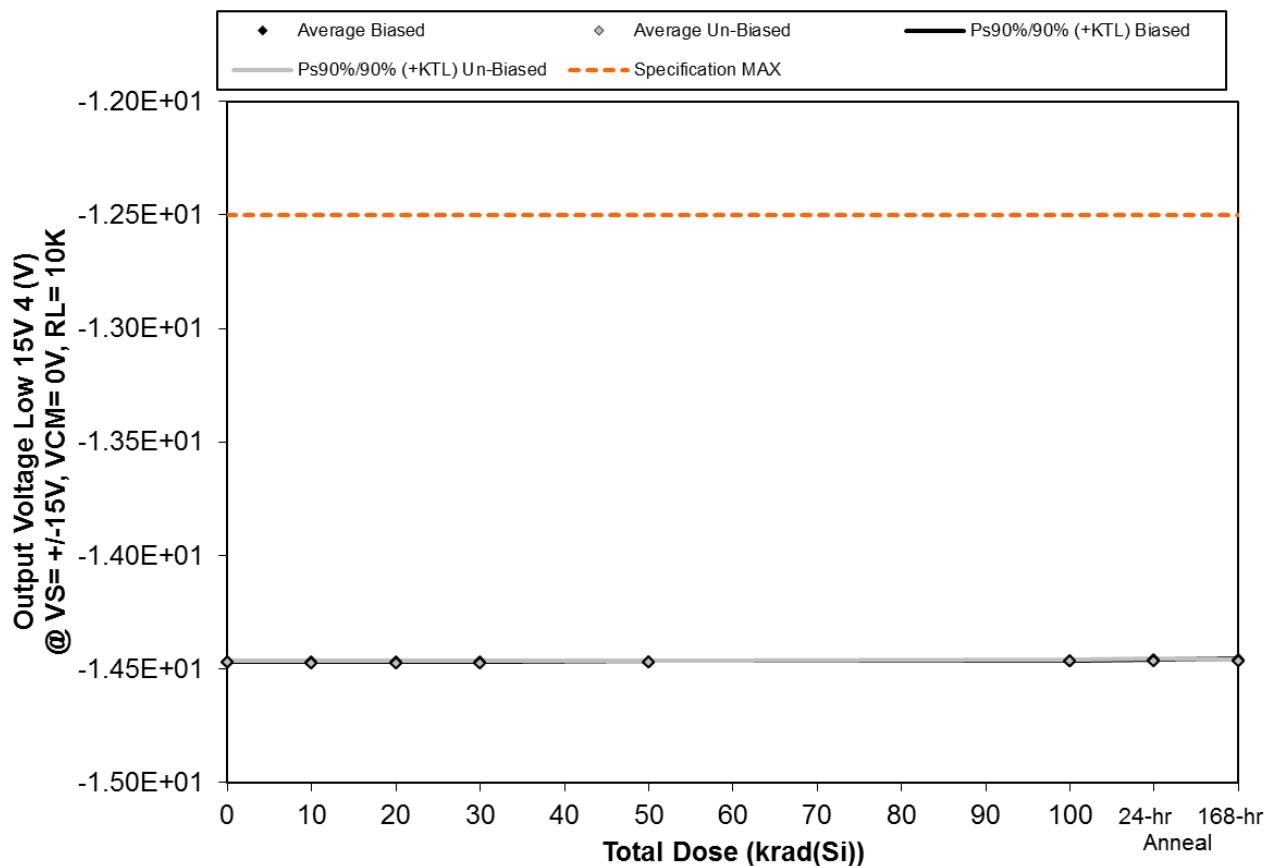


Figure 5.38. Plot of Output Voltage Low 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.38. Raw data for Output Voltage Low 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
260	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
326	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
328	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
329	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
330	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
331	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
334	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
335	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
344	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
346	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Biased Statistics								
Average Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Biased	1.14E-03	1.41E-03	1.14E-03	8.37E-04	1.64E-03	1.41E-03	1.48E-03	1.58E-03
Ps90%/90% (+KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Un-Biased Statistics								
Average Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Std Dev Un-Biased	3.29E-03	3.49E-03	3.42E-03	3.74E-03	3.74E-03	3.96E-03	4.12E-03	3.78E-03
Ps90%/90% (+KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Ps90%/90% (-KTL) Un-Biased	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01	-1.45E+01
Specification MAX	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01	-1.25E+01
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

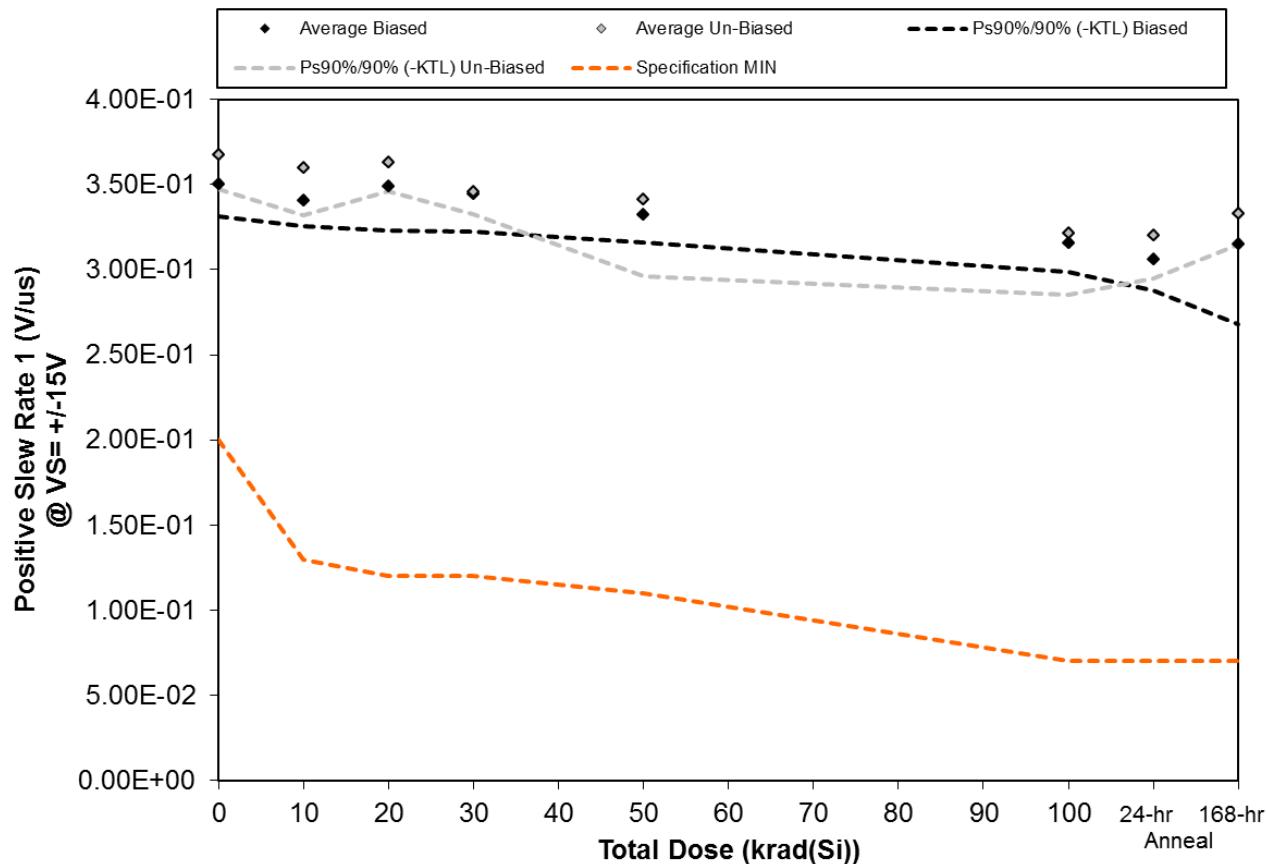


Figure 5.39. Plot of Positive Slew Rate 1 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.39. Raw data for Positive Slew Rate 1 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate 1 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.48E-01	3.46E-01	3.48E-01	3.56E-01	3.40E-01	3.14E-01	3.02E-01	3.27E-01
260	3.60E-01	3.46E-01	3.52E-01	3.41E-01	3.29E-01	3.14E-01	3.00E-01	3.17E-01
326	3.50E-01	3.37E-01	3.37E-01	3.47E-01	3.34E-01	3.10E-01	3.05E-01	2.88E-01
328	3.41E-01	3.34E-01	3.62E-01	3.34E-01	3.24E-01	3.26E-01	3.17E-01	3.11E-01
329	3.51E-01	3.39E-01	3.44E-01	3.44E-01	3.35E-01	3.14E-01	3.05E-01	3.32E-01
330	3.62E-01	3.58E-01	3.59E-01	3.51E-01	3.23E-01	3.23E-01	3.17E-01	3.31E-01
331	3.66E-01	3.75E-01	3.63E-01	3.43E-01	3.67E-01	3.24E-01	3.36E-01	3.39E-01
334	3.62E-01	3.65E-01	3.64E-01	3.47E-01	3.35E-01	3.24E-01	3.16E-01	3.26E-01
335	3.67E-01	3.50E-01	3.57E-01	3.39E-01	3.36E-01	3.00E-01	3.13E-01	3.27E-01
344	3.80E-01	3.52E-01	3.73E-01	3.48E-01	3.45E-01	3.36E-01	3.18E-01	3.40E-01
346	3.58E-01	3.45E-01	3.43E-01	3.36E-01	3.43E-01	3.46E-01	3.47E-01	3.74E-01
Biased Statistics								
Average Biased	3.50E-01	3.40E-01	3.49E-01	3.44E-01	3.32E-01	3.16E-01	3.06E-01	3.15E-01
Std Dev Biased	6.82E-03	5.41E-03	9.32E-03	8.08E-03	6.11E-03	6.07E-03	6.61E-03	1.72E-02
Ps90%/90% (+KTL) Biased	3.69E-01	3.55E-01	3.74E-01	3.67E-01	3.49E-01	3.32E-01	3.24E-01	3.62E-01
Ps90%/90% (-KTL) Biased	3.31E-01	3.26E-01	3.23E-01	3.22E-01	3.16E-01	2.99E-01	2.88E-01	2.68E-01
Un-Biased Statistics								
Average Un-Biased	3.67E-01	3.60E-01	3.63E-01	3.46E-01	3.41E-01	3.21E-01	3.20E-01	3.33E-01
Std Dev Un-Biased	7.40E-03	1.02E-02	6.18E-03	4.67E-03	1.64E-02	1.31E-02	9.14E-03	6.58E-03
Ps90%/90% (+KTL) Un-Biased	3.88E-01	3.88E-01	3.80E-01	3.58E-01	3.86E-01	3.57E-01	3.45E-01	3.51E-01
Ps90%/90% (-KTL) Un-Biased	3.47E-01	3.32E-01	3.46E-01	3.33E-01	2.96E-01	2.85E-01	2.95E-01	3.15E-01
Specification MIN	2.00E-01	1.30E-01	1.20E-01	1.20E-01	1.10E-01	7.00E-02	7.00E-02	7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

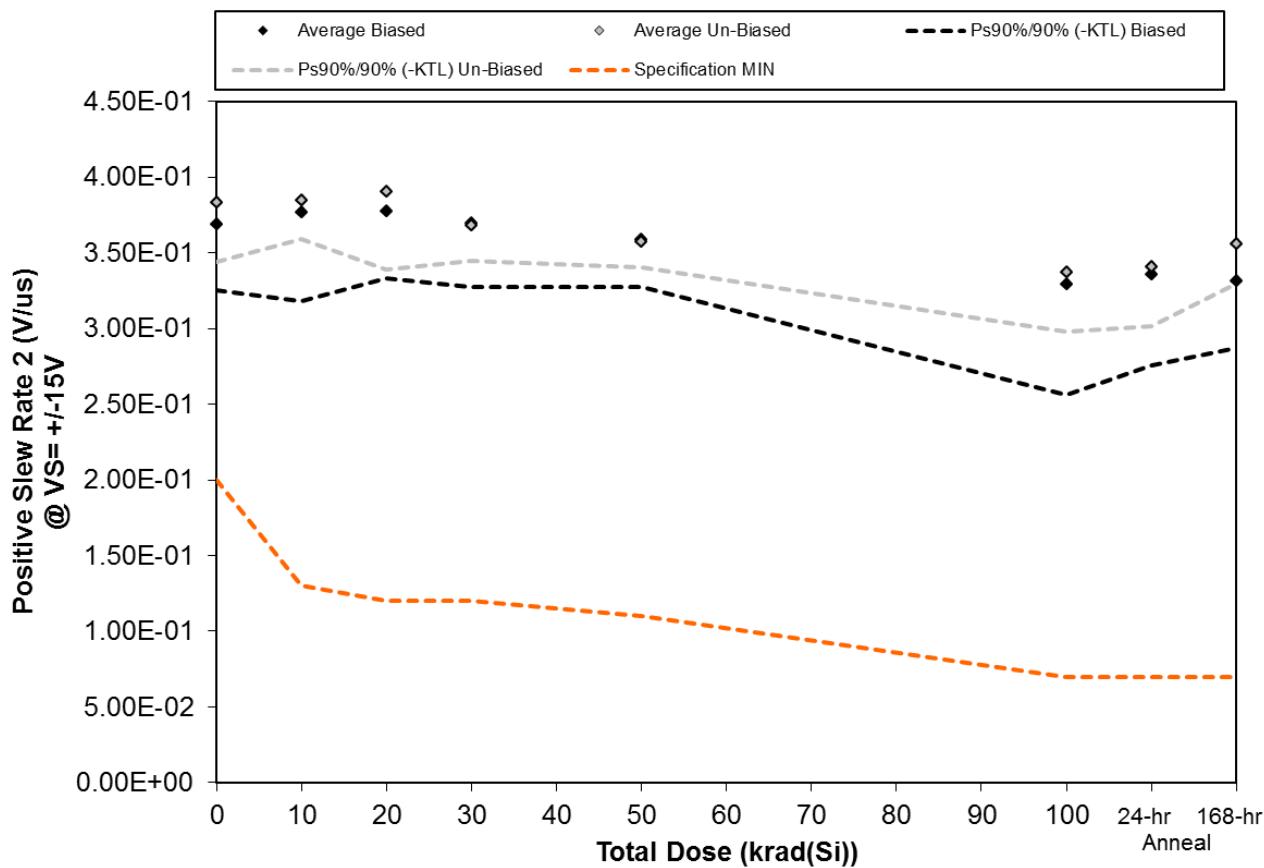


Figure 5.40. Plot of Positive Slew Rate 2 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.40. Raw data for Positive Slew Rate 2 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate 2 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.73E-01	3.87E-01	3.93E-01	3.52E-01	3.60E-01	3.27E-01	3.48E-01	3.40E-01
260	3.67E-01	3.70E-01	3.70E-01	3.75E-01	3.48E-01	3.25E-01	3.20E-01	3.08E-01
326	3.48E-01	3.63E-01	3.58E-01	3.54E-01	3.46E-01	2.95E-01	3.11E-01	3.21E-01
328	3.92E-01	4.09E-01	3.95E-01	3.82E-01	3.73E-01	3.70E-01	3.66E-01	3.45E-01
329	3.64E-01	3.55E-01	3.70E-01	3.83E-01	3.65E-01	3.29E-01	3.33E-01	3.42E-01
330	3.84E-01	3.96E-01	3.82E-01	3.74E-01	3.61E-01	3.22E-01	3.54E-01	3.55E-01
331	3.75E-01	3.90E-01	4.02E-01	3.69E-01	3.57E-01	3.36E-01	3.39E-01	3.56E-01
334	3.80E-01	3.72E-01	3.87E-01	3.54E-01	3.54E-01	3.40E-01	3.47E-01	3.61E-01
335	3.69E-01	3.85E-01	3.66E-01	3.68E-01	3.49E-01	3.29E-01	3.17E-01	3.41E-01
344	4.06E-01	3.80E-01	4.15E-01	3.76E-01	3.65E-01	3.60E-01	3.48E-01	3.67E-01
346	3.87E-01	3.86E-01	3.80E-01	3.94E-01	3.84E-01	3.85E-01	3.74E-01	3.84E-01
Biased Statistics								
Average Biased	3.69E-01	3.77E-01	3.77E-01	3.69E-01	3.58E-01	3.29E-01	3.36E-01	3.31E-01
Std Dev Biased	1.59E-02	2.15E-02	1.61E-02	1.51E-02	1.14E-02	2.67E-02	2.20E-02	1.60E-02
Ps90%/90% (+KTL) Biased	4.12E-01	4.36E-01	4.21E-01	4.11E-01	3.90E-01	4.02E-01	3.96E-01	3.75E-01
Ps90%/90% (-KTL) Biased	3.25E-01	3.18E-01	3.33E-01	3.28E-01	3.27E-01	2.56E-01	2.75E-01	2.87E-01
Un-Biased Statistics								
Average Un-Biased	3.83E-01	3.85E-01	3.90E-01	3.68E-01	3.57E-01	3.37E-01	3.41E-01	3.56E-01
Std Dev Un-Biased	1.41E-02	9.21E-03	1.88E-02	8.61E-03	6.18E-03	1.44E-02	1.44E-02	9.64E-03
Ps90%/90% (+KTL) Un-Biased	4.22E-01	4.10E-01	4.42E-01	3.92E-01	3.74E-01	3.77E-01	3.81E-01	3.82E-01
Ps90%/90% (-KTL) Un-Biased	3.44E-01	3.59E-01	3.39E-01	3.45E-01	3.40E-01	2.98E-01	3.01E-01	3.30E-01
Specification MIN	2.00E-01	1.30E-01	1.20E-01	1.20E-01	1.10E-01	7.00E-02	7.00E-02	7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

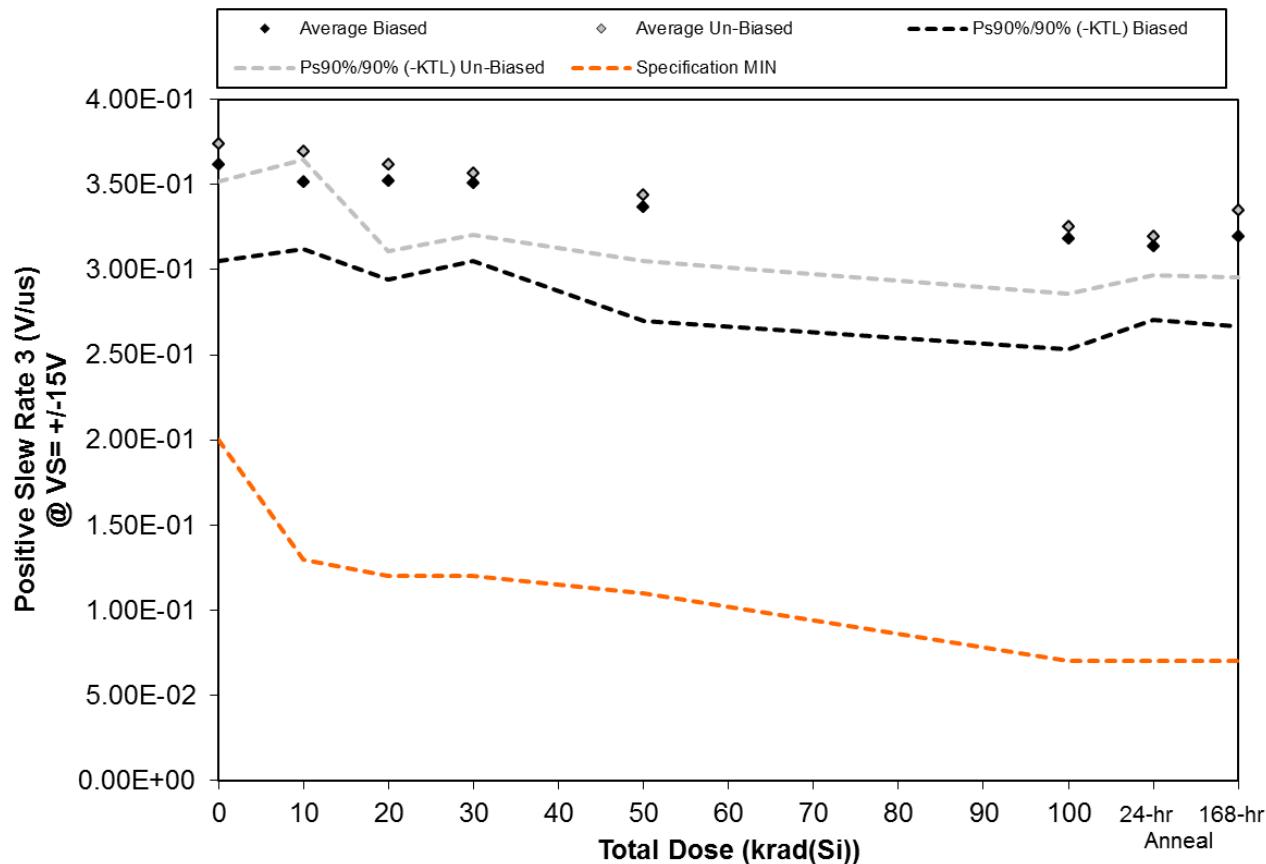


Figure 5.41. Plot of Positive Slew Rate 3 (V/us) @ VS = +/- 15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.41. Raw data for Positive Slew Rate 3 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate 3 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.56E-01	3.60E-01	3.66E-01	3.49E-01	3.40E-01	3.38E-01	3.02E-01	3.14E-01
260	3.59E-01	3.42E-01	3.45E-01	3.37E-01	3.34E-01	2.96E-01	3.08E-01	3.01E-01
326	3.38E-01	3.34E-01	3.20E-01	3.41E-01	3.06E-01	3.00E-01	2.99E-01	3.04E-01
328	3.95E-01	3.70E-01	3.74E-01	3.79E-01	3.74E-01	3.48E-01	3.37E-01	3.47E-01
329	3.61E-01	3.51E-01	3.54E-01	3.47E-01	3.31E-01	3.08E-01	3.22E-01	3.30E-01
330	3.63E-01	3.71E-01	3.57E-01	3.55E-01	3.49E-01	3.35E-01	3.18E-01	3.25E-01
331	3.84E-01	3.70E-01	3.69E-01	3.57E-01	3.46E-01	3.43E-01	3.32E-01	3.56E-01
334	3.71E-01	3.68E-01	3.68E-01	3.54E-01	3.53E-01	3.06E-01	3.16E-01	3.20E-01
335	3.72E-01	3.67E-01	3.32E-01	3.40E-01	3.19E-01	3.18E-01	3.10E-01	3.31E-01
344	3.78E-01	3.70E-01	3.81E-01	3.77E-01	3.53E-01	3.24E-01	3.20E-01	3.41E-01
346	3.58E-01	3.62E-01	3.64E-01	3.72E-01	3.56E-01	3.72E-01	3.69E-01	3.51E-01
Biased Statistics								
Average Biased	3.62E-01	3.51E-01	3.52E-01	3.51E-01	3.37E-01	3.18E-01	3.14E-01	3.19E-01
Std Dev Biased	2.07E-02	1.42E-02	2.10E-02	1.66E-02	2.44E-02	2.35E-02	1.58E-02	1.92E-02
Ps90%/90% (+KTL) Biased	4.19E-01	3.90E-01	4.09E-01	3.96E-01	4.04E-01	3.82E-01	3.57E-01	3.72E-01
Ps90%/90% (-KTL) Biased	3.05E-01	3.12E-01	2.94E-01	3.05E-01	2.70E-01	2.54E-01	2.70E-01	2.66E-01
Un-Biased Statistics								
Average Un-Biased	3.74E-01	3.69E-01	3.61E-01	3.57E-01	3.44E-01	3.25E-01	3.19E-01	3.35E-01
Std Dev Un-Biased	7.89E-03	1.64E-03	1.85E-02	1.32E-02	1.43E-02	1.44E-02	8.07E-03	1.43E-02
Ps90%/90% (+KTL) Un-Biased	3.95E-01	3.74E-01	4.12E-01	3.93E-01	3.83E-01	3.65E-01	3.41E-01	3.74E-01
Ps90%/90% (-KTL) Un-Biased	3.52E-01	3.65E-01	3.11E-01	3.20E-01	3.05E-01	2.86E-01	2.97E-01	2.95E-01
Specification MIN	2.00E-01	1.30E-01	1.20E-01	1.20E-01	1.10E-01	7.00E-02	7.00E-02	7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

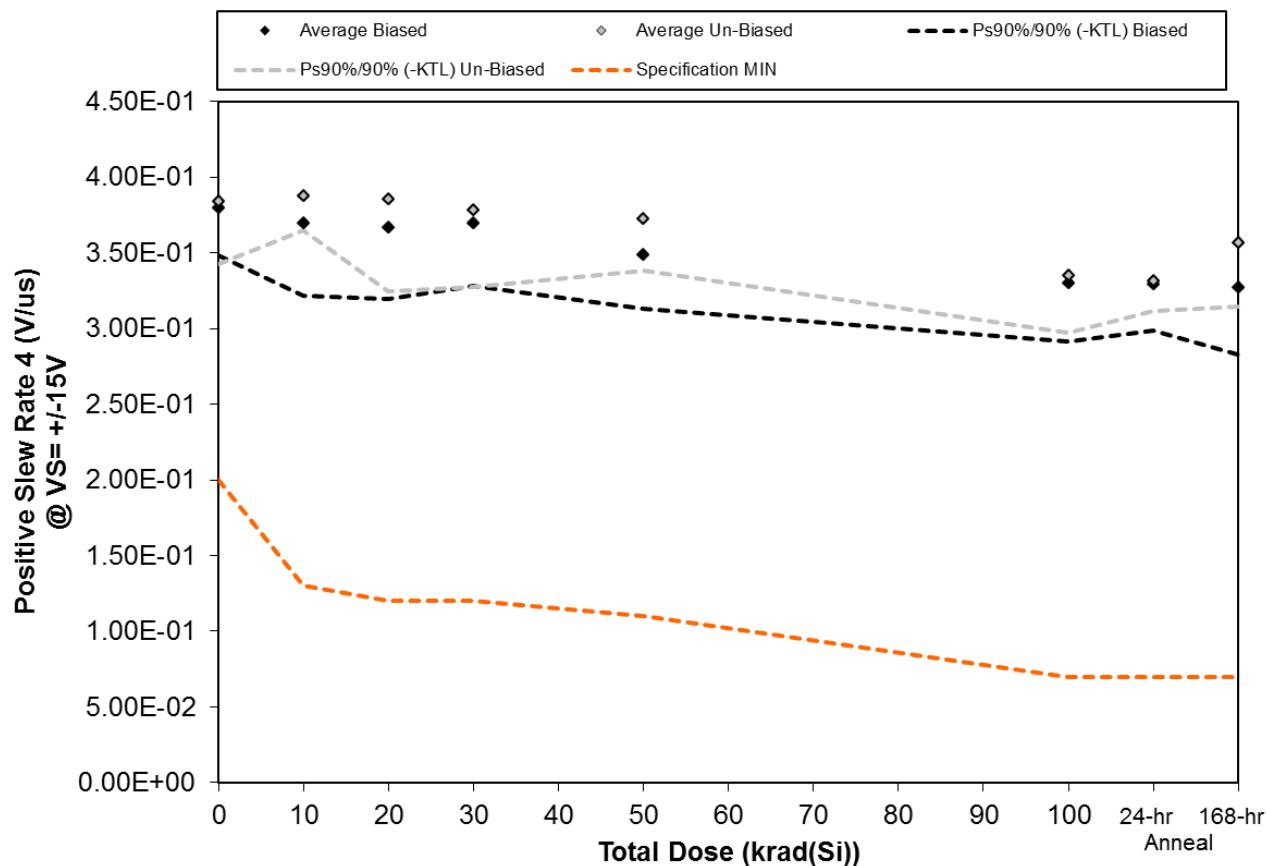


Figure 5.42. Plot of Positive Slew Rate 4 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.42. Raw data for Positive Slew Rate 4 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Slew Rate 4 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.85E-01	3.68E-01	3.71E-01	3.59E-01	3.67E-01	3.42E-01	3.30E-01	3.35E-01
260	3.90E-01	3.59E-01	3.81E-01	3.82E-01	3.48E-01	3.37E-01	3.27E-01	3.33E-01
326	3.82E-01	3.52E-01	3.47E-01	3.61E-01	3.32E-01	3.21E-01	3.15E-01	3.05E-01
328	3.60E-01	3.71E-01	3.50E-01	3.90E-01	3.42E-01	3.10E-01	3.28E-01	3.17E-01
329	3.80E-01	3.98E-01	3.83E-01	3.57E-01	3.54E-01	3.41E-01	3.46E-01	3.46E-01
330	3.88E-01	3.82E-01	3.73E-01	3.82E-01	3.67E-01	3.17E-01	3.30E-01	3.61E-01
331	3.76E-01	3.99E-01	4.19E-01	4.06E-01	3.94E-01	3.48E-01	3.39E-01	3.80E-01
334	4.07E-01	3.92E-01	3.67E-01	3.73E-01	3.62E-01	3.32E-01	3.39E-01	3.41E-01
335	3.80E-01	3.80E-01	3.71E-01	3.56E-01	3.69E-01	3.28E-01	3.22E-01	3.48E-01
344	3.67E-01	3.83E-01	3.97E-01	3.72E-01	3.70E-01	3.49E-01	3.28E-01	3.51E-01
346	3.70E-01	3.88E-01	3.69E-01	3.65E-01	3.85E-01	3.74E-01	3.53E-01	3.73E-01
Biased Statistics								
Average Biased	3.79E-01	3.70E-01	3.66E-01	3.70E-01	3.49E-01	3.30E-01	3.29E-01	3.27E-01
Std Dev Biased	1.15E-02	1.76E-02	1.70E-02	1.51E-02	1.31E-02	1.41E-02	1.11E-02	1.62E-02
Ps90%/90% (+KTL) Biased	4.11E-01	4.18E-01	4.13E-01	4.11E-01	3.85E-01	3.69E-01	3.60E-01	3.72E-01
Ps90%/90% (-KTL) Biased	3.48E-01	3.21E-01	3.20E-01	3.28E-01	3.13E-01	2.92E-01	2.99E-01	2.83E-01
Un-Biased Statistics								
Average Un-Biased	3.84E-01	3.87E-01	3.85E-01	3.78E-01	3.72E-01	3.35E-01	3.32E-01	3.56E-01
Std Dev Un-Biased	1.51E-02	8.04E-03	2.22E-02	1.83E-02	1.25E-02	1.37E-02	7.37E-03	1.51E-02
Ps90%/90% (+KTL) Un-Biased	4.25E-01	4.09E-01	4.46E-01	4.28E-01	4.07E-01	3.72E-01	3.52E-01	3.98E-01
Ps90%/90% (-KTL) Un-Biased	3.42E-01	3.65E-01	3.25E-01	3.28E-01	3.38E-01	2.97E-01	3.11E-01	3.15E-01
Specification MIN	2.00E-01	1.30E-01	1.20E-01	1.20E-01	1.10E-01	7.00E-02	7.00E-02	7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

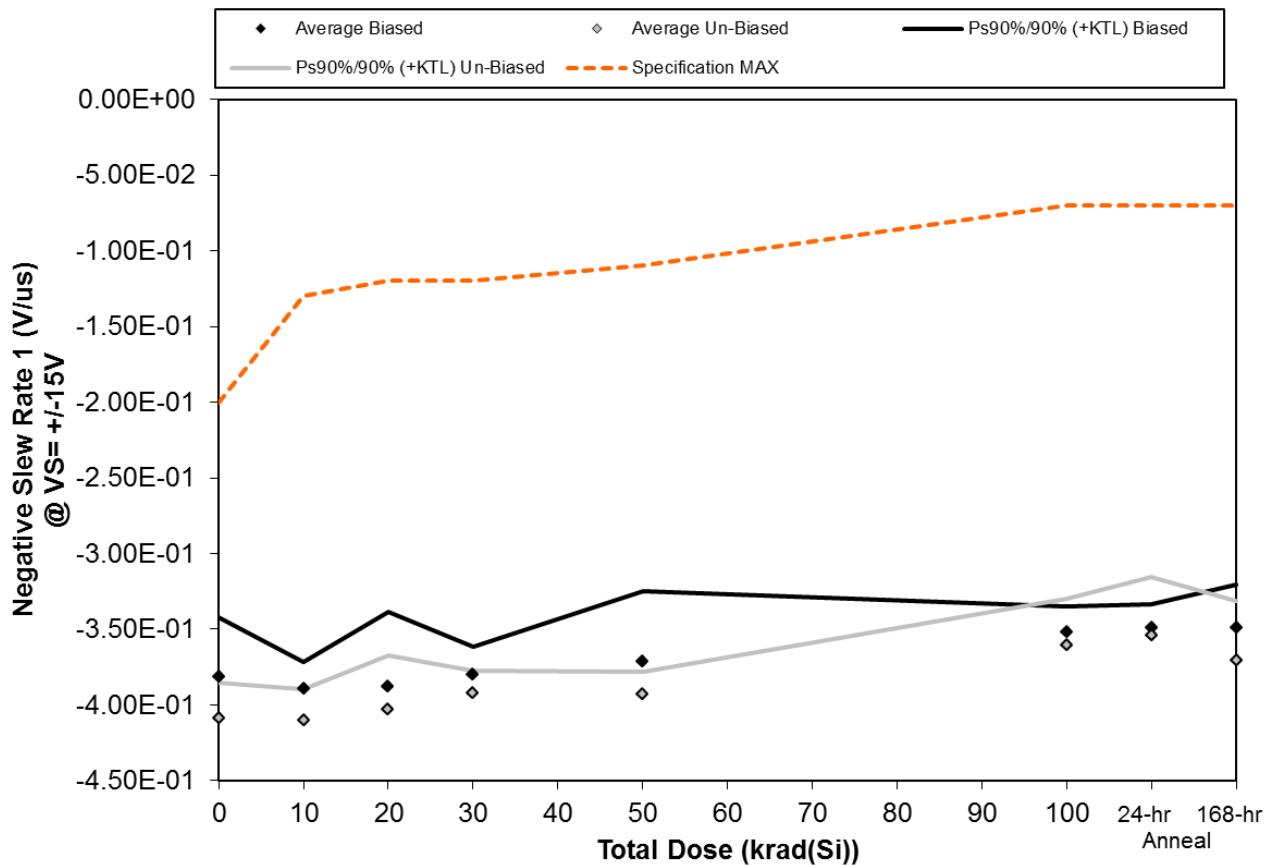


Figure 5.43. Plot of Negative Slew Rate 1 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.43. Raw data for Negative Slew Rate 1 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate 1 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-3.83E-01	-3.83E-01	-4.11E-01	-3.86E-01	-3.77E-01	-3.43E-01	-3.54E-01	-3.48E-01
260	-3.75E-01	-3.98E-01	-3.77E-01	-3.83E-01	-3.69E-01	-3.51E-01	-3.52E-01	-3.60E-01
326	-3.70E-01	-3.93E-01	-3.64E-01	-3.78E-01	-3.43E-01	-3.50E-01	-3.40E-01	-3.33E-01
328	-3.72E-01	-3.84E-01	-3.93E-01	-3.69E-01	-3.86E-01	-3.60E-01	-3.50E-01	-3.55E-01
329	-4.05E-01	-3.88E-01	-3.95E-01	-3.83E-01	-3.80E-01	-3.54E-01	-3.47E-01	-3.48E-01
330	-4.08E-01	-4.14E-01	-4.03E-01	-3.87E-01	-3.90E-01	-3.59E-01	-3.44E-01	-3.55E-01
331	-4.06E-01	-4.12E-01	-4.13E-01	-3.97E-01	-3.96E-01	-3.64E-01	-3.72E-01	-3.82E-01
334	-3.98E-01	-4.02E-01	-4.14E-01	-3.95E-01	-3.88E-01	-3.55E-01	-3.52E-01	-3.88E-01
335	-4.10E-01	-4.20E-01	-3.82E-01	-3.86E-01	-3.89E-01	-3.78E-01	-3.38E-01	-3.62E-01
344	-4.22E-01	-4.03E-01	-4.01E-01	-3.97E-01	-4.00E-01	-3.48E-01	-3.65E-01	-3.64E-01
346	-4.06E-01	-3.82E-01	-4.17E-01	-4.20E-01	-3.92E-01	-3.88E-01	-3.92E-01	-3.87E-01
Biased Statistics								
Average Biased	-3.81E-01	-3.89E-01	-3.88E-01	-3.80E-01	-3.71E-01	-3.52E-01	-3.49E-01	-3.49E-01
Std Dev Biased	1.43E-02	6.30E-03	1.80E-02	6.69E-03	1.68E-02	6.19E-03	5.46E-03	1.02E-02
Ps90%/90% (+KTL) Biased	-3.42E-01	-3.72E-01	-3.39E-01	-3.61E-01	-3.25E-01	-3.35E-01	-3.34E-01	-3.21E-01
Ps90%/90% (-KTL) Biased	-4.20E-01	-4.06E-01	-4.37E-01	-3.98E-01	-4.17E-01	-3.69E-01	-3.64E-01	-3.77E-01
Un-Biased Statistics								
Average Un-Biased	-4.09E-01	-4.10E-01	-4.03E-01	-3.92E-01	-3.93E-01	-3.61E-01	-3.54E-01	-3.70E-01
Std Dev Un-Biased	8.67E-03	7.63E-03	1.29E-02	5.46E-03	5.18E-03	1.13E-02	1.42E-02	1.41E-02
Ps90%/90% (+KTL) Un-Biased	-3.85E-01	-3.89E-01	-3.67E-01	-3.77E-01	-3.78E-01	-3.30E-01	-3.15E-01	-3.32E-01
Ps90%/90% (-KTL) Un-Biased	-4.33E-01	-4.31E-01	-4.38E-01	-4.07E-01	-4.07E-01	-3.92E-01	-3.93E-01	-4.09E-01
Specification MAX	-2.00E-01	-1.30E-01	-1.20E-01	-1.20E-01	-1.10E-01	-7.00E-02	-7.00E-02	-7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

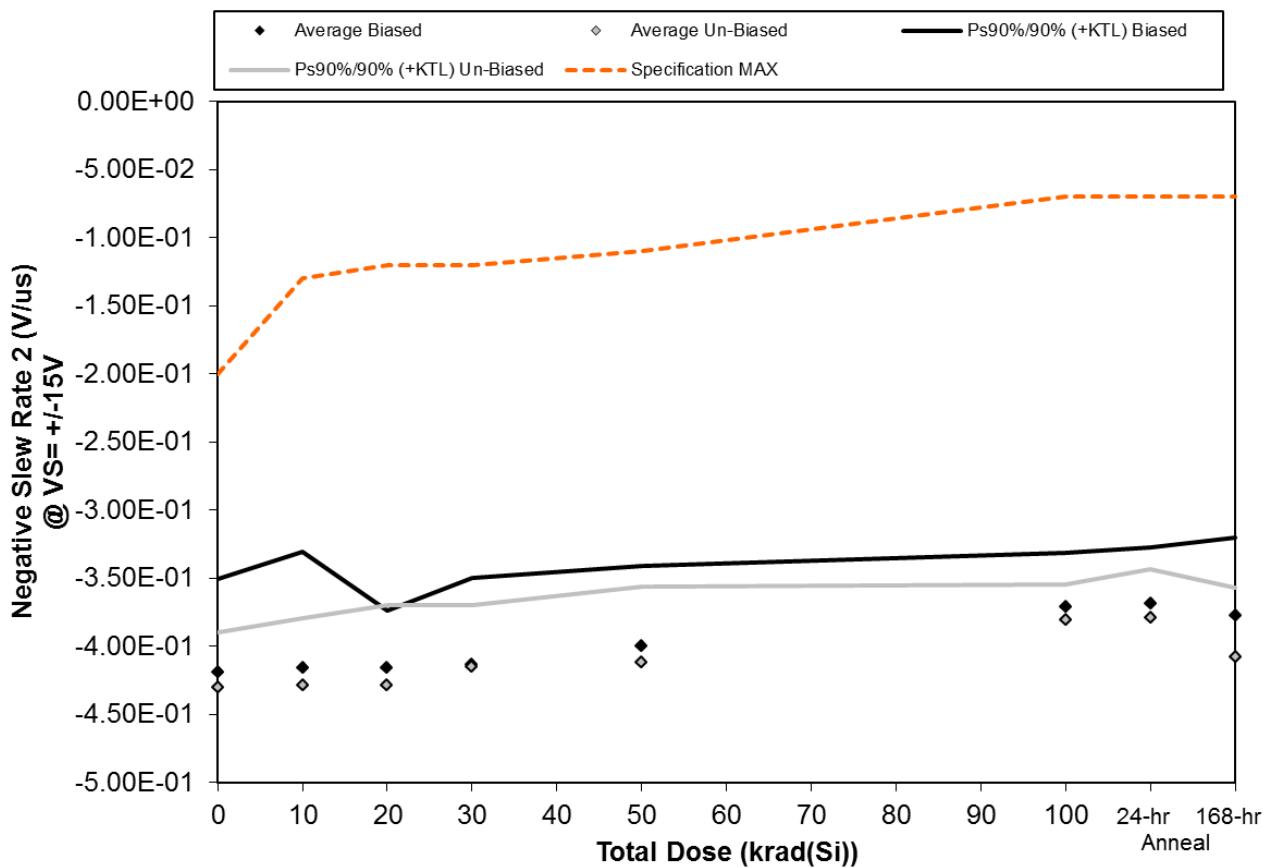


Figure 5.44. Plot of Negative Slew Rate 2 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.44. Raw data for Negative Slew Rate 2 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate 2 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-4.38E-01	-4.30E-01	-4.21E-01	-4.28E-01	-3.95E-01	-3.69E-01	-3.64E-01	-3.85E-01
260	-4.02E-01	-3.94E-01	-4.13E-01	-4.02E-01	-4.12E-01	-3.60E-01	-3.69E-01	-3.67E-01
326	-3.86E-01	-3.86E-01	-3.99E-01	-3.89E-01	-3.71E-01	-3.62E-01	-3.57E-01	-3.59E-01
328	-4.46E-01	-4.62E-01	-4.39E-01	-4.46E-01	-4.27E-01	-3.96E-01	-3.94E-01	-4.11E-01
329	-4.21E-01	-4.05E-01	-4.07E-01	-4.01E-01	-3.92E-01	-3.68E-01	-3.58E-01	-3.66E-01
330	-4.44E-01	-4.53E-01	-4.44E-01	-4.07E-01	-4.31E-01	-3.93E-01	-3.85E-01	-4.04E-01
331	-4.41E-01	-4.35E-01	-4.51E-01	-4.20E-01	-4.30E-01	-3.88E-01	-3.92E-01	-4.29E-01
334	-4.23E-01	-4.29E-01	-4.02E-01	-4.04E-01	-4.12E-01	-3.71E-01	-3.64E-01	-4.05E-01
335	-4.08E-01	-4.05E-01	-4.10E-01	-4.01E-01	-3.81E-01	-3.78E-01	-3.66E-01	-3.80E-01
344	-4.36E-01	-4.19E-01	-4.35E-01	-4.41E-01	-4.06E-01	-3.73E-01	-3.86E-01	-4.19E-01
346	-4.36E-01	-4.35E-01	-4.31E-01	-4.46E-01	-4.15E-01	-4.24E-01	-4.14E-01	-4.32E-01
Biased Statistics								
Average Biased	-4.19E-01	-4.15E-01	-4.16E-01	-4.13E-01	-3.99E-01	-3.71E-01	-3.68E-01	-3.78E-01
Std Dev Biased	2.49E-02	3.09E-02	1.53E-02	2.32E-02	2.12E-02	1.45E-02	1.51E-02	2.10E-02
Ps90%/90% (+KTL) Biased	-3.50E-01	-3.31E-01	-3.74E-01	-3.50E-01	-3.41E-01	-3.31E-01	-3.27E-01	-3.20E-01
Ps90%/90% (-KTL) Biased	-4.87E-01	-5.00E-01	-4.58E-01	-4.77E-01	-4.58E-01	-4.11E-01	-4.10E-01	-4.35E-01
Un-Biased Statistics								
Average Un-Biased	-4.30E-01	-4.28E-01	-4.28E-01	-4.15E-01	-4.12E-01	-3.81E-01	-3.79E-01	-4.07E-01
Std Dev Un-Biased	1.49E-02	1.79E-02	2.14E-02	1.64E-02	2.05E-02	9.56E-03	1.27E-02	1.85E-02
Ps90%/90% (+KTL) Un-Biased	-3.90E-01	-3.79E-01	-3.70E-01	-3.70E-01	-3.56E-01	-3.54E-01	-3.44E-01	-3.57E-01
Ps90%/90% (-KTL) Un-Biased	-4.71E-01	-4.77E-01	-4.87E-01	-4.60E-01	-4.68E-01	-4.07E-01	-4.13E-01	-4.58E-01
Specification MAX	-2.00E-01	-1.30E-01	-1.20E-01	-1.20E-01	-1.10E-01	-7.00E-02	-7.00E-02	-7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

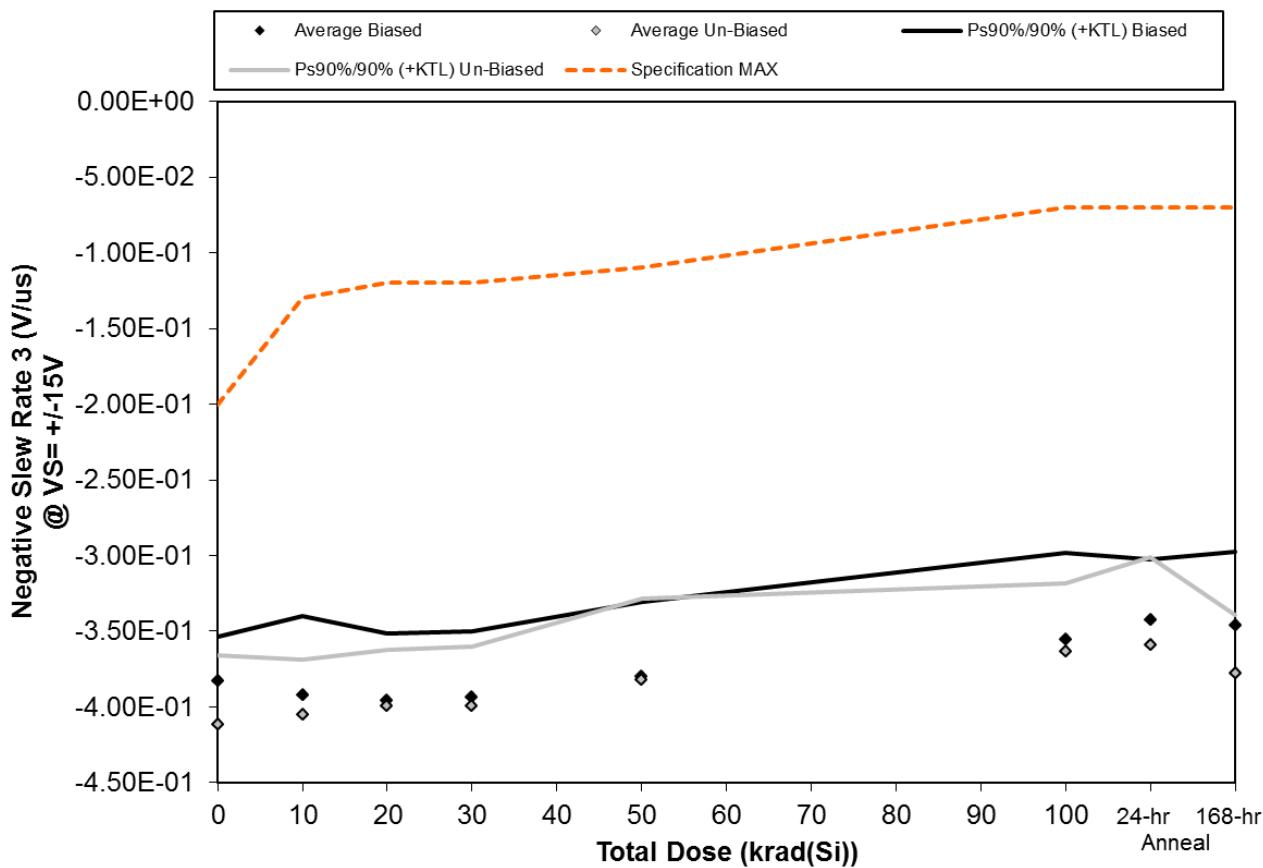


Figure 5.45. Plot of Negative Slew Rate 3 (V/us) @ VS = +/-15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.45. Raw data for Negative Slew Rate 3 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate 3 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-3.92E-01	-4.06E-01	-3.90E-01	-4.14E-01	-3.92E-01	-3.44E-01	-3.38E-01	-3.49E-01
260	-3.82E-01	-3.79E-01	-3.89E-01	-3.89E-01	-3.80E-01	-3.78E-01	-3.39E-01	-3.24E-01
326	-3.65E-01	-3.68E-01	-3.76E-01	-3.73E-01	-3.51E-01	-3.33E-01	-3.28E-01	-3.32E-01
328	-3.89E-01	-4.14E-01	-4.17E-01	-4.05E-01	-3.97E-01	-3.77E-01	-3.67E-01	-3.64E-01
329	-3.87E-01	-3.92E-01	-4.07E-01	-3.88E-01	-3.78E-01	-3.44E-01	-3.40E-01	-3.62E-01
330	-4.21E-01	-3.99E-01	-3.96E-01	-4.12E-01	-4.02E-01	-3.90E-01	-3.77E-01	-3.62E-01
331	-4.27E-01	-4.16E-01	-4.03E-01	-4.13E-01	-3.96E-01	-3.67E-01	-3.77E-01	-3.84E-01
334	-3.89E-01	-3.89E-01	-3.99E-01	-3.92E-01	-3.71E-01	-3.53E-01	-3.35E-01	-3.86E-01
335	-3.99E-01	-3.99E-01	-3.81E-01	-3.79E-01	-3.54E-01	-3.48E-01	-3.37E-01	-3.64E-01
344	-4.22E-01	-4.21E-01	-4.19E-01	-4.01E-01	-3.87E-01	-3.60E-01	-3.68E-01	-3.93E-01
346	-4.17E-01	-4.03E-01	-4.10E-01	-3.98E-01	-4.06E-01	-3.99E-01	-4.09E-01	-4.03E-01
Biased Statistics								
Average Biased	-3.83E-01	-3.92E-01	-3.96E-01	-3.94E-01	-3.80E-01	-3.55E-01	-3.42E-01	-3.46E-01
Std Dev Biased	1.07E-02	1.89E-02	1.62E-02	1.60E-02	1.79E-02	2.08E-02	1.46E-02	1.78E-02
Ps90%/90% (+KTL) Biased	-3.54E-01	-3.40E-01	-3.51E-01	-3.50E-01	-3.31E-01	-2.98E-01	-3.02E-01	-2.97E-01
Ps90%/90% (-KTL) Biased	-4.12E-01	-4.44E-01	-4.40E-01	-4.38E-01	-4.29E-01	-4.12E-01	-3.82E-01	-3.95E-01
Un-Biased Statistics								
Average Un-Biased	-4.12E-01	-4.05E-01	-4.00E-01	-3.99E-01	-3.82E-01	-3.64E-01	-3.59E-01	-3.78E-01
Std Dev Un-Biased	1.66E-02	1.33E-02	1.37E-02	1.43E-02	1.95E-02	1.64E-02	2.11E-02	1.39E-02
Ps90%/90% (+KTL) Un-Biased	-3.66E-01	-3.68E-01	-3.62E-01	-3.60E-01	-3.28E-01	-3.19E-01	-3.01E-01	-3.40E-01
Ps90%/90% (-KTL) Un-Biased	-4.57E-01	-4.41E-01	-4.37E-01	-4.39E-01	-4.36E-01	-4.09E-01	-4.17E-01	-4.16E-01
Specification MAX	-2.00E-01	-1.30E-01	-1.20E-01	-1.20E-01	-1.10E-01	-7.00E-02	-7.00E-02	-7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

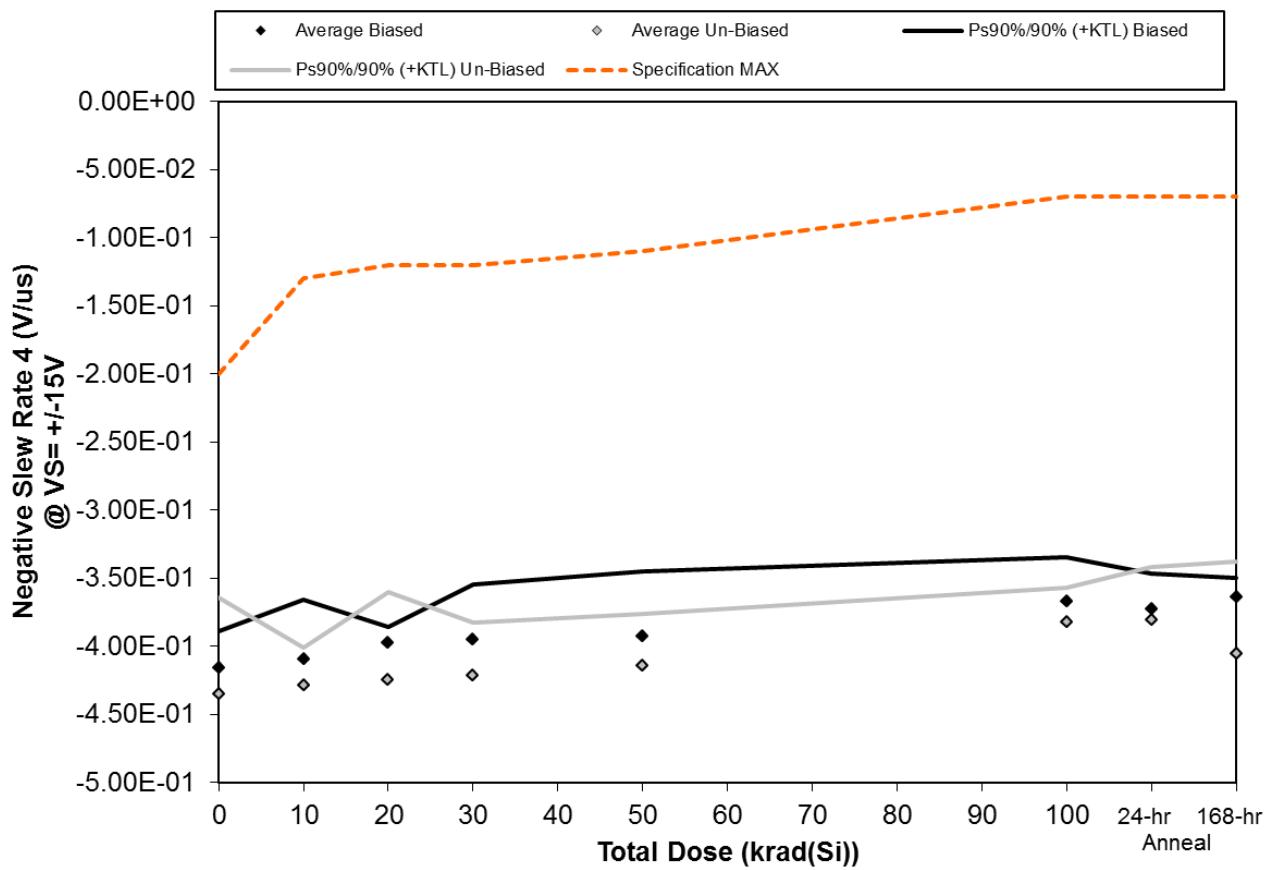


Figure 5.46. Plot of Negative Slew Rate 4 (V/us) @ VS = +/- 15V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.46. Raw data for Negative Slew Rate 4 (V/us) @ VS= +/-15V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Slew Rate 4 (V/us) @ VS= +/-15V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-4.15E-01	-4.06E-01	-3.99E-01	-4.17E-01	-4.18E-01	-3.73E-01	-3.81E-01	-3.68E-01
260	-4.19E-01	-3.99E-01	-3.92E-01	-3.89E-01	-3.79E-01	-3.84E-01	-3.57E-01	-3.64E-01
326	-4.00E-01	-3.94E-01	-4.03E-01	-3.86E-01	-3.75E-01	-3.55E-01	-3.78E-01	-3.63E-01
328	-4.27E-01	-4.13E-01	-3.96E-01	-3.80E-01	-4.00E-01	-3.58E-01	-3.71E-01	-3.56E-01
329	-4.19E-01	-4.35E-01	-3.95E-01	-4.02E-01	-3.91E-01	-3.65E-01	-3.75E-01	-3.69E-01
330	-4.25E-01	-4.18E-01	-4.02E-01	-4.07E-01	-4.04E-01	-3.96E-01	-3.82E-01	-3.85E-01
331	-4.67E-01	-4.42E-01	-4.51E-01	-4.44E-01	-4.25E-01	-3.80E-01	-3.98E-01	-4.37E-01
334	-4.44E-01	-4.32E-01	-4.48E-01	-4.25E-01	-4.20E-01	-3.85E-01	-3.88E-01	-4.27E-01
335	-3.97E-01	-4.33E-01	-4.18E-01	-4.16E-01	-3.95E-01	-3.75E-01	-3.63E-01	-3.88E-01
344	-4.41E-01	-4.19E-01	-4.04E-01	-4.15E-01	-4.26E-01	-3.73E-01	-3.70E-01	-3.90E-01
346	-4.08E-01	-4.01E-01	-4.15E-01	-4.08E-01	-4.14E-01	-4.16E-01	-4.24E-01	-4.25E-01
Biased Statistics								
Average Biased	-4.16E-01	-4.09E-01	-3.97E-01	-3.95E-01	-3.93E-01	-3.67E-01	-3.72E-01	-3.64E-01
Std Dev Biased	9.95E-03	1.60E-02	4.18E-03	1.48E-02	1.73E-02	1.18E-02	9.37E-03	5.15E-03
Ps90%/90% (+KTL) Biased	-3.89E-01	-3.66E-01	-3.86E-01	-3.54E-01	-3.45E-01	-3.35E-01	-3.47E-01	-3.50E-01
Ps90%/90% (-KTL) Biased	-4.43E-01	-4.53E-01	-4.08E-01	-4.35E-01	-4.40E-01	-3.99E-01	-3.98E-01	-3.78E-01
Un-Biased Statistics								
Average Un-Biased	-4.35E-01	-4.29E-01	-4.25E-01	-4.21E-01	-4.14E-01	-3.82E-01	-3.80E-01	-4.05E-01
Std Dev Un-Biased	2.59E-02	1.02E-02	2.36E-02	1.42E-02	1.38E-02	9.20E-03	1.40E-02	2.46E-02
Ps90%/90% (+KTL) Un-Biased	-3.64E-01	-4.01E-01	-3.60E-01	-3.83E-01	-3.76E-01	-3.57E-01	-3.42E-01	-3.38E-01
Ps90%/90% (-KTL) Un-Biased	-5.06E-01	-4.57E-01	-4.89E-01	-4.60E-01	-4.52E-01	-4.07E-01	-4.19E-01	-4.73E-01
Specification MAX	-2.00E-01	-1.30E-01	-1.20E-01	-1.20E-01	-1.10E-01	-7.00E-02	-7.00E-02	-7.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

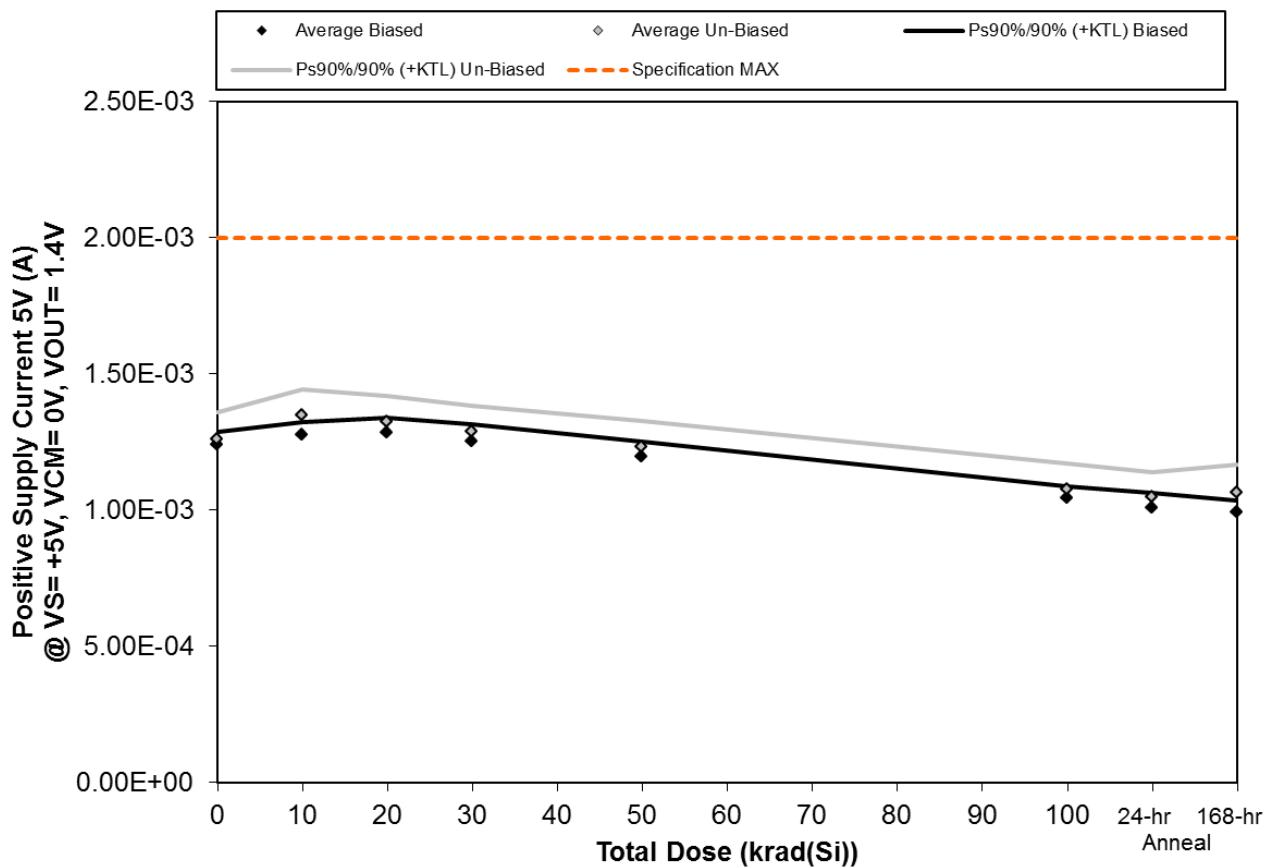


Figure 5.47. Plot of Positive Supply Current 5V (A) @ V_S= +5V, V_{CM}= 0V, V_{OUT}= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.47. Raw data for Positive Supply Current 5V (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Supply Current 5V (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.23E-03	1.27E-03	1.27E-03	1.25E-03	1.19E-03	1.04E-03	9.98E-04	9.82E-04
260	1.24E-03	1.27E-03	1.29E-03	1.25E-03	1.20E-03	1.03E-03	1.00E-03	9.86E-04
326	1.23E-03	1.26E-03	1.26E-03	1.23E-03	1.18E-03	1.03E-03	9.91E-04	9.80E-04
328	1.27E-03	1.30E-03	1.32E-03	1.29E-03	1.23E-03	1.07E-03	1.04E-03	1.02E-03
329	1.24E-03	1.28E-03	1.29E-03	1.25E-03	1.20E-03	1.04E-03	1.01E-03	9.91E-04
330	1.30E-03	1.38E-03	1.36E-03	1.32E-03	1.27E-03	1.11E-03	1.08E-03	1.10E-03
331	1.30E-03	1.38E-03	1.36E-03	1.33E-03	1.27E-03	1.11E-03	1.09E-03	1.11E-03
334	1.23E-03	1.32E-03	1.30E-03	1.26E-03	1.20E-03	1.04E-03	1.02E-03	1.03E-03
335	1.22E-03	1.31E-03	1.28E-03	1.25E-03	1.20E-03	1.05E-03	1.02E-03	1.03E-03
344	1.26E-03	1.35E-03	1.33E-03	1.29E-03	1.23E-03	1.07E-03	1.04E-03	1.06E-03
346	1.27E-03	1.26E-03	1.27E-03	1.26E-03	1.26E-03	1.26E-03	1.26E-03	1.26E-03
Biased Statistics								
Average Biased	1.24E-03	1.28E-03	1.28E-03	1.25E-03	1.20E-03	1.04E-03	1.01E-03	9.92E-04
Std Dev Biased	1.70E-05	1.71E-05	1.99E-05	2.19E-05	1.92E-05	1.55E-05	1.98E-05	1.63E-05
Ps90%/90% (+KTL) Biased	1.29E-03	1.32E-03	1.34E-03	1.31E-03	1.25E-03	1.09E-03	1.06E-03	1.04E-03
Ps90%/90% (-KTL) Biased	1.19E-03	1.23E-03	1.23E-03	1.19E-03	1.15E-03	1.00E-03	9.54E-04	9.47E-04
Un-Biased Statistics								
Average Un-Biased	1.26E-03	1.35E-03	1.33E-03	1.29E-03	1.23E-03	1.08E-03	1.05E-03	1.06E-03
Std Dev Un-Biased	3.65E-05	3.53E-05	3.46E-05	3.35E-05	3.40E-05	3.56E-05	3.31E-05	3.74E-05
Ps90%/90% (+KTL) Un-Biased	1.36E-03	1.44E-03	1.42E-03	1.38E-03	1.33E-03	1.17E-03	1.14E-03	1.17E-03
Ps90%/90% (-KTL) Un-Biased	1.16E-03	1.25E-03	1.23E-03	1.20E-03	1.14E-03	9.78E-04	9.59E-04	9.61E-04
Specification MAX	2.00E-03	2.00E-03	2.00E-03	2.00E-03	2.00E-03	2.00E-03	2.00E-03	2.00E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

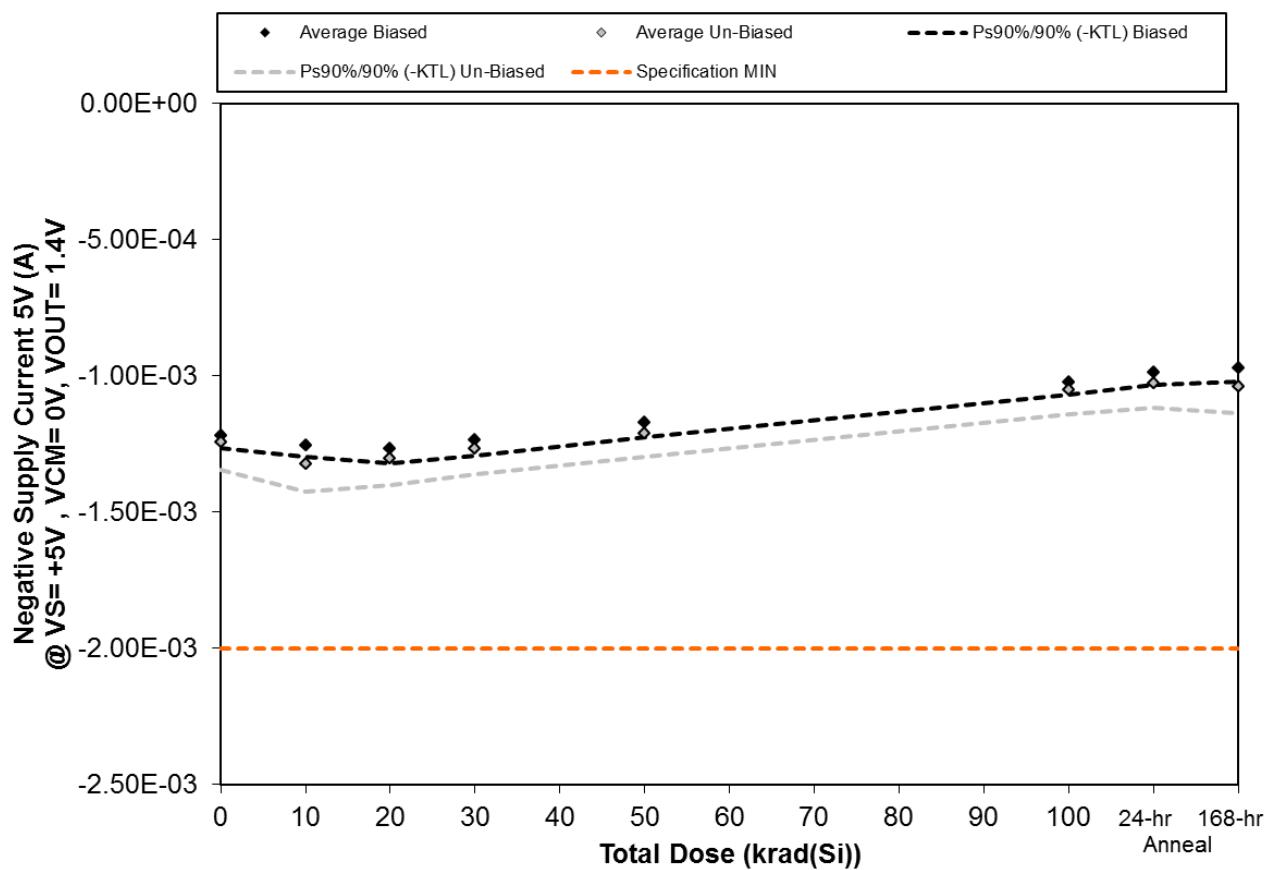


Figure 5.48. Plot of Negative Supply Current 5V (A) @ VS= +5V , VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.48. Raw data for Negative Supply Current 5V (A) @ VS= +5V , VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Supply Current 5V (A) @ VS= +5V , VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	-1.21E-03	-1.25E-03	-1.27E-03	-1.22E-03	-1.16E-03	-1.02E-03	-9.76E-04	-9.62E-04
260	-1.22E-03	-1.25E-03	-1.27E-03	-1.23E-03	-1.18E-03	-1.02E-03	-9.86E-04	-9.72E-04
326	-1.20E-03	-1.24E-03	-1.24E-03	-1.21E-03	-1.15E-03	-1.01E-03	-9.72E-04	-9.58E-04
328	-1.25E-03	-1.28E-03	-1.29E-03	-1.27E-03	-1.20E-03	-1.05E-03	-1.02E-03	-1.00E-03
329	-1.22E-03	-1.26E-03	-1.26E-03	-1.23E-03	-1.17E-03	-1.02E-03	-9.86E-04	-9.70E-04
330	-1.28E-03	-1.36E-03	-1.34E-03	-1.30E-03	-1.24E-03	-1.09E-03	-1.06E-03	-1.07E-03
331	-1.28E-03	-1.36E-03	-1.34E-03	-1.30E-03	-1.24E-03	-1.09E-03	-1.07E-03	-1.08E-03
334	-1.21E-03	-1.29E-03	-1.28E-03	-1.24E-03	-1.18E-03	-1.02E-03	-9.87E-04	-1.00E-03
335	-1.20E-03	-1.28E-03	-1.26E-03	-1.23E-03	-1.18E-03	-1.02E-03	-1.01E-03	-1.01E-03
344	-1.24E-03	-1.33E-03	-1.30E-03	-1.27E-03	-1.21E-03	-1.05E-03	-1.02E-03	-1.03E-03
346	-1.24E-03	-1.24E-03	-1.24E-03	-1.24E-03	-1.25E-03	-1.24E-03	-1.25E-03	-1.25E-03
Biased Statistics								
Average Biased	-1.22E-03	-1.26E-03	-1.27E-03	-1.23E-03	-1.17E-03	-1.02E-03	-9.87E-04	-9.73E-04
Std Dev Biased	1.67E-05	1.47E-05	2.01E-05	2.14E-05	1.85E-05	1.80E-05	1.68E-05	1.73E-05
Ps90%/90% (+KTL) Biased	-1.17E-03	-1.22E-03	-1.21E-03	-1.18E-03	-1.12E-03	-9.72E-04	-9.41E-04	-9.25E-04
Ps90%/90% (-KTL) Biased	-1.27E-03	-1.30E-03	-1.32E-03	-1.29E-03	-1.22E-03	-1.07E-03	-1.03E-03	-1.02E-03
Un-Biased Statistics								
Average Un-Biased	-1.24E-03	-1.32E-03	-1.30E-03	-1.27E-03	-1.21E-03	-1.05E-03	-1.03E-03	-1.04E-03
Std Dev Un-Biased	3.64E-05	3.66E-05	3.56E-05	3.33E-05	3.16E-05	3.28E-05	3.28E-05	3.68E-05
Ps90%/90% (+KTL) Un-Biased	-1.14E-03	-1.22E-03	-1.21E-03	-1.18E-03	-1.12E-03	-9.63E-04	-9.37E-04	-9.37E-04
Ps90%/90% (-KTL) Un-Biased	-1.34E-03	-1.42E-03	-1.40E-03	-1.36E-03	-1.30E-03	-1.14E-03	-1.12E-03	-1.14E-03
Specification MIN	-2.00E-03	-2.00E-03	-2.00E-03	-2.00E-03	-2.00E-03	-2.00E-03	-2.00E-03	-2.00E-03
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

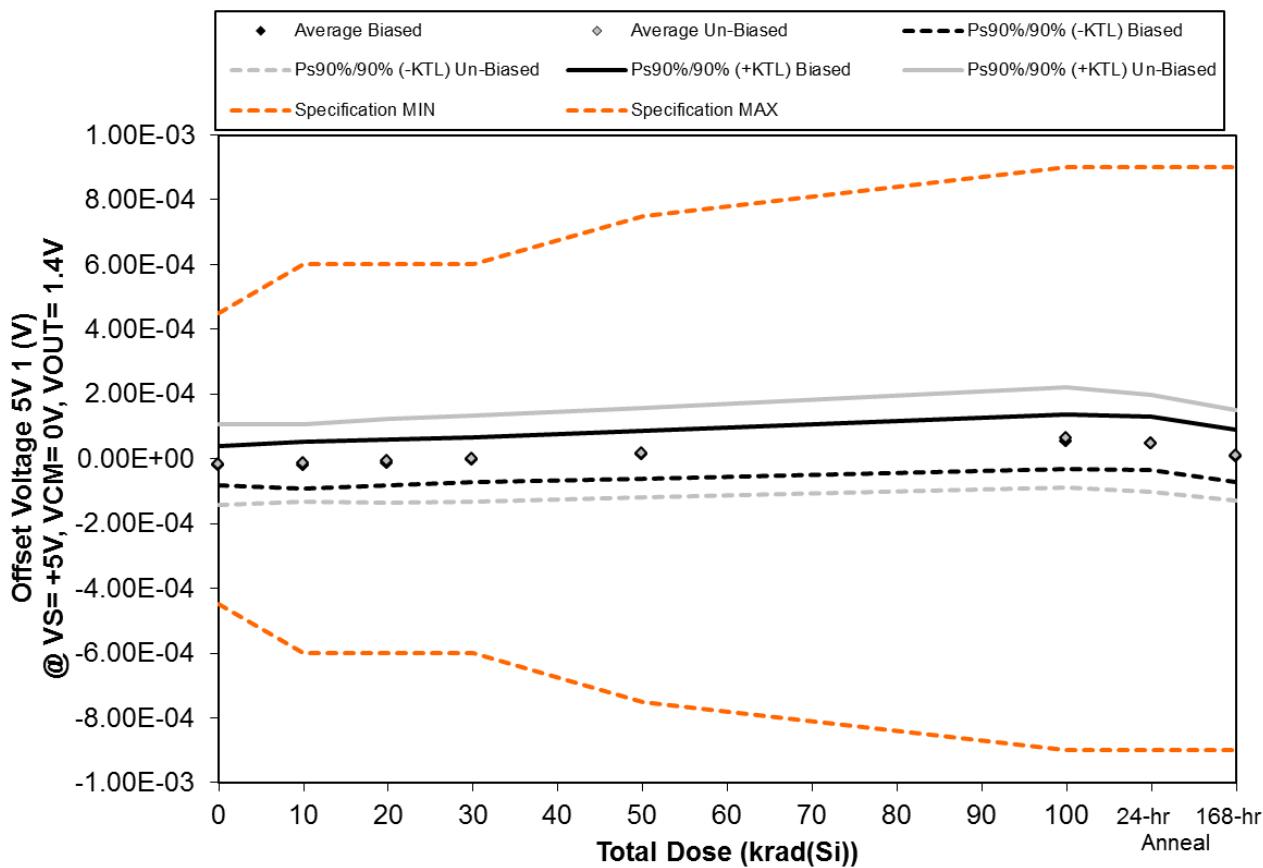


Figure 5.49. Plot of Offset Voltage 5V 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.49. Raw data for Offset Voltage 5V 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 5V 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	-4.82E-05	-4.95E-05	-4.47E-05	-3.66E-05	-2.46E-05	6.70E-06	4.93E-06	-3.32E-05
260	5.99E-06	1.02E-05	1.43E-05	2.32E-05	4.12E-05	8.96E-05	8.25E-05	4.19E-05
326	-3.53E-05	-4.24E-05	-3.26E-05	-2.21E-05	-4.57E-06	4.58E-05	3.37E-05	-9.39E-06
328	-1.77E-05	-1.10E-05	-1.49E-06	6.54E-06	2.46E-05	6.93E-05	6.65E-05	2.42E-05
329	-4.20E-06	-1.41E-06	6.65E-06	1.38E-05	2.66E-05	5.82E-05	5.63E-05	1.89E-05
330	3.51E-05	3.20E-05	4.37E-05	5.27E-05	7.14E-05	1.31E-04	1.13E-04	6.30E-05
331	-6.50E-05	-6.18E-05	-5.88E-05	-5.38E-05	-3.78E-05	3.49E-06	-1.30E-05	-5.16E-05
334	-5.57E-05	-5.23E-05	-4.88E-05	-4.10E-05	-2.73E-05	1.35E-05	-1.56E-06	-3.33E-05
335	-2.01E-05	-1.12E-05	-2.29E-06	9.15E-06	2.47E-05	7.54E-05	6.18E-05	1.71E-05
344	2.44E-05	2.87E-05	3.56E-05	4.43E-05	6.23E-05	1.06E-04	8.54E-05	5.31E-05
346	-4.76E-05	-4.75E-05	-4.78E-05	-4.71E-05	-4.73E-05	-4.79E-05	-4.75E-05	-4.82E-05
Biased Statistics								
Average Biased	-1.99E-05	-1.88E-05	-1.16E-05	-3.03E-06	1.27E-05	5.39E-05	4.88E-05	8.47E-06
Std Dev Biased	2.21E-05	2.60E-05	2.57E-05	2.53E-05	2.66E-05	3.09E-05	3.02E-05	2.97E-05
Ps90%/90% (+KTL) Biased	4.08E-05	5.24E-05	5.89E-05	6.62E-05	8.57E-05	1.39E-04	1.32E-04	8.99E-05
Ps90%/90% (-KTL) Biased	-8.06E-05	-9.01E-05	-8.20E-05	-7.23E-05	-6.04E-05	-3.09E-05	-3.41E-05	-7.29E-05
Un-Biased Statistics								
Average Un-Biased	-1.63E-05	-1.29E-05	-6.12E-06	2.27E-06	1.87E-05	6.59E-05	4.91E-05	9.67E-06
Std Dev Un-Biased	4.54E-05	4.39E-05	4.70E-05	4.84E-05	5.01E-05	5.61E-05	5.46E-05	5.09E-05
Ps90%/90% (+KTL) Un-Biased	1.08E-04	1.07E-04	1.23E-04	1.35E-04	1.56E-04	2.20E-04	1.99E-04	1.49E-04
Ps90%/90% (-KTL) Un-Biased	-1.41E-04	-1.33E-04	-1.35E-04	-1.30E-04	-1.19E-04	-8.79E-05	-1.01E-04	-1.30E-04
Specification MIN	-4.50E-04	-6.00E-04	-6.00E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	4.50E-04	6.00E-04	6.00E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

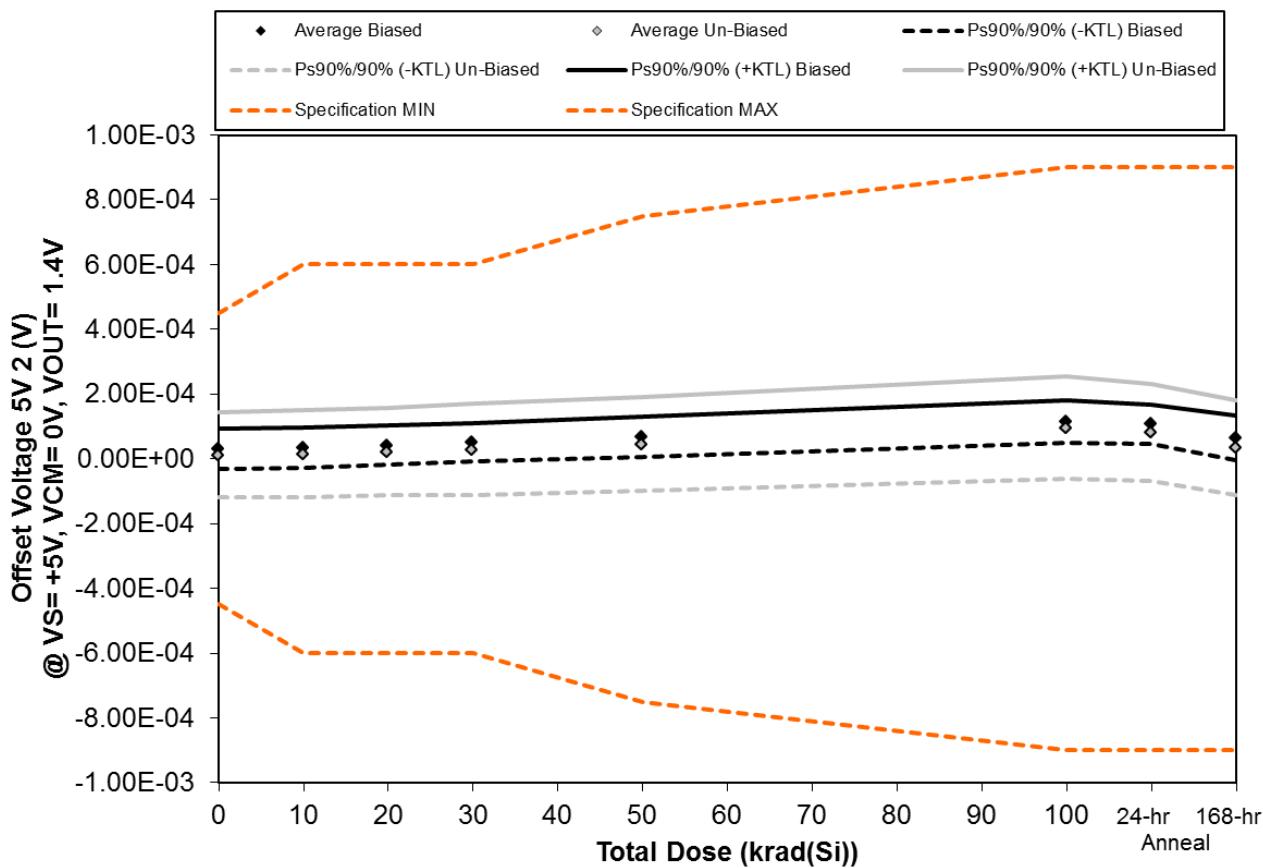


Figure 5.50. Plot of Offset Voltage 5V 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.50. Raw data for Offset Voltage 5V 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 5V 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.89E-05	2.34E-05	3.22E-05	4.32E-05	6.33E-05	1.08E-04	1.05E-04	6.39E-05
260	5.61E-05	6.32E-05	7.15E-05	7.84E-05	1.00E-04	1.51E-04	1.34E-04	9.25E-05
326	2.42E-06	7.35E-06	1.58E-05	2.41E-05	3.76E-05	8.51E-05	7.38E-05	2.32E-05
328	5.37E-05	5.21E-05	5.71E-05	6.63E-05	7.67E-05	1.13E-04	1.13E-04	7.32E-05
329	2.42E-05	2.41E-05	3.51E-05	4.38E-05	6.60E-05	1.24E-04	1.10E-04	6.85E-05
330	1.77E-05	2.49E-05	3.34E-05	4.20E-05	5.95E-05	1.11E-04	9.56E-05	4.63E-05
331	7.92E-05	8.46E-05	8.93E-05	1.00E-04	1.18E-04	1.74E-04	1.55E-04	1.11E-04
334	-5.34E-05	-4.95E-05	-4.45E-05	-3.88E-05	-2.44E-05	2.40E-05	1.61E-05	-3.42E-05
335	2.18E-05	2.11E-05	2.84E-05	3.80E-05	5.69E-05	1.15E-04	9.80E-05	3.80E-05
344	-6.76E-06	-5.45E-06	-8.11E-07	4.95E-06	1.82E-05	5.87E-05	4.27E-05	8.32E-06
346	1.99E-05	2.02E-05	2.05E-05	2.08E-05	2.04E-05	2.05E-05	2.01E-05	2.03E-05
Biased Statistics								
Average Biased	3.11E-05	3.40E-05	4.24E-05	5.12E-05	6.87E-05	1.16E-04	1.07E-04	6.43E-05
Std Dev Biased	2.32E-05	2.29E-05	2.20E-05	2.14E-05	2.26E-05	2.41E-05	2.17E-05	2.54E-05
Ps90%/90% (+KTL) Biased	9.47E-05	9.68E-05	1.03E-04	1.10E-04	1.31E-04	1.82E-04	1.67E-04	1.34E-04
Ps90%/90% (-KTL) Biased	-3.26E-05	-2.88E-05	-1.79E-05	-7.41E-06	6.60E-06	5.02E-05	4.76E-05	-5.37E-06
Un-Biased Statistics								
Average Un-Biased	1.17E-05	1.51E-05	2.12E-05	2.93E-05	4.56E-05	9.63E-05	8.15E-05	3.38E-05
Std Dev Un-Biased	4.81E-05	4.89E-05	4.91E-05	5.12E-05	5.29E-05	5.74E-05	5.41E-05	5.33E-05
Ps90%/90% (+KTL) Un-Biased	1.44E-04	1.49E-04	1.56E-04	1.70E-04	1.91E-04	2.54E-04	2.30E-04	1.80E-04
Ps90%/90% (-KTL) Un-Biased	-1.20E-04	-1.19E-04	-1.13E-04	-1.11E-04	-9.95E-05	-6.09E-05	-6.68E-05	-1.12E-04
Specification MIN	-4.50E-04	-6.00E-04	-6.00E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	4.50E-04	6.00E-04	6.00E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

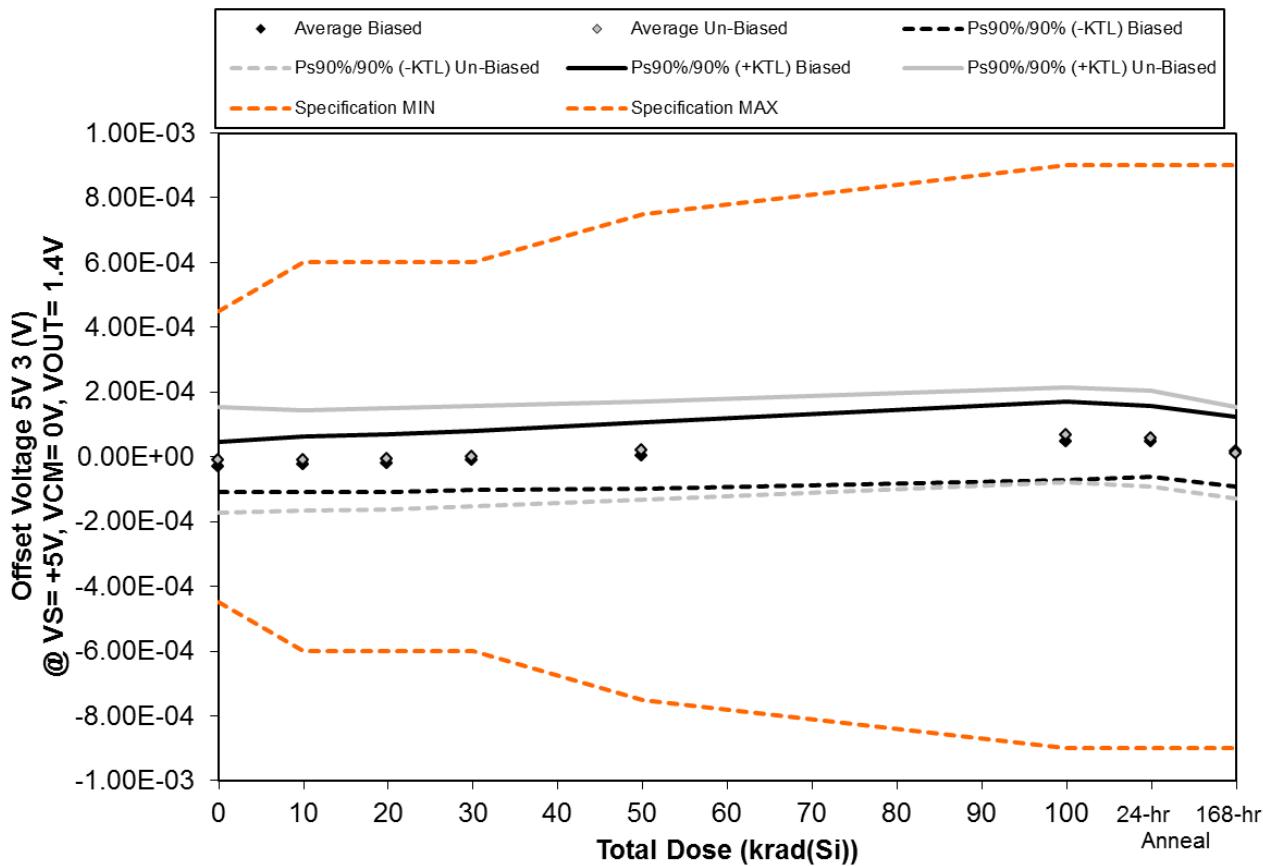


Figure 5.51. Plot of Offset Voltage 5V 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.51. Raw data for Offset Voltage 5V 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 5V 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	-1.11E-06	3.88E-06	1.01E-05	1.73E-05	2.96E-05	7.01E-05	7.13E-05	4.59E-05
260	-1.33E-05	-5.84E-06	1.98E-06	9.45E-06	2.32E-05	6.96E-05	6.28E-05	4.15E-05
326	-1.67E-05	-3.29E-06	2.31E-06	1.20E-05	3.88E-05	9.46E-05	9.03E-05	4.63E-05
328	-6.64E-05	-6.47E-05	-6.24E-05	-5.72E-05	-4.84E-05	-1.64E-05	-8.58E-06	-3.41E-05
329	-5.54E-05	-5.08E-05	-4.45E-05	-3.60E-05	-1.97E-05	2.58E-05	2.22E-05	-1.75E-05
330	5.18E-05	3.76E-05	4.02E-05	4.61E-05	5.92E-05	1.05E-04	8.91E-05	3.91E-05
331	-8.37E-05	-8.25E-05	-7.83E-05	-6.75E-05	-4.71E-05	1.77E-06	-1.13E-05	-5.18E-05
334	-5.70E-05	-5.94E-05	-5.33E-05	-4.72E-05	-2.95E-05	2.76E-05	1.49E-05	-2.78E-05
335	3.85E-05	4.01E-05	4.87E-05	5.55E-05	7.60E-05	1.31E-04	1.19E-04	7.50E-05
344	7.70E-06	1.10E-05	1.68E-05	2.44E-05	3.94E-05	7.83E-05	7.27E-05	2.44E-05
346	2.89E-05	2.86E-05	2.92E-05	2.94E-05	2.97E-05	2.98E-05	2.97E-05	2.90E-05
Biased Statistics								
Average Biased	-3.06E-05	-2.41E-05	-1.85E-05	-1.09E-05	4.70E-06	4.88E-05	4.76E-05	1.64E-05
Std Dev Biased	2.85E-05	3.12E-05	3.27E-05	3.36E-05	3.72E-05	4.41E-05	4.01E-05	3.90E-05
Ps90%/90% (+KTL) Biased	4.77E-05	6.15E-05	7.11E-05	8.12E-05	1.07E-04	1.70E-04	1.57E-04	1.23E-04
Ps90%/90% (-KTL) Biased	-1.09E-04	-1.10E-04	-1.08E-04	-1.03E-04	-9.74E-05	-7.21E-05	-6.22E-05	-9.06E-05
Un-Biased Statistics								
Average Un-Biased	-8.54E-06	-1.07E-05	-5.18E-06	2.25E-06	1.96E-05	6.87E-05	5.69E-05	1.18E-05
Std Dev Un-Biased	5.94E-05	5.68E-05	5.72E-05	5.61E-05	5.48E-05	5.36E-05	5.38E-05	5.13E-05
Ps90%/90% (+KTL) Un-Biased	1.54E-04	1.45E-04	1.52E-04	1.56E-04	1.70E-04	2.16E-04	2.04E-04	1.52E-04
Ps90%/90% (-KTL) Un-Biased	-1.71E-04	-1.66E-04	-1.62E-04	-1.51E-04	-1.31E-04	-7.81E-05	-9.05E-05	-1.29E-04
Specification MIN	-4.50E-04	-6.00E-04	-6.00E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	4.50E-04	6.00E-04	6.00E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

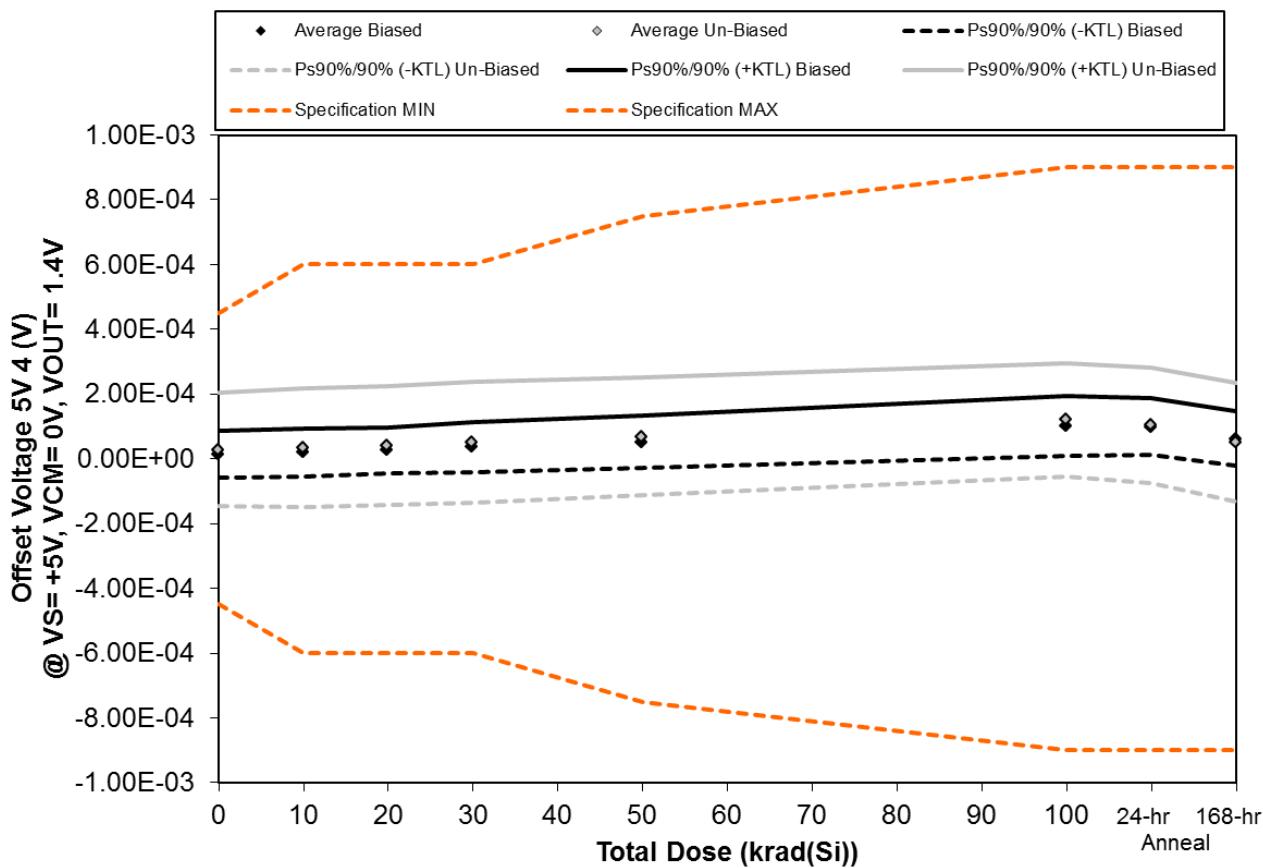


Figure 5.52. Plot of Offset Voltage 5V 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.52. Raw data for Offset Voltage 5V 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Voltage 5V 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.79E-05	3.21E-05	3.89E-05	4.86E-05	6.81E-05	1.15E-04	1.14E-04	7.85E-05
260	-1.43E-07	3.23E-06	1.12E-05	1.88E-05	3.56E-05	7.94E-05	7.02E-05	4.40E-05
326	-1.32E-05	-1.02E-06	7.88E-06	1.79E-05	3.58E-05	9.42E-05	9.07E-05	4.88E-05
328	5.14E-05	6.12E-05	6.74E-05	7.95E-05	9.76E-05	1.53E-04	1.48E-04	1.09E-04
329	-1.86E-06	2.03E-06	1.10E-05	1.59E-05	2.75E-05	6.57E-05	7.38E-05	3.47E-05
330	-3.97E-06	5.81E-07	8.46E-06	1.96E-05	4.12E-05	1.01E-04	8.32E-05	2.12E-05
331	7.27E-05	7.60E-05	8.16E-05	8.83E-05	1.05E-04	1.45E-04	1.26E-04	9.69E-05
334	4.12E-05	4.68E-05	5.15E-05	5.59E-05	6.99E-05	1.16E-04	1.02E-04	5.70E-05
335	9.75E-05	1.08E-04	1.19E-04	1.34E-04	1.52E-04	2.08E-04	1.93E-04	1.30E-04
344	-6.19E-05	-6.27E-05	-5.36E-05	-4.42E-05	-2.44E-05	3.35E-05	1.48E-05	-4.20E-05
346	-8.83E-07	1.86E-07	3.45E-07	3.78E-07	7.76E-07	1.77E-07	3.03E-07	5.97E-07
Biased Statistics								
Average Biased	1.28E-05	1.95E-05	2.73E-05	3.61E-05	5.29E-05	1.01E-04	9.93E-05	6.30E-05
Std Dev Biased	2.63E-05	2.69E-05	2.57E-05	2.77E-05	2.94E-05	3.40E-05	3.21E-05	3.04E-05
Ps90%/90% (+KTL) Biased	8.51E-05	9.32E-05	9.78E-05	1.12E-04	1.34E-04	1.94E-04	1.87E-04	1.46E-04
Ps90%/90% (-KTL) Biased	-5.94E-05	-5.42E-05	-4.32E-05	-3.99E-05	-2.77E-05	8.14E-06	1.12E-05	-2.04E-05
Un-Biased Statistics								
Average Un-Biased	2.91E-05	3.38E-05	4.14E-05	5.07E-05	6.86E-05	1.21E-04	1.04E-04	5.25E-05
Std Dev Un-Biased	6.35E-05	6.69E-05	6.68E-05	6.77E-05	6.63E-05	6.38E-05	6.47E-05	6.68E-05
Ps90%/90% (+KTL) Un-Biased	2.03E-04	2.17E-04	2.25E-04	2.36E-04	2.50E-04	2.96E-04	2.81E-04	2.36E-04
Ps90%/90% (-KTL) Un-Biased	-1.45E-04	-1.50E-04	-1.42E-04	-1.35E-04	-1.13E-04	-5.39E-05	-7.37E-05	-1.31E-04
Specification MIN	-4.50E-04	-6.00E-04	-6.00E-04	-6.00E-04	-7.50E-04	-9.00E-04	-9.00E-04	-9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	4.50E-04	6.00E-04	6.00E-04	6.00E-04	7.50E-04	9.00E-04	9.00E-04	9.00E-04
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

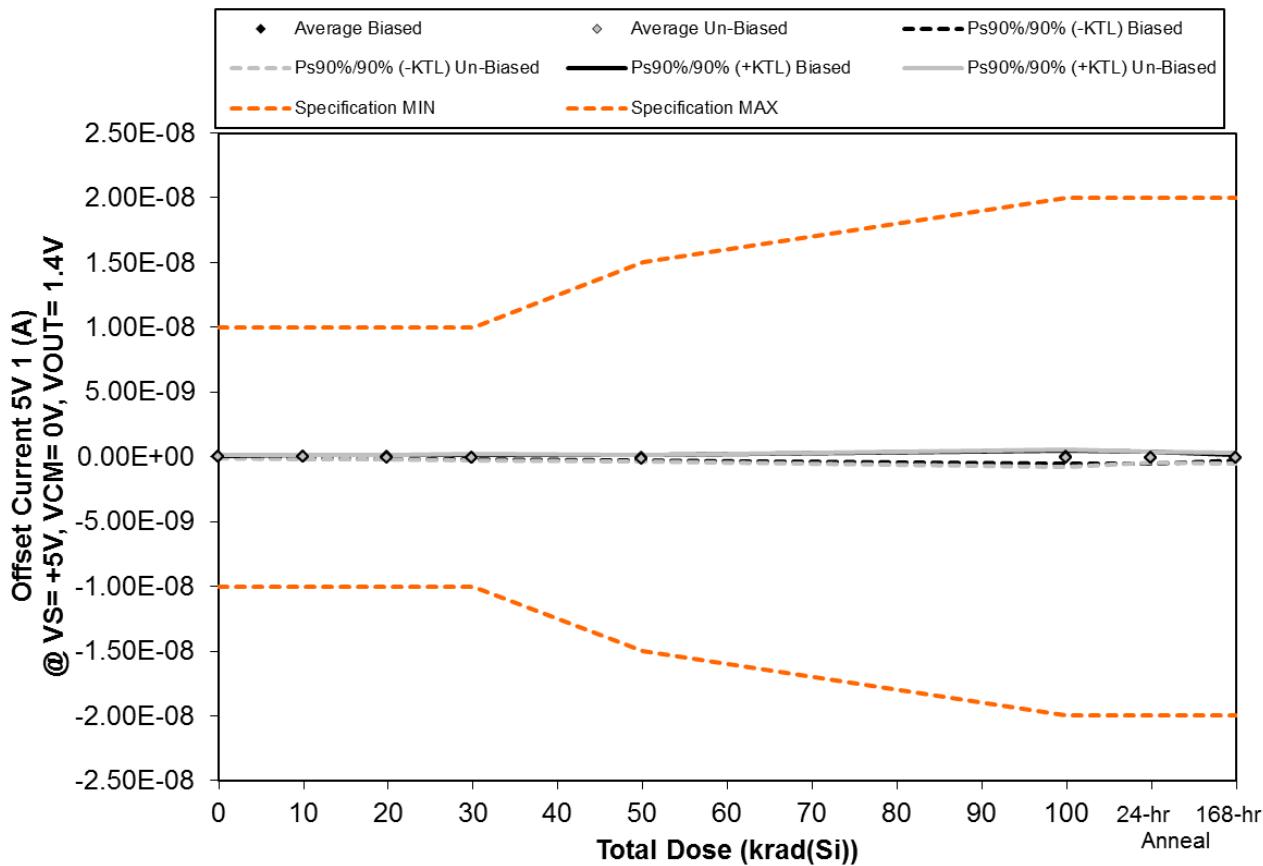


Figure 5.53. Plot of Offset Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.53. Raw data for Offset Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	4.20E-11	3.90E-11	1.80E-11	-7.50E-11	-3.60E-11	2.30E-11	-1.90E-11	-1.43E-10
260	3.00E-11	2.50E-11	7.30E-11	-1.10E-11	-8.90E-11	-1.08E-10	-2.20E-11	2.60E-11
326	2.10E-11	-1.50E-11	4.80E-11	7.50E-11	9.10E-11	1.98E-10	2.46E-10	-2.40E-11
328	3.40E-11	-6.50E-11	-8.60E-11	-4.30E-11	-7.30E-11	5.70E-11	-1.36E-10	-1.51E-10
329	-5.00E-12	-2.50E-11	-5.40E-11	-1.06E-10	-1.28E-10	-2.69E-10	-1.95E-10	-7.10E-11
330	-2.70E-11	-3.20E-11	-7.90E-11	-1.57E-10	3.00E-12	2.89E-10	1.66E-10	1.30E-10
331	6.10E-11	1.90E-11	-9.00E-12	8.00E-11	-8.30E-11	-1.90E-11	3.40E-11	-1.62E-10
334	3.40E-11	-9.70E-11	-1.39E-10	-1.16E-10	-2.30E-10	-3.10E-10	-2.18E-10	-2.72E-10
335	-2.20E-11	-8.00E-12	1.70E-11	-4.90E-11	-1.06E-10	-1.15E-10	-1.18E-10	-7.00E-11
344	1.02E-10	2.00E-11	-5.40E-11	-1.20E-11	-1.42E-10	-3.43E-10	-1.05E-10	6.00E-12
346	-7.10E-11	-4.10E-11	-4.50E-11	-7.50E-11	-4.90E-11	-7.20E-11	-6.60E-11	-3.80E-11
Biased Statistics								
Average Biased	2.44E-11	-8.20E-12	-2.00E-13	-3.20E-11	-4.70E-11	-1.98E-11	-2.52E-11	-7.26E-11
Std Dev Biased	1.81E-11	4.15E-11	6.76E-11	6.95E-11	8.39E-11	1.77E-10	1.69E-10	7.61E-11
Ps90%/90% (+KTL) Biased	7.40E-11	1.06E-10	1.85E-10	1.59E-10	1.83E-10	4.65E-10	4.39E-10	1.36E-10
Ps90%/90% (-KTL) Biased	-2.52E-11	-1.22E-10	-1.86E-10	-2.23E-10	-2.77E-10	-5.05E-10	-4.90E-10	-2.81E-10
Un-Biased Statistics								
Average Un-Biased	2.96E-11	-1.96E-11	-5.28E-11	-5.08E-11	-1.12E-10	-9.96E-11	-4.82E-11	-7.36E-11
Std Dev Un-Biased	5.50E-11	4.83E-11	6.11E-11	9.24E-11	8.50E-11	2.56E-10	1.50E-10	1.54E-10
Ps90%/90% (+KTL) Un-Biased	1.80E-10	1.13E-10	1.15E-10	2.03E-10	1.22E-10	6.01E-10	3.62E-10	3.49E-10
Ps90%/90% (-KTL) Un-Biased	-1.21E-10	-1.52E-10	-2.20E-10	-3.04E-10	-3.45E-10	-8.00E-10	-4.59E-10	-4.96E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

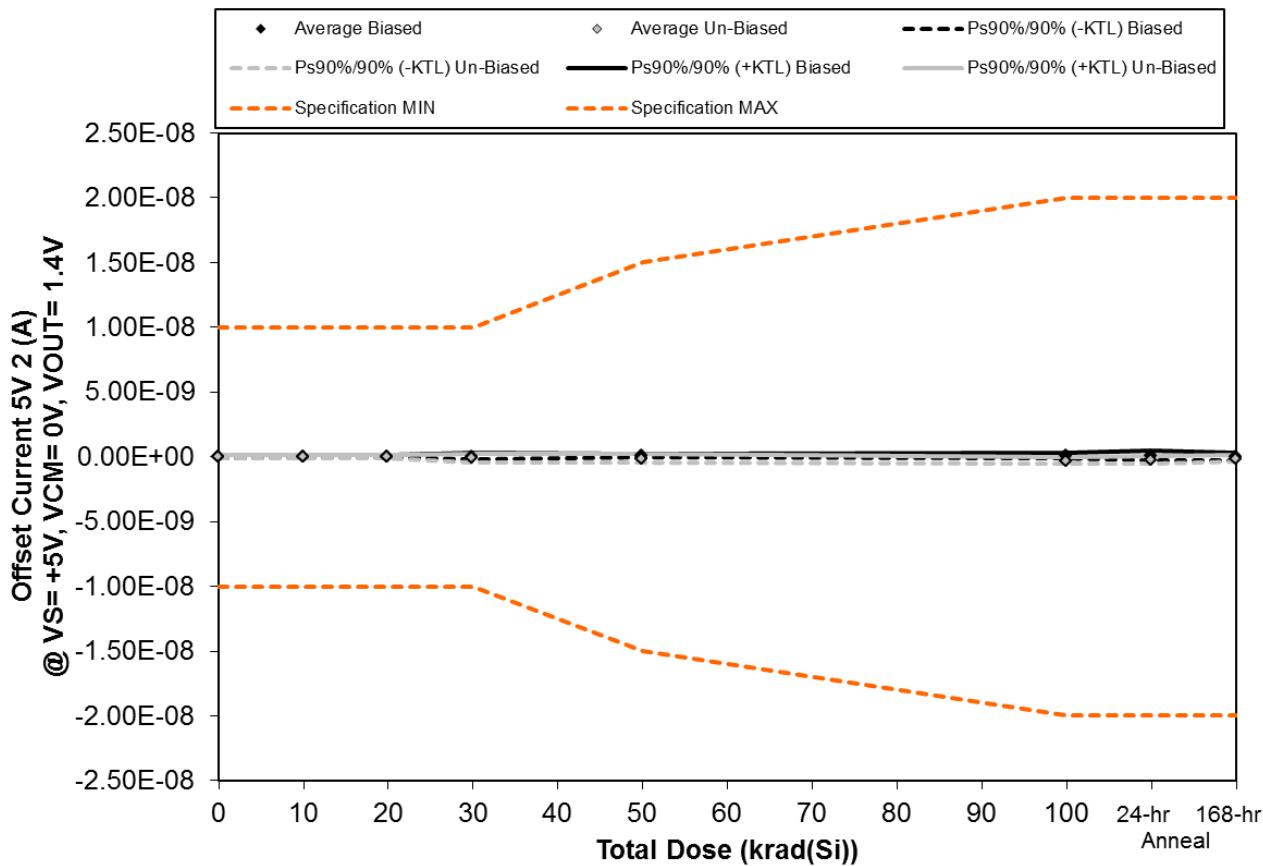


Figure 5.54. Plot of Offset Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.54. Raw data for Offset Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	7.30E-11	6.50E-11	4.20E-11	-1.12E-10	6.60E-11	-2.00E-12	8.90E-11	-9.90E-11
260	1.10E-11	-1.20E-11	5.30E-11	5.60E-11	1.64E-10	2.11E-10	3.18E-10	1.19E-10
326	4.60E-11	1.05E-10	6.30E-11	4.10E-11	5.50E-11	5.30E-11	9.50E-11	-3.00E-12
328	9.40E-11	4.80E-11	7.00E-11	5.70E-11	5.70E-11	1.17E-10	4.40E-11	1.78E-10
329	-2.80E-11	6.80E-11	-5.00E-12	1.30E-10	1.74E-10	1.20E-10	-6.50E-11	-5.50E-11
330	7.20E-11	8.00E-11	-2.70E-11	-1.59E-10	-2.62E-10	-4.42E-10	-4.02E-10	-2.00E-11
331	-1.20E-11	-5.50E-11	-3.90E-11	-1.50E-10	-2.30E-11	-2.16E-10	-1.25E-10	-1.55E-10
334	-2.80E-11	4.40E-11	-2.60E-11	-1.44E-10	-8.80E-11	-2.19E-10	-1.99E-10	-2.20E-10
335	1.50E-11	6.00E-12	-6.70E-11	-1.85E-10	-1.81E-10	-3.04E-10	-2.28E-10	-5.30E-11
344	-8.00E-12	7.30E-11	5.50E-11	1.06E-10	1.10E-11	-2.11E-10	-1.65E-10	-9.30E-11
346	2.80E-11	2.70E-11	7.00E-12	3.20E-11	3.10E-11	5.00E-12	4.30E-11	1.30E-11
Biased Statistics								
Average Biased	3.92E-11	5.48E-11	4.46E-11	3.44E-11	1.03E-10	9.98E-11	9.62E-11	2.80E-11
Std Dev Biased	4.87E-11	4.27E-11	2.97E-11	8.89E-11	6.03E-11	8.00E-11	1.40E-10	1.17E-10
Ps90%/90% (+KTL) Biased	1.73E-10	1.72E-10	1.26E-10	2.78E-10	2.69E-10	3.19E-10	4.79E-10	3.49E-10
Ps90%/90% (-KTL) Biased	-9.44E-11	-6.24E-11	-3.68E-11	-2.09E-10	-6.22E-11	-1.20E-10	-2.87E-10	-2.93E-10
Un-Biased Statistics								
Average Un-Biased	7.80E-12	2.96E-11	-2.08E-11	-1.06E-10	-1.09E-10	-2.78E-10	-2.24E-10	-1.08E-10
Std Dev Un-Biased	3.90E-11	5.56E-11	4.55E-11	1.20E-10	1.13E-10	9.92E-11	1.07E-10	8.02E-11
Ps90%/90% (+KTL) Un-Biased	1.15E-10	1.82E-10	1.04E-10	2.22E-10	2.00E-10	-6.32E-12	6.90E-11	1.12E-10
Ps90%/90% (-KTL) Un-Biased	-9.93E-11	-1.23E-10	-1.46E-10	-4.35E-10	-4.18E-10	-5.50E-10	-5.17E-10	-3.28E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

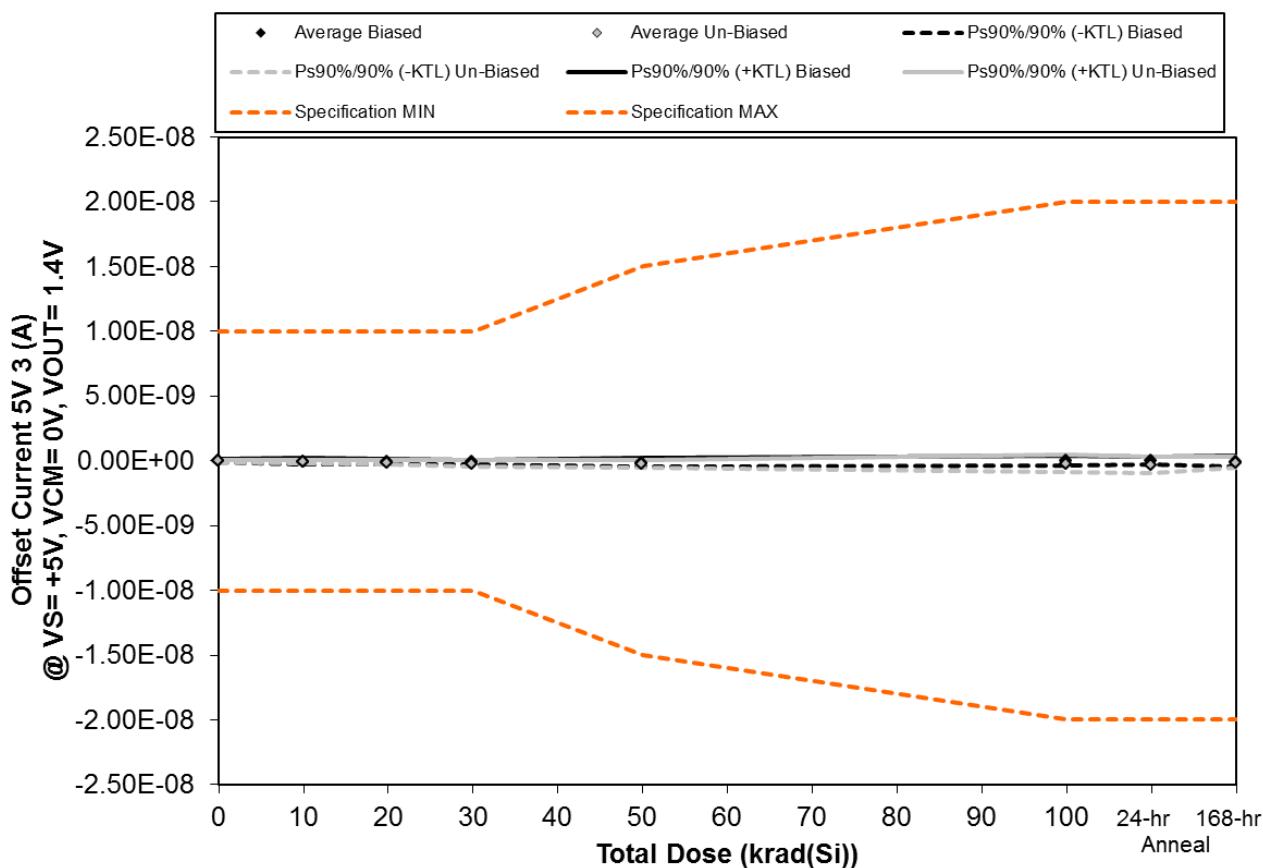


Figure 5.55. Plot of Offset Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.55. Raw data for Offset Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	9.00E-12	-4.70E-11	-1.47E-10	-1.54E-10	-2.03E-10	-7.70E-11	1.20E-11	-2.83E-10
260	7.20E-11	3.90E-11	-3.10E-11	-5.60E-11	-1.16E-10	-2.70E-11	5.40E-11	-3.70E-11
326	-9.00E-12	-1.46E-10	-1.95E-10	-1.14E-10	-2.46E-10	-9.80E-11	-1.18E-10	2.30E-11
328	3.70E-11	7.10E-11	-2.00E-11	0.00E+00	4.20E-11	2.07E-10	1.99E-10	1.07E-10
329	-5.30E-11	-9.90E-11	-5.70E-11	-1.26E-10	-5.80E-11	1.60E-10	1.30E-11	3.20E-11
330	-9.00E-12	-9.80E-11	-1.51E-10	-2.07E-10	-2.14E-10	-7.00E-11	-1.72E-10	7.30E-11
331	-3.10E-11	-7.80E-11	-1.33E-10	-2.64E-10	-9.50E-11	-2.80E-11	-1.28E-10	-4.00E-11
334	-6.90E-11	-1.01E-10	-2.33E-10	-2.49E-10	-3.68E-10	-5.26E-10	-6.38E-10	-3.07E-10
335	4.30E-11	-2.00E-12	-7.40E-11	-5.30E-11	-2.00E-10	1.20E-11	-2.37E-10	-2.64E-10
344	-3.00E-11	-3.80E-11	-7.70E-11	-1.92E-10	-2.81E-10	-4.02E-10	-5.29E-10	-1.37E-10
346	4.40E-11	1.20E-11	1.70E-11	2.10E-11	9.00E-12	-3.00E-11	5.00E-12	6.00E-12
Biased Statistics								
Average Biased	1.12E-11	-3.64E-11	-9.00E-11	-9.00E-11	-1.16E-10	3.30E-11	3.20E-11	-3.16E-11
Std Dev Biased	4.72E-11	9.12E-11	7.70E-11	6.17E-11	1.15E-10	1.41E-10	1.14E-10	1.50E-10
Ps90%/90% (+KTL) Biased	1.41E-10	2.14E-10	1.21E-10	7.92E-11	1.99E-10	4.19E-10	3.44E-10	3.78E-10
Ps90%/90% (-KTL) Biased	-1.18E-10	-2.86E-10	-3.01E-10	-2.59E-10	-4.31E-10	-3.53E-10	-2.80E-10	-4.42E-10
Un-Biased Statistics								
Average Un-Biased	-1.92E-11	-6.34E-11	-1.34E-10	-1.93E-10	-2.32E-10	-2.03E-10	-3.41E-10	-1.35E-10
Std Dev Un-Biased	4.10E-11	4.25E-11	6.51E-11	8.36E-11	1.01E-10	2.44E-10	2.28E-10	1.57E-10
Ps90%/90% (+KTL) Un-Biased	9.31E-11	5.32E-11	4.48E-11	3.63E-11	4.61E-11	4.67E-10	2.85E-10	2.95E-10
Ps90%/90% (-KTL) Un-Biased	-1.31E-10	-1.80E-10	-3.12E-10	-4.22E-10	-5.09E-10	-8.72E-10	-9.67E-10	-5.65E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

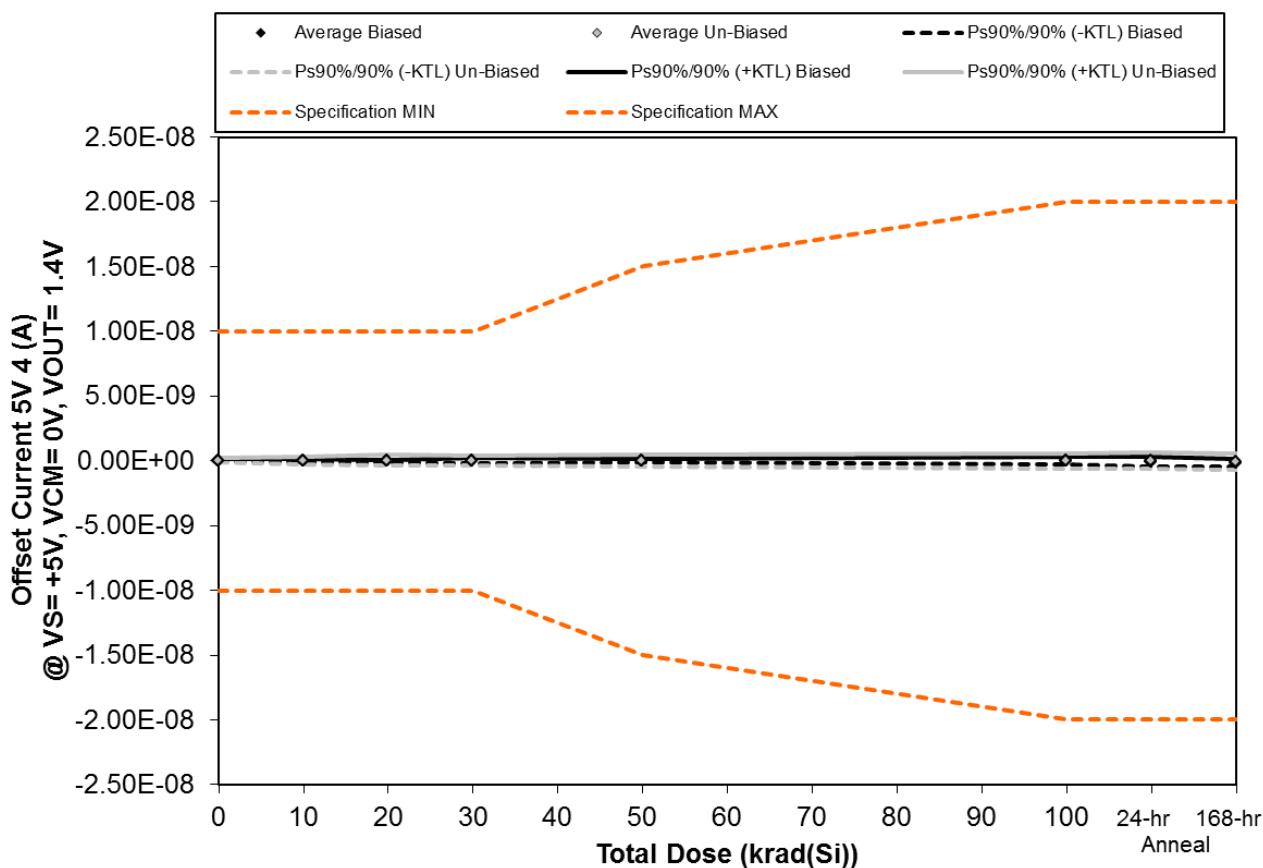


Figure 5.56. Plot of Offset Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.56. Raw data for Offset Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Offset Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device	0	10	20	30	50	100		
259	2.10E-11	3.90E-11	3.80E-11	4.80E-11	-5.80E-11	8.00E-12	-1.12E-10	-2.16E-10
260	4.20E-11	3.60E-11	-2.90E-11	-2.90E-11	-3.10E-11	-1.27E-10	-2.84E-10	-3.07E-10
326	-2.60E-11	-7.90E-11	9.00E-12	5.00E-11	5.80E-11	-4.00E-11	-3.80E-11	-3.00E-11
328	3.90E-11	-7.00E-12	-6.70E-11	-1.33E-10	7.60E-11	-4.70E-11	6.80E-11	-1.47E-10
329	6.00E-11	-2.00E-11	-2.50E-11	-1.70E-11	4.20E-11	1.67E-10	-1.70E-11	-7.10E-11
330	6.60E-11	2.10E-10	2.74E-10	2.24E-10	1.78E-10	2.76E-10	1.55E-10	-2.60E-11
331	1.30E-11	-1.70E-11	-1.06E-10	-1.25E-10	-1.96E-10	-7.00E-12	8.10E-11	-1.25E-10
334	-1.00E-11	-5.30E-11	-1.80E-11	7.00E-12	-6.00E-12	-3.20E-11	-8.80E-11	1.90E-11
335	1.03E-10	6.40E-11	1.35E-10	1.54E-10	1.35E-10	7.20E-11	2.31E-10	2.10E-10
344	-5.50E-11	-2.40E-11	-6.80E-11	-4.90E-11	-1.62E-10	-3.30E-10	-3.36E-10	-4.37E-10
346	-1.10E-10	-8.00E-11	-1.49E-10	-1.00E-10	-1.18E-10	-8.50E-11	-1.05E-10	-8.20E-11
Biased Statistics								
Average Biased	2.72E-11	-6.20E-12	-1.48E-11	-1.62E-11	1.74E-11	-7.80E-12	-7.66E-11	-1.54E-10
Std Dev Biased	3.28E-11	4.83E-11	4.00E-11	7.47E-11	5.86E-11	1.09E-10	1.32E-10	1.11E-10
Ps90%/90% (+KTL) Biased	1.17E-10	1.26E-10	9.47E-11	1.89E-10	1.78E-10	2.91E-10	2.87E-10	1.51E-10
Ps90%/90% (-KTL) Biased	-6.27E-11	-1.39E-10	-1.24E-10	-2.21E-10	-1.43E-10	-3.07E-10	-4.40E-10	-4.59E-10
Un-Biased Statistics								
Average Un-Biased	2.34E-11	3.60E-11	4.34E-11	4.22E-11	-1.02E-11	-4.20E-12	8.60E-12	-7.18E-11
Std Dev Un-Biased	6.23E-11	1.07E-10	1.58E-10	1.44E-10	1.69E-10	2.19E-10	2.26E-10	2.38E-10
Ps90%/90% (+KTL) Un-Biased	1.94E-10	3.28E-10	4.77E-10	4.37E-10	4.53E-10	5.95E-10	6.28E-10	5.80E-10
Ps90%/90% (-KTL) Un-Biased	-1.47E-10	-2.56E-10	-3.90E-10	-3.53E-10	-4.73E-10	-6.04E-10	-6.11E-10	-7.24E-10
Specification MIN	-1.00E-08	-1.00E-08	-1.00E-08	-1.00E-08	-1.50E-08	-2.00E-08	-2.00E-08	-2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	1.00E-08	1.00E-08	1.00E-08	1.00E-08	1.50E-08	2.00E-08	2.00E-08	2.00E-08
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

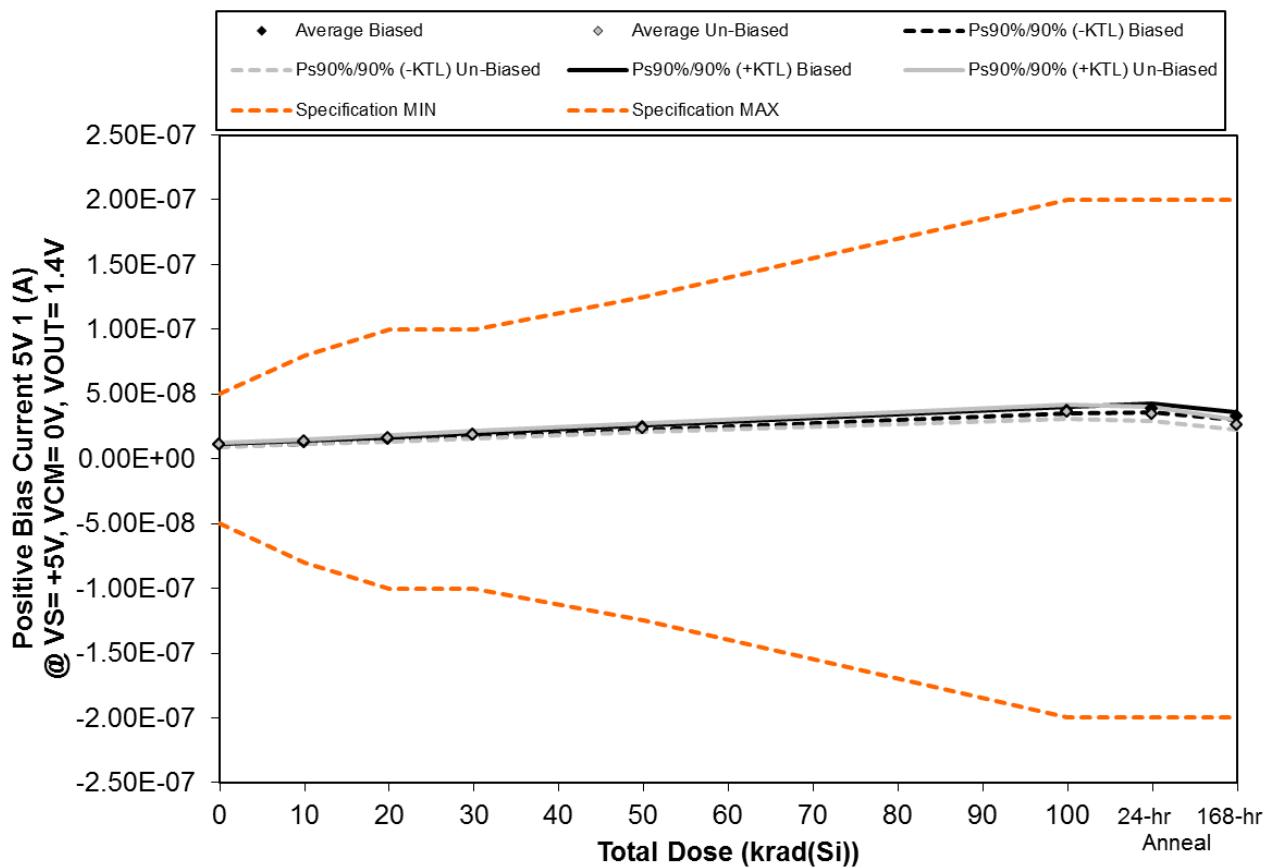


Figure 5.57. Plot of Positive Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.57. Raw data for Positive Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.06E-08	1.29E-08	1.57E-08	1.87E-08	2.45E-08	3.81E-08	3.98E-08	3.29E-08
260	1.10E-08	1.32E-08	1.59E-08	1.94E-08	2.51E-08	3.88E-08	4.06E-08	3.40E-08
326	1.12E-08	1.35E-08	1.60E-08	1.90E-08	2.46E-08	3.78E-08	3.97E-08	3.37E-08
328	1.09E-08	1.29E-08	1.55E-08	1.84E-08	2.38E-08	3.64E-08	3.80E-08	3.23E-08
329	1.03E-08	1.24E-08	1.50E-08	1.81E-08	2.35E-08	3.68E-08	3.81E-08	3.13E-08
330	1.17E-08	1.42E-08	1.69E-08	2.01E-08	2.56E-08	3.83E-08	3.70E-08	2.79E-08
331	1.14E-08	1.39E-08	1.67E-08	1.99E-08	2.57E-08	3.88E-08	3.71E-08	2.79E-08
334	1.02E-08	1.27E-08	1.50E-08	1.79E-08	2.30E-08	3.51E-08	3.33E-08	2.50E-08
335	1.07E-08	1.30E-08	1.55E-08	1.83E-08	2.36E-08	3.54E-08	3.37E-08	2.56E-08
344	1.03E-08	1.25E-08	1.49E-08	1.77E-08	2.29E-08	3.46E-08	3.30E-08	2.49E-08
346	1.15E-08	1.15E-08	1.15E-08	1.15E-08	1.15E-08	1.14E-08	1.15E-08	1.15E-08
Biased Statistics								
Average Biased	1.08E-08	1.30E-08	1.56E-08	1.87E-08	2.43E-08	3.76E-08	3.92E-08	3.28E-08
Std Dev Biased	3.77E-10	4.23E-10	3.90E-10	4.91E-10	6.61E-10	9.85E-10	1.12E-09	1.08E-09
Ps90%/90% (+KTL) Biased	1.18E-08	1.41E-08	1.67E-08	2.01E-08	2.61E-08	4.03E-08	4.23E-08	3.58E-08
Ps90%/90% (-KTL) Biased	9.75E-09	1.18E-08	1.46E-08	1.74E-08	2.25E-08	3.49E-08	3.62E-08	2.99E-08
Un-Biased Statistics								
Average Un-Biased	1.09E-08	1.33E-08	1.58E-08	1.88E-08	2.42E-08	3.65E-08	3.48E-08	2.63E-08
Std Dev Un-Biased	6.99E-10	7.30E-10	9.42E-10	1.13E-09	1.37E-09	1.96E-09	2.04E-09	1.53E-09
Ps90%/90% (+KTL) Un-Biased	1.28E-08	1.53E-08	1.84E-08	2.19E-08	2.79E-08	4.18E-08	4.04E-08	3.05E-08
Ps90%/90% (-KTL) Un-Biased	8.94E-09	1.13E-08	1.32E-08	1.57E-08	2.04E-08	3.11E-08	2.92E-08	2.21E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

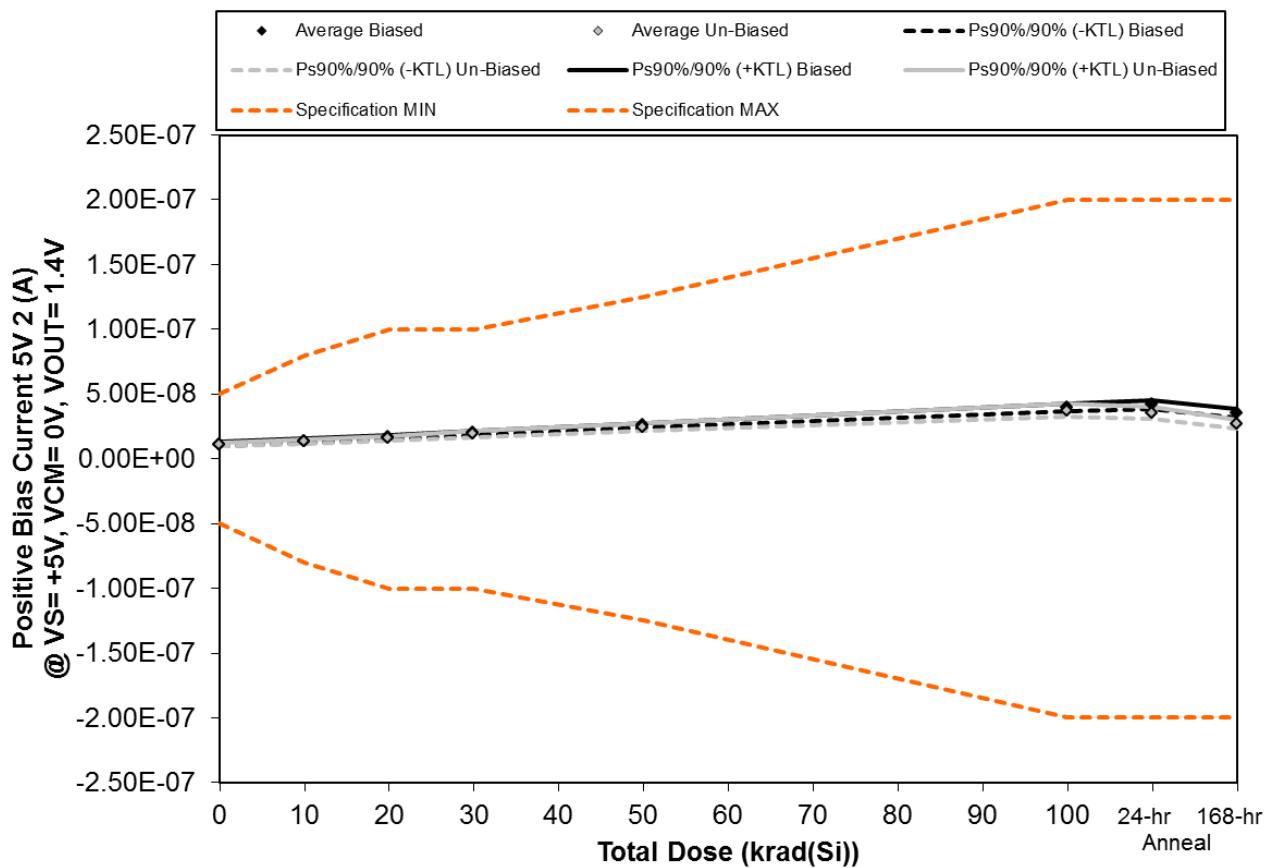


Figure 5.58. Plot of Positive Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.58. Raw data for Positive Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.12E-08	1.36E-08	1.66E-08	1.98E-08	2.56E-08	3.98E-08	4.18E-08	3.44E-08
260	1.20E-08	1.44E-08	1.73E-08	2.08E-08	2.67E-08	4.15E-08	4.34E-08	3.65E-08
326	1.13E-08	1.38E-08	1.63E-08	1.96E-08	2.52E-08	3.88E-08	4.03E-08	3.44E-08
328	1.08E-08	1.32E-08	1.62E-08	1.95E-08	2.53E-08	3.94E-08	4.12E-08	3.41E-08
329	1.20E-08	1.47E-08	1.75E-08	2.08E-08	2.67E-08	4.08E-08	4.27E-08	3.63E-08
330	1.06E-08	1.30E-08	1.56E-08	1.85E-08	2.38E-08	3.57E-08	3.44E-08	2.60E-08
331	1.18E-08	1.43E-08	1.71E-08	2.06E-08	2.63E-08	4.02E-08	3.81E-08	2.87E-08
334	1.07E-08	1.30E-08	1.55E-08	1.82E-08	2.34E-08	3.57E-08	3.39E-08	2.56E-08
335	1.11E-08	1.34E-08	1.62E-08	1.90E-08	2.47E-08	3.73E-08	3.53E-08	2.65E-08
344	1.09E-08	1.33E-08	1.60E-08	1.93E-08	2.50E-08	3.82E-08	3.62E-08	2.71E-08
346	1.15E-08	1.16E-08	1.16E-08	1.15E-08	1.16E-08	1.16E-08	1.16E-08	1.16E-08
Biased Statistics								
Average Biased	1.15E-08	1.39E-08	1.68E-08	2.01E-08	2.59E-08	4.01E-08	4.19E-08	3.51E-08
Std Dev Biased	5.32E-10	6.03E-10	6.03E-10	6.22E-10	7.31E-10	1.09E-09	1.21E-09	1.15E-09
Ps90%/90% (+KTL) Biased	1.29E-08	1.56E-08	1.84E-08	2.18E-08	2.79E-08	4.30E-08	4.52E-08	3.83E-08
Ps90%/90% (-KTL) Biased	1.00E-08	1.23E-08	1.51E-08	1.84E-08	2.39E-08	3.71E-08	3.86E-08	3.20E-08
Un-Biased Statistics								
Average Un-Biased	1.10E-08	1.34E-08	1.61E-08	1.91E-08	2.46E-08	3.74E-08	3.56E-08	2.68E-08
Std Dev Un-Biased	4.55E-10	5.41E-10	6.25E-10	9.10E-10	1.14E-09	1.86E-09	1.64E-09	1.22E-09
Ps90%/90% (+KTL) Un-Biased	1.23E-08	1.49E-08	1.78E-08	2.16E-08	2.77E-08	4.25E-08	4.01E-08	3.01E-08
Ps90%/90% (-KTL) Un-Biased	9.76E-09	1.19E-08	1.44E-08	1.66E-08	2.15E-08	3.23E-08	3.11E-08	2.34E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

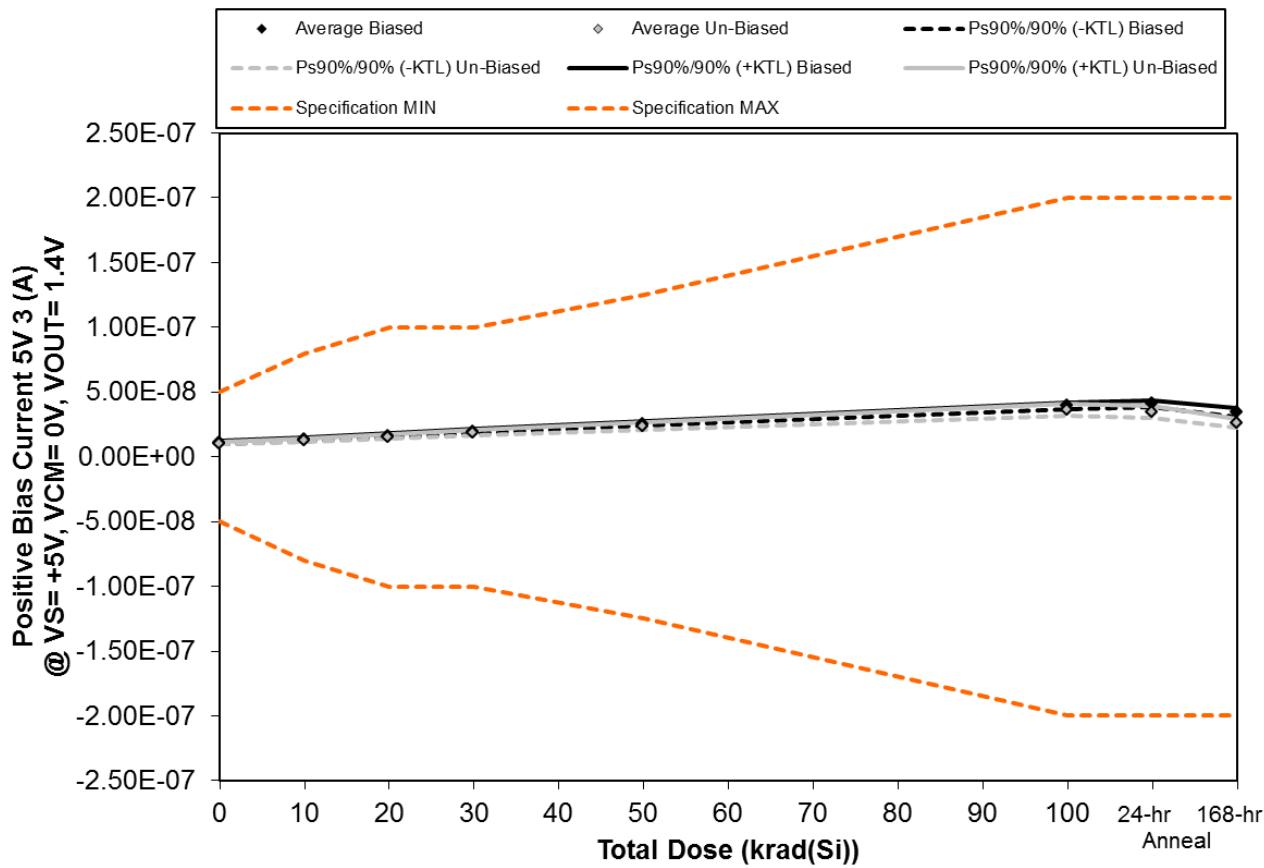


Figure 5.59. Plot of Positive Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.59. Raw data for Positive Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.08E-08	1.33E-08	1.61E-08	1.94E-08	2.53E-08	3.91E-08	4.06E-08	3.36E-08
260	1.15E-08	1.39E-08	1.68E-08	2.03E-08	2.62E-08	4.04E-08	4.22E-08	3.55E-08
326	1.15E-08	1.41E-08	1.68E-08	1.99E-08	2.57E-08	3.93E-08	4.11E-08	3.48E-08
328	1.06E-08	1.30E-08	1.57E-08	1.89E-08	2.48E-08	3.83E-08	3.99E-08	3.28E-08
329	1.17E-08	1.42E-08	1.71E-08	2.03E-08	2.62E-08	4.00E-08	4.19E-08	3.55E-08
330	1.04E-08	1.28E-08	1.52E-08	1.81E-08	2.32E-08	3.50E-08	3.39E-08	2.52E-08
331	1.13E-08	1.37E-08	1.65E-08	1.99E-08	2.53E-08	3.87E-08	3.70E-08	2.77E-08
334	1.03E-08	1.26E-08	1.50E-08	1.76E-08	2.26E-08	3.43E-08	3.28E-08	2.45E-08
335	1.07E-08	1.30E-08	1.57E-08	1.86E-08	2.41E-08	3.61E-08	3.47E-08	2.59E-08
344	1.06E-08	1.31E-08	1.58E-08	1.88E-08	2.44E-08	3.73E-08	3.55E-08	2.62E-08
346	1.08E-08	1.08E-08	1.07E-08	1.07E-08	1.07E-08	1.08E-08	1.07E-08	1.08E-08
Biased Statistics								
Average Biased	1.12E-08	1.37E-08	1.65E-08	1.98E-08	2.56E-08	3.94E-08	4.11E-08	3.44E-08
Std Dev Biased	4.92E-10	5.46E-10	5.76E-10	5.91E-10	6.36E-10	8.36E-10	9.24E-10	1.18E-09
Ps90%/90% (+KTL) Biased	1.26E-08	1.52E-08	1.81E-08	2.14E-08	2.74E-08	4.17E-08	4.37E-08	3.77E-08
Ps90%/90% (-KTL) Biased	9.89E-09	1.22E-08	1.49E-08	1.81E-08	2.39E-08	3.71E-08	3.86E-08	3.12E-08
Un-Biased Statistics								
Average Un-Biased	1.07E-08	1.30E-08	1.57E-08	1.86E-08	2.39E-08	3.63E-08	3.48E-08	2.59E-08
Std Dev Un-Biased	4.18E-10	4.48E-10	5.84E-10	8.37E-10	1.05E-09	1.74E-09	1.60E-09	1.20E-09
Ps90%/90% (+KTL) Un-Biased	1.18E-08	1.43E-08	1.73E-08	2.09E-08	2.68E-08	4.10E-08	3.91E-08	2.92E-08
Ps90%/90% (-KTL) Un-Biased	9.53E-09	1.18E-08	1.41E-08	1.63E-08	2.10E-08	3.15E-08	3.04E-08	2.26E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

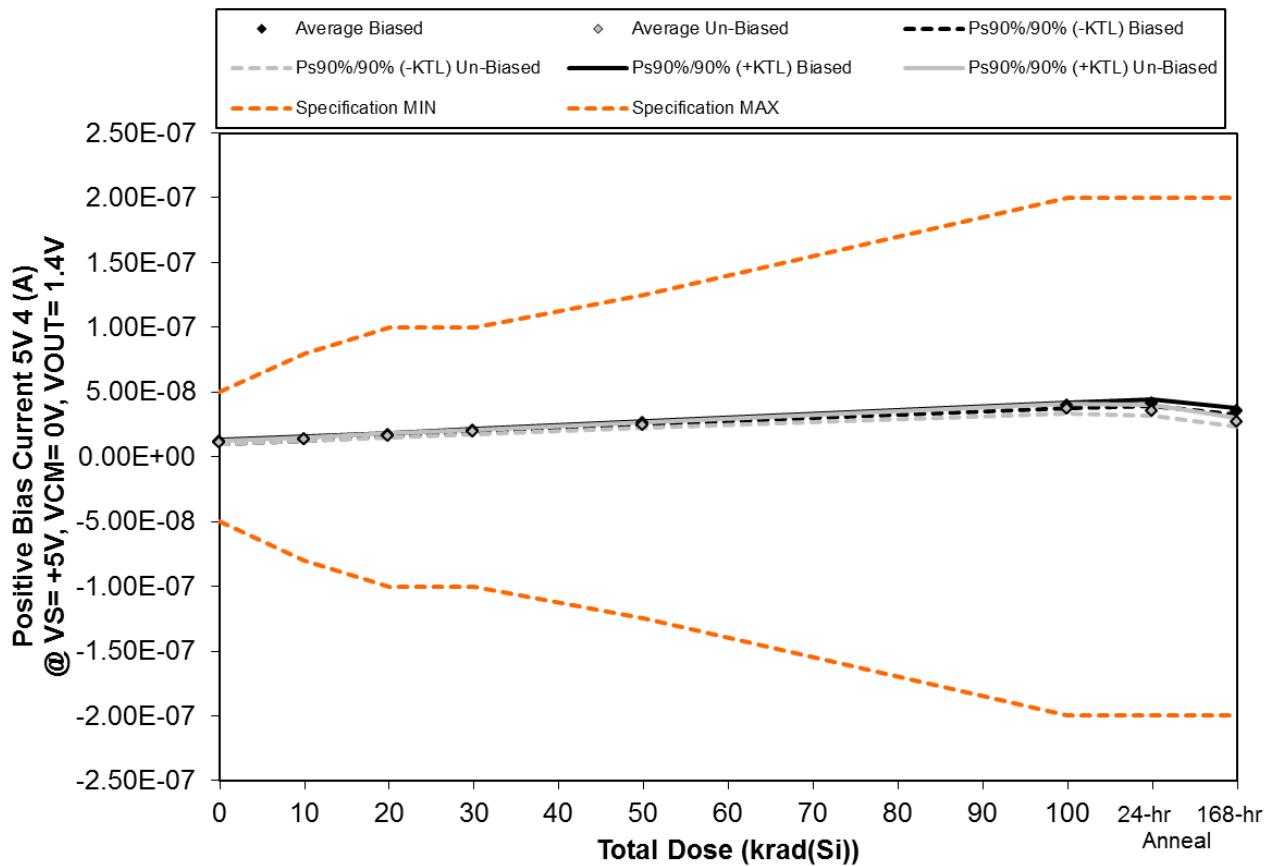


Figure 5.60. Plot of Positive Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.60. Raw data for Positive Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Positive Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.14E-08	1.40E-08	1.68E-08	2.05E-08	2.65E-08	4.08E-08	4.24E-08	3.54E-08
260	1.12E-08	1.36E-08	1.65E-08	1.98E-08	2.59E-08	4.01E-08	4.18E-08	3.52E-08
326	1.24E-08	1.47E-08	1.76E-08	2.08E-08	2.66E-08	4.08E-08	4.28E-08	3.67E-08
328	1.18E-08	1.41E-08	1.67E-08	1.99E-08	2.57E-08	3.92E-08	4.10E-08	3.49E-08
329	1.12E-08	1.34E-08	1.63E-08	1.96E-08	2.54E-08	3.94E-08	4.09E-08	3.39E-08
330	1.20E-08	1.44E-08	1.71E-08	2.03E-08	2.59E-08	3.93E-08	3.81E-08	2.87E-08
331	1.12E-08	1.35E-08	1.64E-08	1.94E-08	2.51E-08	3.84E-08	3.65E-08	2.74E-08
334	1.06E-08	1.31E-08	1.55E-08	1.84E-08	2.37E-08	3.59E-08	3.42E-08	2.55E-08
335	1.11E-08	1.33E-08	1.58E-08	1.89E-08	2.41E-08	3.65E-08	3.48E-08	2.63E-08
344	1.13E-08	1.38E-08	1.64E-08	1.92E-08	2.47E-08	3.74E-08	3.58E-08	2.70E-08
346	1.19E-08	1.18E-08	1.18E-08	1.19E-08	1.19E-08	1.18E-08	1.18E-08	1.19E-08
Biased Statistics								
Average Biased	1.16E-08	1.40E-08	1.68E-08	2.01E-08	2.60E-08	4.01E-08	4.18E-08	3.52E-08
Std Dev Biased	4.98E-10	5.08E-10	5.05E-10	4.89E-10	4.93E-10	7.51E-10	8.37E-10	9.90E-10
Ps90%/90% (+KTL) Biased	1.30E-08	1.53E-08	1.82E-08	2.15E-08	2.74E-08	4.21E-08	4.41E-08	3.79E-08
Ps90%/90% (-KTL) Biased	1.02E-08	1.26E-08	1.54E-08	1.88E-08	2.47E-08	3.80E-08	3.95E-08	3.25E-08
Un-Biased Statistics								
Average Un-Biased	1.12E-08	1.36E-08	1.62E-08	1.93E-08	2.47E-08	3.75E-08	3.59E-08	2.70E-08
Std Dev Un-Biased	5.26E-10	5.28E-10	6.00E-10	7.07E-10	8.68E-10	1.41E-09	1.51E-09	1.19E-09
Ps90%/90% (+KTL) Un-Biased	1.27E-08	1.51E-08	1.79E-08	2.12E-08	2.71E-08	4.13E-08	4.00E-08	3.02E-08
Ps90%/90% (-KTL) Un-Biased	9.80E-09	1.22E-08	1.46E-08	1.73E-08	2.23E-08	3.36E-08	3.17E-08	2.37E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

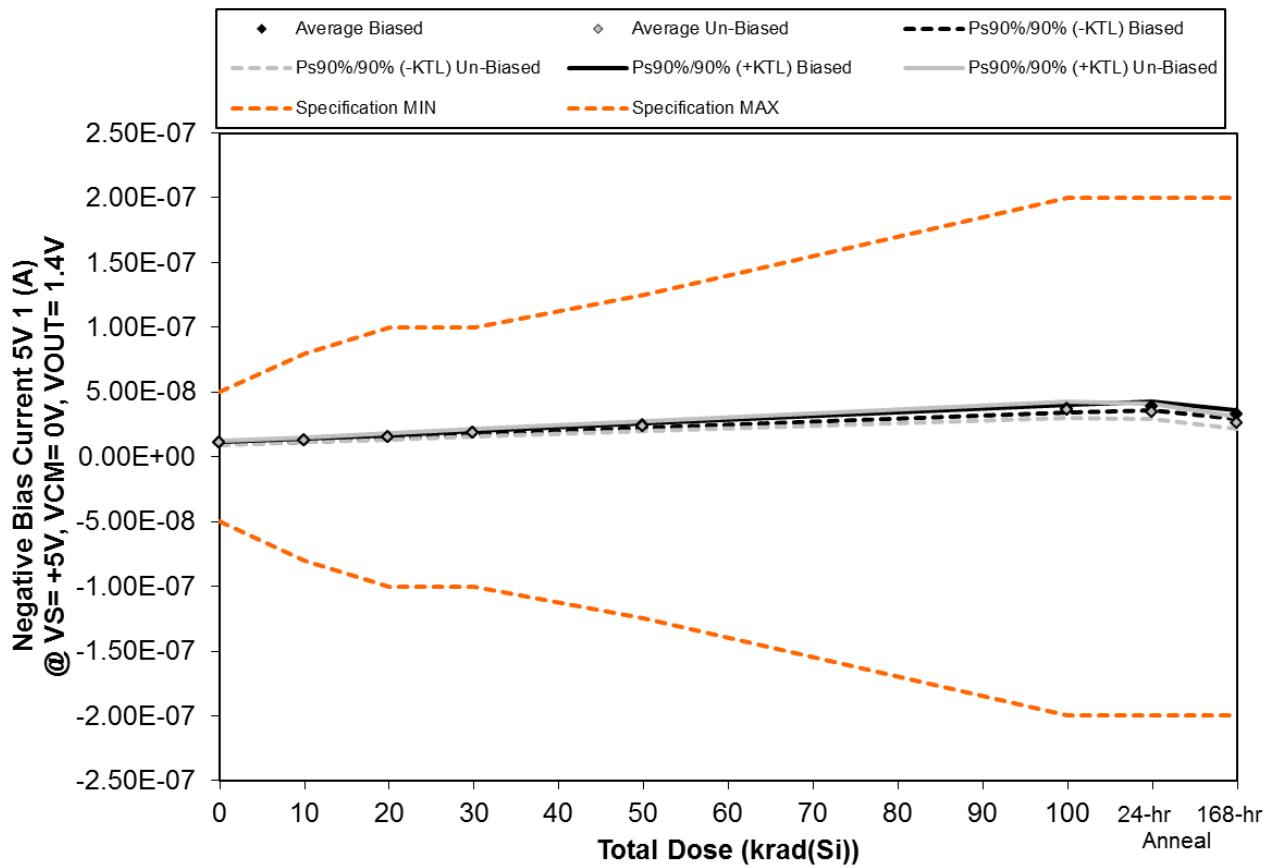


Figure 5.61. Plot of Negative Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.61. Raw data for Negative Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	1.06E-08	1.30E-08	1.55E-08	1.88E-08	2.45E-08	3.81E-08	3.98E-08	3.27E-08	
260	1.10E-08	1.33E-08	1.60E-08	1.92E-08	2.50E-08	3.89E-08	4.07E-08	3.40E-08	
326	1.12E-08	1.34E-08	1.61E-08	1.91E-08	2.47E-08	3.80E-08	4.00E-08	3.38E-08	
328	1.09E-08	1.29E-08	1.54E-08	1.82E-08	2.37E-08	3.63E-08	3.80E-08	3.20E-08	
329	1.02E-08	1.23E-08	1.50E-08	1.79E-08	2.34E-08	3.65E-08	3.81E-08	3.13E-08	
330	1.16E-08	1.42E-08	1.68E-08	1.99E-08	2.55E-08	3.85E-08	3.73E-08	2.80E-08	
331	1.14E-08	1.38E-08	1.66E-08	1.98E-08	2.55E-08	3.88E-08	3.72E-08	2.78E-08	
334	1.02E-08	1.25E-08	1.49E-08	1.77E-08	2.29E-08	3.47E-08	3.31E-08	2.47E-08	
335	1.07E-08	1.29E-08	1.54E-08	1.83E-08	2.34E-08	3.54E-08	3.38E-08	2.55E-08	
344	1.04E-08	1.27E-08	1.50E-08	1.77E-08	2.26E-08	3.44E-08	3.30E-08	2.48E-08	
346	1.14E-08	1.14E-08	1.14E-08	1.15E-08	1.14E-08	1.14E-08	1.14E-08	1.14E-08	1.14E-08
Biased Statistics									
Average Biased	1.08E-08	1.30E-08	1.56E-08	1.86E-08	2.43E-08	3.76E-08	3.93E-08	3.28E-08	
Std Dev Biased	3.76E-10	4.45E-10	4.54E-10	5.39E-10	6.58E-10	1.08E-09	1.20E-09	1.16E-09	
Ps90%/90% (+KTL) Biased	1.18E-08	1.42E-08	1.69E-08	2.01E-08	2.61E-08	4.05E-08	4.26E-08	3.59E-08	
Ps90%/90% (-KTL) Biased	9.76E-09	1.17E-08	1.44E-08	1.72E-08	2.25E-08	3.46E-08	3.60E-08	2.96E-08	
Un-Biased Statistics									
Average Un-Biased	1.09E-08	1.32E-08	1.57E-08	1.87E-08	2.40E-08	3.64E-08	3.49E-08	2.61E-08	
Std Dev Un-Biased	6.28E-10	7.39E-10	8.90E-10	1.09E-09	1.41E-09	2.16E-09	2.18E-09	1.62E-09	
Ps90%/90% (+KTL) Un-Biased	1.26E-08	1.52E-08	1.82E-08	2.17E-08	2.79E-08	4.23E-08	4.08E-08	3.06E-08	
Ps90%/90% (-KTL) Un-Biased	9.14E-09	1.12E-08	1.33E-08	1.57E-08	2.01E-08	3.04E-08	2.89E-08	2.17E-08	
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS	
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS	

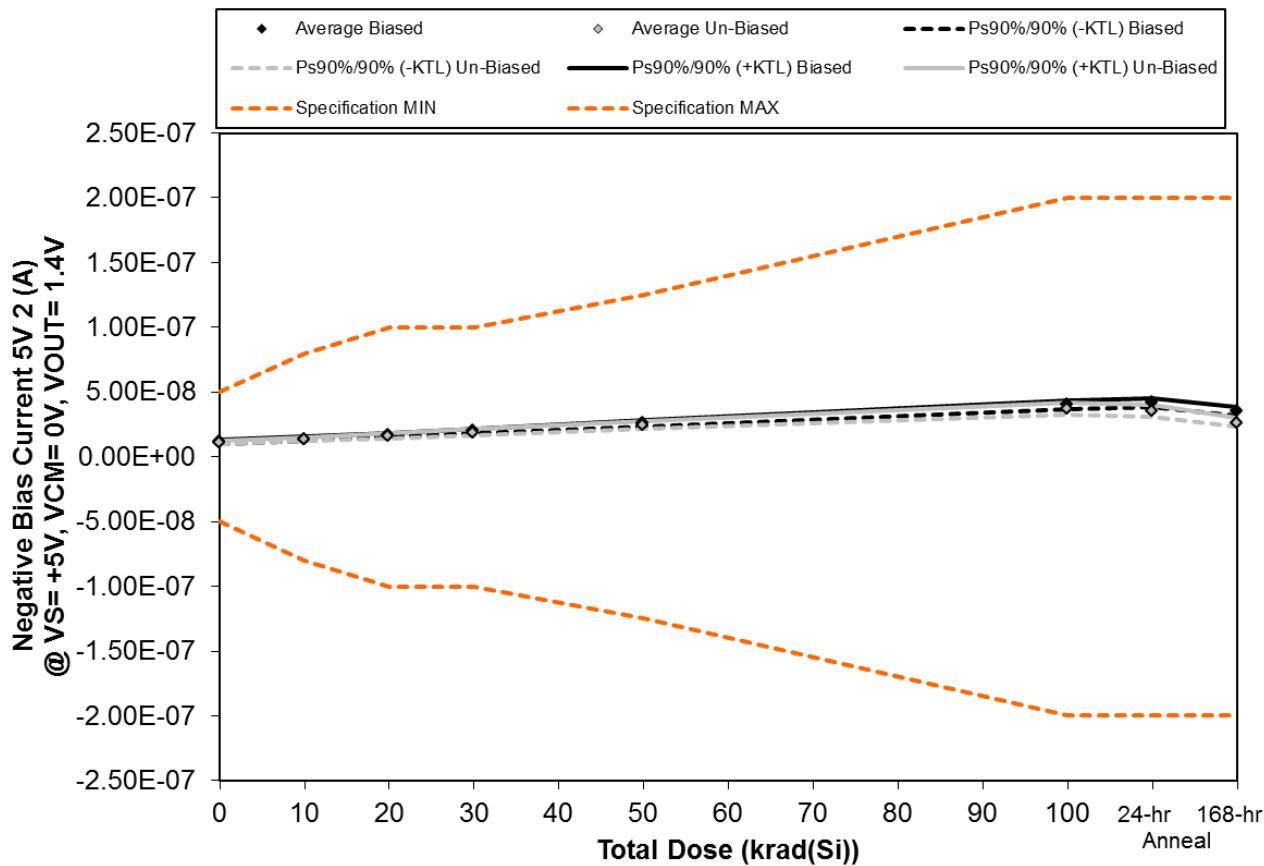


Figure 5.62. Plot of Negative Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.62. Raw data for Negative Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	1.11E-08	1.38E-08	1.65E-08	1.98E-08	2.58E-08	4.01E-08	4.18E-08	3.45E-08	
260	1.19E-08	1.42E-08	1.72E-08	2.07E-08	2.70E-08	4.17E-08	4.36E-08	3.65E-08	
326	1.15E-08	1.40E-08	1.64E-08	1.95E-08	2.50E-08	3.87E-08	4.06E-08	3.45E-08	
328	1.10E-08	1.34E-08	1.63E-08	1.94E-08	2.53E-08	3.96E-08	4.12E-08	3.42E-08	
329	1.22E-08	1.47E-08	1.74E-08	2.07E-08	2.68E-08	4.11E-08	4.27E-08	3.64E-08	
330	1.07E-08	1.30E-08	1.55E-08	1.84E-08	2.35E-08	3.55E-08	3.41E-08	2.58E-08	
331	1.18E-08	1.43E-08	1.72E-08	2.03E-08	2.63E-08	3.98E-08	3.82E-08	2.84E-08	
334	1.05E-08	1.31E-08	1.54E-08	1.82E-08	2.34E-08	3.56E-08	3.39E-08	2.52E-08	
335	1.11E-08	1.35E-08	1.61E-08	1.89E-08	2.43E-08	3.68E-08	3.51E-08	2.65E-08	
344	1.08E-08	1.34E-08	1.61E-08	1.92E-08	2.50E-08	3.80E-08	3.62E-08	2.71E-08	
346	1.16E-08	1.15E-08	1.16E-08	1.16E-08	1.16E-08	1.15E-08	1.16E-08	1.15E-08	
Biased Statistics									
Average Biased	1.16E-08	1.40E-08	1.68E-08	2.00E-08	2.60E-08	4.02E-08	4.20E-08	3.52E-08	
Std Dev Biased	4.90E-10	4.87E-10	4.97E-10	6.42E-10	8.69E-10	1.22E-09	1.21E-09	1.15E-09	
Ps90%/90% (+KTL) Biased	1.29E-08	1.54E-08	1.81E-08	2.18E-08	2.84E-08	4.36E-08	4.53E-08	3.84E-08	
Ps90%/90% (-KTL) Biased	1.02E-08	1.27E-08	1.54E-08	1.83E-08	2.36E-08	3.69E-08	3.87E-08	3.21E-08	
Un-Biased Statistics									
Average Un-Biased	1.10E-08	1.34E-08	1.60E-08	1.90E-08	2.45E-08	3.71E-08	3.55E-08	2.66E-08	
Std Dev Un-Biased	5.32E-10	5.14E-10	7.26E-10	8.37E-10	1.19E-09	1.80E-09	1.77E-09	1.24E-09	
Ps90%/90% (+KTL) Un-Biased	1.24E-08	1.49E-08	1.80E-08	2.13E-08	2.78E-08	4.21E-08	4.03E-08	3.00E-08	
Ps90%/90% (-KTL) Un-Biased	9.53E-09	1.20E-08	1.41E-08	1.67E-08	2.12E-08	3.22E-08	3.07E-08	2.32E-08	
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07	
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS	
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07	
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS	

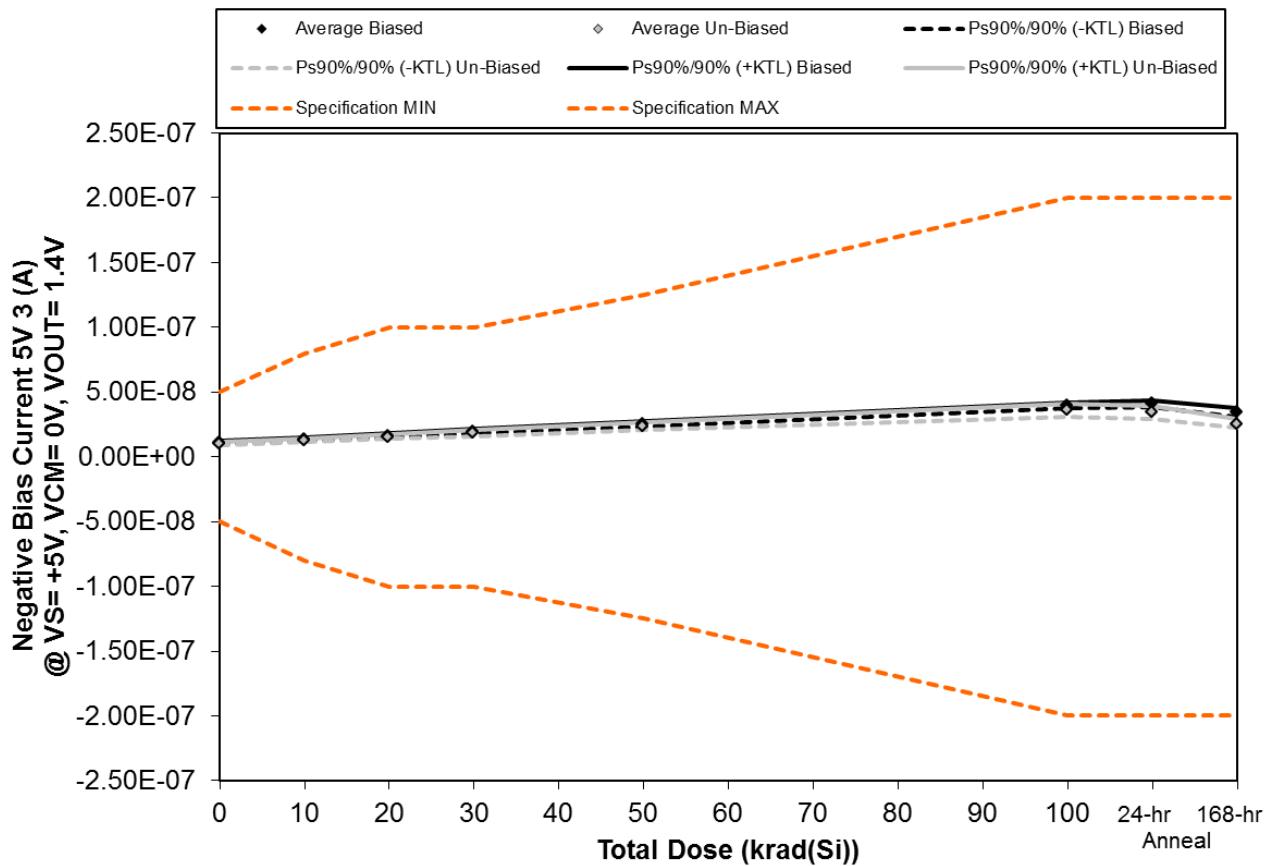


Figure 5.63. Plot of Negative Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.63. Raw data for Negative Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.07E-08	1.33E-08	1.61E-08	1.92E-08	2.50E-08	3.89E-08	4.07E-08	3.33E-08
260	1.16E-08	1.40E-08	1.69E-08	2.03E-08	2.61E-08	4.03E-08	4.24E-08	3.55E-08
326	1.15E-08	1.40E-08	1.66E-08	1.98E-08	2.56E-08	3.93E-08	4.10E-08	3.49E-08
328	1.06E-08	1.29E-08	1.58E-08	1.90E-08	2.47E-08	3.86E-08	4.03E-08	3.30E-08
329	1.17E-08	1.43E-08	1.70E-08	2.03E-08	2.61E-08	4.01E-08	4.19E-08	3.55E-08
330	1.03E-08	1.26E-08	1.51E-08	1.80E-08	2.31E-08	3.50E-08	3.36E-08	2.54E-08
331	1.14E-08	1.37E-08	1.64E-08	1.97E-08	2.53E-08	3.87E-08	3.70E-08	2.76E-08
334	1.02E-08	1.24E-08	1.48E-08	1.74E-08	2.22E-08	3.39E-08	3.22E-08	2.43E-08
335	1.08E-08	1.30E-08	1.57E-08	1.85E-08	2.39E-08	3.62E-08	3.44E-08	2.56E-08
344	1.07E-08	1.29E-08	1.56E-08	1.87E-08	2.41E-08	3.68E-08	3.50E-08	2.61E-08
346	1.07E-08	1.08E-08	1.07E-08	1.06E-08	1.08E-08	1.07E-08	1.08E-08	1.08E-08
Biased Statistics								
Average Biased	1.12E-08	1.37E-08	1.65E-08	1.97E-08	2.55E-08	3.94E-08	4.12E-08	3.44E-08
Std Dev Biased	5.07E-10	5.55E-10	5.28E-10	6.18E-10	6.35E-10	7.52E-10	8.65E-10	1.17E-09
Ps90%/90% (+KTL) Biased	1.26E-08	1.52E-08	1.79E-08	2.14E-08	2.72E-08	4.15E-08	4.36E-08	3.76E-08
Ps90%/90% (-KTL) Biased	9.84E-09	1.22E-08	1.50E-08	1.80E-08	2.37E-08	3.74E-08	3.89E-08	3.12E-08
Un-Biased Statistics								
Average Un-Biased	1.07E-08	1.30E-08	1.55E-08	1.85E-08	2.37E-08	3.61E-08	3.44E-08	2.58E-08
Std Dev Un-Biased	4.64E-10	4.94E-10	6.27E-10	8.83E-10	1.13E-09	1.83E-09	1.75E-09	1.22E-09
Ps90%/90% (+KTL) Un-Biased	1.19E-08	1.43E-08	1.72E-08	2.09E-08	2.68E-08	4.11E-08	3.92E-08	2.92E-08
Ps90%/90% (-KTL) Un-Biased	9.38E-09	1.16E-08	1.38E-08	1.60E-08	2.06E-08	3.11E-08	2.96E-08	2.25E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

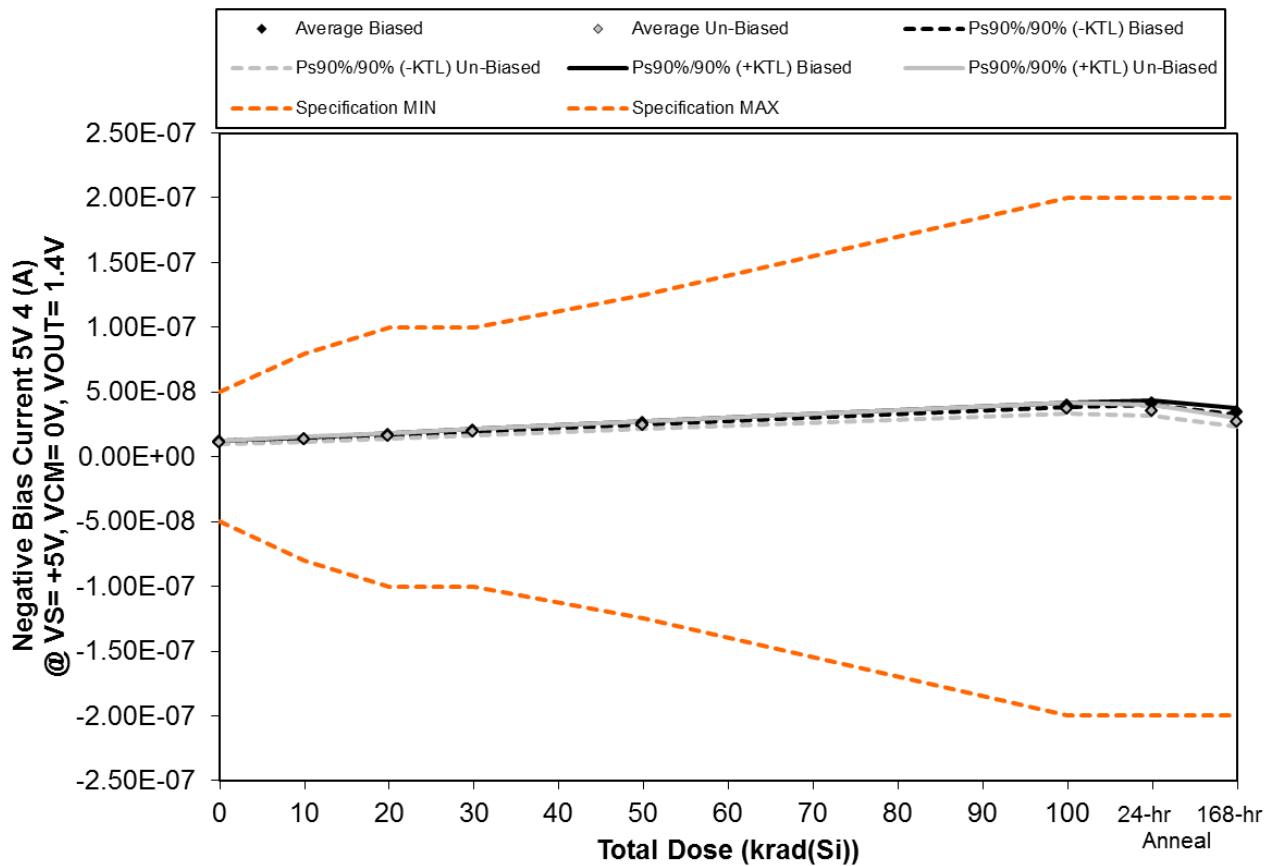


Figure 5.64. Plot of Negative Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.64. Raw data for Negative Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Negative Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.15E-08	1.40E-08	1.69E-08	2.04E-08	2.64E-08	4.07E-08	4.24E-08	3.51E-08
260	1.14E-08	1.37E-08	1.65E-08	1.99E-08	2.58E-08	4.00E-08	4.17E-08	3.50E-08
326	1.22E-08	1.46E-08	1.76E-08	2.09E-08	2.68E-08	4.09E-08	4.27E-08	3.66E-08
328	1.17E-08	1.39E-08	1.67E-08	1.99E-08	2.58E-08	3.94E-08	4.12E-08	3.49E-08
329	1.10E-08	1.35E-08	1.64E-08	1.96E-08	2.56E-08	3.95E-08	4.10E-08	3.38E-08
330	1.20E-08	1.47E-08	1.75E-08	2.06E-08	2.62E-08	3.96E-08	3.83E-08	2.88E-08
331	1.11E-08	1.35E-08	1.62E-08	1.94E-08	2.50E-08	3.85E-08	3.66E-08	2.74E-08
334	1.07E-08	1.30E-08	1.56E-08	1.83E-08	2.35E-08	3.59E-08	3.40E-08	2.56E-08
335	1.11E-08	1.34E-08	1.60E-08	1.89E-08	2.44E-08	3.67E-08	3.51E-08	2.65E-08
344	1.13E-08	1.37E-08	1.63E-08	1.93E-08	2.46E-08	3.71E-08	3.54E-08	2.65E-08
346	1.18E-08	1.18E-08	1.18E-08	1.17E-08	1.17E-08	1.18E-08	1.18E-08	1.18E-08
Biased Statistics								
Average Biased	1.16E-08	1.40E-08	1.68E-08	2.01E-08	2.61E-08	4.01E-08	4.18E-08	3.51E-08
Std Dev Biased	4.16E-10	4.30E-10	4.86E-10	4.88E-10	4.98E-10	6.90E-10	7.33E-10	9.87E-10
Ps90%/90% (+KTL) Biased	1.27E-08	1.51E-08	1.82E-08	2.15E-08	2.74E-08	4.20E-08	4.38E-08	3.78E-08
Ps90%/90% (-KTL) Biased	1.04E-08	1.28E-08	1.55E-08	1.88E-08	2.47E-08	3.82E-08	3.98E-08	3.24E-08
Un-Biased Statistics								
Average Un-Biased	1.12E-08	1.37E-08	1.63E-08	1.93E-08	2.47E-08	3.76E-08	3.59E-08	2.70E-08
Std Dev Un-Biased	4.81E-10	6.36E-10	7.08E-10	8.50E-10	9.76E-10	1.48E-09	1.64E-09	1.20E-09
Ps90%/90% (+KTL) Un-Biased	1.26E-08	1.54E-08	1.82E-08	2.16E-08	2.74E-08	4.16E-08	4.04E-08	3.03E-08
Ps90%/90% (-KTL) Un-Biased	9.93E-09	1.19E-08	1.44E-08	1.70E-08	2.21E-08	3.35E-08	3.14E-08	2.37E-08
Specification MIN	-5.00E-08	-8.00E-08	-1.00E-07	-1.00E-07	-1.25E-07	-2.00E-07	-2.00E-07	-2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS
Specification MAX	5.00E-08	8.00E-08	1.00E-07	1.00E-07	1.25E-07	2.00E-07	2.00E-07	2.00E-07
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

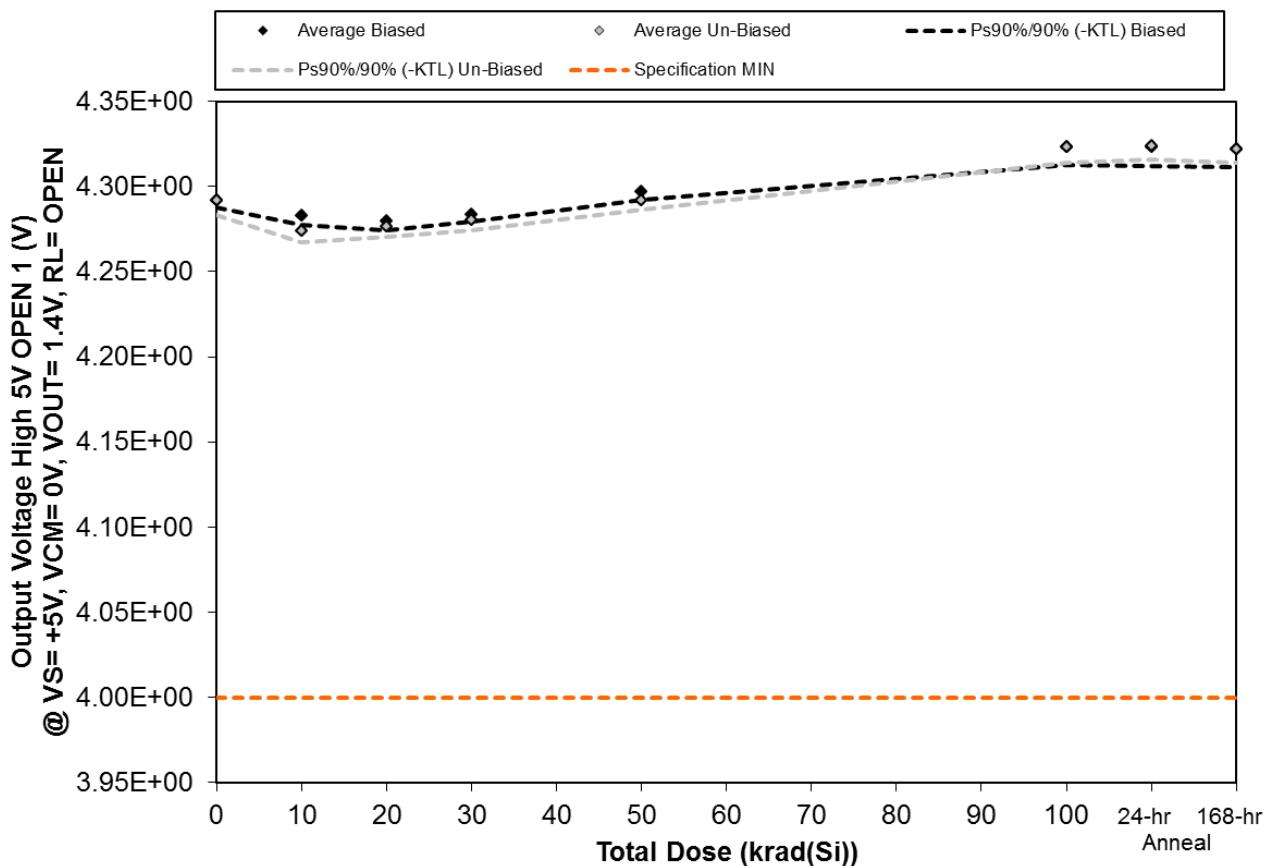


Figure 5.65. Plot of Output Voltage High 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.65. Raw data for Output Voltage High 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.30E+00	4.33E+00	4.32E+00	4.32E+00
260	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
326	4.29E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
328	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
329	4.29E+00	4.29E+00	4.28E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
330	4.29E+00	4.27E+00	4.27E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
331	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
334	4.29E+00	4.27E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.33E+00
335	4.30E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.32E+00
344	4.29E+00	4.27E+00	4.28E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
346	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00
Biased Statistics								
Average Biased	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
Std Dev Biased	1.52E-03	2.12E-03	2.00E-03	1.64E-03	1.79E-03	3.83E-03	4.15E-03	3.83E-03
Ps90%/90% (+KTL) Biased	4.30E+00	4.29E+00	4.29E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Biased	4.29E+00	4.28E+00	4.27E+00	4.28E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
Un-Biased Statistics								
Average Un-Biased	4.29E+00	4.27E+00	4.28E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
Std Dev Un-Biased	2.97E-03	2.28E-03	2.17E-03	2.30E-03	2.00E-03	3.36E-03	2.95E-03	3.00E-03
Ps90%/90% (+KTL) Un-Biased	4.30E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Un-Biased	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.29E+00	4.31E+00	4.32E+00	4.31E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

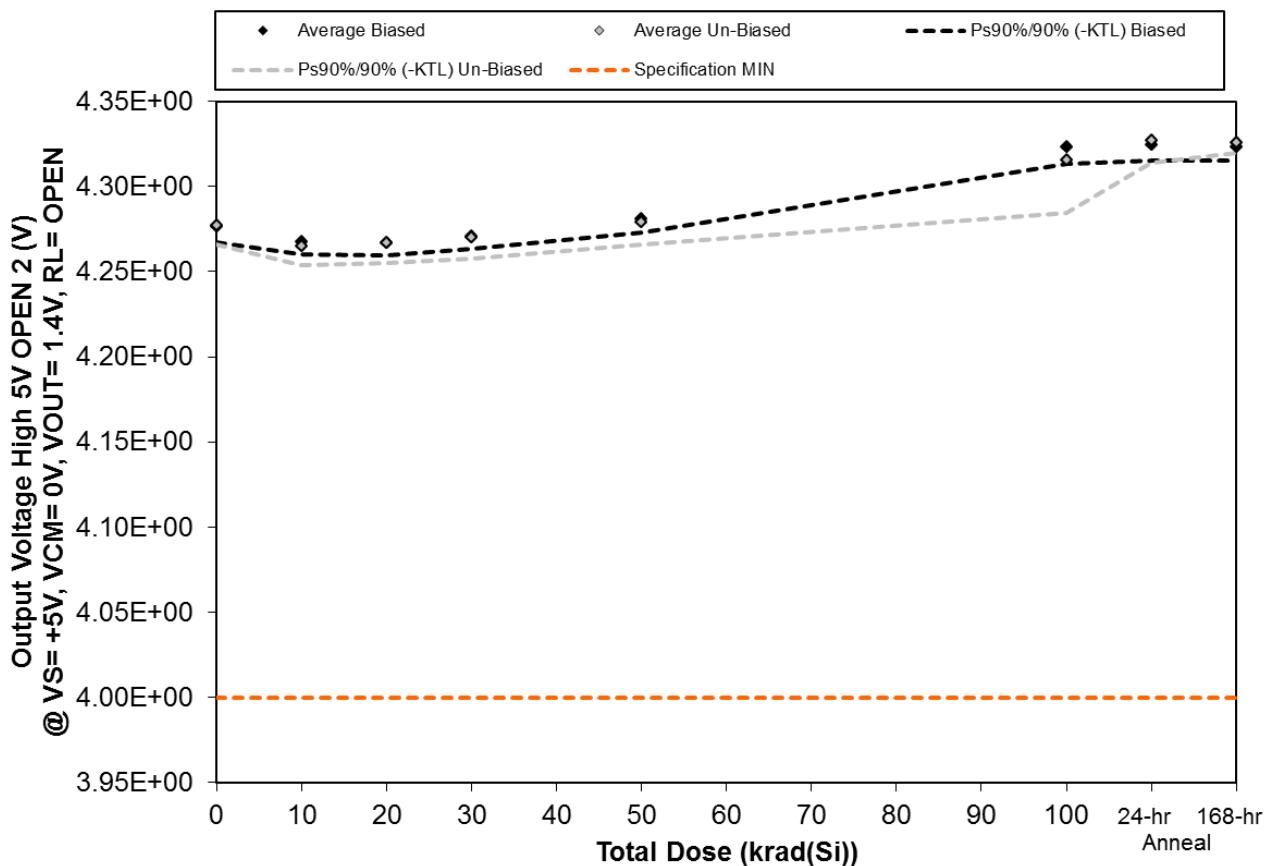


Figure 5.66. Plot of Output Voltage High 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.66. Raw data for Output Voltage High 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	4.28E+00	4.27E+00	4.27E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.33E+00
260	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
326	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
328	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
329	4.27E+00	4.26E+00	4.26E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
330	4.27E+00	4.26E+00	4.26E+00	4.26E+00	4.27E+00	4.30E+00	4.32E+00	4.32E+00
331	4.27E+00	4.26E+00	4.26E+00	4.27E+00	4.28E+00	4.31E+00	4.33E+00	4.32E+00
334	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.33E+00	4.33E+00	4.33E+00
335	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
344	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
346	4.28E+00	4.28E+00	4.28E+00	4.28E+00	4.28E+00	4.28E+00	4.28E+00	4.28E+00
Biased Statistics								
Average Biased	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
Std Dev Biased	3.27E-03	2.61E-03	2.86E-03	2.83E-03	2.92E-03	3.56E-03	3.27E-03	3.05E-03
Ps90%/90% (+KTL) Biased	4.29E+00	4.27E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Biased	4.27E+00	4.26E+00	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.32E+00	4.32E+00
Un-Biased Statistics								
Average Un-Biased	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
Std Dev Un-Biased	4.00E-03	4.15E-03	4.49E-03	4.62E-03	4.74E-03	1.13E-02	4.66E-03	2.35E-03
Ps90%/90% (+KTL) Un-Biased	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.35E+00	4.34E+00	4.33E+00
Ps90%/90% (-KTL) Un-Biased	4.27E+00	4.25E+00	4.25E+00	4.26E+00	4.27E+00	4.28E+00	4.31E+00	4.32E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

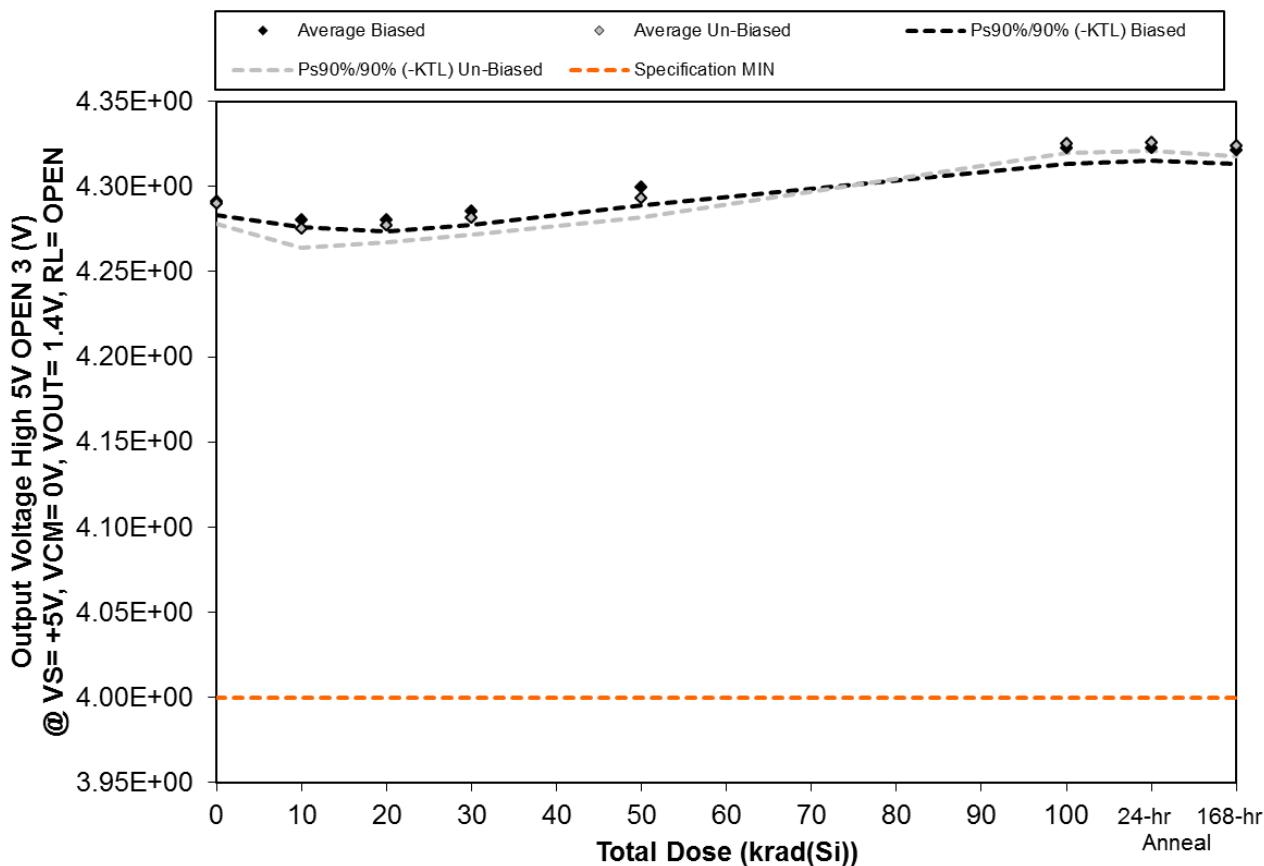


Figure 5.67. Plot of Output Voltage High 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.67. Raw data for Output Voltage High 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	4.30E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
260	4.29E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
326	4.29E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
328	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.32E+00
329	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
330	4.29E+00	4.27E+00	4.27E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
331	4.29E+00	4.27E+00	4.27E+00	4.28E+00	4.29E+00	4.32E+00	4.32E+00	4.32E+00
334	4.30E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
335	4.29E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
344	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.33E+00
346	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00	4.29E+00
Biased Statistics								
Average Biased	4.29E+00	4.28E+00	4.28E+00	4.29E+00	4.30E+00	4.32E+00	4.32E+00	4.32E+00
Std Dev Biased	2.88E-03	1.52E-03	2.51E-03	2.88E-03	3.78E-03	3.36E-03	2.79E-03	2.86E-03
Ps90%/90% (+KTL) Biased	4.30E+00	4.28E+00	4.29E+00	4.29E+00	4.31E+00	4.33E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Biased	4.28E+00	4.28E+00	4.27E+00	4.28E+00	4.29E+00	4.31E+00	4.31E+00	4.31E+00
Un-Biased Statistics								
Average Un-Biased	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.32E+00
Std Dev Un-Biased	4.21E-03	4.09E-03	3.65E-03	3.56E-03	3.94E-03	2.19E-03	1.87E-03	2.17E-03
Ps90%/90% (+KTL) Un-Biased	4.30E+00	4.29E+00	4.29E+00	4.29E+00	4.30E+00	4.33E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Un-Biased	4.28E+00	4.26E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

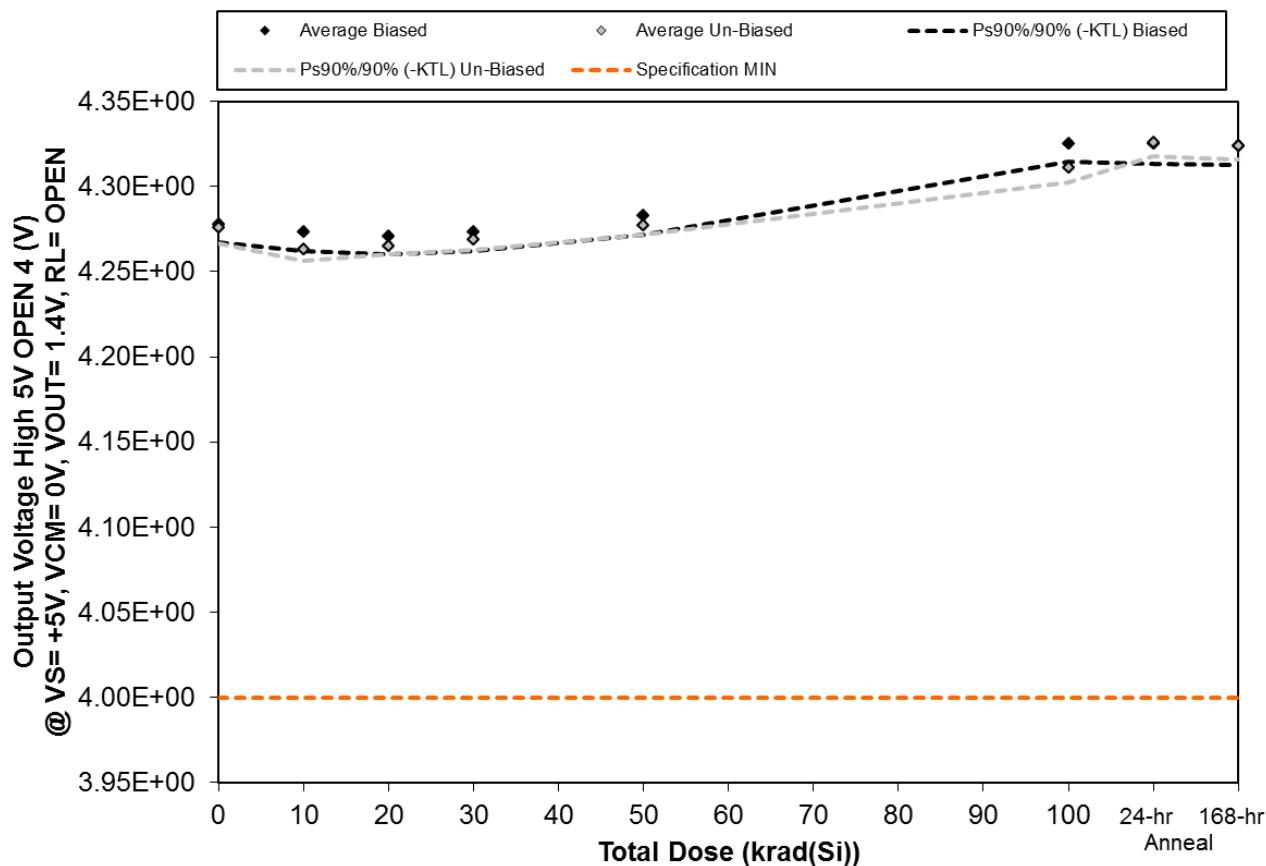


Figure 5.68. Plot of Output Voltage High 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.68. Raw data for Output Voltage High 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.33E+00	4.33E+00	4.33E+00
260	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
326	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
328	4.27E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.32E+00	4.32E+00
329	4.28E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.33E+00	4.33E+00	4.33E+00
330	4.27E+00	4.26E+00	4.26E+00	4.27E+00	4.27E+00	4.31E+00	4.32E+00	4.32E+00
331	4.28E+00	4.26E+00	4.27E+00	4.27E+00	4.28E+00	4.31E+00	4.33E+00	4.32E+00
334	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
335	4.28E+00	4.26E+00	4.27E+00	4.27E+00	4.28E+00	4.31E+00	4.33E+00	4.33E+00
344	4.28E+00	4.26E+00	4.27E+00	4.27E+00	4.28E+00	4.31E+00	4.33E+00	4.33E+00
346	4.27E+00	4.27E+00	4.27E+00	4.27E+00	4.27E+00	4.27E+00	4.27E+00	4.27E+00
Biased Statistics								
Average Biased	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.33E+00	4.33E+00	4.32E+00
Std Dev Biased	3.78E-03	4.00E-03	3.77E-03	4.15E-03	4.18E-03	3.74E-03	4.36E-03	4.04E-03
Ps90%/90% (+KTL) Biased	4.29E+00	4.28E+00	4.28E+00	4.28E+00	4.29E+00	4.34E+00	4.34E+00	4.33E+00
Ps90%/90% (-KTL) Biased	4.27E+00	4.26E+00	4.26E+00	4.26E+00	4.27E+00	4.31E+00	4.31E+00	4.31E+00
Un-Biased Statistics								
Average Un-Biased	4.28E+00	4.26E+00	4.26E+00	4.27E+00	4.28E+00	4.31E+00	4.33E+00	4.32E+00
Std Dev Un-Biased	3.35E-03	2.39E-03	1.79E-03	2.19E-03	1.92E-03	2.95E-03	2.97E-03	3.00E-03
Ps90%/90% (+KTL) Un-Biased	4.28E+00	4.27E+00	4.27E+00	4.27E+00	4.28E+00	4.32E+00	4.33E+00	4.33E+00
Ps90%/90% (-KTL) Un-Biased	4.27E+00	4.26E+00	4.26E+00	4.26E+00	4.27E+00	4.30E+00	4.32E+00	4.32E+00
Specification MIN	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00	4.00E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

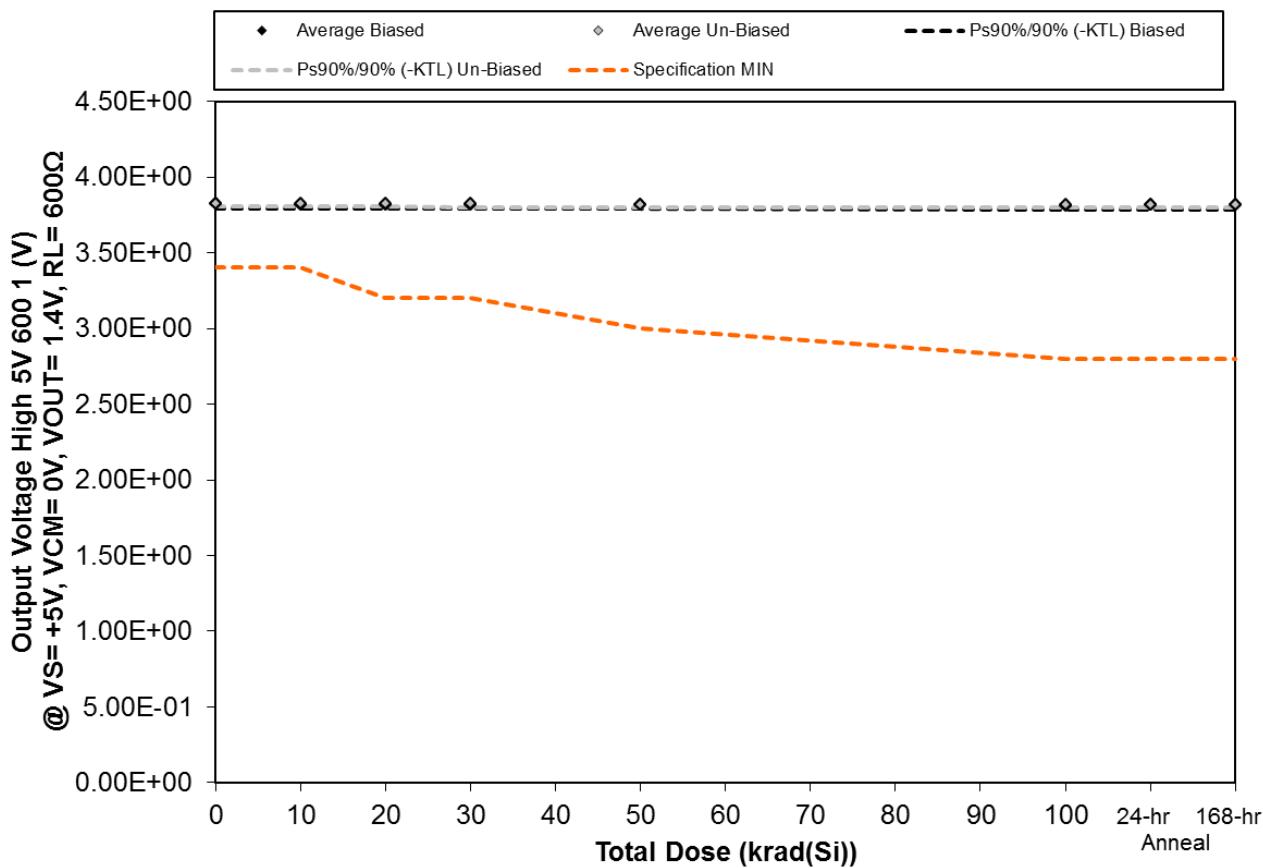


Figure 5.69. Plot of Output Voltage High 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.69. Raw data for Output Voltage High 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
260	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00
326	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.80E+00	3.80E+00
328	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.80E+00	3.81E+00	3.81E+00	3.81E+00
329	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
330	3.82E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00
331	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
334	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.83E+00	3.83E+00	3.83E+00
335	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
344	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
346	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00
Biased Statistics									
Average Biased		3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00
Std Dev Biased		9.68E-03	9.68E-03	9.94E-03	9.96E-03	9.94E-03	1.04E-02	1.06E-02	1.05E-02
Ps90%/90% (+KTL) Biased		3.85E+00	3.85E+00	3.85E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
Ps90%/90% (-KTL) Biased		3.79E+00	3.79E+00	3.79E+00	3.79E+00	3.79E+00	3.78E+00	3.78E+00	3.79E+00
Un-Biased Statistics									
Average Un-Biased		3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
Std Dev Un-Biased		6.58E-03	6.43E-03	6.69E-03	6.80E-03	7.06E-03	7.00E-03	7.19E-03	6.61E-03
Ps90%/90% (+KTL) Un-Biased		3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
Ps90%/90% (-KTL) Un-Biased		3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.80E+00	3.80E+00	3.80E+00	3.80E+00
Specification MIN		3.40E+00	3.40E+00	3.20E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

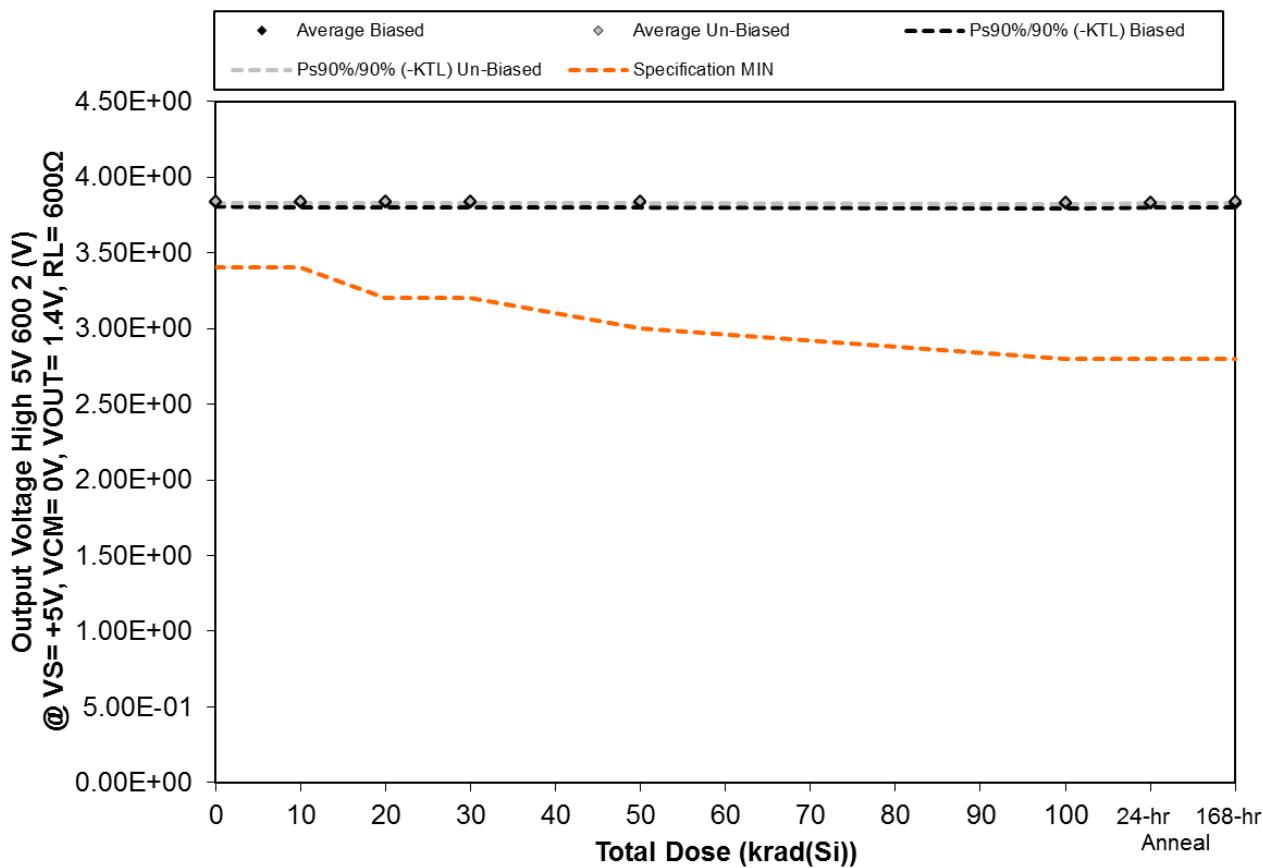


Figure 5.70. Plot of Output Voltage High 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.70. Raw data for Output Voltage High 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.84E+00	3.84E+00
260	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00
326	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00
328	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
329	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
330	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.83E+00
331	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
334	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.83E+00
335	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.83E+00
344	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
346	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00
Biased Statistics								
Average Biased	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.83E+00	3.83E+00
Std Dev Biased	9.75E-03	1.03E-02	1.05E-02	1.05E-02	1.03E-02	1.10E-02	1.09E-02	1.05E-02
Ps90%/90% (+KTL) Biased	3.86E+00	3.86E+00	3.86E+00	3.86E+00	3.86E+00	3.85E+00	3.86E+00	3.85E+00
Ps90%/90% (-KTL) Biased	3.80E+00	3.80E+00	3.80E+00	3.80E+00	3.80E+00	3.79E+00	3.80E+00	3.80E+00
Un-Biased Statistics								
Average Un-Biased	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.84E+00
Std Dev Un-Biased	3.36E-03	3.36E-03	3.24E-03	3.03E-03	3.03E-03	3.56E-03	3.03E-03	3.21E-03
Ps90%/90% (+KTL) Un-Biased	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.84E+00	3.84E+00	3.84E+00
Ps90%/90% (-KTL) Un-Biased	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.83E+00	3.83E+00
Specification MIN	3.40E+00	3.40E+00	3.20E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

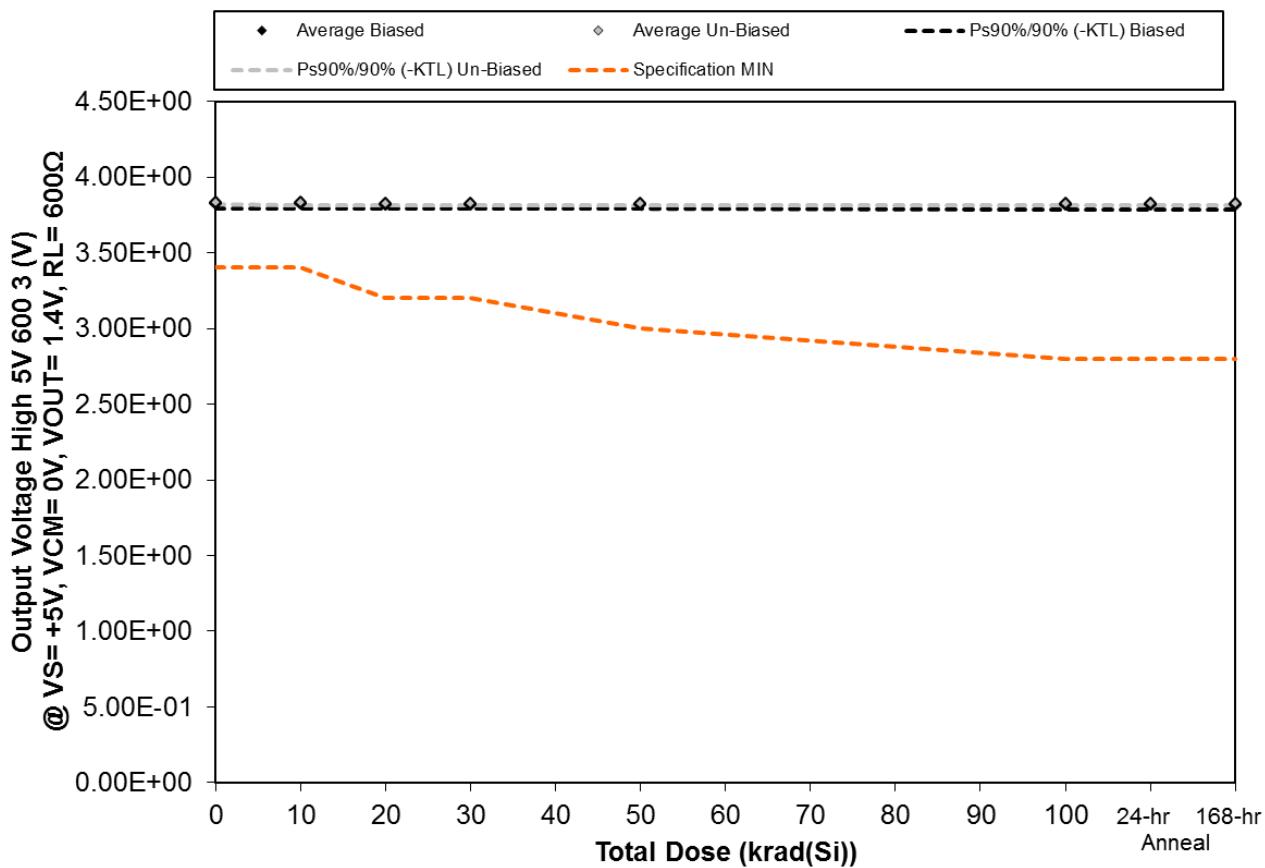


Figure 5.71. Plot of Output Voltage High 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.71. Raw data for Output Voltage High 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00
260	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00
326	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.80E+00
328	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
329	3.82E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00
330	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
331	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.83E+00	3.83E+00
334	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00
335	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
344	3.84E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
346	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
Biased Statistics								
Average Biased	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
Std Dev Biased	1.07E-02	1.10E-02	1.08E-02	1.07E-02	1.09E-02	1.15E-02	1.15E-02	1.14E-02
Ps90%/90% (+KTL) Biased	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00
Ps90%/90% (-KTL) Biased	3.79E+00	3.79E+00	3.79E+00	3.79E+00	3.79E+00	3.78E+00	3.78E+00	3.79E+00
Un-Biased Statistics								
Average Un-Biased	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00
Std Dev Un-Biased	3.90E-03	4.06E-03	3.97E-03	3.97E-03	3.91E-03	3.70E-03	3.83E-03	4.06E-03
Ps90%/90% (+KTL) Un-Biased	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.84E+00
Ps90%/90% (-KTL) Un-Biased	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00
Specification MIN	3.40E+00	3.40E+00	3.20E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

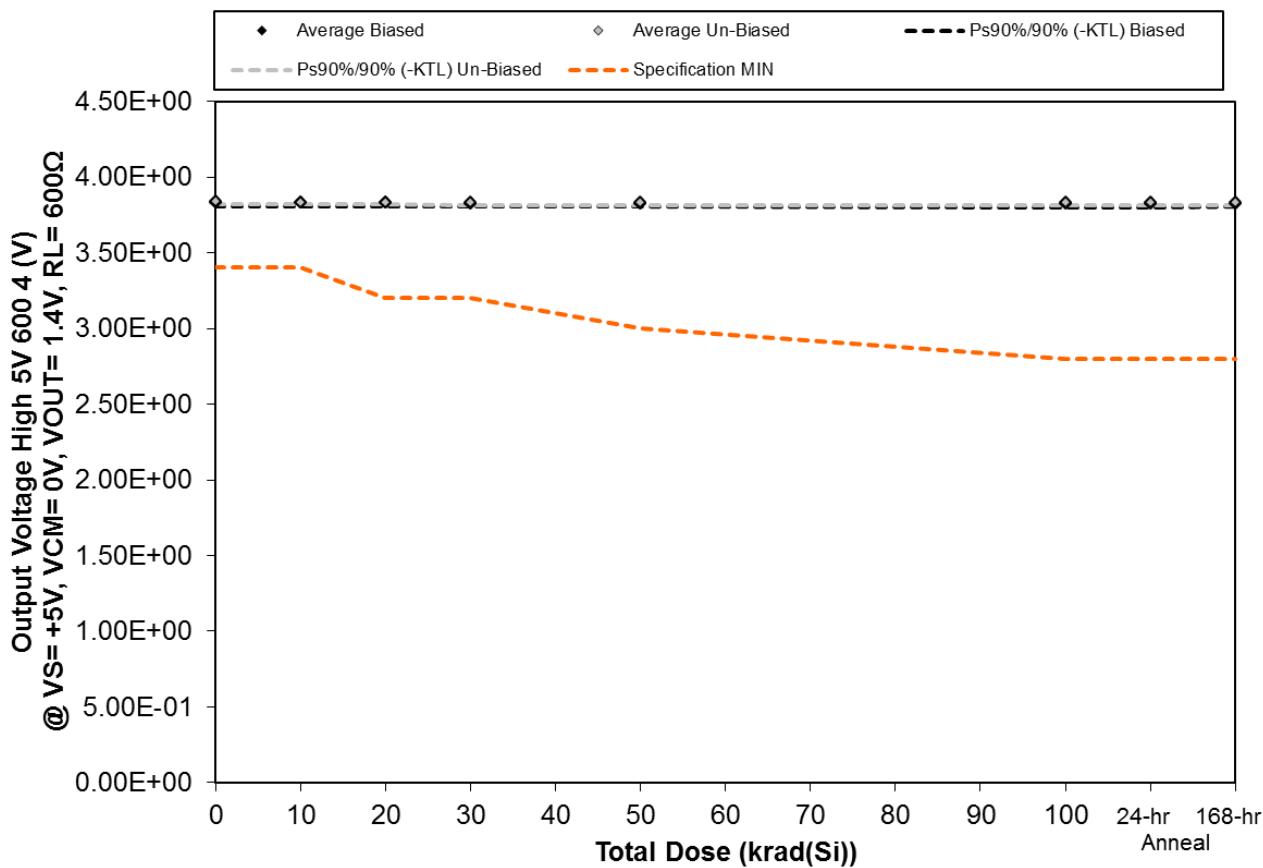


Figure 5.72. Plot of Output Voltage High 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.72. Raw data for Output Voltage High 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage High 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
260	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
326	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
328	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
329	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.84E+00	3.84E+00	3.84E+00
330	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
331	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.84E+00	3.84E+00
334	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.84E+00	3.83E+00	3.83E+00	3.84E+00
335	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
344	3.84E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
346	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00
Biased Statistics									
Average Biased		3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.82E+00	3.82E+00	3.82E+00
Std Dev Biased		7.33E-03	7.26E-03	7.11E-03	7.33E-03	7.26E-03	7.60E-03	8.26E-03	7.52E-03
Ps90%/90% (+KTL) Biased		3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.84E+00	3.85E+00	3.84E+00
Ps90%/90% (-KTL) Biased		3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.81E+00	3.80E+00	3.80E+00	3.80E+00
Un-Biased Statistics									
Average Un-Biased		3.84E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00	3.83E+00
Std Dev Un-Biased		5.97E-03	5.22E-03	5.55E-03	5.85E-03	5.97E-03	6.57E-03	5.97E-03	5.81E-03
Ps90%/90% (+KTL) Un-Biased		3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00	3.85E+00
Ps90%/90% (-KTL) Un-Biased		3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.82E+00	3.81E+00	3.81E+00	3.81E+00
Specification MIN		3.40E+00	3.40E+00	3.20E+00	3.20E+00	3.00E+00	2.80E+00	2.80E+00	2.80E+00
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

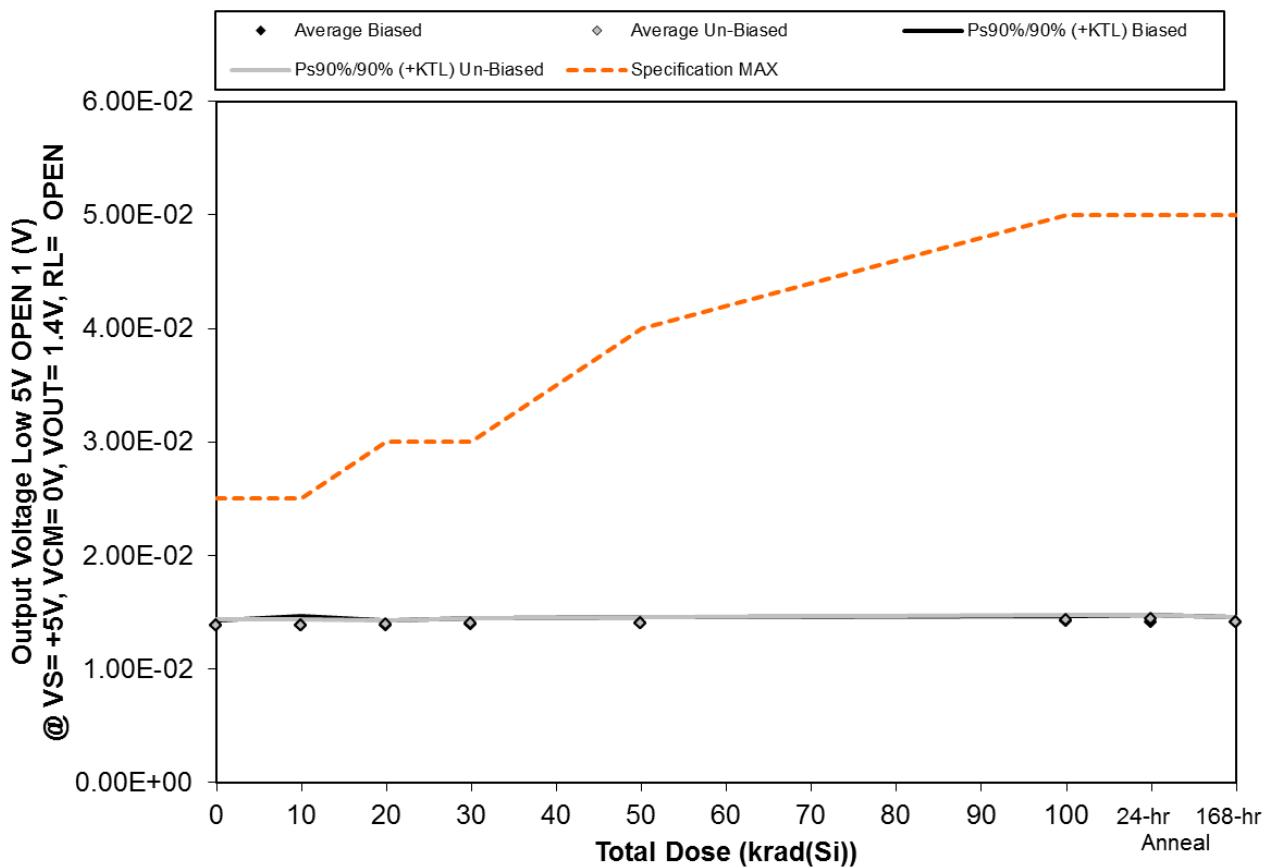


Figure 5.73. Plot of Output Voltage Low 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.73. Raw data for Output Voltage Low 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.38E-02	1.39E-02	1.39E-02	1.39E-02	1.42E-02	1.42E-02	1.43E-02	1.41E-02
260	1.37E-02	1.37E-02	1.38E-02	1.38E-02	1.39E-02	1.41E-02	1.40E-02	1.40E-02
326	1.37E-02	1.37E-02	1.37E-02	1.38E-02	1.38E-02	1.40E-02	1.41E-02	1.39E-02
328	1.38E-02	1.37E-02	1.38E-02	1.39E-02	1.39E-02	1.42E-02	1.40E-02	1.41E-02
329	1.41E-02	1.44E-02	1.41E-02	1.43E-02	1.43E-02	1.45E-02	1.45E-02	1.44E-02
330	1.37E-02	1.36E-02	1.39E-02	1.38E-02	1.38E-02	1.42E-02	1.43E-02	1.39E-02
331	1.36E-02	1.38E-02	1.37E-02	1.39E-02	1.40E-02	1.43E-02	1.42E-02	1.40E-02
334	1.41E-02	1.40E-02	1.41E-02	1.42E-02	1.42E-02	1.44E-02	1.45E-02	1.43E-02
335	1.39E-02	1.40E-02	1.40E-02	1.41E-02	1.42E-02	1.45E-02	1.45E-02	1.42E-02
344	1.39E-02	1.40E-02	1.39E-02	1.41E-02	1.42E-02	1.45E-02	1.45E-02	1.41E-02
346	1.37E-02	1.37E-02	1.38E-02	1.36E-02	1.37E-02	1.36E-02	1.37E-02	1.38E-02
Biased Statistics								
Average Biased	1.38E-02	1.39E-02	1.39E-02	1.39E-02	1.40E-02	1.42E-02	1.42E-02	1.41E-02
Std Dev Biased	1.64E-04	3.03E-04	1.52E-04	2.07E-04	2.17E-04	1.87E-04	2.17E-04	1.87E-04
Ps90%/90% (+KTL) Biased	1.43E-02	1.47E-02	1.43E-02	1.45E-02	1.46E-02	1.47E-02	1.48E-02	1.46E-02
Ps90%/90% (-KTL) Biased	1.34E-02	1.30E-02	1.34E-02	1.34E-02	1.34E-02	1.37E-02	1.36E-02	1.36E-02
Un-Biased Statistics								
Average Un-Biased	1.38E-02	1.39E-02	1.39E-02	1.40E-02	1.41E-02	1.44E-02	1.44E-02	1.41E-02
Std Dev Un-Biased	1.95E-04	1.79E-04	1.48E-04	1.64E-04	1.79E-04	1.30E-04	1.41E-04	1.58E-04
Ps90%/90% (+KTL) Un-Biased	1.44E-02	1.44E-02	1.43E-02	1.45E-02	1.46E-02	1.47E-02	1.48E-02	1.45E-02
Ps90%/90% (-KTL) Un-Biased	1.33E-02	1.34E-02	1.35E-02	1.36E-02	1.36E-02	1.40E-02	1.40E-02	1.37E-02
Specification MAX	2.50E-02	2.50E-02	3.00E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

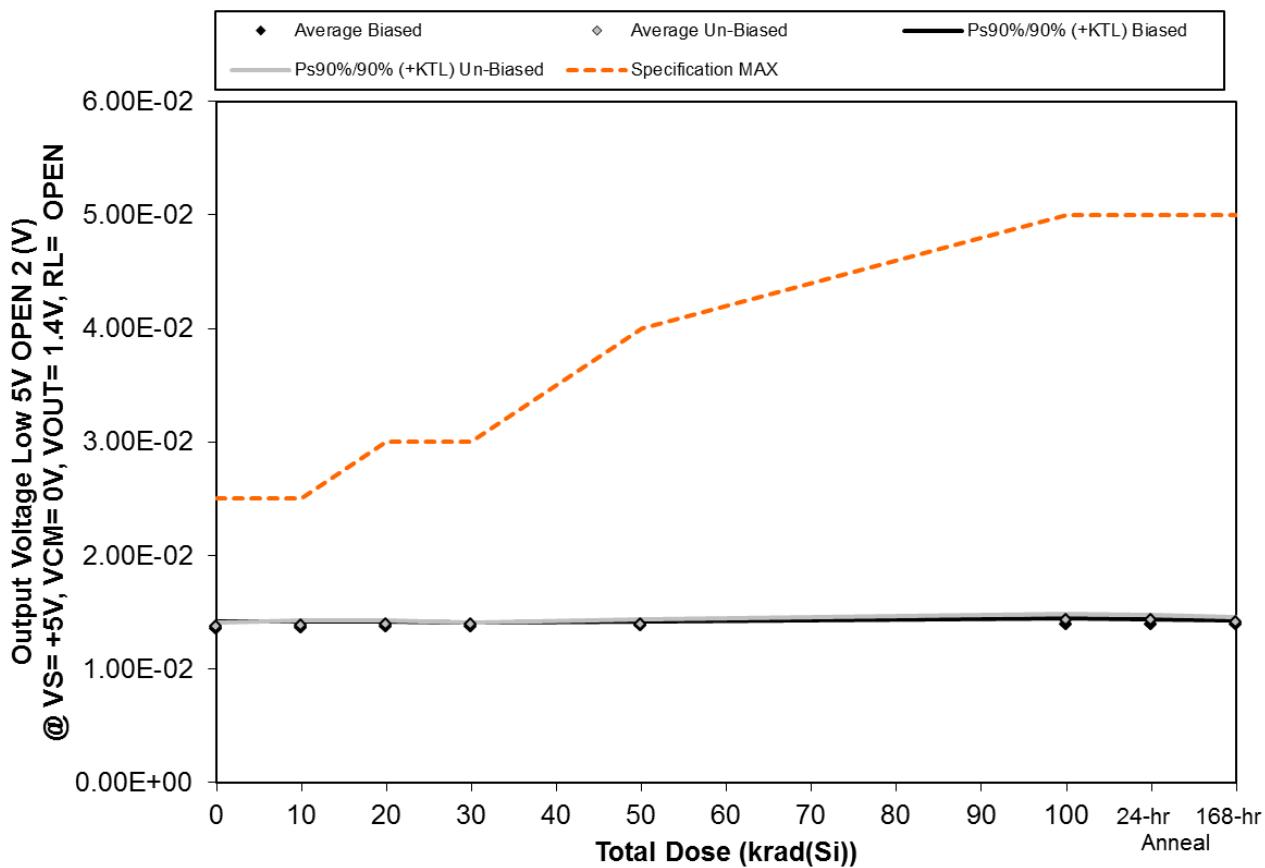


Figure 5.74. Plot of Output Voltage Low 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.74. Raw data for Output Voltage Low 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.39E-02	1.39E-02	1.39E-02	1.39E-02	1.40E-02	1.42E-02	1.42E-02	1.41E-02
260	1.36E-02	1.37E-02	1.37E-02	1.37E-02	1.39E-02	1.40E-02	1.40E-02	1.40E-02
326	1.35E-02	1.37E-02	1.36E-02	1.38E-02	1.38E-02	1.39E-02	1.39E-02	1.38E-02
328	1.37E-02	1.37E-02	1.39E-02	1.37E-02	1.40E-02	1.40E-02	1.40E-02	1.39E-02
329	1.33E-02	1.34E-02	1.35E-02	1.36E-02	1.37E-02	1.37E-02	1.38E-02	1.39E-02
330	1.38E-02	1.37E-02	1.39E-02	1.39E-02	1.39E-02	1.43E-02	1.43E-02	1.40E-02
331	1.36E-02	1.36E-02	1.37E-02	1.39E-02	1.38E-02	1.41E-02	1.43E-02	1.39E-02
334	1.39E-02	1.40E-02	1.40E-02	1.40E-02	1.40E-02	1.44E-02	1.43E-02	1.42E-02
335	1.38E-02	1.39E-02	1.39E-02	1.40E-02	1.41E-02	1.44E-02	1.44E-02	1.42E-02
344	1.39E-02	1.39E-02	1.41E-02	1.40E-02	1.41E-02	1.46E-02	1.46E-02	1.43E-02
346	1.36E-02	1.36E-02	1.34E-02	1.36E-02	1.35E-02	1.36E-02	1.35E-02	1.37E-02
Biased Statistics								
Average Biased	1.36E-02	1.37E-02	1.37E-02	1.37E-02	1.39E-02	1.40E-02	1.40E-02	1.39E-02
Std Dev Biased	2.24E-04	1.79E-04	1.79E-04	1.14E-04	1.30E-04	1.82E-04	1.48E-04	1.14E-04
Ps90%/90% (+KTL) Biased	1.42E-02	1.42E-02	1.42E-02	1.41E-02	1.42E-02	1.45E-02	1.44E-02	1.43E-02
Ps90%/90% (-KTL) Biased	1.30E-02	1.32E-02	1.32E-02	1.34E-02	1.35E-02	1.35E-02	1.36E-02	1.36E-02
Un-Biased Statistics								
Average Un-Biased	1.38E-02	1.38E-02	1.39E-02	1.40E-02	1.40E-02	1.44E-02	1.44E-02	1.41E-02
Std Dev Un-Biased	1.22E-04	1.64E-04	1.48E-04	5.48E-05	1.30E-04	1.82E-04	1.30E-04	1.64E-04
Ps90%/90% (+KTL) Un-Biased	1.41E-02	1.43E-02	1.43E-02	1.41E-02	1.43E-02	1.49E-02	1.47E-02	1.46E-02
Ps90%/90% (-KTL) Un-Biased	1.35E-02	1.34E-02	1.35E-02	1.38E-02	1.36E-02	1.39E-02	1.40E-02	1.37E-02
Specification MAX	2.50E-02	2.50E-02	3.00E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

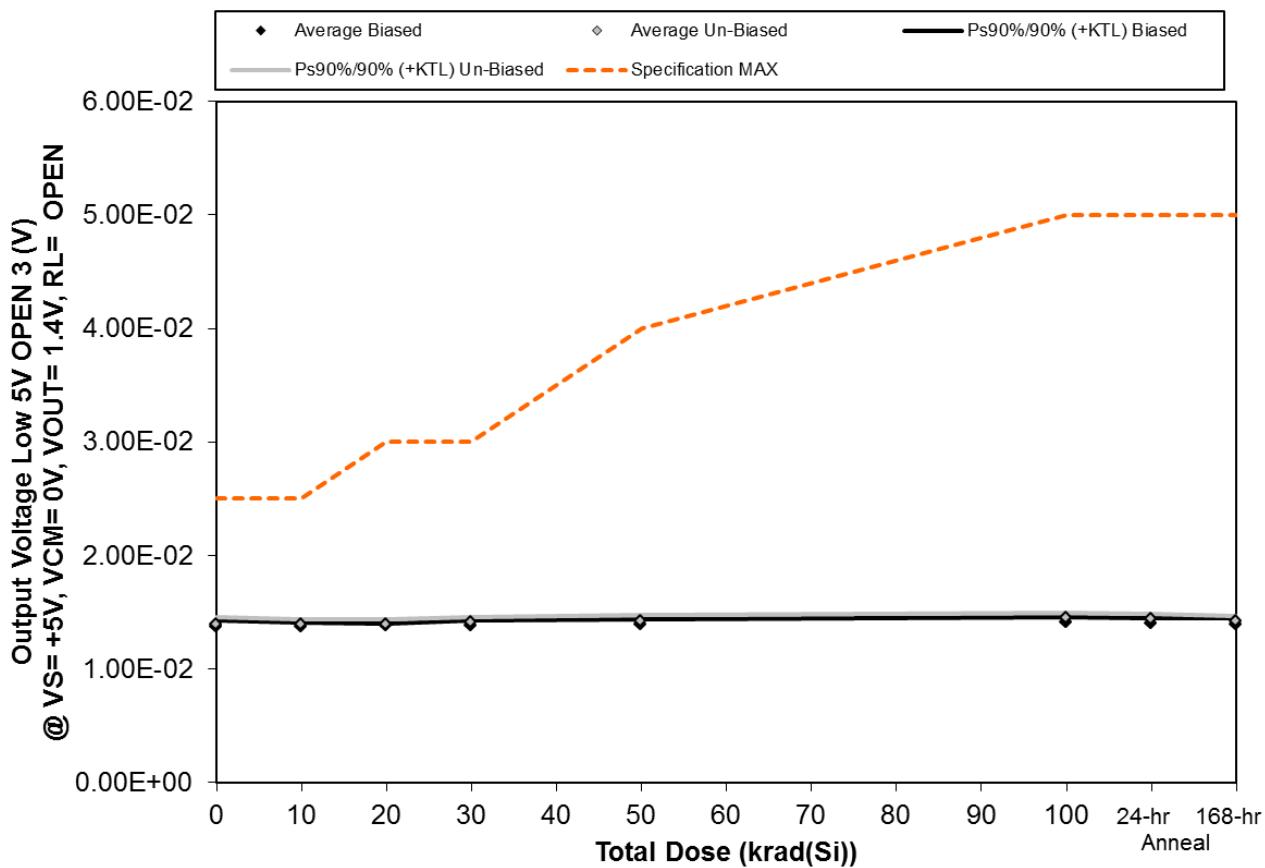


Figure 5.75. Plot of Output Voltage Low 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.75. Raw data for Output Voltage Low 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.40E-02	1.39E-02	1.39E-02	1.41E-02	1.42E-02	1.44E-02	1.43E-02	1.42E-02
260	1.38E-02	1.38E-02	1.38E-02	1.38E-02	1.39E-02	1.41E-02	1.41E-02	1.39E-02
326	1.37E-02	1.37E-02	1.38E-02	1.38E-02	1.39E-02	1.41E-02	1.39E-02	1.40E-02
328	1.38E-02	1.39E-02	1.39E-02	1.40E-02	1.41E-02	1.41E-02	1.41E-02	1.40E-02
329	1.35E-02	1.36E-02	1.37E-02	1.37E-02	1.38E-02	1.39E-02	1.40E-02	1.37E-02
330	1.38E-02	1.40E-02	1.39E-02	1.40E-02	1.42E-02	1.45E-02	1.44E-02	1.42E-02
331	1.37E-02	1.38E-02	1.38E-02	1.39E-02	1.40E-02	1.44E-02	1.43E-02	1.40E-02
334	1.42E-02	1.41E-02	1.41E-02	1.43E-02	1.43E-02	1.45E-02	1.45E-02	1.44E-02
335	1.40E-02	1.39E-02	1.41E-02	1.41E-02	1.43E-02	1.45E-02	1.45E-02	1.43E-02
344	1.42E-02	1.41E-02	1.41E-02	1.43E-02	1.45E-02	1.48E-02	1.47E-02	1.44E-02
346	1.37E-02	1.37E-02	1.37E-02	1.37E-02	1.37E-02	1.37E-02	1.37E-02	1.37E-02
Biased Statistics								
Average Biased	1.38E-02	1.38E-02	1.38E-02	1.39E-02	1.40E-02	1.41E-02	1.41E-02	1.40E-02
Std Dev Biased	1.82E-04	1.30E-04	8.37E-05	1.64E-04	1.64E-04	1.79E-04	1.48E-04	1.82E-04
Ps90%/90% (+KTL) Biased	1.43E-02	1.41E-02	1.40E-02	1.43E-02	1.44E-02	1.46E-02	1.45E-02	1.45E-02
Ps90%/90% (-KTL) Biased	1.33E-02	1.34E-02	1.36E-02	1.34E-02	1.35E-02	1.36E-02	1.37E-02	1.35E-02
Un-Biased Statistics								
Average Un-Biased	1.40E-02	1.40E-02	1.40E-02	1.41E-02	1.43E-02	1.45E-02	1.45E-02	1.43E-02
Std Dev Un-Biased	2.28E-04	1.30E-04	1.41E-04	1.79E-04	1.82E-04	1.52E-04	1.48E-04	1.67E-04
Ps90%/90% (+KTL) Un-Biased	1.46E-02	1.43E-02	1.44E-02	1.46E-02	1.48E-02	1.50E-02	1.49E-02	1.47E-02
Ps90%/90% (-KTL) Un-Biased	1.34E-02	1.36E-02	1.36E-02	1.36E-02	1.38E-02	1.41E-02	1.41E-02	1.38E-02
Specification MAX	2.50E-02	2.50E-02	3.00E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

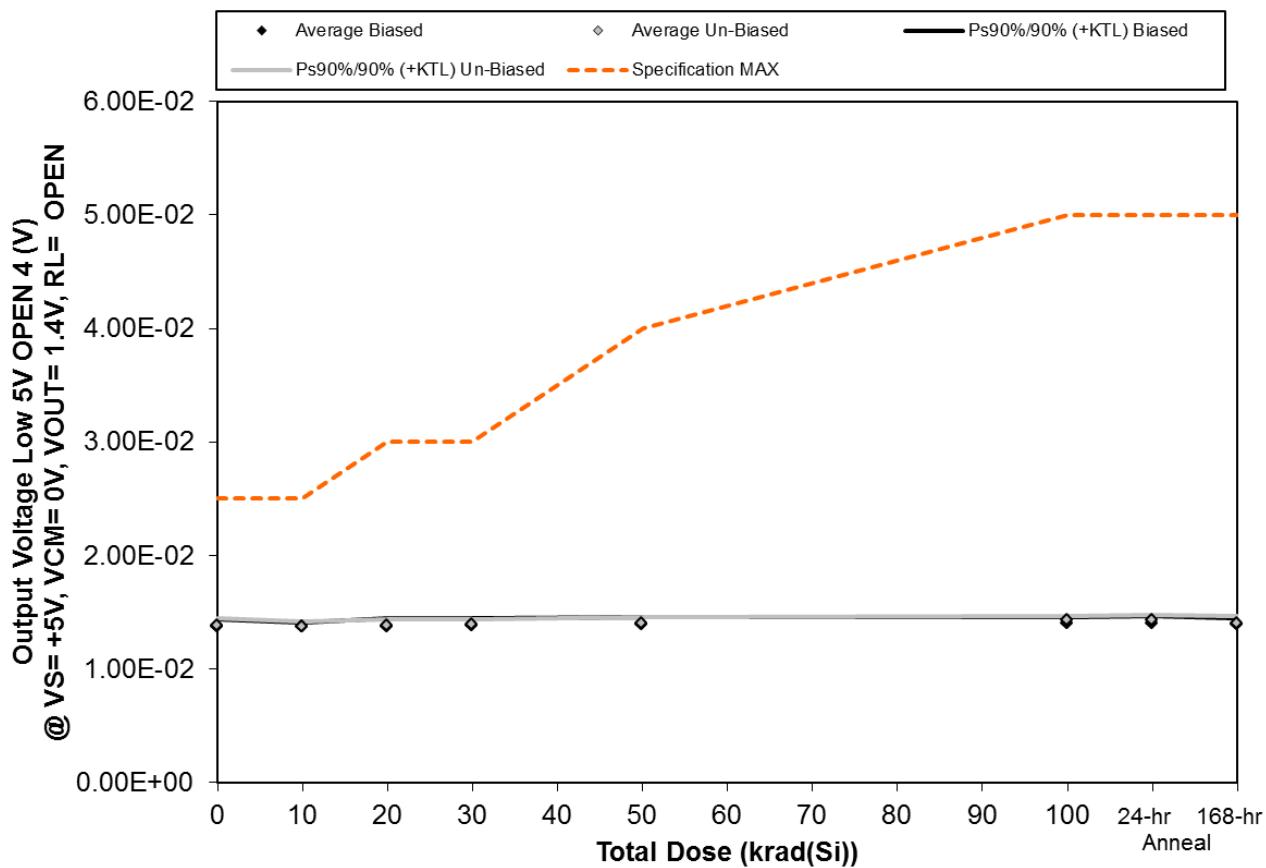


Figure 5.76. Plot of Output Voltage Low 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.76. Raw data for Output Voltage Low 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	1.38E-02	1.38E-02	1.38E-02	1.40E-02	1.41E-02	1.41E-02	1.41E-02	1.40E-02
260	1.37E-02	1.37E-02	1.38E-02	1.38E-02	1.38E-02	1.40E-02	1.41E-02	1.40E-02
326	1.35E-02	1.37E-02	1.35E-02	1.37E-02	1.38E-02	1.40E-02	1.38E-02	1.38E-02
328	1.38E-02	1.37E-02	1.37E-02	1.37E-02	1.38E-02	1.39E-02	1.40E-02	1.39E-02
329	1.41E-02	1.40E-02	1.42E-02	1.42E-02	1.43E-02	1.44E-02	1.44E-02	1.43E-02
330	1.36E-02	1.36E-02	1.36E-02	1.37E-02	1.38E-02	1.42E-02	1.42E-02	1.38E-02
331	1.36E-02	1.37E-02	1.37E-02	1.38E-02	1.39E-02	1.42E-02	1.41E-02	1.39E-02
334	1.41E-02	1.40E-02	1.41E-02	1.41E-02	1.42E-02	1.45E-02	1.45E-02	1.43E-02
335	1.39E-02	1.38E-02	1.39E-02	1.39E-02	1.41E-02	1.44E-02	1.44E-02	1.42E-02
344	1.40E-02	1.39E-02	1.40E-02	1.41E-02	1.42E-02	1.44E-02	1.44E-02	1.42E-02
346	1.35E-02	1.36E-02	1.36E-02	1.36E-02	1.35E-02	1.36E-02	1.36E-02	1.36E-02
Biased Statistics								
Average Biased	1.38E-02	1.38E-02	1.38E-02	1.39E-02	1.40E-02	1.41E-02	1.41E-02	1.40E-02
Std Dev Biased	2.17E-04	1.30E-04	2.55E-04	2.17E-04	2.30E-04	1.92E-04	2.17E-04	1.87E-04
Ps90%/90% (+KTL) Biased	1.44E-02	1.41E-02	1.45E-02	1.45E-02	1.46E-02	1.46E-02	1.47E-02	1.45E-02
Ps90%/90% (-KTL) Biased	1.32E-02	1.34E-02	1.31E-02	1.33E-02	1.33E-02	1.36E-02	1.35E-02	1.35E-02
Un-Biased Statistics								
Average Un-Biased	1.38E-02	1.38E-02	1.39E-02	1.39E-02	1.40E-02	1.43E-02	1.43E-02	1.41E-02
Std Dev Un-Biased	2.30E-04	1.58E-04	2.07E-04	1.79E-04	1.82E-04	1.34E-04	1.64E-04	2.17E-04
Ps90%/90% (+KTL) Un-Biased	1.45E-02	1.42E-02	1.44E-02	1.44E-02	1.45E-02	1.47E-02	1.48E-02	1.47E-02
Ps90%/90% (-KTL) Un-Biased	1.32E-02	1.34E-02	1.33E-02	1.34E-02	1.35E-02	1.40E-02	1.39E-02	1.35E-02
Specification MAX	2.50E-02	2.50E-02	3.00E-02	3.00E-02	4.00E-02	5.00E-02	5.00E-02	5.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

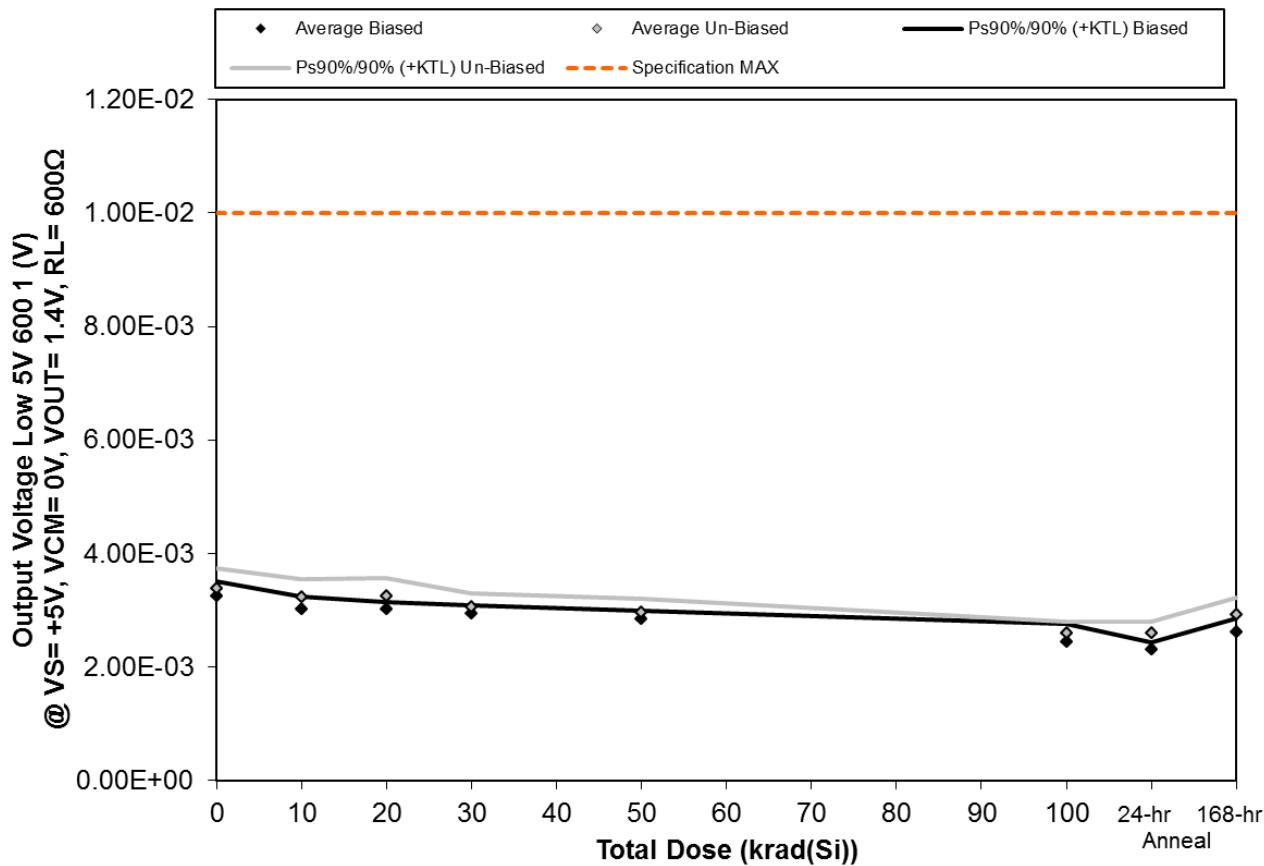


Figure 5.77. Plot of Output Voltage Low 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.77. Raw data for Output Voltage Low 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	3.30E-03	3.00E-03	3.00E-03	2.90E-03	2.80E-03	2.60E-03	2.30E-03	2.70E-03	
260	3.30E-03	3.10E-03	3.00E-03	3.00E-03	2.80E-03	2.50E-03	2.30E-03	2.60E-03	
326	3.30E-03	3.00E-03	3.00E-03	2.90E-03	2.80E-03	2.30E-03	2.30E-03	2.60E-03	
328	3.10E-03	2.90E-03	3.00E-03	2.90E-03	2.90E-03	2.40E-03	2.30E-03	2.50E-03	
329	3.30E-03	3.10E-03	3.10E-03	3.00E-03	2.90E-03	2.40E-03	2.40E-03	2.70E-03	
330	3.30E-03	3.20E-03	3.20E-03	3.00E-03	2.90E-03	2.60E-03	2.60E-03	2.80E-03	
331	3.60E-03	3.40E-03	3.40E-03	3.10E-03	3.10E-03	2.70E-03	2.70E-03	3.10E-03	
334	3.40E-03	3.10E-03	3.30E-03	3.00E-03	2.90E-03	2.60E-03	2.60E-03	2.90E-03	
335	3.30E-03	3.20E-03	3.10E-03	3.00E-03	2.90E-03	2.50E-03	2.60E-03	2.90E-03	
344	3.30E-03	3.30E-03	3.30E-03	3.20E-03	3.00E-03	2.60E-03	2.50E-03	2.90E-03	
346	3.30E-03	2.90E-03	3.00E-03	3.00E-03	3.00E-03	3.00E-03	3.00E-03	3.30E-03	
Biased Statistics									
Average Biased		3.26E-03	3.02E-03	3.02E-03	2.94E-03	2.84E-03	2.44E-03	2.32E-03	2.62E-03
Std Dev Biased		8.94E-05	8.37E-05	4.47E-05	5.48E-05	5.48E-05	1.14E-04	4.47E-05	8.37E-05
Ps90%/90% (+KTL) Biased		3.51E-03	3.25E-03	3.14E-03	3.09E-03	2.99E-03	2.75E-03	2.44E-03	2.85E-03
Ps90%/90% (-KTL) Biased		3.01E-03	2.79E-03	2.90E-03	2.79E-03	2.69E-03	2.13E-03	2.20E-03	2.39E-03
Un-Biased Statistics									
Average Un-Biased		3.38E-03	3.24E-03	3.26E-03	3.06E-03	2.96E-03	2.60E-03	2.60E-03	2.92E-03
Std Dev Un-Biased		1.30E-04	1.14E-04	1.14E-04	8.94E-05	8.94E-05	7.07E-05	7.07E-05	1.10E-04
Ps90%/90% (+KTL) Un-Biased		3.74E-03	3.55E-03	3.57E-03	3.31E-03	3.21E-03	2.79E-03	2.79E-03	3.22E-03
Ps90%/90% (-KTL) Un-Biased		3.02E-03	2.93E-03	2.95E-03	2.81E-03	2.71E-03	2.41E-03	2.41E-03	2.62E-03
Specification MAX		1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

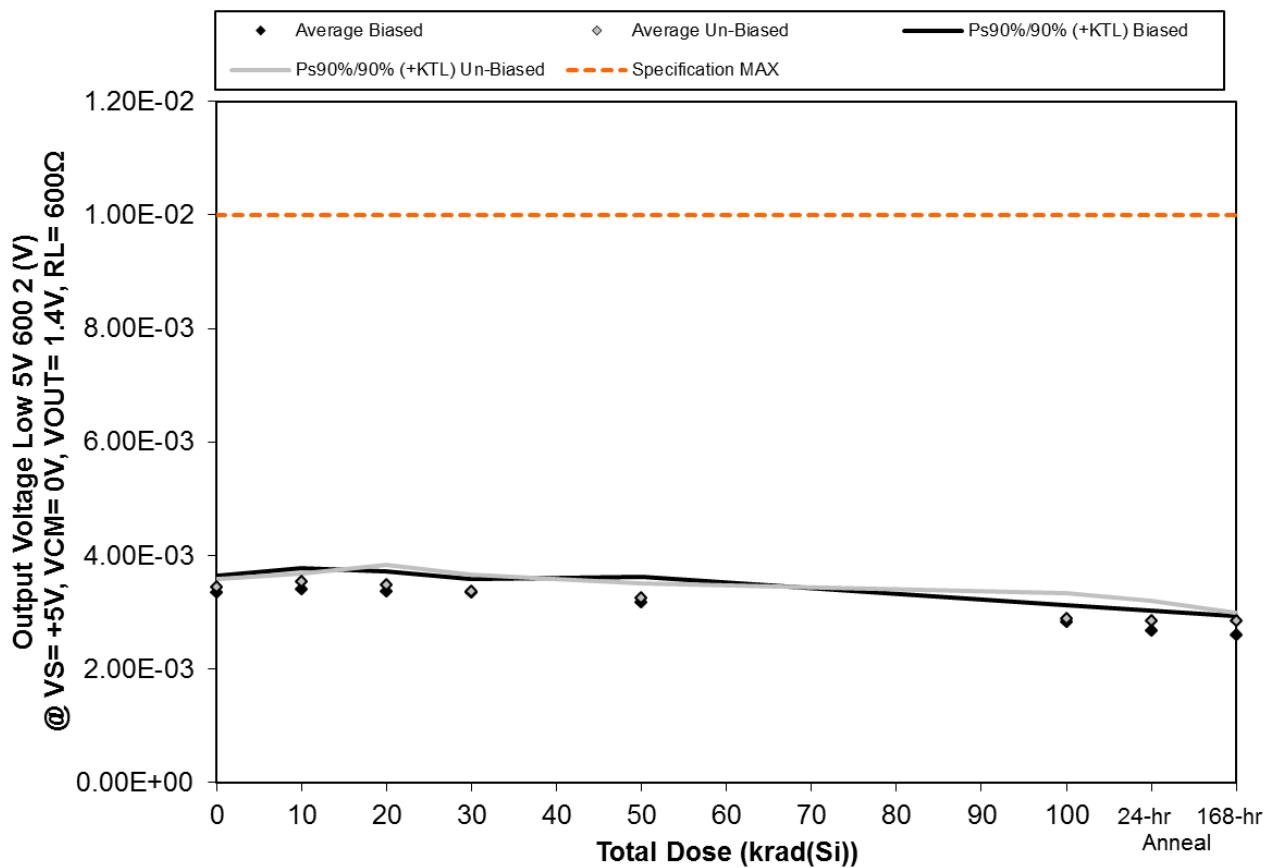


Figure 5.78. Plot of Output Voltage Low 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.78. Raw data for Output Voltage Low 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	3.40E-03	3.40E-03	3.30E-03	3.40E-03	3.30E-03	2.80E-03	2.60E-03	2.60E-03	
260	3.30E-03	3.40E-03	3.30E-03	3.20E-03	3.10E-03	2.80E-03	2.60E-03	2.50E-03	
326	3.20E-03	3.20E-03	3.30E-03	3.30E-03	3.00E-03	2.70E-03	2.60E-03	2.50E-03	
328	3.50E-03	3.60E-03	3.60E-03	3.40E-03	3.40E-03	3.00E-03	2.90E-03	2.80E-03	
329	3.30E-03	3.40E-03	3.30E-03	3.40E-03	3.10E-03	2.80E-03	2.70E-03	2.60E-03	
330	3.40E-03	3.60E-03	3.50E-03	3.40E-03	3.30E-03	3.10E-03	2.90E-03	2.90E-03	
331	3.50E-03	3.50E-03	3.60E-03	3.50E-03	3.40E-03	3.00E-03	2.90E-03	2.80E-03	
334	3.40E-03	3.50E-03	3.30E-03	3.20E-03	3.20E-03	2.70E-03	2.70E-03	2.80E-03	
335	3.40E-03	3.50E-03	3.40E-03	3.30E-03	3.20E-03	2.80E-03	2.70E-03	2.80E-03	
344	3.50E-03	3.60E-03	3.60E-03	3.40E-03	3.20E-03	2.80E-03	3.00E-03	2.90E-03	
346	3.40E-03	3.40E-03	3.40E-03	3.40E-03	3.30E-03	3.30E-03	3.40E-03	3.40E-03	
Biased Statistics									
Average Biased		3.34E-03	3.40E-03	3.36E-03	3.34E-03	3.18E-03	2.82E-03	2.68E-03	2.60E-03
Std Dev Biased		1.14E-04	1.41E-04	1.34E-04	8.94E-05	1.64E-04	1.10E-04	1.30E-04	1.22E-04
Ps90%/90% (+KTL) Biased		3.65E-03	3.79E-03	3.73E-03	3.59E-03	3.63E-03	3.12E-03	3.04E-03	2.94E-03
Ps90%/90% (-KTL) Biased		3.03E-03	3.01E-03	2.99E-03	3.09E-03	2.73E-03	2.52E-03	2.32E-03	2.26E-03
Un-Biased Statistics									
Average Un-Biased		3.44E-03	3.54E-03	3.48E-03	3.36E-03	3.26E-03	2.88E-03	2.84E-03	2.84E-03
Std Dev Un-Biased		5.48E-05	5.48E-05	1.30E-04	1.14E-04	8.94E-05	1.64E-04	1.34E-04	5.48E-05
Ps90%/90% (+KTL) Un-Biased		3.59E-03	3.69E-03	3.84E-03	3.67E-03	3.51E-03	3.33E-03	3.21E-03	2.99E-03
Ps90%/90% (-KTL) Un-Biased		3.29E-03	3.39E-03	3.12E-03	3.05E-03	3.01E-03	2.43E-03	2.47E-03	2.69E-03
Specification MAX		1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

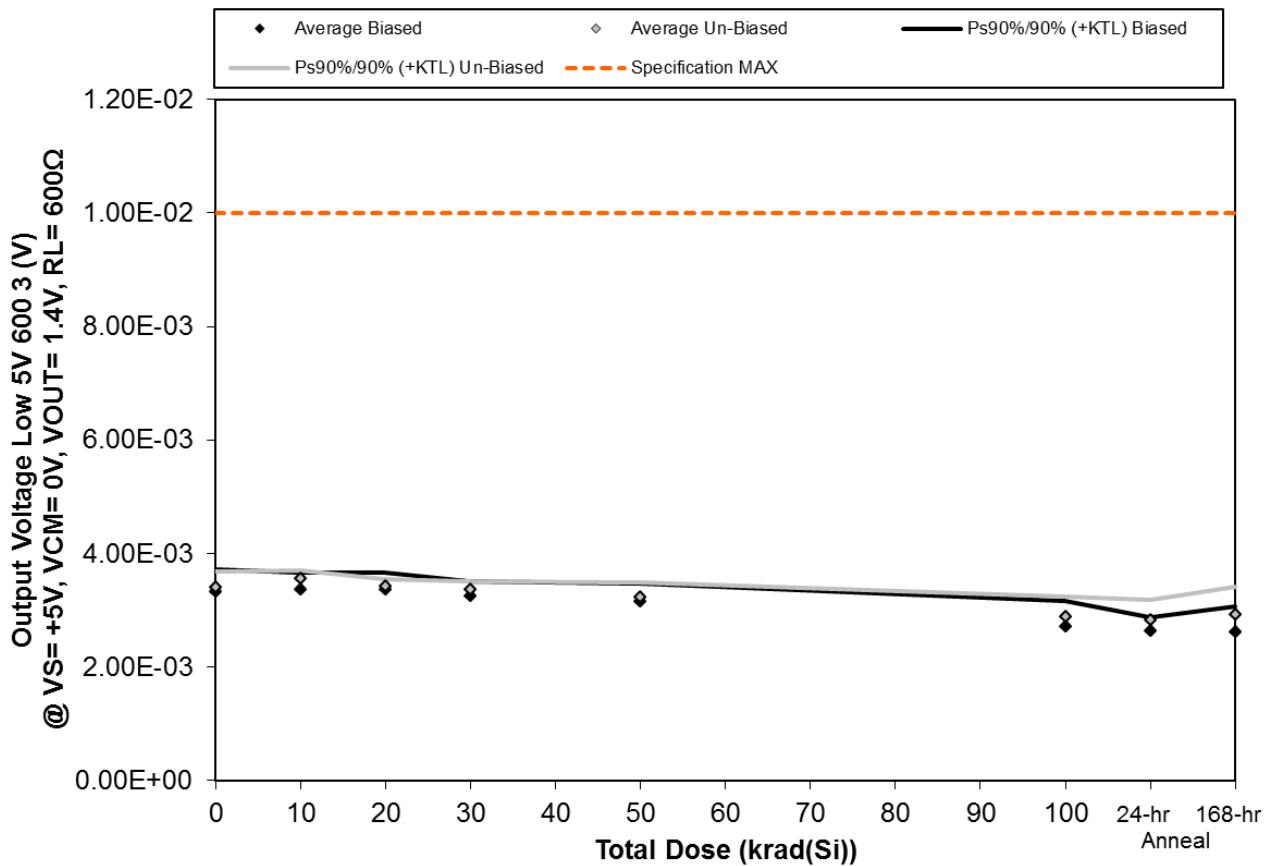


Figure 5.79. Plot of Output Voltage Low 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.79. Raw data for Output Voltage Low 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω		Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
Device		0	10	20	30	50	100		
259	3.40E-03	3.30E-03	3.40E-03	3.20E-03	3.20E-03	2.70E-03	2.60E-03	2.50E-03	
260	3.30E-03	3.40E-03	3.30E-03	3.30E-03	3.10E-03	2.70E-03	2.60E-03	2.60E-03	
326	3.10E-03	3.20E-03	3.20E-03	3.20E-03	3.00E-03	2.60E-03	2.60E-03	2.50E-03	
328	3.50E-03	3.50E-03	3.50E-03	3.40E-03	3.30E-03	3.00E-03	2.80E-03	2.90E-03	
329	3.30E-03	3.40E-03	3.40E-03	3.20E-03	3.20E-03	2.60E-03	2.60E-03	2.60E-03	
330	3.40E-03	3.60E-03	3.40E-03	3.40E-03	3.30E-03	3.00E-03	2.90E-03	2.90E-03	
331	3.50E-03	3.60E-03	3.50E-03	3.40E-03	3.30E-03	3.00E-03	3.00E-03	3.10E-03	
334	3.30E-03	3.50E-03	3.40E-03	3.30E-03	3.10E-03	2.70E-03	2.70E-03	2.70E-03	
335	3.30E-03	3.50E-03	3.40E-03	3.30E-03	3.20E-03	2.80E-03	2.70E-03	2.80E-03	
344	3.50E-03	3.60E-03	3.40E-03	3.40E-03	3.30E-03	2.90E-03	2.80E-03	3.10E-03	
346	3.40E-03	3.40E-03	3.40E-03	3.30E-03	3.30E-03	3.40E-03	3.40E-03	3.40E-03	
Biased Statistics									
Average Biased		3.32E-03	3.36E-03	3.36E-03	3.26E-03	3.16E-03	2.72E-03	2.64E-03	2.62E-03
Std Dev Biased		1.48E-04	1.14E-04	1.14E-04	8.94E-05	1.14E-04	1.64E-04	8.94E-05	1.64E-04
Ps90%/90% (+KTL) Biased		3.73E-03	3.67E-03	3.67E-03	3.51E-03	3.47E-03	3.17E-03	2.89E-03	3.07E-03
Ps90%/90% (-KTL) Biased		2.91E-03	3.05E-03	3.05E-03	3.01E-03	2.85E-03	2.27E-03	2.39E-03	2.17E-03
Un-Biased Statistics									
Average Un-Biased		3.40E-03	3.56E-03	3.42E-03	3.36E-03	3.24E-03	2.88E-03	2.82E-03	2.92E-03
Std Dev Un-Biased		1.00E-04	5.48E-05	4.47E-05	5.48E-05	8.94E-05	1.30E-04	1.30E-04	1.79E-04
Ps90%/90% (+KTL) Un-Biased		3.67E-03	3.71E-03	3.54E-03	3.51E-03	3.49E-03	3.24E-03	3.18E-03	3.41E-03
Ps90%/90% (-KTL) Un-Biased		3.13E-03	3.41E-03	3.30E-03	3.21E-03	2.99E-03	2.52E-03	2.46E-03	2.43E-03
Specification MAX		1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status		PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

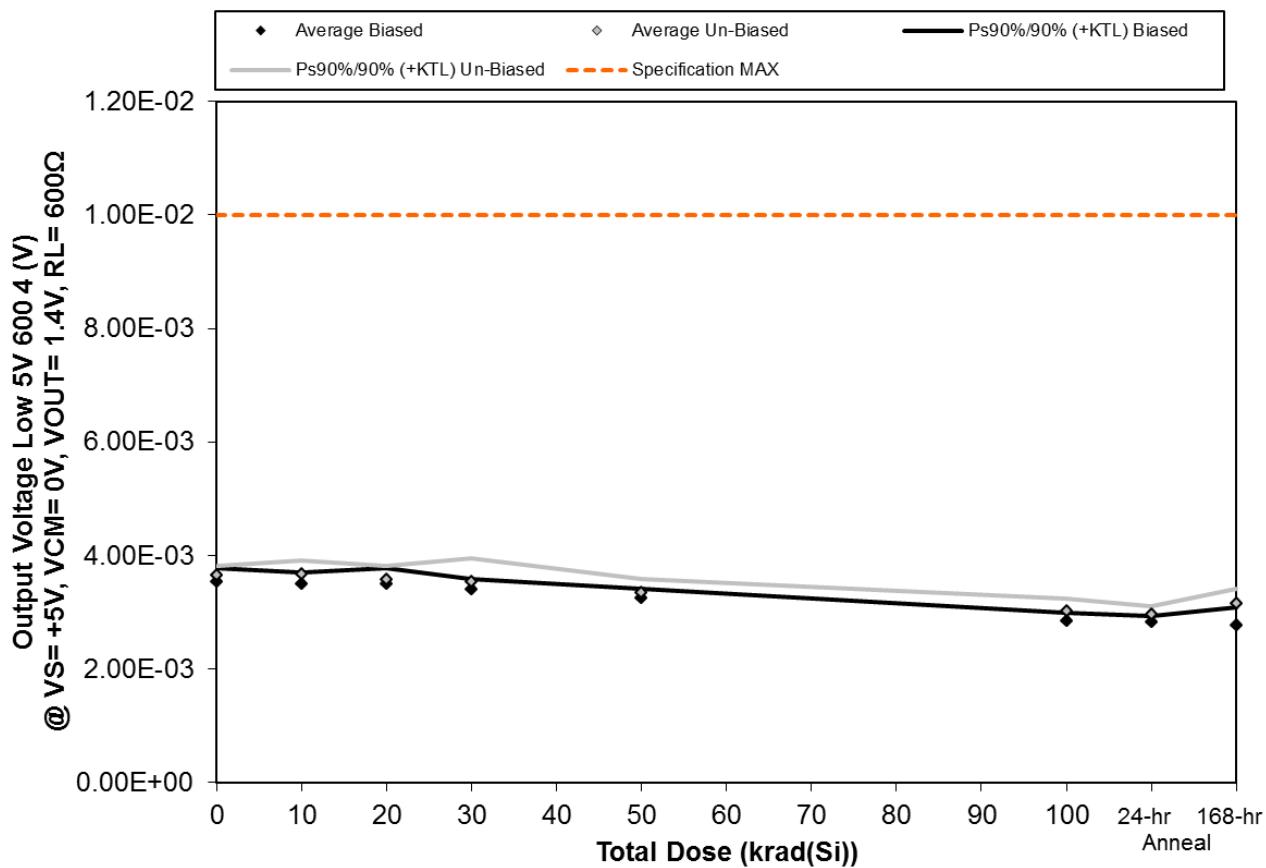


Figure 5.80. Plot of Output Voltage Low 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600 Ω versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.80. Raw data for Output Voltage Low 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Device	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
259	3.60E-03	3.50E-03	3.60E-03	3.50E-03	3.30E-03	2.90E-03	2.80E-03	2.90E-03
260	3.60E-03	3.50E-03	3.60E-03	3.40E-03	3.30E-03	2.90E-03	2.80E-03	2.70E-03
326	3.40E-03	3.50E-03	3.40E-03	3.30E-03	3.20E-03	2.80E-03	2.80E-03	2.70E-03
328	3.50E-03	3.40E-03	3.40E-03	3.40E-03	3.30E-03	2.80E-03	2.80E-03	2.70E-03
329	3.60E-03	3.60E-03	3.50E-03	3.40E-03	3.20E-03	2.80E-03	2.90E-03	2.90E-03
330	3.60E-03	3.60E-03	3.50E-03	3.40E-03	3.30E-03	3.10E-03	3.00E-03	3.10E-03
331	3.70E-03	3.70E-03	3.60E-03	3.70E-03	3.50E-03	3.10E-03	3.00E-03	3.30E-03
334	3.70E-03	3.60E-03	3.70E-03	3.50E-03	3.30E-03	2.90E-03	3.00E-03	3.10E-03
335	3.60E-03	3.80E-03	3.50E-03	3.40E-03	3.30E-03	3.00E-03	2.90E-03	3.10E-03
344	3.70E-03	3.70E-03	3.60E-03	3.70E-03	3.30E-03	3.00E-03	2.90E-03	3.20E-03
346	3.50E-03	3.50E-03	3.40E-03	3.30E-03	3.40E-03	3.30E-03	3.30E-03	3.40E-03
Biased Statistics								
Average Biased	3.54E-03	3.50E-03	3.50E-03	3.40E-03	3.26E-03	2.84E-03	2.82E-03	2.78E-03
Std Dev Biased	8.94E-05	7.07E-05	1.00E-04	7.07E-05	5.48E-05	5.48E-05	4.47E-05	1.10E-04
Ps90%/90% (+KTL) Biased	3.79E-03	3.69E-03	3.77E-03	3.59E-03	3.41E-03	2.99E-03	2.94E-03	3.08E-03
Ps90%/90% (-KTL) Biased	3.29E-03	3.31E-03	3.23E-03	3.21E-03	3.11E-03	2.69E-03	2.70E-03	2.48E-03
Un-Biased Statistics								
Average Un-Biased	3.66E-03	3.68E-03	3.58E-03	3.54E-03	3.34E-03	3.02E-03	2.96E-03	3.16E-03
Std Dev Un-Biased	5.48E-05	8.37E-05	8.37E-05	1.52E-04	8.94E-05	8.37E-05	5.48E-05	8.94E-05
Ps90%/90% (+KTL) Un-Biased	3.81E-03	3.91E-03	3.81E-03	3.96E-03	3.59E-03	3.25E-03	3.11E-03	3.41E-03
Ps90%/90% (-KTL) Un-Biased	3.51E-03	3.45E-03	3.35E-03	3.12E-03	3.09E-03	2.79E-03	2.81E-03	2.91E-03
Specification MAX	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02	1.00E-02
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

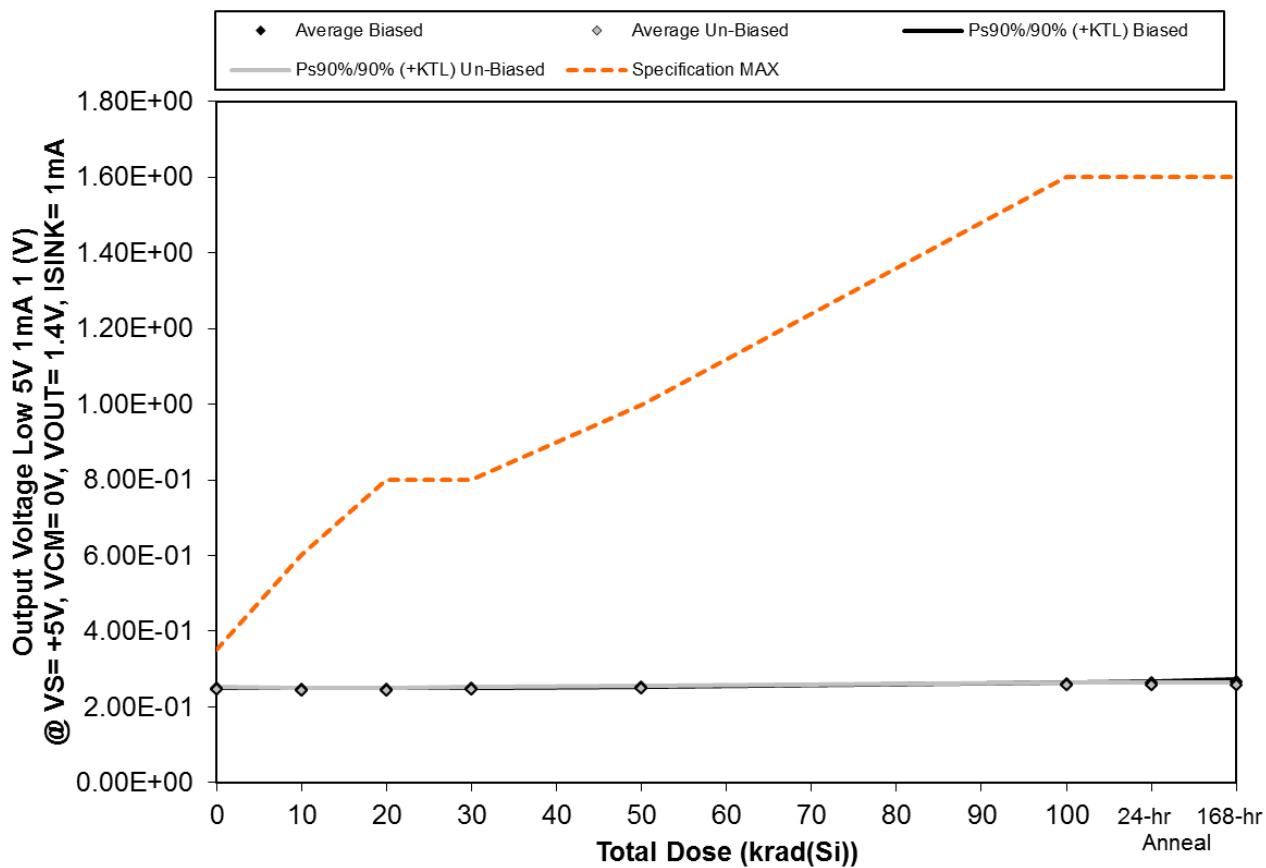


Figure 5.81. Plot of Output Voltage Low 5V 1mA 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.

Table 5.81. Raw data for Output Voltage Low 5V 1mA 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 1mA 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.48E-01	2.46E-01	2.46E-01	2.47E-01	2.50E-01	2.60E-01	2.63E-01	2.66E-01
260	2.48E-01	2.47E-01	2.47E-01	2.48E-01	2.51E-01	2.61E-01	2.64E-01	2.68E-01
326	2.50E-01	2.48E-01	2.48E-01	2.49E-01	2.52E-01	2.63E-01	2.66E-01	2.70E-01
328	2.47E-01	2.47E-01	2.46E-01	2.47E-01	2.50E-01	2.60E-01	2.63E-01	2.68E-01
329	2.48E-01	2.47E-01	2.46E-01	2.47E-01	2.50E-01	2.59E-01	2.62E-01	2.65E-01
330	2.49E-01	2.46E-01	2.46E-01	2.48E-01	2.51E-01	2.59E-01	2.61E-01	2.61E-01
331	2.48E-01	2.46E-01	2.46E-01	2.48E-01	2.51E-01	2.59E-01	2.60E-01	2.59E-01
334	2.45E-01	2.41E-01	2.42E-01	2.43E-01	2.45E-01	2.54E-01	2.55E-01	2.55E-01
335	2.45E-01	2.42E-01	2.42E-01	2.44E-01	2.47E-01	2.55E-01	2.57E-01	2.57E-01
344	2.44E-01	2.41E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.56E-01	2.56E-01
346	2.48E-01	2.48E-01	2.48E-01	2.48E-01	2.48E-01	2.48E-01	2.47E-01	2.47E-01
Biased Statistics								
Average Biased	2.48E-01	2.47E-01	2.47E-01	2.48E-01	2.51E-01	2.61E-01	2.64E-01	2.67E-01
Std Dev Biased	1.10E-03	7.07E-04	8.94E-04	8.94E-04	8.94E-04	1.52E-03	1.52E-03	1.95E-03
Ps90%/90% (+KTL) Biased	2.51E-01	2.49E-01	2.49E-01	2.50E-01	2.53E-01	2.65E-01	2.68E-01	2.73E-01
Ps90%/90% (-KTL) Biased	2.45E-01	2.45E-01	2.44E-01	2.45E-01	2.48E-01	2.56E-01	2.59E-01	2.62E-01
Un-Biased Statistics								
Average Un-Biased	2.46E-01	2.43E-01	2.44E-01	2.45E-01	2.48E-01	2.56E-01	2.58E-01	2.58E-01
Std Dev Un-Biased	2.17E-03	2.59E-03	2.19E-03	2.59E-03	2.83E-03	2.59E-03	2.59E-03	2.41E-03
Ps90%/90% (+KTL) Un-Biased	2.52E-01	2.50E-01	2.50E-01	2.52E-01	2.56E-01	2.63E-01	2.65E-01	2.64E-01
Ps90%/90% (-KTL) Un-Biased	2.40E-01	2.36E-01	2.38E-01	2.38E-01	2.40E-01	2.49E-01	2.51E-01	2.51E-01
Specification MAX	3.50E-01	6.00E-01	8.00E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

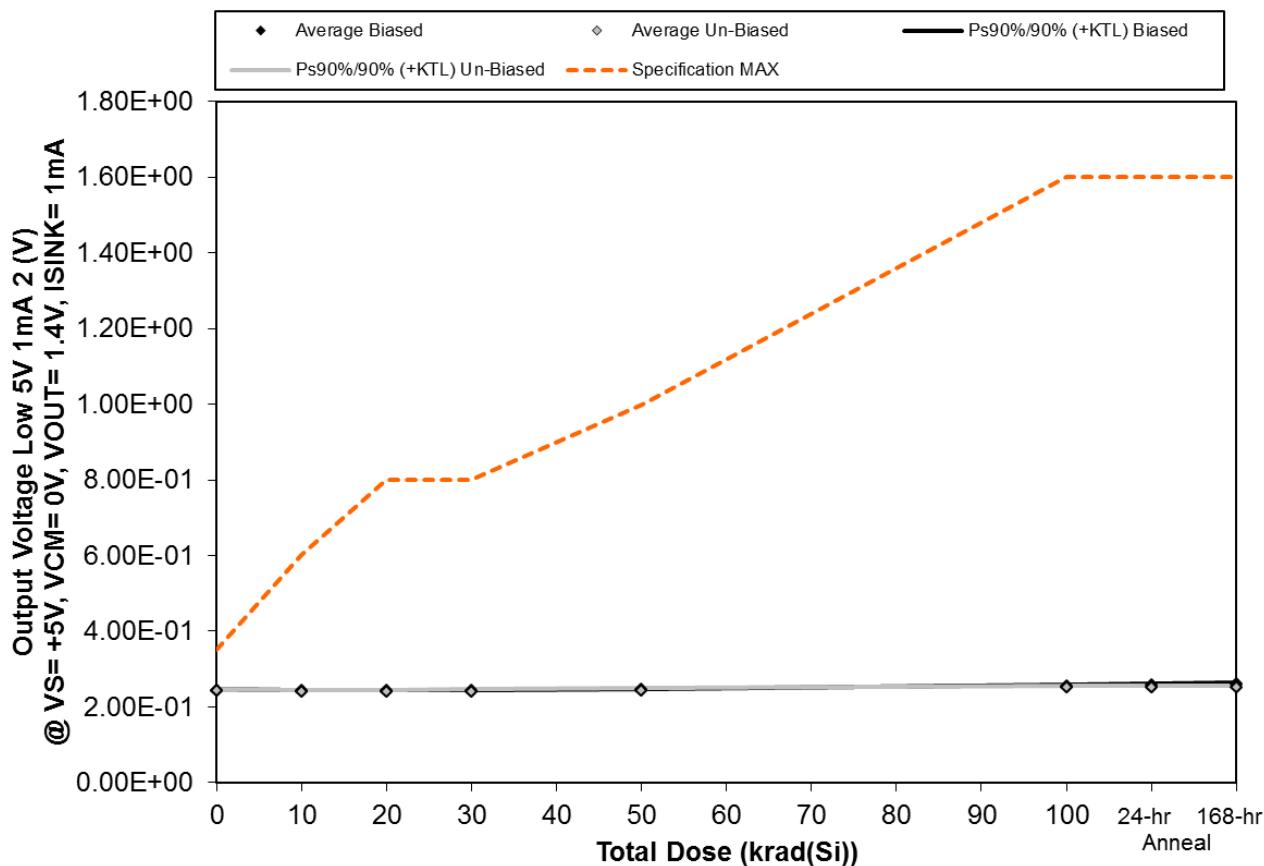


Figure 5.82. Plot of Output Voltage Low 5V 1mA 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.82. Raw data for Output Voltage Low 5V 1mA 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 1mA 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.44E-01	2.42E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.57E-01	2.60E-01
260	2.44E-01	2.42E-01	2.42E-01	2.43E-01	2.46E-01	2.55E-01	2.57E-01	2.60E-01
326	2.44E-01	2.42E-01	2.42E-01	2.44E-01	2.47E-01	2.56E-01	2.58E-01	2.61E-01
328	2.42E-01	2.41E-01	2.41E-01	2.42E-01	2.45E-01	2.52E-01	2.54E-01	2.57E-01
329	2.44E-01	2.42E-01	2.42E-01	2.44E-01	2.46E-01	2.55E-01	2.57E-01	2.60E-01
330	2.39E-01	2.36E-01	2.37E-01	2.38E-01	2.40E-01	2.47E-01	2.49E-01	2.49E-01
331	2.43E-01	2.40E-01	2.41E-01	2.42E-01	2.45E-01	2.52E-01	2.52E-01	2.52E-01
334	2.42E-01	2.37E-01	2.38E-01	2.40E-01	2.42E-01	2.50E-01	2.51E-01	2.51E-01
335	2.44E-01	2.42E-01	2.42E-01	2.44E-01	2.46E-01	2.53E-01	2.54E-01	2.54E-01
344	2.42E-01	2.40E-01	2.40E-01	2.41E-01	2.44E-01	2.51E-01	2.53E-01	2.53E-01
346	2.44E-01	2.43E-01	2.43E-01	2.43E-01	2.44E-01	2.43E-01	2.42E-01	2.42E-01
Biased Statistics								
Average Biased	2.44E-01	2.42E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.57E-01	2.60E-01
Std Dev Biased	8.94E-04	4.47E-04	4.47E-04	8.37E-04	7.07E-04	1.52E-03	1.52E-03	1.52E-03
Ps90%/90% (+KTL) Biased	2.46E-01	2.43E-01	2.43E-01	2.45E-01	2.48E-01	2.59E-01	2.61E-01	2.64E-01
Ps90%/90% (-KTL) Biased	2.41E-01	2.41E-01	2.41E-01	2.41E-01	2.44E-01	2.50E-01	2.52E-01	2.55E-01
Un-Biased Statistics								
Average Un-Biased	2.42E-01	2.39E-01	2.40E-01	2.41E-01	2.43E-01	2.51E-01	2.52E-01	2.52E-01
Std Dev Un-Biased	1.87E-03	2.45E-03	2.07E-03	2.24E-03	2.41E-03	2.30E-03	1.92E-03	1.92E-03
Ps90%/90% (+KTL) Un-Biased	2.47E-01	2.46E-01	2.45E-01	2.47E-01	2.50E-01	2.57E-01	2.57E-01	2.57E-01
Ps90%/90% (-KTL) Un-Biased	2.37E-01	2.32E-01	2.34E-01	2.35E-01	2.37E-01	2.44E-01	2.47E-01	2.47E-01
Specification MAX	3.50E-01	6.00E-01	8.00E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

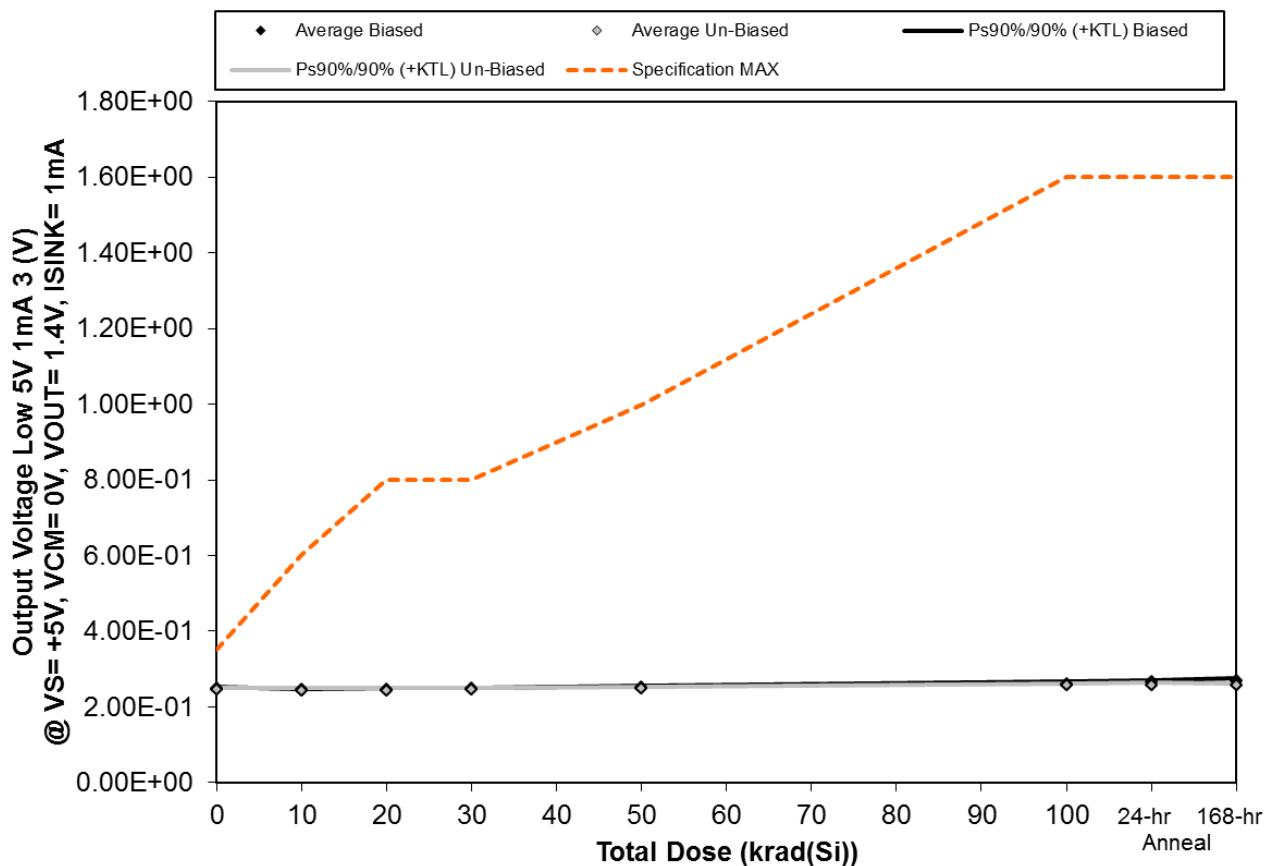


Figure 5.83. Plot of Output Voltage Low 5V 1mA 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.83. Raw data for Output Voltage Low 5V 1mA 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 1mA 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.49E-01	2.47E-01	2.47E-01	2.48E-01	2.51E-01	2.61E-01	2.65E-01	2.68E-01
260	2.49E-01	2.46E-01	2.47E-01	2.48E-01	2.51E-01	2.61E-01	2.65E-01	2.69E-01
326	2.50E-01	2.47E-01	2.48E-01	2.49E-01	2.53E-01	2.63E-01	2.67E-01	2.71E-01
328	2.47E-01	2.46E-01	2.45E-01	2.47E-01	2.49E-01	2.58E-01	2.61E-01	2.64E-01
329	2.50E-01	2.47E-01	2.48E-01	2.49E-01	2.53E-01	2.63E-01	2.66E-01	2.70E-01
330	2.44E-01	2.41E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.56E-01	2.56E-01
331	2.47E-01	2.45E-01	2.45E-01	2.47E-01	2.50E-01	2.58E-01	2.59E-01	2.58E-01
334	2.46E-01	2.42E-01	2.43E-01	2.45E-01	2.47E-01	2.57E-01	2.58E-01	2.58E-01
335	2.49E-01	2.46E-01	2.47E-01	2.48E-01	2.50E-01	2.58E-01	2.60E-01	2.60E-01
344	2.47E-01	2.43E-01	2.44E-01	2.46E-01	2.49E-01	2.57E-01	2.60E-01	2.59E-01
346	2.48E-01	2.47E-01	2.48E-01	2.48E-01	2.48E-01	2.48E-01	2.47E-01	2.47E-01
Biased Statistics								
Average Biased	2.49E-01	2.47E-01	2.47E-01	2.48E-01	2.51E-01	2.61E-01	2.65E-01	2.68E-01
Std Dev Biased	1.22E-03	5.48E-04	1.22E-03	8.37E-04	1.67E-03	2.05E-03	2.28E-03	2.70E-03
Ps90%/90% (+KTL) Biased	2.52E-01	2.48E-01	2.50E-01	2.50E-01	2.56E-01	2.67E-01	2.71E-01	2.76E-01
Ps90%/90% (-KTL) Biased	2.46E-01	2.45E-01	2.44E-01	2.46E-01	2.47E-01	2.56E-01	2.59E-01	2.61E-01
Un-Biased Statistics								
Average Un-Biased	2.47E-01	2.43E-01	2.44E-01	2.46E-01	2.48E-01	2.57E-01	2.59E-01	2.58E-01
Std Dev Un-Biased	1.82E-03	2.07E-03	1.92E-03	1.92E-03	1.82E-03	1.64E-03	1.67E-03	1.48E-03
Ps90%/90% (+KTL) Un-Biased	2.52E-01	2.49E-01	2.49E-01	2.51E-01	2.53E-01	2.61E-01	2.63E-01	2.62E-01
Ps90%/90% (-KTL) Un-Biased	2.42E-01	2.38E-01	2.39E-01	2.41E-01	2.43E-01	2.52E-01	2.54E-01	2.54E-01
Specification MAX	3.50E-01	6.00E-01	8.00E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS

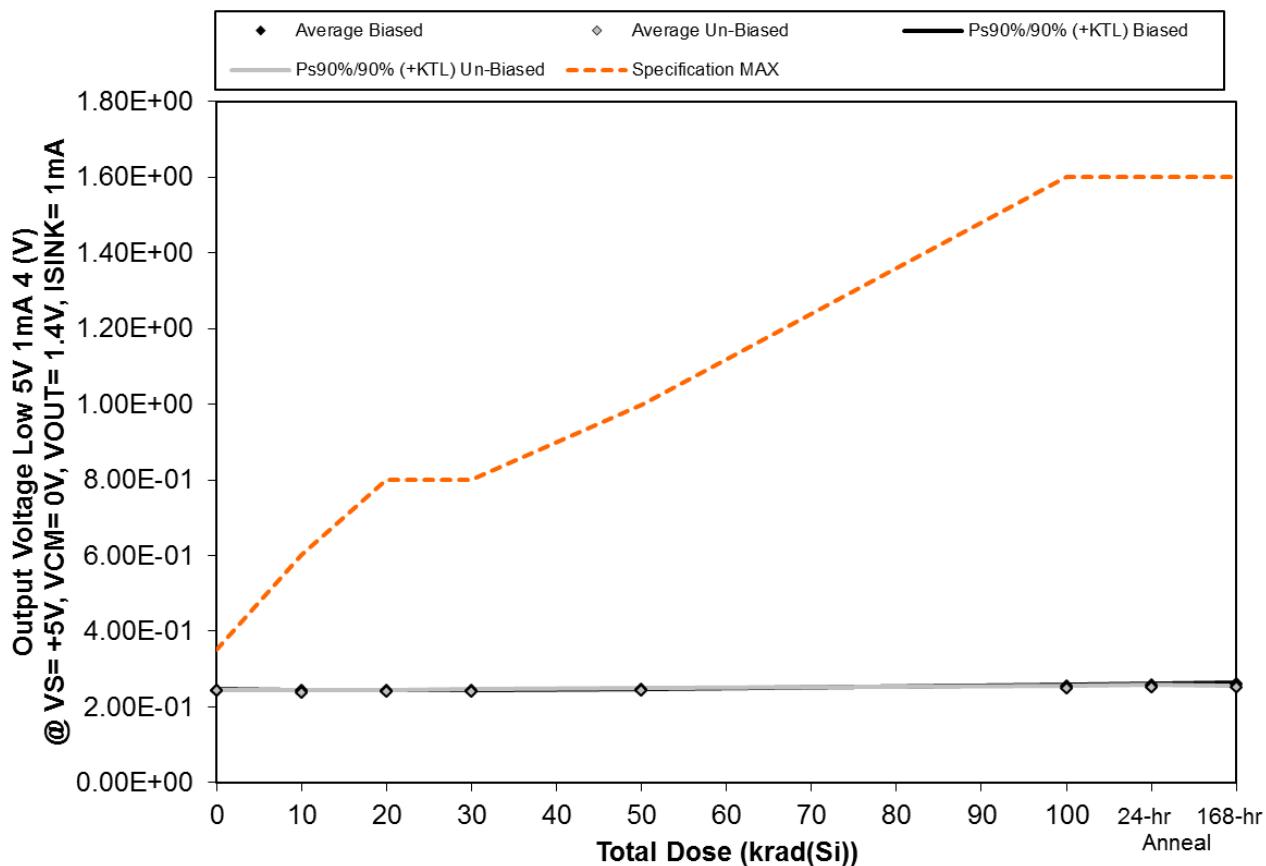


Figure 5.84. Plot of Output Voltage Low 5V 1mA 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose. The solid diamonds are the average of the measured data points for the samples irradiated under electrical bias while the shaded diamonds are the average of the measured data points for the samples irradiated with all pins tied to ground. The black lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated under electrical bias while the gray lines (solid and/or dashed) are the upper and/or lower confidence limits, as determined by KTL statistics, on the samples irradiated in the unbiased condition. The red dotted line(s) are the pre- and/or post-irradiation minimum and/or maximum specification value as defined in the datasheet and/or test plan.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table 5.84. Raw data for Output Voltage Low 5V 1mA 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA versus total dose, including the statistical analysis, specification and the status of the testing (pass/fail).

Output Voltage Low 5V 1mA 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA	Total Dose (krad(Si))						24-hr Anneal	168-hr Anneal
	0	10	20	30	50	100		
Device								
259	2.44E-01	2.43E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.57E-01	2.59E-01
260	2.43E-01	2.43E-01	2.42E-01	2.44E-01	2.46E-01	2.54E-01	2.58E-01	2.60E-01
326	2.45E-01	2.44E-01	2.44E-01	2.44E-01	2.47E-01	2.56E-01	2.59E-01	2.62E-01
328	2.42E-01	2.42E-01	2.41E-01	2.42E-01	2.45E-01	2.53E-01	2.55E-01	2.59E-01
329	2.44E-01	2.43E-01	2.43E-01	2.44E-01	2.46E-01	2.55E-01	2.57E-01	2.60E-01
330	2.43E-01	2.41E-01	2.41E-01	2.43E-01	2.46E-01	2.53E-01	2.54E-01	2.54E-01
331	2.43E-01	2.41E-01	2.41E-01	2.43E-01	2.45E-01	2.52E-01	2.53E-01	2.53E-01
334	2.41E-01	2.36E-01	2.38E-01	2.38E-01	2.41E-01	2.48E-01	2.50E-01	2.50E-01
335	2.41E-01	2.38E-01	2.38E-01	2.39E-01	2.42E-01	2.49E-01	2.49E-01	2.50E-01
344	2.41E-01	2.37E-01	2.38E-01	2.39E-01	2.41E-01	2.48E-01	2.49E-01	2.50E-01
346	2.43E-01	2.42E-01	2.43E-01	2.43E-01	2.43E-01	2.43E-01	2.42E-01	2.42E-01
Biased Statistics								
Average Biased	2.44E-01	2.43E-01	2.42E-01	2.43E-01	2.46E-01	2.54E-01	2.57E-01	2.60E-01
Std Dev Biased	1.14E-03	7.07E-04	1.14E-03	8.94E-04	7.07E-04	1.14E-03	1.48E-03	1.22E-03
Ps90%/90% (+KTL) Biased	2.47E-01	2.45E-01	2.46E-01	2.46E-01	2.48E-01	2.58E-01	2.61E-01	2.63E-01
Ps90%/90% (-KTL) Biased	2.40E-01	2.41E-01	2.39E-01	2.41E-01	2.44E-01	2.51E-01	2.53E-01	2.57E-01
Un-Biased Statistics								
Average Un-Biased	2.42E-01	2.39E-01	2.39E-01	2.40E-01	2.43E-01	2.50E-01	2.51E-01	2.51E-01
Std Dev Un-Biased	1.10E-03	2.30E-03	1.64E-03	2.41E-03	2.35E-03	2.35E-03	2.35E-03	1.95E-03
Ps90%/90% (+KTL) Un-Biased	2.45E-01	2.45E-01	2.44E-01	2.47E-01	2.49E-01	2.56E-01	2.57E-01	2.57E-01
Ps90%/90% (-KTL) Un-Biased	2.39E-01	2.32E-01	2.35E-01	2.34E-01	2.37E-01	2.44E-01	2.45E-01	2.46E-01
Specification MAX	3.50E-01	6.00E-01	8.00E-01	8.00E-01	1.00E+00	1.60E+00	1.60E+00	1.60E+00
Status	PASS	PASS	PASS	PASS	PASS	PASS	PASS	PASS



6.0. Summary / Conclusions

The total ionizing dose testing described in this final report was performed using the facilities at Aeroflex RAD's Longmire Laboratories in Colorado Springs, CO. The high dose rate total ionizing dose (TID) source is a JLSA 81-24 irradiator modified to provide a panoramic exposure. The Co-60 rods are held in the base of the irradiator heavily shielded by lead, during the radiation exposures the rod is raised by an electronic timer/controller and the exposure is performed in air. The dose rate for this irradiator in this configuration ranges from <1rad(Si)/s to a maximum of approximately 300rad(Si)/s, determined by the distance from the source.

The parametric data was obtained as "read and record" and all the raw data plus an attributes summary are contained in this report as well as in a separate Excel file. The attributes data contains the average, standard deviation and the average with the KTL values applied. The KTL value used in this work is 2.742 per MIL-HDBK-814 using one sided tolerance limits of 90/90 and a 5-piece sample size. The 90/90 KTL values were selected to match the statistical levels specified in the MIL-PRF-38535 sampling plan for the qualification of a radiation hardness assured (RHA) component. Note that the following criteria must be met for a device to pass the total ionizing dose test: following the radiation exposure each of the 5 pieces irradiated under electrical bias shall pass the specification value. The units irradiated without electrical bias and the KTL statistics are included in this report for reference only. If any of the 5 pieces irradiated under electrical bias exceed the device post radiation data sheet specification limits, then the lot could be logged as a failure.

Based on this criterion the RH1014MW Quad Precision Operational Amplifier (from the lot date code identified on the first page of this test report) PASSED the total ionizing dose test to the maximum tested dose level of 100krad(Si) with all parameters remaining within their datasheet specifications. Further, the data in this report can be analyzed along with the low dose rate report titled "Enhanced Low Dose Rate Sensitivity (ELDRS) Radiation Testing of the RH1014MW Quad Precision Operational Amplifier for Linear Technology" to demonstrate that these parts do not exhibit ELDRS as defined in the current test method.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Appendix A: Photograph of Packing Label and a Sample Unit-Under-Test to Show Part Traceability





TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Appendix B: Radiation Bias Connections and Absolute Maximum Ratings

TID Radiation Biased Conditions: Extracted from Linear Technology RH1014M Quad Precision Operational Amplifier Datasheet Revision G.

Pin	Function	Connection / Bias
1	OUT A	To Pin 2 Via10kΩ Resistor
2	-IN A	To Pin 1 Via10kΩ Resistor
3	+IN A	8V Via 10kΩ Resistor
4	V+	+15V Decoupled to GND w/ 0.1μF
5	+IN B	8V Via 10kΩ Resistor
6	-IN B	To Pin 7 Via10kΩ Resistor
7	OUT B	To Pin 6 Via10kΩ Resistor
8	OUT C	To Pin 9 Via10kΩ Resistor
9	-IN C	To Pin 8 Via10kΩ Resistor
10	+IN C	8V Via 10kΩ Resistor
11	V-	-15V Decoupled to GND w/ 0.1μF
12	+IN D	8V Via 10kΩ Resistor
13	-IN D	To Pin 14 Via10kΩ Resistor
14	OUT D	To Pin 13 Via10kΩ Resistor

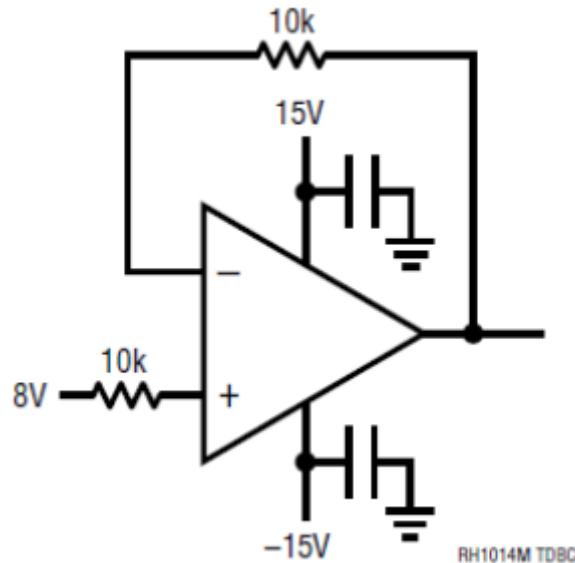


Figure B.1. Irradiation bias circuit. This figure was extracted from Linear Technology RH1014M Quad Precision Operational Amplifier Datasheet Revision G.

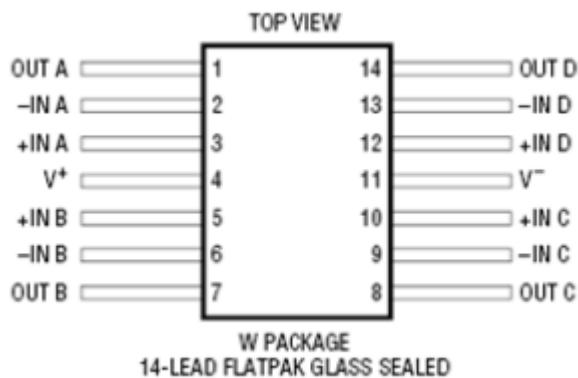


Figure B.2. Package drawing (for reference only). This figure was extracted from Linear Technology RH1014M Quad Precision Operational Amplifier Datasheet Revision G.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

TID Radiation Unbiased Conditions: All pins grounded.

Pin	Function	Connection / Bias
1	OUT A	GND
2	-IN A	GND
3	+IN A	GND
4	V+	GND
5	+IN B	GND
6	-IN B	GND
7	OUT B	GND
8	OUT C	GND
9	-IN C	GND
10	+IN C	GND
11	V-	GND
12	+IN D	GND
13	-IN D	GND
14	OUT D	GND

Absolute Maximum Ratings:

Parameter	Max Rating
Supply Voltage	±22V
Differential Input Voltage	±30V
Input Voltage	Equal to Positive Supply Voltage, 5V Below Negative Supply Voltage
Output Short-Circuit Duration	Indefinite



Appendix C: Electrical Test Parameters and Conditions

The expected ranges of values as well as the measurement conditions are taken from Linear Technology RH1014M Quad Precision Operational Amplifier Datasheet Revision G. All electrical tests for this device are performed on one of Aeroflex RAD's LTS2020 Test Systems. The LTS2020 Test System is a programmable parametric tester that provides parameter measurements for a variety of digital, analog and mixed signal products including voltage regulators, voltage comparators, D to A and A to D converters. The LTS2020 Test System achieves accuracy and sensitivity through the use of software self-calibration and an internal relay matrix with separate family boards and custom personality adapter boards. The tester uses this relay matrix to connect the required test circuits, select the appropriate voltage / current sources and establish the needed measurement loops for all the tests performed. The measured parameters and test conditions are shown in Table C.1.

A listing of the measurement precision/resolution for each parameter is shown in Table C.2. The precision/resolution values were obtained from test data or from the DAC resolution of the LTS-2020 for the particular test shown, whichever is greater. To generate the precision/resolution shown in Table C.2, one of the units-under-test was tested repetitively (a total of 10-times with re-insertion between tests) to obtain the average test value and standard deviation. Using this test data MIL-HDBK-814 90/90 KTL statistics were applied to the measured standard deviation to generate the final measurement range. This value encompasses the precision/resolution of all aspects of the test system, including the LTS2020 mainframe, family board, socket assembly and DUT board as well as insertion error. In some cases, the measurement resolution is limited by the internal DACs, which results in a measured standard deviation of zero. In these instances the precision/resolution will be reported back as the LSB of the DAC.

Note that the testing and statistics used in this document are based on an “analysis of variables” technique, which relies on small sample sizes to qualify much larger lot sizes (see MIL-HDBK-814, p. 91 for a discussion of statistical treatments). Not all measured parameters are well suited to this approach due to inherent large variations. If necessary, larger samples sizes could be used to qualify these parameters using an “attributes” approach.



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table C.1. Measured parameters and test conditions for the RH1014MW Quad Precision Operational Amplifier.

Parameter	Symbol	Test Conditions
Positive Supply Current 15V (A)	+IS_15V	VS= +/-15V, VCM= 0V
Negative Supply Current 15V (A)	-IS_15V	VS= +/-15V, VCM= 0V
Offset Voltage 15V 1 (V)	VOS1_15V	VS= +/-15V, VCM= 0V
Offset Voltage 15V 2 (V)	VOS2_15V	VS= +/-15V, VCM= 0V
Offset Voltage 15V 3 (V)	VOS3_15V	VS= +/-15V, VCM= 0V
Offset Voltage 15V 4 (V)	VOS4_15V	VS= +/-15V, VCM= 0V
Offset Current 15V 1 (A)	IOS1_15V	VS= +/-15V, VCM= 0V
Offset Current 15V 2 (A)	IOS2_15V	VS= +/-15V, VCM= 0V
Offset Current 15V 3 (A)	IOS3_15V	VS= +/-15V, VCM= 0V
Offset Current 15V 4 (A)	IOS4_15V	VS= +/-15V, VCM= 0V
Positive Bias Current 15V 1 (A)	+IB1_15V	VS= +/-15V, VCM= 0V
Positive Bias Current 15V 2 (A)	+IB2_15V	VS= +/-15V, VCM= 0V
Positive Bias Current 15V 3 (A)	+IB3_15V	VS= +/-15V, VCM= 0V
Positive Bias Current 15V 4 (A)	+IB4_15V	VS= +/-15V, VCM= 0V
Negative Bias Current 15V 1 (A)	-IB1_15V	VS= +/-15V, VCM= 0V
Negative Bias Current 15V 2 (A)	-IB2_15V	VS= +/-15V, VCM= 0V
Negative Bias Current 15V 3 (A)	-IB3_15V	VS= +/-15V, VCM= 0V
Negative Bias Current 15V 4 (A)	-IB4_15V	VS= +/-15V, VCM= 0V
Common Mode Rejection Ratio 1 (dB)	CMRR1	VS= +/-15V, VCM= 13V to -15V
Common Mode Rejection Ratio 2 (dB)	CMRR2	VS= +/-15V, VCM= 13V to -15V
Common Mode Rejection Ratio 3 (dB)	CMRR3	VS= +/-15V, VCM= 13V to -15V
Common Mode Rejection Ratio 4 (dB)	CMRR4	VS= +/-15V, VCM= 13V to -15V
Power Supply Rejection Ratio 1 (dB)	PSRR1	VS= +/-10V to +/-18V, VCM= 0V
Power Supply Rejection Ratio 2 (dB)	PSRR2	VS= +/-10V to +/-18V, VCM= 0V
Power Supply Rejection Ratio 3 (dB)	PSRR3	VS= +/-10V to +/-18V, VCM= 0V
Power Supply Rejection Ratio 4 (dB)	PSRR4	VS= +/-10V to +/-18V, VCM= 0V
Open Loop Gain 1 (V/mV)	AVOL1	VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
Open Loop Gain 2 (V/mV)	AVOL2	VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
Open Loop Gain 3 (V/mV)	AVOL3	VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
Open Loop Gain 4 (V/mV)	AVOL4	VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K

An ISO 9001:2008 and DLA Certified Company



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Output Voltage High 15V 1 (V)	+VOUT1_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage High 15V 2 (V)	+VOUT2_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage High 15V 3 (V)	+VOUT3_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage High 15V 4 (V)	+VOUT4_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage Low 15V 1 (V)	-VOUT1_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage Low 15V 2 (V)	-VOUT2_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage Low 15V 3 (V)	-VOUT3_15V	VS= +/-15V, VCM= 0V, RL= 10K
Output Voltage Low 15V 4 (V)	-VOUT4_15V	VS= +/-15V, VCM= 0V, RL= 10K
Positive Slew Rate 1 (V/us)	+SlewRate1	VS= +/-15V
Positive Slew Rate 2 (V/us)	+SlewRate2	VS= +/-15V
Positive Slew Rate 3 (V/us)	+SlewRate3	VS= +/-15V
Positive Slew Rate 4 (V/us)	+SlewRate4	VS= +/-15V
Negative Slew Rate 1 (V/us)	-SlewRate1	VS= +/-15V
Negative Slew Rate 2 (V/us)	-SlewRate2	VS= +/-15V
Negative Slew Rate 3 (V/us)	-SlewRate3	VS= +/-15V
Negative Slew Rate 4 (V/us)	-SlewRate4	VS= +/-15V
Positive Supply Current 5V (A)	+IS_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Negative Supply Current 5V (A)	-IS_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Voltage 5V 1 (V)	VOS1_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Voltage 5V 2 (V)	VOS2_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Voltage 5V 3 (V)	VOS3_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Voltage 5V 4 (V)	VOS4_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Current 5V 1 (A)	IOS1_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Current 5V 2 (A)	IOS2_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Current 5V 3 (A)	IOS3_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Offset Current 5V 4 (A)	IOS4_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Positive Bias Current 5V 1 (A)	+IB1_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Positive Bias Current 5V 2 (A)	+IB2_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Positive Bias Current 5V 3 (A)	+IB3_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Positive Bias Current 5V 4 (A)	+IB4_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Negative Bias Current 5V 1 (A)	-IB1_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Negative Bias Current 5V 2 (A)	-IB2_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Negative Bias Current 5V 3 (A)	-IB3_5V	VS= +5V, VCM= 0V, VOUT= 1.4V
Negative Bias Current 5V 4 (A)	-IB4_5V	VS= +5V, VCM= 0V, VOUT= 1.4V

An ISO 9001:2008 and DLA Certified Company



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Output Voltage High 5V OPEN 1 (V)	+VOUT1_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage High 5V OPEN 2 (V)	+VOUT2_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage High 5V OPEN 3 (V)	+VOUT3_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage High 5V OPEN 4 (V)	+VOUT4_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage High 5V 600 1 (V)	+VOUT1_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage High 5V 600 2 (V)	+VOUT2_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage High 5V 600 3 (V)	+VOUT3_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage High 5V 600 4 (V)	+VOUT4_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage Low 5V OPEN 1 (V)	-VOUT1_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage Low 5V OPEN 2 (V)	-VOUT2_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage Low 5V OPEN 3 (V)	-VOUT3_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage Low 5V OPEN 4 (V)	-VOUT4_5V OPEN	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
Output Voltage Low 5V 600 1 (V)	-VOUT1_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage Low 5V 600 2 (V)	-VOUT2_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage Low 5V 600 3 (V)	-VOUT3_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage Low 5V 600 4 (V)	-VOUT4_5V 600	VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
Output Voltage Low 5V 1mA 1 (V)	-VOUT1_5V 1mA	VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
Output Voltage Low 5V 1mA 2 (V)	-VOUT2_5V 1mA	VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
Output Voltage Low 5V 1mA 3 (V)	-VOUT3_5V 1mA	VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
Output Voltage Low 5V 1mA 4 (V)	-VOUT4_5V 1mA	VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA



TID Report
16-0066 07/28/16 R1.0

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

Table C.2. Measured parameters, pre-irradiation specifications and measurement precision for the RH1014MW Quad Precision Operational Amplifier.

Parameter	Pre-Irradiation Specification		Measurement Precision/Resolution
	MIN	MAX	
Positive Supply Current 15V (A)		2.20E-03	±4.33E-06
Negative Supply Current 15V (A)	-2.20E-03		±4.79E-06
Offset Voltage 15V (V)	-3.00E-04	3.00E-04	±1.27E-06
Offset Current 15V (A)	-1.00E-08	1.00E-08	±4.68E-11
Positive Bias Current 15V (A)	-3.00E-08	3.00E-08	±1.36E-10
Negative Bias Current 15V (A)	-3.00E-08	3.00E-08	±1.36E-10
Common Mode Rejection Ratio (dB)	9.70E+01		±2.60E+00
Power Supply Rejection Ratio (dB)	1.00E+02		±1.06E+00
Open Loop Gain (V/mV)	1.20E+03		±6.28E+01%
Output Voltage High 15V (V)	1.25E+01		±1.44E-03
Output Voltage Low 15V (V)		-1.25E+01	±1.07E-03
Positive Slew Rate (V/us)	2.00E-01		±2.16E-02
Negative Slew Rate (V/us)		-2.00E-01	±3.04E-02
Positive Supply Current 5V (A)		2.00E-03	±7.51E-06
Negative Supply Current 5V (A)	-2.00E-03		±5.26E-06
Offset Voltage 5V (V)	-4.50E-04	4.50E-04	±9.98E-07
Offset Current 5V (A)	-1.00E-08	1.00E-08	±6.63E-11
Positive Bias Current 5V (A)	-5.00E-08	5.00E-08	±1.73E-10
Negative Bias Current 5V (A)	-5.00E-08	5.00E-08	±7.62E-09
Output Voltage High 5V OPEN (V)	4.00E+00		±1.07E-03
Output Voltage High 5V 600 (V)	3.40E+00		±1.09E-03
Output Voltage Low 5V OPEN (V)		2.50E-02	±1.81E-04
Output Voltage Low 5V 600 (V)		1.00E-02	±1.46E-04
Output Voltage Low 5V 1mA (V)		3.50E-01	±1.07E-03

Appendix D: List of Figures Used in the Results Section (Section 5)

- 5.1. Positive Supply Current 15V (A) @ VS= +/-15V, VCM= 0V
- 5.2. Negative Supply Current 15V (A) @ VS= +/-15V, VCM= 0V
- 5.3. Offset Voltage 15V 1 (V) @ VS= +/-15V, VCM= 0V
- 5.4. Offset Voltage 15V 2 (V) @ VS= +/-15V, VCM= 0V
- 5.5. Offset Voltage 15V 3 (V) @ VS= +/-15V, VCM= 0V
- 5.6. Offset Voltage 15V 4 (V) @ VS= +/-15V, VCM= 0V
- 5.7. Offset Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
- 5.8. Offset Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
- 5.9. Offset Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
- 5.10. Offset Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
- 5.11. Positive Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
- 5.12. Positive Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
- 5.13. Positive Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
- 5.14. Positive Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
- 5.15. Negative Bias Current 15V 1 (A) @ VS= +/-15V, VCM= 0V
- 5.16. Negative Bias Current 15V 2 (A) @ VS= +/-15V, VCM= 0V
- 5.17. Negative Bias Current 15V 3 (A) @ VS= +/-15V, VCM= 0V
- 5.18. Negative Bias Current 15V 4 (A) @ VS= +/-15V, VCM= 0V
- 5.19. Common Mode Rejection Ratio 1 (dB) @ VS= +/-15V, VCM= 13V to -15V
- 5.20. Common Mode Rejection Ratio 2 (dB) @ VS= +/-15V, VCM= 13V to -15V
- 5.21. Common Mode Rejection Ratio 3 (dB) @ VS= +/-15V, VCM= 13V to -15V
- 5.22. Common Mode Rejection Ratio 4 (dB) @ VS= +/-15V, VCM= 13V to -15V
- 5.23. Power Supply Rejection Ratio 1 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
- 5.24. Power Supply Rejection Ratio 2 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
- 5.25. Power Supply Rejection Ratio 3 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
- 5.26. Power Supply Rejection Ratio 4 (dB) @ VS= +/-10V to +/-18V, VCM= 0V
- 5.27. Open Loop Gain 1 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
- 5.28. Open Loop Gain 2 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
- 5.29. Open Loop Gain 3 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
- 5.30. Open Loop Gain 4 (V/mV) @ VS= +/-15V, VCM= 0V, VO= +/-10V, RL= 10K
- 5.31. Output Voltage High 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.32. Output Voltage High 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.33. Output Voltage High 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.34. Output Voltage High 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.35. Output Voltage Low 15V 1 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.36. Output Voltage Low 15V 2 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.37. Output Voltage Low 15V 3 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.38. Output Voltage Low 15V 4 (V) @ VS= +/-15V, VCM= 0V, RL= 10K
- 5.39. Positive Slew Rate 1 (V/us) @ VS= +/-15V
- 5.40. Positive Slew Rate 2 (V/us) @ VS= +/-15V

- 5.41. Positive Slew Rate 3 (V/us) @ VS= +/-15V
- 5.42. Positive Slew Rate 4 (V/us) @ VS= +/-15V
- 5.43. Negative Slew Rate 1 (V/us) @ VS= +/-15V
- 5.44. Negative Slew Rate 2 (V/us) @ VS= +/-15V
- 5.45. Negative Slew Rate 3 (V/us) @ VS= +/-15V
- 5.46. Negative Slew Rate 4 (V/us) @ VS= +/-15V
- 5.47. Positive Supply Current 5V (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.48. Negative Supply Current 5V (A) @ VS= +5V , VCM= 0V, VOUT= 1.4V
- 5.49. Offset Voltage 5V 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.50. Offset Voltage 5V 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.51. Offset Voltage 5V 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.52. Offset Voltage 5V 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.53. Offset Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.54. Offset Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.55. Offset Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.56. Offset Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.57. Positive Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.58. Positive Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.59. Positive Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.60. Positive Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.61. Negative Bias Current 5V 1 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.62. Negative Bias Current 5V 2 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.63. Negative Bias Current 5V 3 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.64. Negative Bias Current 5V 4 (A) @ VS= +5V, VCM= 0V, VOUT= 1.4V
- 5.65. Output Voltage High 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.66. Output Voltage High 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.67. Output Voltage High 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.68. Output Voltage High 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.69. Output Voltage High 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.70. Output Voltage High 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.71. Output Voltage High 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.72. Output Voltage High 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.73. Output Voltage Low 5V OPEN 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.74. Output Voltage Low 5V OPEN 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.75. Output Voltage Low 5V OPEN 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.76. Output Voltage Low 5V OPEN 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= OPEN
- 5.77. Output Voltage Low 5V 600 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.78. Output Voltage Low 5V 600 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.79. Output Voltage Low 5V 600 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.80. Output Voltage Low 5V 600 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, RL= 600Ω
- 5.81. Output Voltage Low 5V 1mA 1 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
- 5.82. Output Voltage Low 5V 1mA 2 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA



**TID Report
16-0066 07/28/16 R1.0**

Aeroflex RAD
5030 Centennial Blvd.
Colorado Springs, CO 80919
(719) 531-0800

- 5.83. Output Voltage Low 5V 1mA 3 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA
5.84. Output Voltage Low 5V 1mA 4 (V) @ VS= +5V, VCM= 0V, VOUT= 1.4V, ISINK= 1mA